


Copper Flat Project

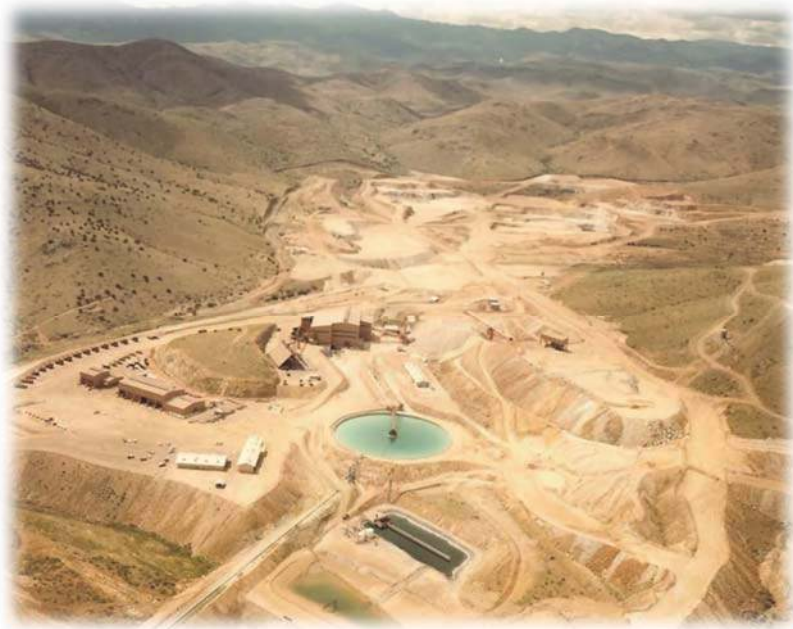

Form 43-101F1 Technical Report Feasibility Study Update

New Mexico, USA

Note: Several Figures From Report in Separate File.

REVISION 1

Prepared For:

THEMAC
RESOURCES

Qualified Persons:

Richard K. Zimmerman, R.G. SME-RM

Jeffrey C. Smith, P.E.

John M. Marek, P.E.

Thomas L. Drielick, P.E.

David A. Kidd, P.E.

DATE AND SIGNATURES PAGE

The effective date of this report is 11 December 2018. The issue date of this report is 9 April 2020.

<u>(Signed) "Richard K Zimmerman"</u> Richard K Zimmerman, R.G., SME-RM	<u>April 9, 2020</u>
<u>(Signed) "Jeffrey C. Smith"</u> Jeffrey C. Smith, P.E.	<u>April 9, 2020</u>
<u>(Signed) "John Marek"</u> John Marek, P.E.	<u>April 9, 2020</u>
<u>(Signed) "Thomas L. Drielick"</u> Thomas L. Drielick, P.E.	<u>April 9, 2020</u>
<u>(Signed) "David A. Kidd"</u> David A. Kidd, P.E.	<u>April 9, 2020</u>

COPPER FLAT PROJECT
FORM 43-101F1 TECHNICAL REPORT

TABLE OF CONTENTS

SECTION	PAGE
DATE AND SIGNATURES PAGE	I
TABLE OF CONTENTS	II
LIST OF FIGURES AND ILLUSTRATIONS.....	IX
LIST OF TABLES	XI
1 SUMMARY	1
1.1 PRINCIPAL FINDINGS	1
1.2 INTRODUCTION	2
1.3 RELIANCE ON OTHER EXPERTS.....	3
1.4 PROPERTY DESCRIPTION AND LOCATION.....	3
1.5 ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY	9
1.6 HISTORY	10
1.7 GEOLOGY AND MINERALIZATION	11
1.8 DEPOSIT TYPES	13
1.9 EXPLORATION	13
1.10 DRILLING	14
1.11 SAMPLE PREPARATION, ANALYSES AND SECURITY	14
1.12 DATA VERIFICATION	15
1.13 MINERAL PROCESSING AND METALLURGICAL TESTING	15
1.14 MINERAL RESOURCE ESTIMATES	17
1.15 MINERAL RESERVE ESTIMATES.....	17
1.16 MINING METHODS.....	19
1.17 RECOVERY METHODS.....	21
1.18 PROJECT INFRASTRUCTURE	22
1.19 MARKETING STUDIES AND CONTRACTS	23
1.20 ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT	24
1.20.1 Studies.....	24
1.20.2 Tailing Disposal and Waste Management	24
1.20.3 Permitting and Bonding	25
1.20.4 Social	26
1.20.5 Mine Closure and Reclamation	26
1.21 CAPITAL AND OPERATING COST ESTIMATES.....	27
1.21.1 Operating Cost	27

	1.21.2	Capital Cost.....	27
1.22		ECONOMIC ANALYSIS.....	28
1.23		ADJACENT PROPERTIES.....	29
1.24		PROJECT DEVELOPMENT	29
1.25		INTERPRETATION AND CONCLUSIONS.....	29
	1.25.1	Risks	30
	1.25.2	Opportunities	30
1.26		RECOMMENDATIONS	31
	1.26.1	Mining and Modeling	32
	1.26.2	Metallurgy.....	32
	1.26.3	Tailings Storage Facility.....	32
	1.26.4	Environmental	32
	1.26.5	Project Development	32
	1.26.6	Water Resources.....	32
1.27		REFERENCES.....	32
2		INTRODUCTION.....	33
	2.1	PURPOSE.....	33
	2.2	SOURCES OF INFORMATION.....	33
	2.3	LIST OF QUALIFIED PERSONS	34
	2.4	SITE VISIT & PERSONAL INSPECTIONS	35
	2.5	TERMS OF REFERENCE AND UNITS OF MEASURE.....	35
	2.5.1	Mineral Resources	36
	2.5.2	Mineral Reserves.....	36
	2.5.3	Glossary	37
	2.5.4	Copper Flat Rock Types.....	38
	2.5.5	Abbreviations	39
3		RELIANCE ON OTHER EXPERTS.....	43
	3.1	PROPERTY OWNERSHIP AND TITLE	43
	3.2	ROYALTIES	43
	3.3	TAXES	43
	3.4	ENVIRONMENTAL COMPLIANCE	43
4		PROPERTY DESCRIPTION AND LOCATION	44
	4.1	LOCATION.....	44
	4.2	MINERAL TENURE.....	45
	4.3	LOCATION OF MINERALIZATION	49
	4.4	ROYALTIES, AGREEMENTS AND ENCUMBRANCES	49
	4.4.1	Initial Option and Purchase Agreement.....	49
	4.4.2	2013 Real Estate Purchase Agreement.....	49
	4.4.3	Other Encumbrances.....	50

4.5	ENVIRONMENTAL LIABILITIES	50
4.5.1	Identified Environmental Liabilities.....	50
4.5.2	Environmental Compliance	51
4.6	PERMITTING.....	52
4.7	OTHER FACTORS AND RISKS AFFECTING ACCESS, TITLE, RIGHT OR ABILITY TO PERFORM	56
5	ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY	57
5.1	PHYSIOGRAPHY AND VEGETATION	57
5.2	CLIMATE	57
5.3	ACCESSIBILITY	57
5.4	LOCAL COMMUNITIES	58
5.5	REGIONAL TRANSPORTATION.....	58
5.6	POWER SUPPLY.....	59
5.7	WATER SUPPLY.....	59
5.8	PLANT SITE	61
5.9	TAILINGS STORAGE AREA	61
5.10	MATERIAL STOCKPILES.....	61
5.11	SOURCE OF PERSONNEL	61
5.12	SUFFICIENCY OF SURFACE RIGHTS FOR MINING OPERATIONS.....	62
6	HISTORY.....	63
6.1	OWNERSHIP.....	63
6.2	HISTORIC EXPLORATION AND DEVELOPMENT	64
6.3	HISTORIC RESERVE ESTIMATES AND AUDITS	64
6.4	HISTORIC PRODUCTION	65
7	GEOLOGICAL SETTING AND MINERALIZATION.....	67
7.1	REGIONAL GEOLOGY	67
7.2	LOCAL GEOLOGY	68
7.3	GEOLOGY OF THE COPPER FLAT OREBODY.....	68
7.3.1	Lithology.....	70
7.3.2	Structure.....	70
7.3.3	Mineralization.....	71
8	DEPOSIT TYPES.....	72
9	EXPLORATION	73
10	DRILLING.....	74
11	SAMPLE PREPARATION, ANALYSES AND SECURITY	76
11.1	HISTORIC SAMPLE PREPARATION	76
11.2	THEMAC PROCEDURES	77
11.3	DRILL HOLE COLLAR SURVEYS.....	78

11.4	ASSEMBLY OF DATABASE	78
12	DATA VERIFICATION	80
12.1	PULP REASSAYS BY THEMAC AND SRK	80
12.2	THEMAC QAQC.....	81
12.2.1	Blanks	81
12.2.2	Standards	81
12.2.3	Field Duplicates.....	83
12.2.4	Check Assays	83
12.3	HISTORIC DRILLING VS THEMAC DRILLING.....	86
12.4	DATA CORRECTIONS	88
12.4.1	2010-2011 Down Hole Surveys.....	88
12.4.2	Underground Drift Data	88
13	MINERAL PROCESSING AND METALLURGICAL TESTING	90
13.1	METALLURGICAL TESTING PROGRAM	90
13.2	METALLURGICAL TESTING RESULTS	91
13.2.1	Comminution	91
13.2.2	Solid-Liquid Separation.....	93
13.2.3	Flotation.....	94
13.2.4	Gold Deportment and Recovery	95
13.3	BASIS FOR RECOVERY ESTIMATES.....	96
13.4	REPRESENTATIVENESS OF TESTING AND CHARACTERIZATION.....	97
13.5	PROCESSING FACTORS AND DELETERIOUS ELEMENTS.....	97
13.6	CONCEPTUAL PROCESS FLOWSHEET.....	98
14	MINERAL RESOURCE ESTIMATES	100
14.1	BLOCK MODEL	100
14.1.1	Model Location	100
14.1.2	Drill Hole Data	100
14.1.3	Model Geology.....	101
14.1.4	Variography and Grade Boundaries.....	103
14.1.5	Block Grade Estimation	107
14.1.6	Density Assignment	109
14.1.7	Classification	109
14.2	MINERAL RESOURCE.....	109
15	MINERAL RESERVE ESTIMATES.....	111
15.1	FLOATING CONES.....	111
15.2	FINAL PIT DESIGN.....	112
15.3	MINERAL RESERVE.....	116
16	MINING METHODS	118
16.1	PHASE DESIGN	118
16.2	MINE PRODUCTION SCHEDULE	119

16.3	WASTE AND LOW GRADE STORAGE.....	121
16.4	MINE EQUIPMENT REQUIREMENTS	122
16.5	MANPOWER REQUIREMENTS.....	122
16.6	MINE AND WASTE STORAGE PLANS.....	125
17	RECOVERY METHODS	138
17.1	PROCESS FACILITY DESCRIPTION	138
17.2	CRUSHING	140
17.3	COARSE ORE STOCKPILE.....	140
17.4	GRINDING	140
17.5	FLOTATION	141
17.6	MOLYBDENITE FLOTATION	142
17.7	CONCENTRATE DEWATERING.....	142
17.7.1	Copper Concentrate Dewatering	142
17.7.2	Molybdenite Concentration	143
17.8	TAILING DEWATERING	143
17.9	REAGENT STORAGE AND MIXING	143
17.10	WATER SYSTEMS	144
18	PROJECT INFRASTRUCTURE	145
18.1	ROADS	145
18.2	POWER.....	145
18.3	WATER	146
18.4	RAIL	146
18.5	MATERIAL STOCKPILES.....	146
18.6	TAILINGS STORAGE FACILITY	146
18.7	SANITARY WASTEWATER TREATMENT	146
18.8	CENTRAL INFRASTRUCTURE CONTROL AND COMMUNICATIONS SYSTEMS.....	147
18.8.1	Concentrator Monitoring and Control Center	147
18.8.2	Safety Systems.....	148
19	MARKET STUDIES AND CONTRACTS	149
19.1	MARKET STUDIES.....	149
19.2	CONTRACTS	149
20	ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT.....	150
20.1	ENVIRONMENTAL STUDIES	150
20.2	TAILING DISPOSAL AND WASTE MANAGEMENT	151
20.2.1	Site Description	154
20.2.2	Design Studies	154

	20.2.3	Design Criteria	160
	20.2.4	Permitting Authorities	161
	20.2.5	Earthworks and Liner Construction	161
	20.2.6	Tailings Transport and Distribution	169
	20.2.7	Process Water Reclaim	176
	20.2.8	Water Balance.....	176
20.3		WASTE MANAGEMENT.....	178
	20.3.1	Mine Waste Rock.....	178
	20.3.2	Hazardous Materials and Petroleum Products	178
	20.3.3	Wastewater Treatment.....	179
	20.3.4	Solid Waste Disposal.....	179
	20.3.5	Spill Contingency Plan	179
20.4		PERMIT STATUS	180
20.5		SOCIOECONOMICS AND COMMUNITY	182
20.6		MINE CLOSURE, RECLAMATION, AND BONDING	183
	20.6.1	Reclamation Plan	183
	20.6.2	Reclamation Bond.....	183
21		CAPITAL AND OPERATING COSTS.....	185
	21.1	PROCESS OPERATING COST ESTIMATE	185
	21.1.1	Process Labor and Fringes	185
	21.1.2	Reagents.....	185
	21.1.3	Maintenance Wear Parts and Consumables	186
	21.1.4	Process Facilities Maintenance	186
	21.1.5	Electrical Power.....	186
	21.1.6	Process Supplies and Services	186
	21.1.7	General and Administration Costs	187
21.2		MINE OPERATING COSTS	187
21.3		CAPITAL COST ESTIMATE.....	190
	21.3.1	Mine Capital Cost	190
	21.3.2	Plant Capital Costs	193
	21.3.3	Tailings Capital and Operating Cost	195
	21.3.4	Current Value of Existing Infrastructure.....	197
22		ECONOMIC ANALYSIS.....	198
	22.1	INTRODUCTION	198
	22.2	MINE PRODUCTION STATISTICS	198
	22.3	PLANT PRODUCTION STATISTICS	198
	22.3.1	Smelter Terms	199
	22.3.2	Capital Expenditure	199
	22.3.3	Sustaining Capital.....	200
	22.3.4	Working Capital	200
	22.3.5	Residual and Salvage Value	200
	22.3.6	Revenue.....	200

22.4	CASH OPERATING COST	200
22.4.1	Royalty	200
22.5	TOTAL PRODUCTION COST	201
22.5.1	Reclamation and Closure	201
22.5.2	Depreciation	201
22.6	DEPLETION	201
22.7	TAXATION	202
22.7.1	Income Tax	202
22.7.2	New Mexico Gross Receipts Tax	202
22.7.3	Other Applicable Taxes	202
22.8	PROJECT FINANCING	204
22.9	NET INCOME AFTER TAX	204
22.10	NET PRESENT VALUE AND INTERNAL RATE OF RETURN	204
22.11	COPPER PRICE SENSITIVITY CASES	204
23	ADJACENT PROPERTIES	209
24	OTHER RELEVANT DATA AND INFORMATION	210
25	INTERPRETATION AND CONCLUSIONS	211
25.1	CONCLUSIONS	211
25.2	RISKS	211
25.2.1	Tailings Risks	212
25.3	OPPORTUNITIES	213
25.3.1	Tailings Opportunities	213
26	RECOMMENDATIONS	215
26.1	MINING AND MODELING	215
26.2	METALLURGY	215
26.3	TAILING STORAGE FACILITY	215
26.4	ENVIRONMENTAL	215
26.5	PROJECT DEVELOPMENT	215
26.6	WATER RESOURCES	215
27	REFERENCES	216
	APPENDIX A: FEASIBILITY STUDY CONTRIBUTORS AND PROFESSIONAL QUALIFICATIONS	221

LIST OF FIGURES AND ILLUSTRATIONS

FIGURE	DESCRIPTION	PAGE
Figure 1-1:	Copper Flat Project Location Map	4
Figure 1-2:	Copper Flat Mine in 1982	5
Figure 1-3:	Copper Flat Claim and Land Right Map.....	6
Figure 1-4:	Regional Geology of Copper Flat Project Altered from P. Dunn (1982).....	11
Figure 1-5:	Geology of the Copper Flat Mine, Dunn, 1982	12
Figure 1-6:	East-West Section Looking North, Dunn, 1982	13
Figure 1-7:	Conceptual Process Flowsheet	16
Figure 4-1:	Project Location Map	45
Figure 4-2:	Land Status Map.....	47
Figure 4-3:	Noncontiguous Mill Site Map	48
Figure 6-1:	Copper Flat Mine in 1982	66
Figure 7-1:	Regional Geology of Copper Flat Project Altered from P. Dunn (1982).....	67
Figure 7-2:	Geology of the Copper Flat Mine, Dunn, 1982	69
Figure 7-3:	East-West Section Looking North, Dunn, 1982	69
Figure 10-1:	Copper Flat Drill Holes with Data.....	75
Figure 12-1:	Standards Results for THEMAC 2010, 2011 & 2012 Drilling	82
Figure 12-2:	THEMAC Field Duplicate Assay Results for 2010-2012	84
Figure 12-3:	Check Assay Results, Skyline vs ALS Chemex.....	85
Figure 12-4:	Nearest Neighbor Comparison of New vs Old Holes for Copper (Samples are 25 ft composites, Grades are in % Total Copper)	87
Figure 13-1:	Conceptual Process Flowsheet	99
Figure 14-1:	Map of Grade Estimation Domains Based on Structural Blocks and Zones (The Map Covers the Model Area).....	103
Figure 14-2:	Copper Indicator Variogram 0.40% Discriminator.....	105
Figure 14-3:	Moly Indicator Variogram 0.012% Discriminator	106
Figure 15-1:	Floating Cone Guidance for Final Pit (\$2.25/lb Copper Cone).....	114
Figure 15-2:	Final Pit Design for Mine Plan and Mineral Reserve	115
Figure 16-1:	Relative Location of Phase Designs (5425 Bench).....	119
Figure 16-2:	Periodic Mine Plan Map - End of Preproduction	126
Figure 16-3:	Periodic Mine Plan Map- End of Year 1 Q1	127
Figure 16-4:	Periodic Mine Plan Map – End of Year 1 Q2	128
Figure 16-5:	Periodic Mine Plan Map - End of Year 1 Q3	129

Figure 16-6: Periodic Mine Plan Map - End of Year 1 Q4	130
Figure 16-7: Periodic Mine Plan Map - End of Year 2	131
Figure 16-8: Periodic Mine Plan Map – End of Year 3	132
Figure 16-9: Periodic Mine Plan Map - End of Year 4	133
Figure 16-10: Periodic Mine Plan Map - End of Year 5	134
Figure 16-11: Periodic Mine Plan Map – End of Year 7	135
Figure 16-12: Periodic Mine Plan Map – End of Year 10	136
Figure 16-13: Periodic Mine Plan Map – End of Year 12	137
Figure 17-1: Conceptual Process Flowsheet	139
Figure 20-1: Existing Conditions and Proposed Facilities Plan	153
Figure 20-2: Site Exploration Plan and Geologic Cross Sections Locations	156
Figure 20-3: Geologic Cross-Section A-A'	157
Figure 20-4: Tailings Storage Facility Grading Plan	163
Figure 20-5: Tailings Storage Facility Grading Plan Phase 1	164
Figure 20-6: Tailings Storage Facility at Final Buildout	165
Figure 20-7: Tailings Storage Facility Cross-Sections	166
Figure 20-8: Dam and Impoundment Underdrain Plan	167
Figure 20-9: Seepage Collection Pond Plan	170
Figure 20-10: Cyclone Plant and Emergency Pond Area Plan	171
Figure 20-11: Tailings Delivery and Distribution Piping Plan	172
Figure 20-12: General Process Flow Diagram Tailings	173
Figure 20-13: Water Reclaim System Piping Plan	174
Figure 20-14: Water Balance Analysis Results	177

LIST OF TABLES

TABLE	DESCRIPTION	PAGE
Table 1-1:	List of Qualified Persons	2
Table 1-2:	Permits and Approvals Required for the Copper Flat Project	7
Table 1-3:	Copper Flat Drill Data, Available for Determination of Resources	14
Table 1-4:	Estimated Metal Recoveries	15
Table 1-5:	Mineral Resources (7 October 2013).....	17
Table 1-6:	Copper Flat Project Mineral Reserves (7 October 2013)	18
Table 1-7:	Copper Flat Mine Production Schedule	20
Table 1-8:	Smelter Treatment Factors	23
Table 1-9:	Life of Mine Operating Cost	27
Table 1-10:	Initial Capital	28
Table 1-11:	Recovered Metal Production.....	28
Table 1-12:	After-Tax Sensitivity Analysis.....	29
Table 2-1:	List of Qualified Persons	35
Table 4-1:	Summary of Copper Flat Properties.....	49
Table 4-2:	Summary of Copper Flat Properties Acquired in 2013.....	50
Table 4-3:	Major Permits and Approvals Required for the Copper Flat Project	52
Table 5-1:	NMCC Water Rights	60
Table 6-1:	Historical Mine Reserve Estimates Comparison for Copper Flat*.....	65
Table 6-2:	Quintana Minerals, Inc. Mine Production at Copper Flat	66
Table 10-1:	Copper Flat Drill Data, Available for Determination of Resources	74
Table 12-1:	Nearest Neighbor Comparison – 2010 and 2011 THEMAC Drilling vs. Historic Drilling – 25 ft Down Hole Composites Spaced 50 ft Apart.....	88
Table 13-1:	Comparative Flotation Response from CSMRI 1976 Locked Cycle Test/1982 Mill Operating Results and MAG R&D Flotation Tests	91
Table 13-2:	Comminution Test Results	92
Table 13-3:	Comminution Test Results	92
Table 13-4:	Wear Rates for Copper Flat Samples	93
Table 13-5:	Flotation Test Results	94
Table 13-6:	Particle Size and Chemical Analysis.....	95
Table 13-7:	Gravity Recovery with Grind Size	96
Table 13-8:	Gravity Recoverable Gold Modeling Results	96
Table 13-9:	Estimated Metal Recovery Rates.....	97

Table 13-10: Design Parameters for the Conceptual Process Flowsheet.....	98
Table 14-1: Block Model Size and Location.....	100
Table 14-2: Drill Hole Data.....	101
Table 14-3: Indicator Kriging Parameters – Block Grade Estimation	108
Table 14-4: Grade Kriging Parameters – Block Grade Estimation	108
Table 14-5: Mineral Resources (7 October 2013).....	110
Table 15-1: Floating Cone Input.....	113
Table 15-2: Mineral Reserves (7 October 2013).....	117
Table 16-1: Mine Production Schedule	121
Table 16-2: Mine Major Equipment Fleet on Hand.....	122
Table 16-3: Mine Hourly Labor Requirements	123
Table 16-4: Salaried Staff Labor Requirements	124
Table 17-1: Estimated Reagent Consumption Rates for Sulfide Ore.....	144
Table 20-1: Design Criteria	160
Table 20-2: Major Permits and Approvals Required for the Copper Flat Mine.....	180
Table 20-3: Current Copper Flat Reclamation Bonds	184
Table 21-1: Process Operating Cost Summary.....	185
Table 21-2: Process Labor Summary	185
Table 21-3: Process Plant Reagents	186
Table 21-4: Grinding Media and Wear Items	186
Table 21-5: General Administration Summary	187
Table 21-6: Summary of Mine Operating Costs (\$US).....	189
Table 21-7: Summary of Mine Capital and Operating Costs.....	190
Table 21-8: Mine Equipment Capital Costs.....	192
Table 21-9: Tailings Storage Facility Capital and Operating Cost Estimate.....	196
Table 21-10: Current Value Cost of Reused Quintana Infrastructure	197
Table 22-1: Life of Mine Ore, Waste Quantities, and Ore Grade	198
Table 22-2: Average Metallurgical Recoveries.....	198
Table 22-3: Recovered Metal Production.....	198
Table 22-4: Smelter Treatment Factors	199
Table 22-5: Estimated Payable Metals	199
Table 22-6: Initial Capital	200
Table 22-7: Life of Mine Net Direct Cash Cost (C1 Cost)	201
Table 22-8: After-Tax Sensitivity Analysis.....	204

Table 22-9: Financial Return by Copper Price	205
Table 22-10: Financial Model (Page 1 of 3)	206
Table 22-11: Financial Model (Page 2 of 3)	207
Table 22-12: Financial Model (Page 3 of 3)	208

LIST OF APPENDICES

APPENDIX	DESCRIPTION
A	Feasibility Study Contributors and Professional Qualifications <ul style="list-style-type: none">• Certificate of Qualified Person (“QP”) and Consent of Author

1 SUMMARY

M3 Engineering & Technology Corporation (M3) has been commissioned by THEMAC Resources Group Limited (THEMAC) to prepare a Feasibility Study update for the Copper Flat Copper/Molybdenum Project (Copper Flat or the Project) compliant with Canadian Securities Administrators (CSA) National Instrument 43-101 (NI 43-101). The Project is owned and operated by New Mexico Copper Corporation (NMCC), a wholly owned subsidiary of THEMAC Resources Group Limited. NMCC was incorporated in New Mexico in July 2009. This section includes key elements from the study, including a brief description of the main results, and summaries of the property description and ownership, geology and mineralization, the status of exploration, development and operations, mineral resource and mineral reserve estimates, and the authors' conclusions and recommendations. All reference documentation is available in the NMCC corporate offices.

1.1 PRINCIPAL FINDINGS

The key results of this study are as follows:

- The Project currently has 113.1 million short tons (Mst) of proven and probable mineral reserves (78.9 Mst Proven and 34.2 Mst Probable).
- The Project currently has 305.2 million short tons of measured and indicated resources, as well as 27.6 million short tons of inferred resources, inclusive of reserves. Mineral resources that are not mineral reserves do not have demonstrated economic viability.
- The project is expected to process an average 10.8 million tons per year, for a total of 113.1 million short tons over the life of mine. The mine life based on reserves is expected to be 11.1 years.
- Estimated life-of-mine recoveries in thousands of pounds (klbs) or troy ounces (koz) from the process include the following:

○ Copper	628,015 klbs
○ Molybdenum	15,717 klbs
○ Gold	227 kozs
○ Silver	5,950 kozs
- The operating costs average \$12.14 per ton processed over the life of the mine, for a total of approximately \$1,374 million.
- Initial capital costs total \$374 million. The total life of mine sustaining capital is estimated to be \$41 million (expended over an 8-year period).
- The base case net income after taxes amounts to \$545 million. The Project has an after-tax NPV@8% of 235 million, IRR of 20.8%, and a payback period of 3.3 years.
- The sensitivity analysis shows that metal prices have the most impact on the project while variance in the operating cost has the least impact on project economics. For example, if metals prices increased by 20% from the estimate, the IRR would increase to 31.5%.
- Water supply for the mine must be addressed for the Project to proceed to production. NMCC acquired 7,481 acre-feet per year (acre-ft/yr) of declared water rights consisting of perfected and inchoate rights in 2010; however, the State of New Mexico Third District Court in 2017 ruled that the full amount of inchoate water rights and a portion of the perfected water rights held by the Company were invalid and extinguished. The Company is appealing that decision and also pursuing options to secure the full amount of water needed for the operation.

- M3 recommends proceeding to detail engineering. Cost of detailed engineering is included in the capital cost estimate.

1.2 INTRODUCTION

Copper Flat is a copper-molybdenum mining project located in South Central New Mexico, near the town of Hillsboro, approximately 150 miles south of Albuquerque, and approximately 20 miles southwest of Truth or Consequences. M3 Engineering & Technology Corporation (M3) has been commissioned by THEMAC to prepare a Feasibility Study for the Project compliant with the CSA NI 43-101. This report has been prepared in accordance with the guidelines provided in NI 43-101 Standards of Disclosure for Mineral Projects and conforms to Form 43-101F1 for technical reports.

The goal of the work is to potentially re-open and expand the project facilities. This Feasibility Study Report is intended for the use of THEMAC for the further development and advancement of Copper Flat towards the detailed design stage. It provides a mineral resource estimate, a classification of resources in accordance with the Canadian Institute of Mining, Metallurgy and Petroleum (CIM) classification system and an evaluation of the property, which presents a current view of the potential project economic outcome. The intent of this report is to provide the reader with a comprehensive review of the potential economics of this mining operation and related project activities, and to provide recommendations for future work programs to advance the Project.

Imperial units (American System) of measurement are used in this report. Abbreviations and a glossary are included in Section 2. All monetary values are in U.S. dollars (\$) unless otherwise noted.

The following authors were responsible for the study sections as listed in Table 1-1.

Table 1-1: List of Qualified Persons

Author	Company	Designation	Section Responsibility
Richard K Zimmerman	M3 Eng.	R.G. SME-RM	1, 2, 3, 7, 8, 9, 19, 24, 25, 26.4, 26.5, 26.6, 27
Jeffrey C. Smith	THEMAC	P.E.	4, 5, 6, 18, 20, 23
John Marek	IMC	P.E.	10, 11, 12, 14, 15, 16, 21.2, 21.3.1, 26.1
Thomas L. Drielick	M3 Eng.	P.E.	13, 17 (M3 drawings), 21.1, 21.3.2, 21.3.4, 22, 26.2
David A. Kidd	Golder	P.E.	20.2, 21.3.3, 25.2.1, 25.3.1, 26.3

Site visits of study participants include:

- Richard K Zimmerman, SME-RM visited the site on January 31, 2013 with other M3 personnel including Matt Murray and Tim Reiter, who designed the general arrangements; Shelby Madrid, the civil engineer for the project; Shannon Orr, the lead estimator; and Oscar Avilucea; the structural lead. Peter Olszewski, who was responsible for the water supply system design, visited the site on January 15, 2013. During the site visit, M3's inspection included the access road, previous mill site area, waste dumps, the top of the primary crusher structure, most of the foundation of the former concentrator building, and the floor slab of the former truck shop.
- Jeffrey C. Smith maintains an office at the Copper Flat and is onsite on a regular basis and was at the site as recently as the week of March 23, 2020. There have been no changes in site conditions since the last technical report.
- John Marek of IMC visited the Copper Flat Project on September 7-8, 2011. The storage facilities for drill core were visited, and historic pulp data were reviewed.

- David Kidd of Golder has visited the project site. His most recent visit to the site was on March 2, 2012. His visit included surface examinations of the proposed location of the tailings storage facility and surrounding areas that may be appropriate for obtaining materials for construction of the facility and reclamation cover.

1.3 RELIANCE ON OTHER EXPERTS

The Copper Flat Technical Report relies on reports and statements from legal and technical experts who are not Qualified Persons as defined by NI 43-101. The Qualified Persons responsible for preparation of this report have reviewed the information and conclusions provided and determined that they conform to industry standards, are professionally sound, and are acceptable for use in this report. Documentation relied upon is included in the Reference Section 27. These other experts are as follows:

- Legal review of the Copper Flat property ownership and title was completed by Mr. Mark K. Adams, an attorney with the New Mexico law firm Rodey, Dickason, Sloan, Akin & Robb, PA (the Rodey Law Firm). Mr. Adams review and legal opinion are summarized in a June 2013 report titled *Updated Title Report - Copper Flat Properties - Sierra County, New Mexico* (Adams, 2013). In a letter prepared on October 28, 2013, Mr. Adams summarized the content of the June 2013 Updated Title Report and concluded that on the basis of his examination, NMCC owns a 100% interest in the mineral and surface estates in the patented mining claims, other patented lands, and unpatented mining claims and mill sites included in the Copper Flat Properties, subject only to the royalties and advance royalties described in Part B and C of the Updated Title Report (Adams, 2013b). Mr. Adams updated the assessment of the property status in a letter dated February 6, 2020 (Adams, 2020).
- Interpretation of royalty obligations for economic modeling was provided by Mr. Mark K. Adams of the Rodey Law Firm.
- Examination and interpretation of New Mexico resource tax obligations for economic modeling was provided by Ms. Bobbi Hayes, a Certified Public Accountant (CPA) with Accounting and Consulting Group, LLP (ACG), a New Mexico accounting firm.

THEMAC also researched the utilization of a local Industrial Revenue Bond (IRB) to be issued by Sierra County to offset the New Mexico Gross Receipts tax obligations towards certain tangible personal equipment which includes eligible equipment and machinery to be installed and operated at the mine. The applicability of utilizing an IRB was evaluated by Alan Hall, J.D. of the Rodey Law Firm in a memorandum dated October 1, 2013 (Hall, 2013). The capital equipment review was performed by Marcus Mims, CPA of CliftonLarsonAllen LLP (Clifton) (Mims, 2013). By segregating IRB-qualifying equipment from disqualifying equipment, Clifton quantified the potential tax benefit dependent on issuance of an IRB by Sierra County.

- Stuart Butzier, Vice President at the law firm of Modrall Sperling Roehl & Sisk PA (Modrall Sperling) has provided legal assistance concerning permitting and environmental issues. Mr. Butzier issued an opinion that "NMCC's management, and staff and NMCC's technical consultants have maintained compliance with all state and federal environmental compliance and permitting requirements" in a letter dated March 19, 2020 (Butzier, 2020).

1.4 PROPERTY DESCRIPTION AND LOCATION

The Copper Flat Project is a copper-molybdenum porphyry deposit located in Sierra County, South Central New Mexico. Copper Flat is located in the Hillsboro Mining District in South Central New Mexico, in Sierra County. The center of the mineralization is at approximately 32.970300N latitude, 107.533527W longitude. The Project is approximately 150 miles south of Albuquerque, New Mexico and approximately 20 miles southwest of Truth or Consequences, New Mexico (straight line distances). Access from Truth or Consequences is by 24 miles of paved highway and 3 miles of all-weather gravel road. The Project location is shown in Figure 1-1.

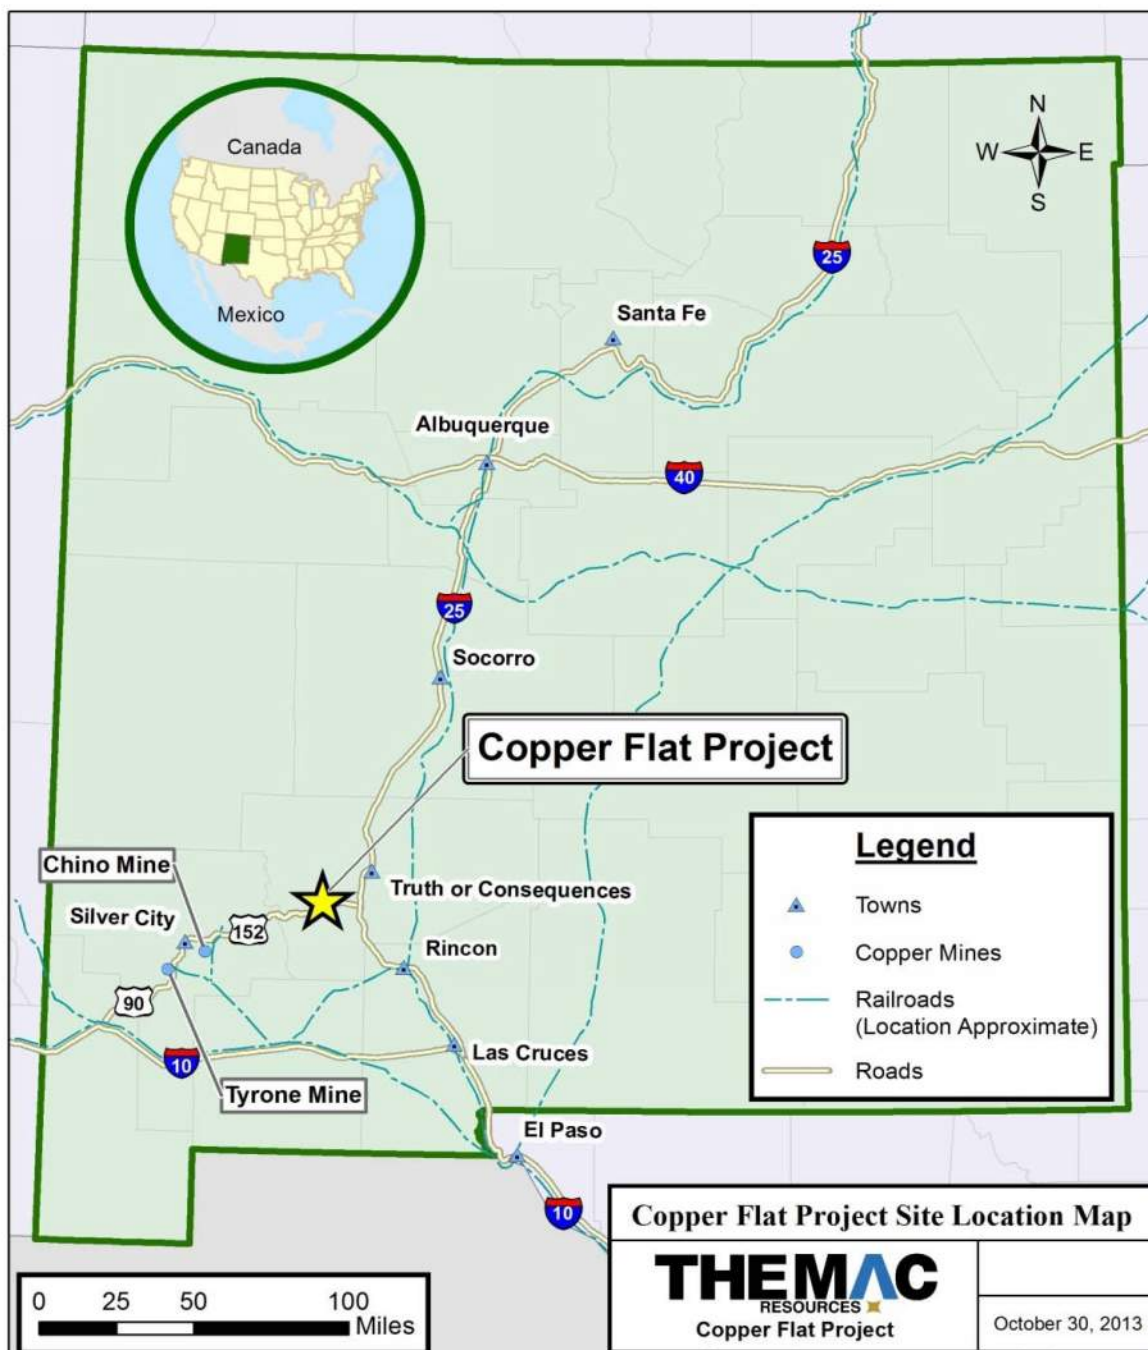


Figure 1-1: Copper Flat Project Location Map

In 1982, Quintana Minerals Corporation (Quintana Minerals) brought the property into production as an open pit mine with a mill and concentrator (rated at 15,000 short tons per day). The mine was in production for three and a half months, but operations were halted when copper prices declined. Figure 1-2 shows an aerial photo of the mine from 1982.

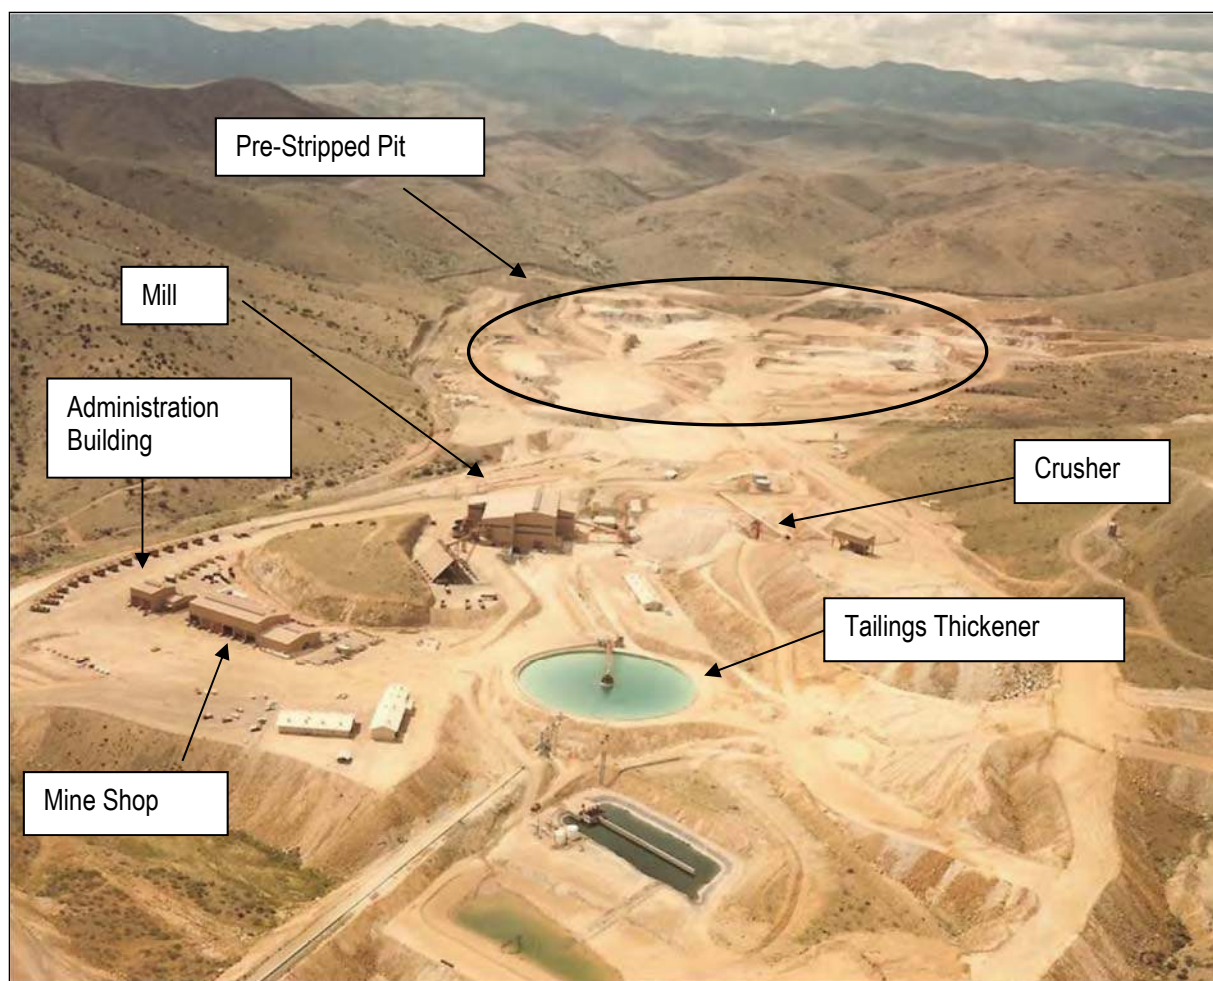


Figure 1-2: Copper Flat Mine in 1982

The property was placed on care and maintenance until 1986 at which point all the buildings and equipment were removed and sold. However, considerable foundations and other infrastructure remain on site.

The Project includes 26 patented mining claims and 231 unpatented mining claims, (202 lode claims and 29 placer claims), 9 unpatented mill sites, and 16 fee land parcels in contiguous and noncontiguous land parcels and claim blocks. An additional 1,200 acres in five tracts of land located within or adjacent to the property were acquired by NMCC through an agreement from a local rancher in April 2013, bringing the projects contiguous and non-contiguous land parcels and claim blocks to approximately 4,741 total acres. Within the project, a total of 2189.5 acres has been designated as the permit area. The permit area consists of both patented and unpatented mining claims and fee lands, all of which are controlled by NMCC, subject to royalties and agreements discussed below. Figure 1-3 shows the project land status.

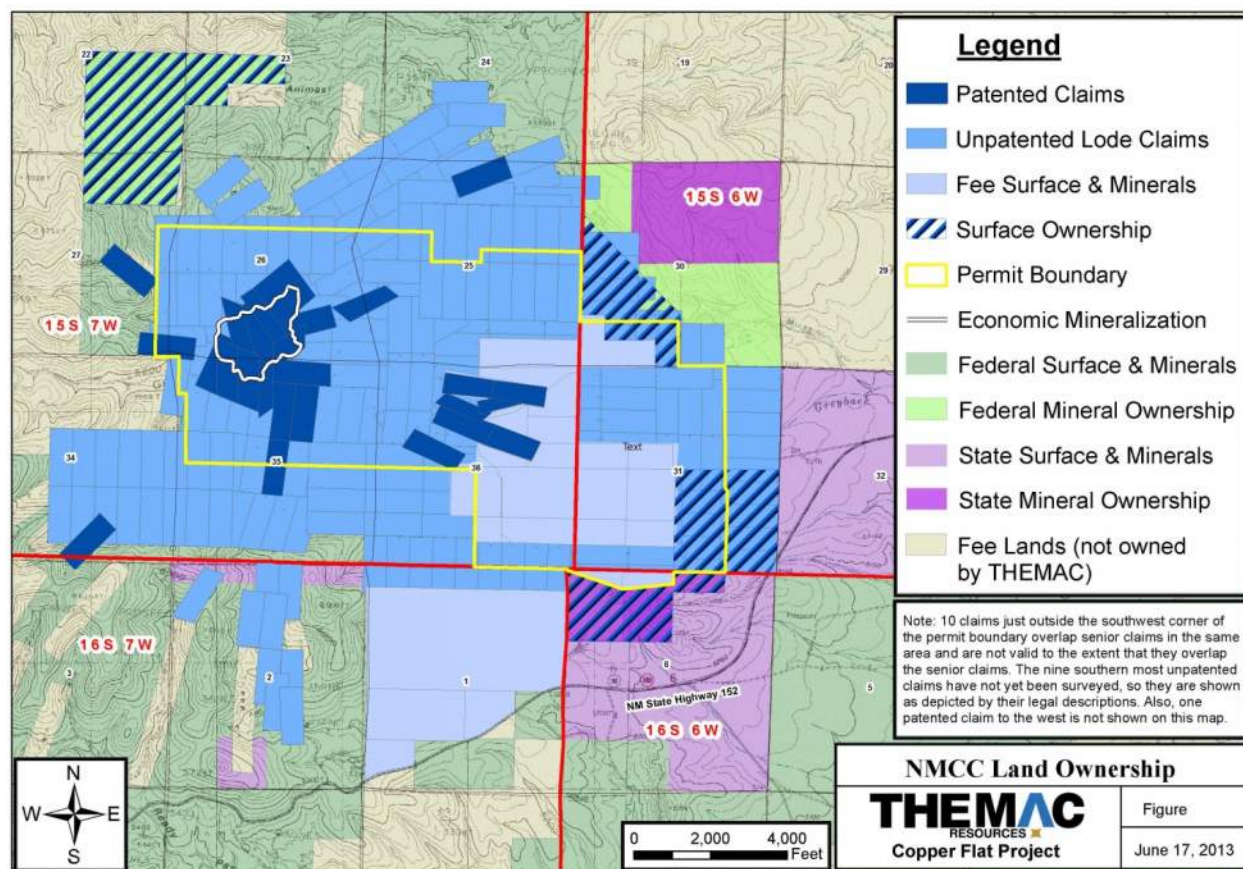


Figure 1-3: Copper Flat Claim and Land Right Map

The Project is subject to two substantive and one lessor royalty obligations:

- 1) Starting within the third calendar month following the calendar month in which NMCC has obtained all state and federal permits required for the commercial operation of the Mine, and continuing every three months thereafter, NMCC shall pay an Advance Royalty. If the copper price during the period of three calendar months preceding the month in which the Advance Royalty payment is due is \$ 2.00 or more, the Advance Royalty payment will be \$112,500. If the copper price during that period is less than \$2.00, the Advance Royalty payment will be \$50,000. NMCC's obligation to pay the Advance Royalty continues until the aggregate amount of all payments of the Advance Royalty and the NSR Royalty described in the following paragraph reaches \$10,000,000, or when NMCC has relinquishes and terminates any and all rights to conduct commercial production on the Properties.
- 2) For any quarter in which there is "gross revenue" from the Properties, a 3.25% NSR Royalty may be due. The royalty agreement provides that the Advance Royalty payments shall be credited against NSR Royalty payments. NMCC's obligation to pay NSR Royalty does not start until after (i) "Mineral Products" produced from the Properties are sold and (ii) the aggregate amount of the NSR Royalty payments due exceeds the aggregate amount of the Advance Royalty payments. The NSR Royalty is payable on "Gross Revenue" less "Permissible Deductions." "Gross Revenue," in essence, is revenue from the sale of "Mineral Products" produced from the Properties.
- 3) In addition to the advance and NSR royalties described above, the Chance, Feeder, Xmas and Extension patented claims are subject to a 5 percent net smelter return royalty owned by a third party. However, the

likelihood of mineral production from these claims is small and payments associated with this royalty are not expected to be significant.

When the site was originally operated by Quintana Minerals in 1982, it was closed with some environmental issues unresolved. THEMAC prepared a Stage I Abatement Plan for the New Mexico Environment Department (NMED), which was approved on February 7, 2012 and initiated in January 2013. As of the publication of this report, four quarters of environmental data have been collected and a new groundwater monitoring well installed under the scope of the approved Abatement Plan.

Table 1-2 presents the permits required to proceed with the Copper Flat Project.

Table 1-2: Permits and Approvals Required for the Copper Flat Project

Permit/Approval	Authority	Status
Federal Permits and Approvals		
Environmental Impact Study	US Bureau of Land Management (BLM)	<u>Complete</u> Final EIS issued April 2019; BLM Record of Decision approving the alternative that conforms to NMCC's Copper Flat Operating Plan issued August 2019
Biological Opinion	US Fish and Wildlife Service	<u>Complete</u> USFWS Consultation completed and biological opinion issued February 25, 2019. BO included with FEIS-ROD.
Cultural Resource Inventory and Protection Plan	US Bureau of Land Management (BLM)	<u>Complete</u> Field surveys and 3 rd Party consultations complete. Programmatic Agreement for the Copper Flat Mine signed with BLM and state agencies December 2016. Field plan prepared and ready to submit/implement ahead of construction
Clean Water Act Permit	US Army Corps of Engineers (ACOE)	<u>Complete</u> Approval under Nationwide Permit 44 (Mining) issued February 2020.
43 CFR 3809 Plan of Operations (POO)	US Bureau of Land Management (BLM)	Plan of Operations reflecting EIS approved alternative complete and submitted to BLM; approval expected with completion of financial assurance plan.
Reclamation/Closure Plan and Financial Assurance	US Bureau of Land Management (BLM)	BLM is cooperating agency with State Agencies. BLM has accepted plan, assumptions and cost calculations. Final approval pending Agency approval of financial assurance plan.
National Pollutant Discharge Elimination System (NPDES)	US Environmental Protection Agency (EPA)	Initiate with construction decision.
Mine Registration	Mining Safety and Health Administration (MSHA)	Initiate with construction decision.
FCC License	Federal Communications Commission (FCC)	Initiate with construction decision.
Explosives Permit	Bureau of Alcohol, Tobacco, and Firearms (BATF)	Initiate with construction decision.

State Permits and Approvals		
Air Quality Permit	NMED Air Quality Bureau	<u>Complete</u> New Source Permit 0365-M3 issued June 2013.
Groundwater Discharge Permit	NMED Groundwater Bureau	<u>Complete</u> Groundwater Discharge Permit issued December 2018.
Stage I and Stage II Abatement Plans	NMED Groundwater Bureau	<u>Complete</u> Requirement satisfied by rolling conditions into DP-1840
Cultural Resource Inventory and Protection Plan	NM Department of Cultural Affairs - State Historic Preservation Office	Field surveys and 3 rd Party consultations complete. Programmatic Agreement for the Copper Flat Mine signed with BLM and state agencies December 2016. Field plan prepared and ready to submit/implement ahead of construction
State Highway Use Authority	NMDOT	<u>Complete</u> Transportation and road engineering studies complete and MOU regarding protections for State Highway 152 executed with NMDOT in July 2018
Mine Operating Permit	NMEMNRD Mining & Minerals Division (MMD)	Permit Application Package considered approvable in July 13, 2018, letter from Agency; financial assurance plan started. Agency Order reopening technical review and suspending financial assurance review issued March 31, 2020.
Reclamation/Closure Plan and Financial Assurance	NMEMNRD MMD & NMED	Cost estimate presented to Cooperating Agencies; agencies advise NMCC response to technical questions satisfactory and no additional technical comments. NMCC developing options for establishing reclamation bond. Agency Order reopening technical review and suspending financial assurance review issued March 31, 2020
Water Supply	NMOSE	Acquired 861 acre-feet (AF) of perfected water right for mining use in Aug 2018. Lease executed Mar 2019 for 2400 AF; application accepted by OSE December 2019. Additional sources identified and negotiations ongoing.
New Dam Permit (TSF)	NMOSE Dam Safety Bureau	Initiate with TSF detail design
Mine Registration	NM EMNRD	Initiate with construction decision.
Landfill Permit	NMED Solid Waste Bureau	Initiate with construction decision.

The following environmental liabilities are identified at the Copper Flat Mine area:

- Bury and reclaim the exposed concentrator foundation
- Breach the legacy TSF dam
- Reclaim legacy waste rock storage areas
- Remove NMCC owned water supply well equipment and reclaim supply sites located on public land
- Remove other equipment from public land

NMCC and THEMAC have not received any letters of non-compliance from state or federal agencies and THEMAC knows of no site conditions or reports that are not in compliance with state or federal environmental laws.

1.5 ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY

The project area lies within the Mexican Highlands section of the Basin and Range Physiographic Province. The Copper Flat Property is located in the Las Animas Hills, along the western edge of the Rio Grande Valley. The Rio Grande Valley is approximately 30 miles wide and trends north-south. The Rio Grande river flows north-south along the eastern edge of the valley and is about 14 miles east of the site.

Elevations generally range from about 5,200 feet above mean sea level (famsl) on the southeast side of the property (tailings dam area), to around 5,700 famsl on the northwest side of the property. The highest elevation locally is Animas Peak (on the north side of the property), which tops at about 6,160 famsl. The mountains of the Black Range rise to elevations above 9,000 famsl about 25 miles west of the project site. The Project site exhibits plant communities dominated by desert grassland, creosote bush, and juniper woodlands (BLM, 1999).

Much of the project site has been disturbed by previous mining activities. Existing disturbance created by the Quintana Minerals Operation in the early 1980s includes a pre-stripped pit area, waste rock piles, mill site with concrete foundations, and the tailings storage facility. Additional disturbance within the project area includes historic placer mining disturbance and recent placer mining disturbance from recreational mining activities.

The climate in Sierra County is semi-arid high desert, with four distinct seasons. Summer temperatures are warm (maximum temperatures average 91°F; the recorded maximum is 107°F) and winter temperatures drop below freezing but are relatively mild (minimum temperatures average 25°F; the recorded minimum is -10°F).

The property is easily accessed by motor vehicle using Federal and State highway systems. From the east, the project site is reached by traveling north or south on US Highway 25, which is part of the US Federal Interstate Highway System, then west on State Highway 152 approximately 13 miles to the mine access road turnoff. Traveling from the west, the property access road is approximately 65 road miles using State Highway 152 from Silver City, NM, a major copper mining center located in southwestern New Mexico. After leaving State Highway 152, the property gate is reached by traveling approximately 2.5 miles on an existing all-weather gravel road. Road closures resulting from inclement weather in the area are extremely rare.

Power in Sierra County is supplied by Tri-State Generation and Transmission Association and distributed by Sierra Electric Cooperative, Inc. The Tri-State transmission line serving the mine area is a 115 kV voltage power line that parallels US Interstate Highway 25 approximately 12.5 miles east of the mine site. The dedicated 115 kV power line between the switching station and the mine is inactive; recent inspection determined that the line is in fair condition and can be returned to service with a limited amount of maintenance.

In addition to the Tri-State transmission lines, a 345 kV power transmission line owned by El Paso Electric, a regional electric utility providing generation, transmission and distribution service in southern New Mexico and west Texas, runs in a north-south direction and crosses the inactive 115 kV power line approximately 7.0 miles east of the mine site.

NMCC acquired 7,481 acre-ft/yr of declared water rights, consisting of perfected and inchoate rights, through purchase agreements with two separate parties in 2010. All payments required under the purchase agreements have been completed and full title to the acquired water rights has passed to NMCC.

In 2015, the Company filed for court adjudication of the acquired water rights. On December 28, 2017, the State of New Mexico Third District Court ruled that the full amount of inchoate water rights and a portion of the perfected water rights held by the Company were invalid and extinguished as the result of non-use and the failure to pursue a continuous plan of development by prior owners of the water rights; leaving the Company with approximately 862 acre feet of perfected groundwater rights. The Company filed an appeal of this decision on March 27, 2018. A date to hear oral arguments has not been established by the Court as of the date of this report.

NMCC has prepared an overall site water balance for the Copper Flat Operation that incorporates project design and operating plans. This water balance results in a groundwater pumping requirement equal to approximately 5,444 acre-feet of water per year (approximately 3,375 gallons per minute). Fresh water make-up will come from multiple sources, including captured storm water, mine pit dewatering, and groundwater supply wells.

The mine water supply wells and an 8-mile long, 20" diameter steel pipeline from wells to the mine were constructed in the 1980s by Quintana Minerals. NMCC installed pumps in two of the primary wells for an aquifer and well test in 2012. JSAI performed a specific capacity analysis of the primary and secondary wells; results demonstrated that these wells remain capable of supplying the quantity of water needed for the operation. A physical inspection of the pipeline was conducted along a 1-mile section of the pipeline. The inspection and subsequent engineering evaluation of the pipeline determined that the pipeline is in good condition and can be returned to service. Furthermore, engineering analysis by M3 concludes that the existing pipeline is capable of providing water in excess of 6,000 gallons per minute (9,660 acre feet per year).

1.6 HISTORY

The first recorded production of placer and lode gold from the Hillsboro Mining District (the District), New Mexico occurred in 1877. Over 285,000 oz of placer and lode gold, valued at \$8.5 million, was produced over the next 100 years. Most of the gold and silver production came from underground and placer operations, located in and around the Copper Flat area (Harley, 1934; Segerstrom et al., 1975; Dunn, 1982, 1984). Gold was initially recovered using arrastras (stone grinding) and then by stamp mills in the district prior to 1881. A tent city named Gold Dust was founded in 1881 in the district and was home to numerous prospectors looking for placer gold deposits. A 10-stamp mill operated at the Bobtail mine on the Snake vein from about 1881 to 1884 and had a capacity of 20 to 25tpd. Placer deposits in Snake Gulch located southwest of the Project were also mined using hydraulic mining methods. Mills operated at the Richmond (1890-1892), Bonanza (1890-1910), Ready Pay/Porter (1898-1913), Snake (1910), and Wicks mines. A copper-matte smelter (capacity 30tpd) in the town of Hillsboro was built in 1892 and operated until the early 1900's. The Stenborg copper mine, located at the Project, was in operation between 1911 and 1931. Small-scale copper and precious metals mining took place in the district up until 1941 (Harley, 1934; Segerstrom et al., 1975; Dunn, 1982, 1984; Raugust, 2003).

Newmont Mining Company (Newmont) explored the District for copper in 1952, followed by Hilltop Mining, Bear Creek Mining Company (BCMC), and Inspiration Development Company (Inspiration). Hilltop Mining worked in the area prior to BCMC, which was involved with the Project between 1958 and 1959. Inspiration acquired the Project in 1967 and leased it to Quintana Minerals in 1974 (Segerstrom et al., 1975; Dunn, 1982, 1984).

In 1979, Quintana Minerals formed a partnership with Phibro Minerals Enterprises, Inc. forming the Copper Flat Partnership, which was financed by Canadian Imperial Bank of Commerce (CIBC) located in Toronto, Ontario, Canada. Under this partnership, Quintana Minerals was the operator (Segerstrom et al., 1975; Dunn, 1982, 1984).

In August 1987, Inspiration leased its mining claims to Hydro Resources with the option to purchase, which was finalized by 1989. In 1989, Rio Gold optioned Copper Flat from Hydro Resources.

The Copper Flat Partnership, which at this time included Copper Flat Mining Co. Ltd, a subsidiary of Rio Gold, maintained control of the Project and held the property until 1993 when Gold Express optioned the Project. Gold Express acquired Copper Flat from Rio Gold with the intent of placing the property into production employing the 1982 design parameters. The following year, in June 1994, Alta Gold acquired the option on the Project from Gold Express. Alta Gold held the Project until its bankruptcy in 1999.

The property reverted back to Hydro Resources in 2001, in conjunction with Cu Flat and GCM (collectively the vendors). In July 2009, NMCC acquired an exclusive option over the Copper Flat property from the vendors. In May 2011, NMCC made the final payment on the exclusion option and now owns the property in total.

In mid-March 1982 after a \$112 million capital investment, the Copper Flat open pit copper mine began full production at a rated capacity 15,000 tpd, a waste to ore ratio of 1.8:1, and a cut-off grade of 0.25 percent copper. After just 3.5 months of production, the mine shut down on June 30, 1982, due to low copper prices (\$0.70/lb) and high interest rates on the CIBC loan. The mine produced 1.48 Mst of ore recovering 7.4 Mlbs of copper, 2,301 oz of gold, and 55,966 oz of silver during the period.

1.7 GEOLOGY AND MINERALIZATION

Copper Flat is a porphyry copper-molybdenum deposit containing minor recoverable gold and silver mineralization hosted by a quartz monzonite stock which intrudes an andesitic volcanic complex. The Cretaceous (75 million years before present [Ma]) Copper Flat quartz monzonite (CFQM) hosts mineralization dominated by pyrite and chalcopyrite with subsidiary molybdenite, minor bornite and minor concentrations of recoverable gold and silver. A recent rhenium-osmium (Re-Os) age date on molybdenite yielded an age of 76.2 Ma, which is in close agreement with previous age dates of the andesite and CFQM. The mineralization is focused along intersecting northeast- and northwest-trending faults, and these intersections may have originally controlled emplacement of the CFQM. The surface geology of the Copper Flat region is shown in Figure 1-4.

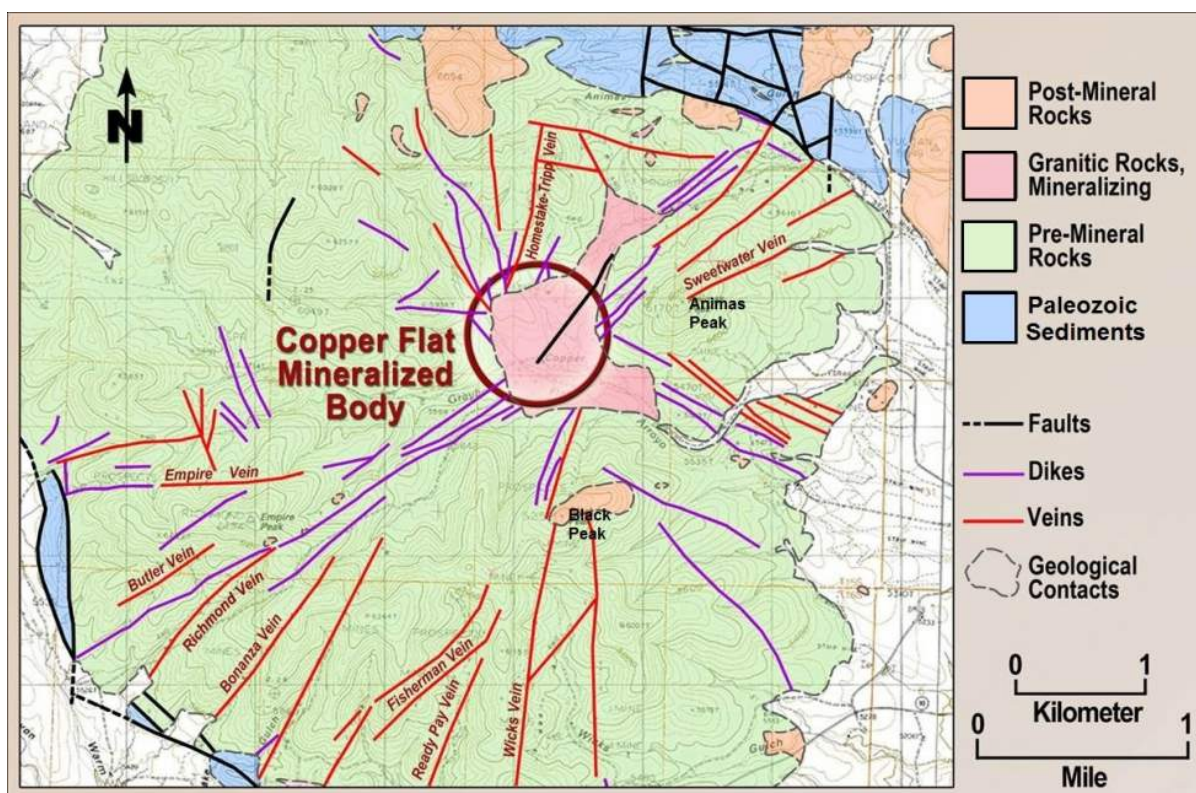


Figure 1-4: Regional Geology of Copper Flat Project Altered from P. Dunn (1982)

Sulfide mineralization is present as veinlets and disseminations in the quartz monzonite but is most strongly developed in and adjacent to the west end of a steeply dipping breccia pipe, that is centrally located within the CFQM stock and elongated in the northwest-southeast direction roughly along, but south of the Patten fault. The sulfide mineralization

first formed in narrow veinlets and as disseminations in the quartz monzonite with weakly developed sericitic alteration. This stage of mineralization was followed by the formation of the breccia pipe and the introduction of coarse “clotty” pyrite and chalcopyrite along with veinlet controlled molybdenite and milky quartz, and the development of strong potassic alteration. Typically, the total sulfide content ranges from 1 percent (by volume) in the eastern part of the breccia pipe and the surrounding CFQM to 5 percent in the CFQM to the south and west. Sulfide content is highly variable within the breccia, with portions in its western part reportedly containing as much as 20 percent sulfide minerals.

The breccia pipe, which can best be described as a crackle breccia, consists of rotated angular to subangular fragments of quartz monzonite varying from 1 inch to more than 18 inches in diameter. Previous workers have suggested that the breccia may have formed by autobrecciation resulting from retrograde boiling. Two types of breccia have been identified as distinguishable units based on the dominant mineral filling the matrix between clasts. Drilling has shown that the two breccia types, biotite breccia and feldspar breccia, grade into one another as well as with the CFQM. Interestingly from a recovery perspective, metallurgical testing has shown that the mineralization behaves virtually the same irrespective of the lithology.

Molybdenite occurs occasionally in quartz veins or as thin coatings on fractures. Minor sphalerite and galena are present in both carbonate and quartz veinlets in the CFQM stock. Preliminary evaluations of the mineralization at Copper Flat in 2011 indicate that copper mineralization concentrates and trends along the N50°W structural influences, whereas the molybdenum, gold and silver appear to favor a N10°-20°E trend.

The mine geology itself is shown in Figure 1-5 and Figure 1-6.

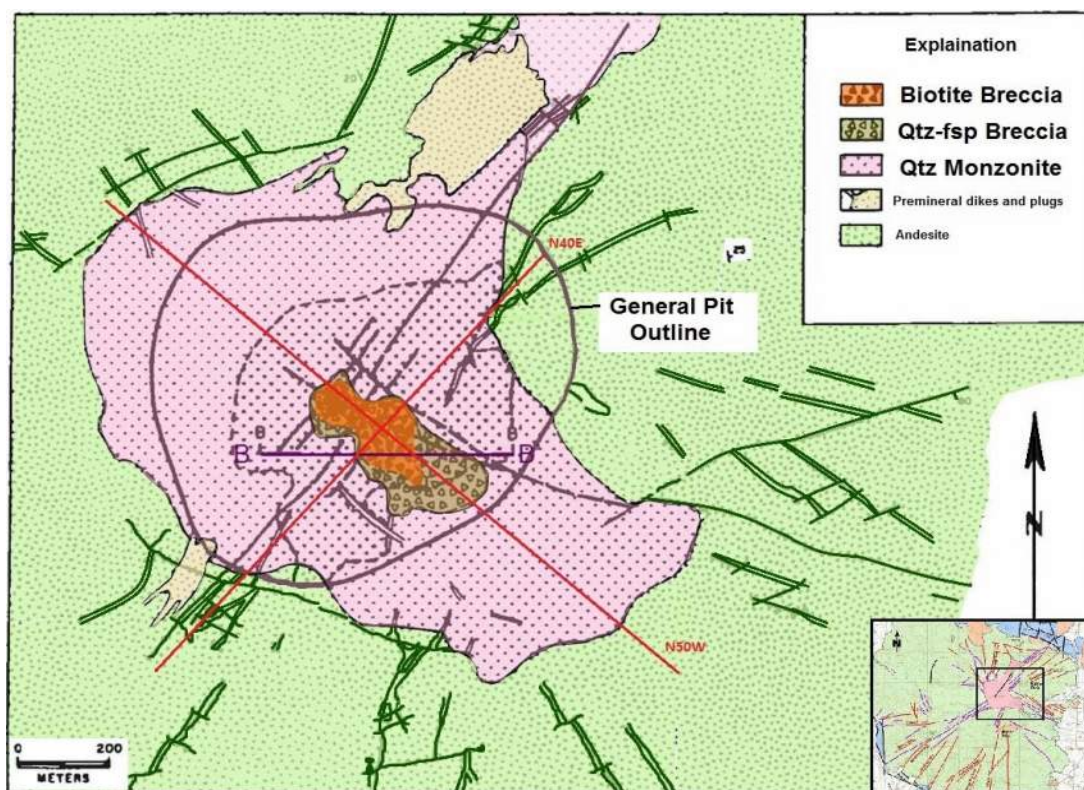


Figure 1-5: Geology of the Copper Flat Mine, Dunn, 1982

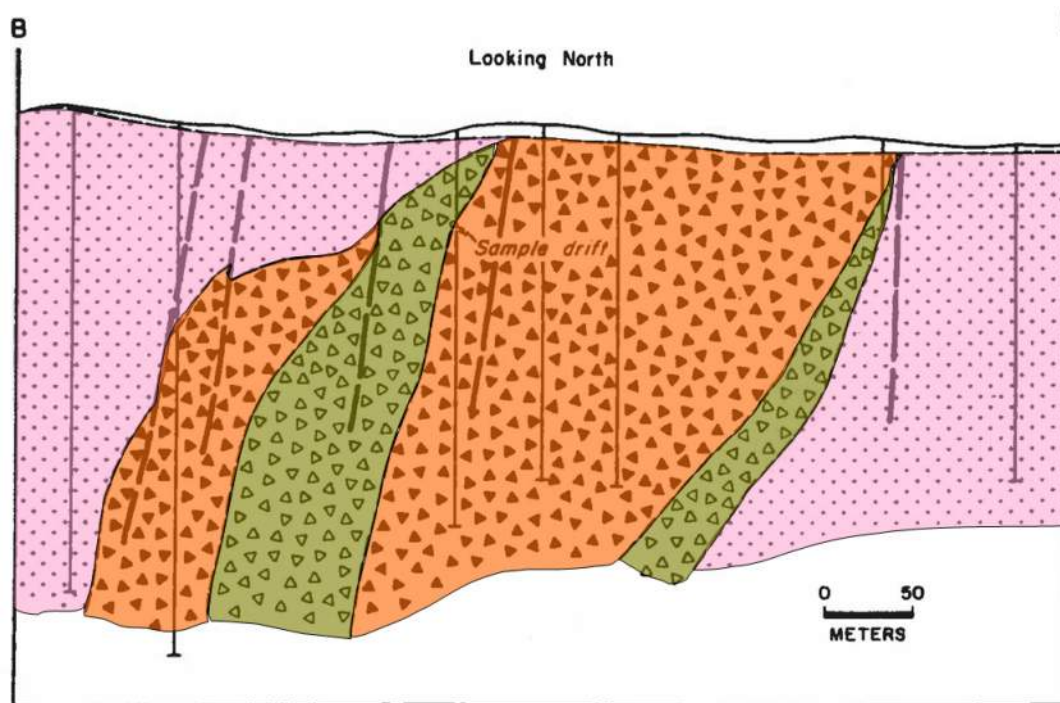


Figure 1-6: East-West Section Looking North, Dunn, 1982

1.8 DEPOSIT TYPES

Copper Flat is a porphyry copper- molybdenum deposit that is approximately 1,400 by 2,100 ft in plan view occurring within a small structurally controlled quartz monzonite stock that has intruded a circular block of andesite approximately 4 miles in diameter. The porphyry includes a variably mineralized west-northwest-trending hydrothermal “breccia pipe,” that lies immediately south of the Patten fault, that is about 1,400 ft long and 500 ft wide.

1.9 EXPLORATION

Copper Flat is an advanced development project that was in production for only a few months in the early 1980's. As such, most of the exploration completed since that time has been the addition of diamond drilling to confirm, expand, and better understand the deposit.

During the 2012 exploration program, THEMAC personnel completed detailed surface mapping of all exposures within the historical pit, drainage cuts, and most of the outlying project area. Surface geochemical sampling was also completed to improve the understanding of the precious metal distribution outside of the deposit, as well as identify other potential exploration targets.

In addition to drilling, all of the historical core has been relogged to obtain lithologic and structural information using core photographs; additional mineralogical and metallurgical studies have been undertaken; geotechnical studies have been completed and a CSAMT geophysical survey completed in the central part of the project that was designed to investigate and define the extent of the CFQM and sulfide mineralization.

With the completion of the 2012 drilling program, the Copper Flat deposit is now considered to be characterized to the extent necessary for a Feasibility Study. However, upon commencement of mining, it may be possible to expand the copper known reserve and resource with additional drilling. This drilling should be focused on attempting to extend the

deposit to depth (below the planned pit bottom), better defining the margins of the deposit and extending and better defining the extreme northeastern lobe of the deposit.

1.10 DRILLING

Most of the drilling since 1982 has been diamond drilling. THEMAC personnel have completed detailed surface mapping of all exposures within the old pit, drainage cuts, and much of the remaining project during the last two years. Additionally, some surface sampling has been completed to improve the understanding of the precious metal distribution outside of the main ore zone, and most of the historical core has been re-logged using core photographs.

During the period 2009-2012, THEMAC undertook annual drilling programs designed to better define the known mineralization; upgrade and expand existing resources; convert resources to reserves with increased drilling density; gain a better understanding of the lithologic and structural controls of mineralization; obtain material for metallurgical testing; extend and evaluate the mineralization at depth and undertake geotechnical studies.

Table 1-3 summarizes the drill programs completed on the project where there is data available for the determination of mineral resources. All of the drilling summarized below is diamond core drilling.

Table 1-3: Copper Flat Drill Data, Available for Determination of Resources

Company	Dates	Drill holes	IMC comments	Elements Asayed	IMC Summary
Inspiration Consolidated	1967-1973	CF-1 to CF-20	20 drill holes, 4 with no assay CF-14,CF-15,CF-20 and CF-5	Totcu (%) Moly (%)	769 assay intervals, 9,350 ft of drilling
Inspiration Development	1968-1971	IDC-1to IDC-29	31 drill holes, 4 holes no assay IDC-20, -29,-30,-31	totcu (%) moly (%) gold(opt) silver (opt)	3,290 assay intervals, 27,183 ft of drilling
Quintana Minerals	1974-1978	H Series	134 drill holes total, 129 w/total copper, 21 holes assayed for gold and silver	Totcu (%) Moly (%) Gold(opt) Silver (opt)	9,709 assay intervals, 97,210 ft of drilling
NMCC	2009-2012	CF Series & CNI Series	48 drill holes, 2 holes no assay CF-12-19,-20	Totcu (%) Moly (%) Gold(ppb) Silver (ppm)	8,422 assay intervals, 47,583 ft of drilling

1.11 SAMPLE PREPARATION, ANALYSES AND SECURITY

The majority of the database available of Copper Flat sample results was developed by Quintana during the 1970's and 1980's. Recent drilling by THEMAC has been added to the data base to confirm and expand the historic information. Sample results for diamond core drilling conducted by Inspiration and Quintana appear to be acceptable, though the documentation may not meet current standards. Quintana adopted a rigorous sample preparation procedure when early checks on reproducibility were not acceptable.

Recent drilling by ECR Minerals, PLC (formerly Mercator Gold PLC) and THEMAC follow industry-standard sampling preparation, handling, and documentation procedures. Sample analyses have been undertaken by Skyline Assayers & Laboratory in Tucson, Arizona using industry-standard procedures. Quality assurance and quality control procedures include inserting blanks, standards, and duplicates in the sample shipments and conducting check assays at the rate of 5 percent. Additionally, in the 2012 program, duplicate pulps of every tenth sample, including historical pulps, were submitted to ALS Minerals, Reno, NV for check assay using methods similar to that used by Skyline. Historical data was compiled from electronic and paper records and combined with results from the 2009 to 2012 drilling results by Independent Mining Consultants (IMC) to form the basis for the current reserve and resource estimation.

IMC and John Marek (QP) hold the opinion that the sample preparation, analysis, and security of the database is reliable based on the result of the comparison between historic and modern data and site review of the modern procedures that are being followed.

1.12 DATA VERIFICATION

The drill hole data base for Copper Flat has been in existence since the 1980's. Previous work in 2010 and 2011 by THEMAC and their contractors completed a number of verifications steps to develop some confidence in the historic data. During 2011 and 2012, THEMAC drilled additional holes in order to: 1) provide additional confirmation of the historic drilling, 2) test for extensions to the mineralization, and 3) provide geotechnical information for slope stability.

IMC and John Marek (QP) hold the opinion that the database as assembled for this study is reliable for the purposes of estimating mineral resources and mineral reserves. In assembling the data set for determination of mineral resources and reserves, some questionable historic data items have been removed from the data base.

1.13 MINERAL PROCESSING AND METALLURGICAL TESTING

A significant amount of process design and metallurgical testing was accomplished prior to the Quintana operation of the property in 1982. Additional testing has been accomplished since then by others contemplating redevelopment of the property, including recent work by Minerals Advisory Group Research and Development (MAG), of Tucson, Arizona, commissioned by THEMAC. The process flow design and recovery estimation presented here is supported by the current test data as well as results from the Quintana operation. The flow sheet was developed for processing 29,600 tpd for the first 6 years followed by 27,125 tpd for the remaining mine life. The mill is planned to operate 92.5% efficiency. The Copper Flat conceptual processing flow sheet is shown in Figure 1-7.

M3 conducted a thorough review of the metallurgical testing conducted to date on the Copper Flat ores and concluded that there are no adverse processing factors that require any extraordinary process engineering or deleterious elements in the ore, and that the ore is of medium hardness, amenable to copper/moly flotation, gives products that thicken and filter readily and will produce saleable copper and moly concentrates. Testing reviewed included comminution, flotation, concentrate dewatering, and tailing dewatering. Table 1-4 below provides estimated recoveries of copper, molybdenum, silver, and gold.

Table 1-4: Estimated Metal Recoveries

Product	LOM Average	Years 1 – 5	Years 6 - LOM
Copper	93.1 %	94.6%	91.2%
Molybdenum	78.0%	81.9%	73.4%
Gold	73.7%	73.7%	73.7%
Silver	82.7%	82.7%	82.7%

* Includes additional 2.6% recovery from gravity circuit

1.14 MINERAL RESOURCE ESTIMATES

The Resource and Reserves definitions are as set forth in the Appendix to Companion Policy 43-101CP, CIM – Definitions Adopted by CIM Council, June 30, 2011. Mineral Resources for Copper Flat are as summarized in Table 1-5. Mineral resources that are not mineral reserves do not have demonstrated economic viability.

Table 1-5: Mineral Resources (7 October 2013)

Classification	Cutoff Grade NSR/Ton	Tonnage and Grade					Contained Metal			
		Ktons	Copper %	Moly %	Gold Oz/ton	Silver Oz/ton	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000
Measured	\$6.11	126,655	0.28	0.009	0.003	0.06	709,268	22,798	380	7,599
Indicated	\$6.11	<u>178,571</u>	<u>0.19</u>	<u>0.005</u>	<u>0.002</u>	<u>0.04</u>	<u>678,570</u>	<u>17,857</u>	<u>357</u>	<u>7,143</u>
Meas + Ind		305,226	0.23	0.007	0.002	0.05	1,387,838	40,655	737	14,742
Inferred	\$6.11	27,646	0.20	0.004	0.001	0.02	110,584	2,212	28	553

Notes:

Mineral Resources stated above include the mineral reserve
Mineral Resources are contained within a floating cone pit geometry at prices listed in text
Ktons means 1000 short tons. Short tons = 2000 lbs
Copper and Molybdenum grades are percent of dry weight
Gold and Silver are reported in Troy ounces / short ton

Metal Prices:

\$3.00/lb Copper, \$8.00/lb Mo, \$1350 /oz Gold, \$20.00/oz Silver

1.15 MINERAL RESERVE ESTIMATES

The mineral reserve was developed by tabulating the contained measured and indicated (proven and probable) material inside of the designed pit at an NSR cutoff grade of \$6.11/ton. The mine plan and schedule indicate that the operating cutoff is slightly higher during the first five years in an effort to improve front end head grade and maximize return on investment. The NSR for application of cutoff grade includes a benefit from copper, molybdenum, gold and silver.

Low grade material that is above the internal cutoff of \$6.11/ton NSR and less than mill feed cutoff in the early years will be stored in two low-grade stockpiles that are located to the northeast of the pit and northeast of the crusher. That material is planned to be re-mined and delivered to the mill in years 13 and 14. The mineral reserve is summarized on Table 1-6. The mineral resource in addition to the mineral reserve is included for clarity.

Table 1-6: Copper Flat Project Mineral Reserves (7 October 2013)

Classification	Cutoff Grade NSR/Ton	Mineral Reserves					Contained Metal				Recovered, Saleable Metal			
		Ktons	Copper %	Moly %	Gold Oz/ton	Silver Oz/ton	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000
Proven	Variable By Year \$12.75 to \$6.11	78,857	0.32	0.010	0.003	0.07	504,685	15,771	237	5,520	432,538	9,169	117	3,424
Probable	\$12.75 to \$6.11	<u>34,227</u>	<u>0.25</u>	<u>0.007</u>	<u>0.003</u>	<u>0.04</u>	<u>171,135</u>	<u>4,792</u>	<u>103</u>	<u>1,369</u>	<u>146,670</u>	<u>2,786</u>	<u>51</u>	<u>849</u>
Total Prov + Prob		113,084	0.30	0.009	0.003	0.06	675,820	20,563	340	6,889	579,208	11,955	168	4,273

Mineral Resources in Addition to Mineral Reserves														
Classification	Cutoff Grade NSR/Ton	Tonnage and Grade					Contained Metal							
		Ktons	Copper %	Moly %	Gold Oz/ton	Silver Oz/ton	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000				
Measured	\$6.11	47,798	0.21	0.007	0.003	0.04	204,583	7,027	143	2,079				
Indicated	\$6.11	<u>144,344</u>	<u>0.18</u>	<u>0.005</u>	<u>0.002</u>	<u>0.04</u>	<u>507,435</u>	<u>13,065</u>	<u>254</u>	<u>5,774</u>				
Meas + Ind		192,142	0.19	0.005	0.002	0.04	712,018	20,092	397	7,853				
Inferred	\$6.11	27,646	0.20	0.004	0.001	0.02	110,584	2,212	28	553				

Notes:

Mineral reserves equal the total ore planned for processing from the mine plan
Mineral Resources stated above do not include the mineral reserve
Mineral Resources are contained within a floating cone pit geometry at prices listed below.
Ktons means 1000 short tons. Short tons = 2000 lbs
Copper and Molybdenum grades are percent of dry weight
Gold and Silver are reported in Troy ounces / short ton

Metal Prices:

Mineral Reserve \$3.00 Copper, \$8.00 Moly \$1350 Gold, \$20.00 Silver, No Economic Credit to Inferred
Mineral Resource \$3.00 Copper, \$8.00 Moly \$1350 Gold, \$20.00 Silver

1.16 MINING METHODS

The Copper Flat Project is planned for production using conventional hard rock open pit mining methods. Ore production to the mill is planned at 29,600 tpd (10,800 ktons/yr) for the first 6 years followed by 27,125 tpd (9,900 ktons/yr) for the remaining mine life. The mine production schedule was developed with the goal of filling the mill at required ore rate and maximizing the project return on investment. The total material rate is tied to equipment productivity and amounts to 17,500 ktons/yr or 47,945 tpd for the first 5 years. The mine is scheduled to operate 365 days/yr with two, 12 hour shifts/day. Bench heights are currently planned to be 25 ft high. Drilling will be completed with three rotary blast hole rigs with 45,000 lb pull down capacity and 6.5 in diameter blast holes. The blasted rock will be loaded into 100 ton haul trucks using two 19 cu yd front end loaders.

The mine plan was developed with a phased approach. The floating cone algorithm was used as a guide to the design of the phases or pushbacks. Three phases were designed for the Copper Flat Project with approximately 300 ft of operating width on each bench within a phase. Phase 1 was sized to contain roughly 1.5 years of ore. The phases were tabulated from the block model and those three tabulations were used as input to the development of the mine production schedule.

The mine production schedule was developed with the goal of feeding the mill at through put rates of 29,600 tpd (years 1-5) and 27,125 tpd (remaining LOM) and maximizing the project return on investment. Multiple mine production schedules were developed that analyzed alternative cutoff grade strategies versus mine total material movement. The best overall production schedule on an economic and practical basis is summarized in Table 1-7.

Table 1-7: Copper Flat Mine Production Schedule

Mine Plan Schedule											
Year	Cutoff NSR/ton \$/ton	Direct Mill Feed Ore						Waste			Total Material Ktons
		Ore Ktons	NSR \$/ton	Copper %	Moly %	Gold oz/ton	Silver Oz/ton	WSF 1 Ktons	WSF 2 Ktons	WSF 3 Ktons	
Preprod	\$12.00	360	22.824	0.43	0.007	0.003	0.06	32	30	48	470
Yr1 Q1	\$12.75	1,540	20.681	0.38	0.008	0.003	0.07	719	678	1,438	4,375
Yr1 Q2	\$12.75	2,000	22.960	0.41	0.012	0.004	0.08	541	279	1,555	4,375
Yr1 Q3	\$12.75	2,700	23.354	0.41	0.012	0.004	0.08	440	199	1,036	4,375
Yr1 Q4	\$12.75	2,700	23.533	0.42	0.013	0.004	0.08	373	190	1,112	4,375
Yr2	\$11.25	10,800	23.050	0.40	0.011	0.004	0.09	1,055	2,333	3,312	17,500
Yr3	\$10.00	10,800	16.338	0.29	0.007	0.003	0.06		2,544	4,156	17,500
Yr4	\$10.00	10,800	20.475	0.36	0.010	0.003	0.07		1,756	4,944	17,500
Yr5	\$9.25	10,800	18.193	0.32	0.011	0.003	0.07		628	6,072	17,500
Yr6	\$6.11	10,025	11.761	0.21	0.005	0.002	0.05			5,924	15,949
Yr7	\$6.11	9,900	11.986	0.21	0.005	0.002	0.05			2,491	12,391
Yr8	\$6.11	9,900	13.752	0.24	0.007	0.002	0.05			718	10,618
Yr9	\$6.11	9,900	16.008	0.28	0.008	0.002	0.06			71	9,971
Yr10	\$6.11	9,900	16.208	0.29	0.010	0.002	0.06			3	9,903
Yr11	\$6.11	9,900	15.940	0.27	0.012	0.003	0.06			1	9,901
Yr12	\$6.11	1,059	12.722	0.21	0.010	0.002	0.05			4	1,063
Totals		113,084	16.965	0.30	0.009	0.003	0.06	3,160	8,637	32,885	157,766

Mineral Reserve is the direct feed ore planned for processing.
Stockpiles are not included in the statement of mineral reserves.

The waste storage facilities are built to at 3 to 1 slopes (18.4 degrees) in order to facilitate reclamation at the end of the mine life. Dump lifts are 75 ft high and are dumped at angle of repose (35.54 degrees) with 120 ft setbacks left between lifts to maintain the 3 to 1 overall angle for future reclamation.

The three waste storage facilities have been segregated by cutoff grades. Waste Storage Facility 1 (WSF 1) contains the highest-grade material. Waste Storage Facility 2 (WSF 2) contains the next highest-grade material. Waste Storage Facility 3 (WSF 3) contains all the remaining material. WSF 1 & 2 are planned so that they could be remined for a future processing opportunity or reclaimed in their current configuration.

Waste Storage Facility 1 is located to the northeast of the mine pit. The location of WSF 1 was selected to be a reasonable haul during the mine life for the storage of the material as well as a short haul distance to the crusher if becomes economical to remine it. WSF 1 will store 3,160 ktons over the mine life.

Waste Storage Facility 2 is located northeast of the crusher and west of WSF 3. WSF 2 will be placed above WSF 3 starting at the 5,500 elevation. The location of WSF 1 was selected to be a reasonable haul during the mine life for the storage of the material as well as a short haul distance to the crusher if becomes economical to remine it. WSF 1 will store 8,637 ktons over the mine life.

Waste Storage Facility 3 is located 3,000 to 4,000 ft east of the pit exit. The storage of waste material over the mine life is 32,885 ktons.

1.17 RECOVERY METHODS

Recent metallurgical testing (MAG, 2013a) confirms the original testing and operational data from the Quintana Minerals operations. Those all lead to the conclusion that there are no deleterious elements in the ore or adverse processing factors that require extraordinary process engineering. The ore is of medium hardness, amenable to copper/moly flotation, gives products that thicken and filter readily and will produce salable copper and moly concentrates.

The process for recovering copper and molybdenum (moly) minerals from the Copper Flat ore is very similar to the one used successfully by Quintana in the 1980s with certain upgrades to reflect the current state-of-the-art in mineral process technology. The process consists of crushing and grinding to a fine size, flotation to concentrate sulfide particles, regrinding and cleaning to develop copper and moly concentrates, thickening and filtering concentrates, and disposal of tailings in a lined surface impoundment.

Crushing and grinding begins with run of mine ore crushed by a gyratory crusher to reduce the size to less than 175 millimeters and conveying the coarse ore to a covered stockpile. Coarse ore reclaimed from beneath the stockpile is conveyed to a 32 ft by 14 ft semi-autogenous (SAG) mill for primary grinding and to a 24 ft by 35 ft ball mill. Oversized pebbles are removed from the SAG mill discharge, crushed, and returned to the SAG mill. The ball mill operates in a closed circuit with hydrocyclones to deliver slurry with 80 percent of the particles less the 140 microns (μ) to the flotation circuit.

Most of the hydrocyclone underflow slurry will report to the ball mill, but a portion of the underflow will be taken through a Knelson-type gravity concentrator circuit to collect gravity-recoverable gold. The gravity separation circuit will consist of two Knelson-type concentrators each of which will have an upstream scalping screen to remove oversize material. The gravity concentrates will pass through magnetic separators for removal of tramp iron and broken grinding media. The tailings from the gravity concentrators will be pumped back to the cyclone feed sump.

Flotation begins by separation of a bulk copper-moly concentrate with a series of six 9,000-cubic foot (ft³) rougher flotation cells. Flotation concentrate is reground in the copper regrind mill in a closed circuit with hydrocyclones. Regrind

cyclone overflow is cleaned and scavenged. Eight, 180- ft³ tank-type cleaner flotation cells, six, 180- ft³ tank-type first cleaner scavenger cells, and two copper second cleaner column cells are used to produce the copper-moly concentrate. Moly will be separated from the copper minerals in a moly flotation circuit. The moly flotation circuit will consist of moly separation (rougher) flotation, moly first cleaner flotation, concentrate regrind, moly second cleaner flotation and moly third cleaner flotation. The result of flotation is a final copper concentrate and a molybdenite concentrate.

Final copper concentrate is a combination of tailings from copper-moly separation flotation and moly first cleaner flotation cells. The copper concentrate is pumped to the copper concentrate thickener, to a copper concentrate stock tank, and to an automatic pressure filter for copper concentrate. Filter cake batches discharge to a covered concentrate stockpile and the copper concentrate will be loaded into highway haul trucks and transported to market.

Moly concentrate from the third moly cleaner column cell flows by gravity to the moly filter feed tank that feeds the moly filtering and drying circuit. Filter cake is discharged to a conveyor that feeds a Holoflite-type hot oil dryer and a screw conveyor to the moly concentrate storage bins and bagged in 2-ton super sacks for shipment by trucks to market.

Water systems for the plant site include freshwater and reclaim water systems. Freshwater is supplied from offsite wells. Water from the wells is pumped through two booster stations to a freshwater tank at the reclaim water reservoir where it can flow by gravity to the reclaim water reservoir or be pumped to the fresh-fire water storage tank. Freshwater from the storage tank flows by gravity to feed the fire water loop, potable water tank system, gland seal water tank, water trucks for dust control, and process use points (e.g. crusher dust suppression, column flotation, reagent mixing, moly plant).

Reclaim water is recovered from thickeners, the tailings storage facility, pit dewatering, storm water, and moisture in the ore. Overflow from the copper-moly, and copper concentrate thickeners and molybdenite concentrate filtering circuit are collected in the reclaim water reservoir. Reclaim water from the tailings (cyclone overflow) thickener, seepage collection sump, and supernatant water pond is pumped to the reclaim water reservoir. Make up water from the freshwater tank is added at the reclaim water reservoir and pumped to reclaim water storage tank for gravity flow to the concentrator usage points.

1.18 PROJECT INFRASTRUCTURE

Significant infrastructure upgrades are necessary for operation of the Copper Flat Project including site facilities such as stockpiles and a new tailing storage facility, road improvements, power lines, and water supply. Stockpiles will be constructed near the crusher (east of the mine pit). The tailing storage facility will be constructed in the location of the existing Quintana Minerals facility. Road improvements include adding turn lanes on Highway 152 for the mine access road, regrading the access road, and relocating approximately 2,500 ft of the access road that is within the new tailings footprint. Railcar loading facilities will also be constructed to ship concentrate. A new substation needs to be constructed to bring 345 kV power from an El Paso Electric transmission main to the Quintana 115kV power line, which needs to be refurbished, and a new power line installed between the mine and freshwater supply wellfield. The freshwater supply system needs to be refurbished with groundwater pumps, pumping stations, and water line improvements.

The Project receives significant benefit from existing infrastructure that remains from the Quintana Minerals operation. The estimated value of the existing infrastructure is \$53.9 Million. Components of the existing infrastructure that will be placed back into service for the new operation are:

- Concrete foundations and structures required for the primary crusher, concentrator, mine substation, truck shop, assay lab and administration building;

- Conveyor tunnels for the crusher discharge belt and the coarse ore stockpile reclaim system;
- Four freshwater wells, two of which are equipped with pumps at this time, and eight miles of 20" steel pipeline to convey freshwater from the well field to the mill site;
- Twelve miles of 115 kV power line and structures connecting the mine substation to the utility power grid;
- Several mine roads, including a 2.5-mile gravel access road connecting the mine site to State Highway 152 and more than 2 miles of mine haul roads and service roads connecting the pit to the crusher, the mine shop and material stockpile areas.
- Other earthworks including mill site and mine shop grading, storm water culverts, and a water diversion structure and channel to divert a major watershed around the pit; and
- Nearly 2 million tons of pre-preproduction stripping to expose the ore body.

1.19 MARKETING STUDIES AND CONTRACTS

No Market Studies were undertaken or purchased in conjunction to the preparation of this Technical Report.

Concentrates produced by the Copper Flat Mine are expected to be clean with no deleterious elements expected in amounts to cause material penalties. The copper concentrates are assumed to be shipped to a smelter in Asia for this report, however additional markets for the sale of concentrates exist in North America and Europe. Molybdenum concentrates are assumed to be saleable in the domestic US market. Gold concentrates are assumed to be shipped to a gold smelter/refinery for final processing.

Concentrate treatment factors used in this report have been compiled by THEMAC using public information sources.

Table 1-8: Smelter Treatment Factors

Copper Concentrates	
Payable Copper (%)	96.5
Payable Gold (%)	94.0
Gold Deduction (troy ounces per dry ton)	0
Payable Silver (%)	90.0
Silver Deduction (troy ounces per dry ton)	0
Treatment Charge	\$85.00
Refining Charge – Cu (per pound)	\$0.085
Refining Charge – Au (per troy ounce)	\$6.00
Refining Charge – Ag (per troy ounce)	\$0.50
Transportation Charges (per wt)	\$158.00
Moisture (%)	8.0
Molybdenum Concentrate	
Payable Molybdenum (%)	99.0
Roasting Charges (per pound)	\$1.50
Transportation Charges (per wet ton)	\$57.00
Moisture (%)	8.0

Copper Flat is presently under development and there are no sales contracts or offtake agreements for mine products currently in place. When operating, the Copper Flat mine will mine and process ores that contain copper, molybdenum, gold, and silver, which will be recovered for sale in the form of copper concentrate, molybdenum concentrate, and gravity gold concentrate as described in Section 17. Copper Flat will sell into a world market for these metals and the

mine will be subject to prevailing smelting and refining costs and metal prices for the mine products. Sales contracts will be developed by THEMAC as financing for the project advances.

1.20 ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT

Environmental and socioeconomic baseline studies were completed as part of prior efforts to reopen the Copper Flat Mine in the late 1990s. Data from these past studies were incorporated as appropriate or otherwise updated in newly completed and on-going studies that have been undertaken in accordance with state and federal standards of data acquisition, quality assurance and reporting.

1.20.1 Studies

Environmental data has been collected by various mining companies in the Copper Flat Mine permit area and surrounding areas of interest since the late 1970s. In 2010, NMCC prepared a Sampling and Analysis Plan (SAP) for collecting environmental data at Copper Flat in accordance with state and federal requirements. Since that time, NMCC has undertaken and completed numerous environmental studies to evaluate existing conditions, including:

- Development of the environmental baseline of the mine permit and surrounding areas.
- Geochemical characterization of the site's potential for acid rock drainage and predictive geochemical modeling for the tailing storage facility, waste rock disposal facility and the future pit lake.
- Completion of an aquifer pumping test to measure response at other supply wells in area to support development of a groundwater pumping and response model for the Copper Flat water supply wells
- Completion of the Federal Environmental Impact Statement and State Environmental Evaluation.

1.20.2 Tailing Disposal and Waste Management

1.20.2.1 Tailings

A new tailings storage facility (TSF) will be constructed at Copper Flat in the location of the former Quintana Resources facility that was constructed and briefly operated in 1981 and 1982. The new TSF will occupy the site of the old facility and will extend approximately 1,000 feet to the east of the old starter dam (the tailings expansion area). While the old Quintana TSF was an unlined facility, the new TSF will be underlain by a geomembrane liner and tailings drainage collection system.

Design studies completed in support of the feasibility level design of the TSF include the following:

- Site exploration and geotechnical testing;
- Tailings characterization;
- Foundation settlement potential evaluation; and
- Consolidation modeling and storage capacity estimation

The new TSF design will be required to comply with the design and dam safety guidelines and regulations of the OSE Dam Safety Bureau. The NMED Groundwater Division will be the permitting authority for the State of New Mexico discharge permit program. NMED has provided guidance on anticipated design requirements for the impoundment liner system, which have been incorporated in the feasibility level design.

Drainage from future tailings will be collected in two separate underdrain systems and routed to the seepage collection pond. Drainage from the impoundment interior will be collected in a continuous underdrain constructed over the geomembrane liner. A separate blanket drain will underlie the tailings dam (dam underdrain).

The seepage collection pond will contain seepage from the impoundment underdrain and the dam underdrain, as well as runoff from the downstream face of the tailings dam.

The TSF reclaim system will consist of a set of submersible turbine pumps placed in the seepage collection pond in a reinforced concrete sump. These pumps will be capable of completely draining the seepage collection pond. Barge mounted pumps will also be placed in the TSF for water reclaim purposes. Reclaimed water will be returned to the process water reservoir. Reclaim pump capacity will be 13,500 gpm from the TSF barge and 4,000 gpm from the seepage reclaim pond. On average, approximately 12,000 to 13,000 gpm of water will be delivered to the TSF with the cyclone overflow and underflow. The estimated average process water recovery rate is 9,215 gpm. The estimated average TSF make-up water requirement will be approximately 3,169 over the life of the project.

The TSF water balance examines reclaim rates for average rainfall conditions. If the site experiences periods where precipitation rates vary from average conditions, reclaim rates and make-up water requirements can also be expected to vary. The water reclaim system is capable of recovering water at an adequate rate to meet make-up water requirements and temporarily reduce demand on external water sources. The water balance does not consider additions from the open pit or waste rock disposal facility stormwater ponds.

1.20.2.2 Waste Rock

Three waste rock disposal facilities (WRDFs) were designed by Independent Mining Consultants (IMC). These WRDFs are designated as WSF-1, WSF-2, and WSF-3. Three runoff and sediment collection ponds will be constructed to contain runoff from the waste rock disposal facilities. Stormwater impoundments will be lined and designed for containment of the runoff volume associated with a 100-year, 24-hour storm event. Stormwater collected in the runoff and sediment collection ponds is pumped to the mill as process water or will have evaporated. At closure, the runoff and sedimentation ponds will be reclaimed. The WRDFs will be covered, graded and vegetated such that surface water runoff from the reclaimed facility will be non-impacted surface water.

Based on the IMC layout, a schedule of capital and reclamation costs for the WRDF site work has been estimated and incorporated in the economic analysis. Capital costs cover topdressing and reclamation cover salvage and stockpiling and construction of conveyance and diversion ditches, runoff and sediment collection pond construction. Reclamation costs address reclamation cover placement and seeding.

1.20.3 Permitting and Bonding

A table listing permits for Copper Flat is shown in Section 1.4.

NMCC has received several required permits including BLM Record of Decision on the Final EIS, U.S. Army Corps of Engineer authorization under the US Clean Water Act, State Air Quality Permit, and State Groundwater Discharge Permit.

Work to obtain a mining permit from the NM Mines and Minerals Division (MMD) is ongoing. The Copper Flat Mine is being permitted as a new mine under Part 6 of the New Mexico Mining Regulations. The NMCC permit application package, which includes construction, operation, reclamation and closure plans, has been submitted to MMD and was determined to be approvable by the Agency in a July 13, 2018 letter to NMCC. On March 31, 2020, the Director of the MMD signed and issued to NMCC an Order to reopen the permit review process and to suspend MMD review of the

reclamation plan cost estimate. NMCC is reviewing the contents of the Order in order to understand the issues presented and develop a response plan.

Financial assurance for reclamation and closure of the Copper Flat Mine requires approval by MMD, NMED and BLM. The Company prepared and submitted to the Agencies a proposed reclamation and closure cost estimate for the life-of-mine plan and has revised the calculations to address Agency comments as the work progressed. In correspondence dated August 21, 2019, MMD and NMED stated that NMCC's response to technical comments on the FA calculations was satisfactory and there were no additional technical comments regarding the calculations. In a separate action on the 3809 Plan of Operations, BLM indicated agreement with the State decision. NMCC has been considering options for the schedule and form of financial assurance according to 19.10.12.1205(C) through 19.10.12.1207-1208 NMAC; however, on March 31, 2020, the Director of the MMD signed and issued to NMCC an Order to reopen the permit review process and to suspend MMD review of the reclamation plan cost estimate. NMCC is currently reviewing the contents of the Order in order to understand the issues presented and develop a response plan.

1.20.4 Social

The Arrowhead Center at New Mexico State University was contracted in September 2011 to complete a socioeconomic study of the Copper Flat Mine project in Sierra County. The final socioeconomic study was completed in August 2012.

The report conclusions are presented in 2012 dollars and indicated that the mine would create over 181 jobs in Sierra County and an additional 1,170 jobs within the state. The report noted that the number of jobs projected to be generated in the county was larger than the average number of unemployed.

The report indicates the mine operation will generate significant monies to the state of New Mexico and Sierra County by payment of severance taxes, processor's tax, property taxes, gross receipts taxes, compensating taxes, personal income tax and corporate tax.

1.20.5 Mine Closure and Reclamation

NMCC has prepared a detailed reclamation and closure plan (Mine Closure Plan) and cost estimate to describe how the mine will be reclaimed to meet the performance standards and requirements of the New Mexico Mining Act described in New Mexico Administrative Code (NMAC) 19.10.6.602.D.(15) and 19.10.6.603; meet closure requirements in the Copper Mine Rules described in 20.6.7.18 NMAC, 20.6.7.33 NMAC, 20.6.7.34 NMAC and 20.6.7.35 NMAC; and meet mine reclamation regulations set forth by the Bureau of Land Management (BLM) (3809.401(b)(3) and 3809.420(b)(3)). The Mine Closure Plan is designed to configure and stabilize the site against erosion; return the site to the current land uses of wildlife habitat, livestock grazing, and recreation; and develop a self-sustaining ecosystem. Key aspects of the Closure Plan are:

1. Salvage topsoil and growth media during construction and operation and store for use in reclamation.
2. Remove and properly dispose of operating materials, supplies, and waste materials.
3. Remove surface facilities, building foundations, and equipment.
4. Regrade disturbed areas for stability and reclamation cover placement.
5. Cover disturbed areas with topsoil and growth media to support vegetation growth.
6. Re-seed disturbed areas with approved vegetation species.
7. Provide stormwater management and erosion protection.

8. Long-term monitoring of groundwater quality and reclamation progress.
9. Reclamation works repair and maintenance.

The Company has calculated the cost to reclaim and perform closure activities at the Copper Flat Mine for the purpose of establishing financial assurance to complete the Mine Closure Plan to meet the requirements of 19.10.12 NMAC and BLM Reclamation Cost Estimation Guidelines. Reclamation and closure costs were compiled by SRK Consulting Inc. under the direction of NMCC. These costs include costs for contractor performance of all reclamation and closure activities outlined in the Mine Closure Plan, rental fees for all equipment required to perform the work, contractor mobilization and demobilization fees, water management services, long-term sampling and monitoring services, and agency management and contract administration costs. The financial assurance calculation for reclamation, closure, and long-term management of the Copper Flat property, including contractor completion, equipment rental, and agency oversight, totals \$71.3 million.

In addition to the financial assurance calculation, the Company has also estimated costs for completing reclamation and closure costs using Company labor and equipment, supplemented by contractors and rental equipment as needed. The calculation includes water management services, long-term sampling and monitoring services, and contingency. The cost estimate for Company performed reclamation, closure, and long-term management of the Copper Flat property, including contingency, totals \$45.4 million.

1.21 CAPITAL AND OPERATING COST ESTIMATES

Capital and operating cost estimates were developed for the Copper Flat Project, as defined in this document. Capital costs were estimated by IMC for the mine, M3 for the processing plant, Golder Associates Inc. (Golder) for the tailing storage facility, Livingston Associates for the water supply system, and T&D services, a New Mexico power engineering consulting firm for the cost to reestablish power.

1.21.1 Operating Cost

The average cash operating cost over the life of the mine is estimated to be \$12.14 per ton of ore processed, excluding the cost of the capitalized pre-stripping. Cash operating cost includes mine operations, process plant operations, site general administrative cost, smelting and refining charges, royalties, and shipping charges. Table 1-9 shows the estimated operating cost by area per metric ton of ore processed, and the total over the life of mine assuming 113.1 million short tons of ore are processed.

Table 1-9: Life of Mine Operating Cost

Cost Center	\$/Ore Ton	\$/lb Cu
Mine	\$2.75	\$0.50
Process Plant	\$5.01	\$0.90
General Administration	\$0.53	\$0.10
Smelting/Refining Treatment	\$3.24	\$0.58
Royalty	\$0.61	\$0.11
Total Operating Cost Before By-Product Revenue	\$12.14	\$2.19
By-Product Revenue		(\$0.84)
Total Operating Cost After By-Product Credits		\$1.35

1.21.2 Capital Cost

The total initial capital cost for Copper Flat is expected to be \$374 million, as shown in Table 1-10.

Table 1-10: Initial Capital

	\$ in millions
Mining (includes preproduction)	\$10.5
Process Plant	\$328.5
Owner's Cost	\$35.0
Total	\$374.0

The total life of mine sustaining capital is estimated to be \$40.9 million. The sustaining capital will be expended during a 12-year period.

1.22 ECONOMIC ANALYSIS

The design basis for the process plant is 10.8 million tons per year. The recoveries are projected to average the following for the life of the mine:

- Copper 93.1%
- Molybdenum 78.1%
- Gold 73.7%
- Silver 82.7%

Metal sales prices used in the evaluation are as follows:

- Copper \$3.25/pound
- Molybdenum \$10.50/pound
- Gold \$1,300.00/ounce
- Silver \$16.00/ounce

Estimated life-of-mine recoveries from the process plant are presented in Table 1-11.

Table 1-11: Recovered Metal Production

Metal	Life of Mine Production
Copper (klbs)	628,015
Molybdenum (klbs)	15,717
Gold (kozs)	227
Silver (kozs)	5,950

The base case Net Income After Tax amounts to \$545 million and indicates that the project has an Internal Rate of Return (IRR) of 20.8 percent with a payback period of 3.3 years. Table 1-12 compares the base case project financial indicators with the financial indicators when different variables are applied. The results show that metal prices have the most impact on the project while variance in the operating cost has the least impact on project economics.

Table 1-12: After-Tax Sensitivity Analysis

		NPV @ 0%	NPV @ 8%	IRR	Payback (yrs)
Base Case		\$545,158	\$235,174	20.8%	3.3
Metal Prices	20%	\$933,871	\$474,972	31.5%	2.4
	-20%	\$146,812	(\$14,141)	6.9%	7.1
Capital Cost	20%	\$481,671	\$173,043	16.3%	3.9
	-20%	\$607,132	\$295,781	26.8%	2.7
Operating Cost	20%	\$387,326	\$136,923	15.7%	3.8
	-20%	\$700,288	\$330,247	25.5%	2.9

1.23 ADJACENT PROPERTIES

Adjacent lands include federal, state and private property. Federal lands are administered by the BLM, and locally there are numerous placer and lode claims on the federal land held by individuals and clubs for recreational gold panning from surface mineral concentrations. There are no other known porphyry copper deposits within 30 miles of the Copper Flat Project.

1.24 PROJECT DEVELOPMENT

Acquisition of water rights, financial assurance, project financing, obtaining the mine permit and tailings dam permit, developing a project development plan, and detailed engineering remain to be completed before making the decision to proceed with construction of the project.

1.25 INTERPRETATION AND CONCLUSIONS

A significant amount of development-level work has been recently completed as part of the overall development and evaluation of the Copper Flat Project. This includes metallurgical testing, environmental and economic assessment, permitting, evaluation of existing foundations and infrastructure, as well as the complete assessment of the project's reserves. The economic analysis provided in this report demonstrates that the project is economically viable.

The reserve model and reserve classification developed for this report meets or exceeds CIM reporting standards. It is believed that the quality and quantity of the data used to develop the reserve model is sufficient and the methodology used to prepare the reserve model is correct. Consequently, it is believed that the reserve model will be a reasonable predictor of the copper and molybdenum grades and tonnages specified in the report's mine plan.

Comprehensive metallurgical testing conducted on the Copper Flat mineralization more than thirty years ago and the process used in the 1982 Quintana Minerals operation are still valid, as confirmed by recent metallurgical test results. The results of the CSMRI pilot plant tests, recent metallurgical testing, and operation of the Quintana concentrator for three and-a-half months in 1982 demonstrate the success of the process and that there are no adverse processing factors that require any extraordinary process engineering or deleterious elements in the Copper Flat ore. The ore is of medium hardness, amenable to copper/moly flotation, gives products that thicken and filter readily and will produce saleable copper and moly concentrates. The conceptual process flow sheet and processing design developed as part of this study is considered "Standard" practice in the mining industry. It is believed that the processing plant is capable

of achieving an average of 10.8 million tons per year and that the process will yield metal recoveries as stated in the report.

The tailings storage facility design developed for this study utilizes best technological practices to ensure containment of the processed tailings. Additionally, the design capacity of the tailings storage facility is sufficient to contain the reserves stated in this report in an environmentally sound manner.

Access to electrical power necessary to sustain the operation as specified in this report is believed to be reasonable and achievable. Access to all of the land within the permit boundary has been secured removing uncertainties concerning the ability to implement the plans in this report in terms of land access.

1.25.1 Risks

The following risk aspects are noted:

- Market risks associated with base metal and precious metal mining projects always exist. The economics of this project used a base case of \$3.25 copper price, 10.50 molybdenum price, \$1,300 gold price and \$16 silver price.
- Capital costs and construction estimates were based on recent prevailing costs in the construction industry, which are presently competitive. If the competitiveness of the construction industry were to change, the cost of the project could increase at the time of actual construction.
- Water supply for the mine must be addressed for the Project to proceed to production. NMCC acquired 7,481 acre-ft/yr of declared water rights consisting of perfected and inchoate rights in 2010; however, the State of New Mexico Third District Court in 2017 ruled that the full amount of inchoate water rights and a portion of the perfected water rights held by the Company were invalid and extinguished. The Company is appealing that decision and also pursuing options to secure the full amount of water needed for the operation.

The following risks with respect to the TSF are noted:

- Unexpected site conditions could impact borrow material availability and construction costs.
- Alternatives for TSF construction are constrained by existing permit limits.
- Buried infrastructure from the old Quintana TSF may impact construction costs.
- Unthickened cyclone overflow delivered at the proposed processing rate will exhibit less than optimum consolidation behavior under field conditions due to the fine-grained nature of the tailings and a high rate of rise inside the TSF. Failure to maximize sand recovery through cyclone plant operation will result in the discharge of whole tailings into the TSF and as a consequence, sand and storage capacity will be lost.
- Variations in the mined ore and the tailings delivered to the impoundment could potentially impact predicted TSF operation and performance.
- Given the current site constraints, mine processing plan and ore reserve, designing a TSF with the capacity to meet tailings storage requirements places a high demand on the availability of cyclone underflow sand for dam construction. The operator will be required to commit to continuous cyclone plant operation and rigorous cyclone plant operating procedures.

1.25.2 Opportunities

The following opportunity aspects are noted:

- Upside market potential associated with base metal and precious metal pricing exists.
- Other activities as discussed in the recommendations section of this report, once implemented, have the potential to improve Project economics.
- The economic model forming the basis of the study assumes all mill processing equipment is purchased new. However, the standard mining and ore treatment methods considered create an opportunity to reduce project capital costs through the utilization of used, refurbished equipment or equipment that becomes available through canceled orders.
- The study assumes mining is self-performed with leased mining equipment. An opportunity to realize a benefit in the overall operation may exist through employment of a contract miner. Mining costs are typically increased with a contract miner; however, offsetting benefits may be realized by contracting the mine operations and mine maintenance functions to an outside party.

The following opportunities with respect to the TSF are noted:

- Initial earthwork requirements could be substantially reduced if alternative sources for construction borrow and reclamation cover materials could be developed outside the TSF footprint.
- The operator should monitor tailings consolidation and post deposition density during operations. If tailings consolidation rates exceed predictions, it may be possible to decrease cyclone plant utilization, reduce the ultimate height of the TSF, and reduce sand demand.

There are several tailings distribution system design features that will facilitate high cyclone plant utilization.

- The plant will contain 20 cyclones in a single cluster with 16 cyclones required to process the tailings inflow. There will be extra cyclones that can be brought online if one fails. Normal maintenance of the cyclones can be undertaken while the plant is in operation.
- Cyclones have no moving parts and while subject to wear they are relatively maintenance free.
- It is assumed that the operator will monitor cyclone plant conditions and conduct maintenance of other cyclone plant components coincident with process facility maintenance shutdowns.
- If the cyclone plant cannot be operated for short periods of time, discharge from the flotation plant can be routed to an emergency pond for temporary storage.
- The cyclone underflow distribution system has two legs, one routed southward and one northward around the TSF. Each leg is capable of transporting the entire cyclone underflow and can be operated independently. Underflow discharge can be maintained in one leg while the other is serviced or relocated. The availability of two underflow distribution pipes will facilitate continuous sand placement on the dam.
- Replacement of individual cyclones is a relatively easy process. The operator should have spares on site to cover this eventuality.

1.26 RECOMMENDATIONS

Because the economic analysis provided in this report demonstrates that the project is economically viable, the THEMAC management team should focus on further development and evaluation of the project including moving forward on detailed engineering. Costs for detailed engineering estimated at \$14.7 million are included in the feasibility study capital cost estimate.

1.26.1 Mining and Modeling

THEMAC should consider the following regarding mining and modeling:

- 1) Geologic interpretation of rock type and structure should continue as detailed engineering advances. Improved definitions of rock and structure could improve grade estimation and prediction of process response.
- 2) Communication should be continued between the project geology team and the process design engineers. Updated understanding of geology could impact process design and testing in the future.
- 3) Geotechnical work in the pit may be considered as detailed engineering advances. Improved understanding of pit slope stability could have an impact on future pit designs.

1.26.2 Metallurgy

Metallurgical testing was conducted as part of the feasibility study, as presented in Section 13. The results of that work in conjunction with previous testing and review of production data from the previous operation of the mine are deemed to be sufficient to support development of the project. No additional metallurgical testing is recommended at this time.

1.26.3 Tailings Storage Facility

No additional testing work is recommended at this time. Detailed engineering of the TSF should include the development of an operating plan that will facilitate meeting cyclone plant operation and sand production requirements.

1.26.4 Environmental

The mine waste dumps will be constructed to facilitate final grading for reclamation. During detailed operating plan development, consider and advance strategies to complete final grading, topsoil spreading and seeding concurrently with mining activities.

1.26.5 Project Development

Proceed with development of a project execution plan to guide activities leading to and initiating project construction.

1.26.6 Water Resources

Secure a water supply in full amount needed to support the operation.

1.27 REFERENCES

All supplemental reference documentation is available in NMCC's corporate offices. See Section 27 for a complete list of references for this study.

2 INTRODUCTION

2.1 PURPOSE

M3 Engineering & Technology Corporation (M3) has been commissioned by THEMAC Resources Group Limited (THEMAC) to prepare a Feasibility Study for the Copper Flat Copper/Molybdenum Project (Copper Flat or the Project) compliant with Canadian Securities Administrators (CSA) National Instrument 43-101 (NI 43-101). The Project is owned and operated by New Mexico Copper Corporation (NMCC), a wholly owned subsidiary of THEMAC Resources Group Limited. NMCC was incorporated in New Mexico in July 2009. Copper Flat is located in South Central New Mexico, near the town of Hillsboro, approximately 150 miles south of Albuquerque, and approximately 20 miles southwest of Truth or Consequences (straight-line distances).

This report has been prepared in accordance with the guidelines provided in NI 43-101 Standards of Disclosure for Mineral Projects and conforms to Form 43-101F1 for technical reports. The Resource and Reserves definitions are as set forth in the Appendix to Companion Policy 43-101CP, CIM – Definitions Adopted by CIM Council, May 10, 2014. THEMAC may also use this Feasibility Study Report for any lawful purpose to which it is suited. The intent of this report is to provide the reader with a comprehensive review of the potential economics of this mining operation and related project activities, and to provide recommendations for future work programs to advance the Project.

The Copper Flat Project is a brownfield project located in the Hillsboro Mining District (also known as the Las Animas Mining District), which has a history of gold and silver mining dating back to 1877 and copper mining back to 1911 (McLemore, 2001). Modern exploration activities date back to 1952 and ultimately led to the development and construction of a 15,000 ton per day commercial copper mining operation in 1982, which was operated by Quintana Mining Corporation (Quintana). Low copper prices and high interest rates led to the cessation of the Quintana Mill after 3 months of operation; however, the Quintana mill produced 7.4 million pounds of copper during this period (Raugust, 2003). A significant amount of infrastructure was left in place when the mine was reclaimed in 1986. The remaining Quintana infrastructure is described and quantified in Section 21.2.4 of this report. Subsequent to Quintana, Alta Gold Co. of Nevada implemented permitting activities to reactivate the Copper Flat Mine, which was unsuccessful due to the financial failure of the company in 1999, but not before significant environmental and other studies were completed. NMCC has obtained copies of several of the studies and other information prepared by Alta Gold for its use.

Building on historic information and experience, NMCC carried out due diligence on the Project. Steps in the due diligence process are outlined in several NI 43-101 Technical Reports, listed below and available on the SEDAR website operated by the Canadian Securities Administrators (www.sedar.com).

- A preliminary economic assessment of the project was prepared for THEMAC and summarized in a NI 43-101 Technical Report prepared by SRK dated June 30, 2010 (SRK, 2010).
- A prefeasibility study of the project was prepared for THEMAC and summarized in a NI 43-101 Technical Report prepared by M3 dated August 22, 2012 (M3, 2012a).
- A feasibility study of the project was prepared for THEMAC and summarized in a NI 43-101 Technical Report prepared by M3 dated November 21, 2013 (M3, 2013).

2.2 SOURCES OF INFORMATION

The sources of information include data and reports supplied by THEMAC personnel, and documents referenced in Section 27. M3 used its experience to determine if the information from previous reports was suitable for inclusion in this report and adjusted information that required amending. Revisions to previous data were based on research, recalculations and information from other projects. The level of detail utilized is appropriate for this level of study.

This Feasibility Study is based on the following sources of information.

- Personal inspection of the Copper Flat site and surrounding area.
- Technical information provided to M3 by THEMAC through various reports.
- Information provided to M3 by Independent Mining Consultants (IMC) related to resource model generation and the mine plan.
- Budgetary quotes from vendors for engineered equipment.
- Information provided to M3 by Golder Associates, Inc. (Golder) concerning the tailings disposition and water reclamation design.
- Technical and cost information provided by Tri-State Generation and Transmission Association, Inc. (Tri-State) concerning power supply for the project.
- Technical and economic information subsequently developed by M3 and associated consultants.
- Information provided by other experts with specific knowledge and expertise in their fields as described in Section 3 of this report, Reliance on Other Experts.
- Additional information obtained from public domain sources.

The information contained in this report is based on documentation believed to be reliable. Information utilized in this report will either be retained in THEMAC's offices in New Mexico or will be readily available from THEMAC's consultants project files subject to an appropriate level of confidentiality and non-disclosure. The recommendations and conclusions stated in this report are based on information provided to M3.

2.3 LIST OF QUALIFIED PERSONS

The individuals who have provided input to this Feasibility Study have extensive experience in the mining industry and are members in good standing of appropriate professional institutions. Richard K Zimmerman, R.G. SME-RM (M3) is the primary Qualified Person (QP) for this report, especially geological setting and mineralization, and deposit types (Sections 1-3, 7-9, 19, 24, 25, 26.4, 26.5, 26.6 and 27). John Marek, P.E. (IMC), is the QP for drilling, sample analysis, data verification, resource and reserve estimation, and mining methods and costs (Sections 10-12, 14-16, 21.2, 21.3.1, and 26.1). Thomas Drielick, Principal Metallurgist (M3), is the QP for the mineral processing, metallurgical testing, recovery methods, process plant operating and capital costs, and economic analysis (Sections 13, 17, 21.1, 21.3.2, 21.3.4, 22, and 26.2). Jeffrey C. Smith, P.E. SME-RM (THEMAC) is the QP for property, accessibility, history, infrastructure, environmental studies and permitting, and adjacent properties (Sections 4, 5, 6, 18, 20, and 23). David Kidd, P.E. (Golder) is the QP for tailings design and costs (Sections 20.2, 21.3.3, 25.2.1, 25.3.1 and 26.3). Certificates for each QP are provided in Appendix A.

The following authors are responsible for the sections as listed in Table 2-1.

Table 2-1: List of Qualified Persons

Author	Company	Designation	Section Responsibility
Richard K Zimmerman	M3 Eng.	R.G. SME-RM	1, 2, 3, 7, 8, 9, 19, 24, 25, 26.4, 26.5, 26.6, 27
Jeffrey C. Smith	THEMAC	P.E.	4, 5, 6, 18, 20, 23
John Marek	IMC	P.E.	10, 11, 12, 14, 15, 16, 21.2, 21.3.1, 26.1
Thomas L. Drielick	M3 Eng.	P.E.	13, 17 (M3 drawings), 21.1, 21.3.2, 21.3.4, 22, 26.2
David A. Kidd	Golder	P.E.	20.2, 21.3.3, 25.2.1, 25.3.1, 26.3

2.4 SITE VISIT & PERSONAL INSPECTIONS

Richard K Zimmerman, SME-RM visited the site on January 31, 2013 with other M3 personnel including Matt Murray and Tim Reiter, who designed the general arrangements; Shelby Madrid, the civil engineer for the project; Shannon Orr, the lead estimator; and Oscar Avilucea; the structural lead. Peter Olszewski, who was responsible for the water supply system design, visited the site on January 15, 2013. During the site visit, M3's inspection included the access road, previous mill site area, waste dumps, the top of the primary crusher structure, most of the foundation of the former concentrator building, and the floor slab of the former truck shop.

Jeffrey C. Smith maintains an office at the Copper Flat and is onsite on a regular basis and was at the site as recently as the week of March 23, 2020. There have been no changes in site conditions since the last technical report.

John Marek of IMC visited the Copper Flat Project September 7-8, 2011. The storage facilities for drill core were visited, and historic pulp data were reviewed. During that visit, IMC observed the following procedures in progress:

- Diamond Drilling
- Core Photography
- Core Geotechnical Logging
- Core Geologic Logging
- Core Sawing for Sample Shipment
- Sample Handling and Labeling Procedures

The visit provided familiarity with the local terrain and site conditions for mine and waste storage design. Observation of the primary rock types in pit wall exposure and in core with guidance from the Copper Flat site geologists was also accomplished by IMC personnel. Additional data regarding drillhole locations, orientations, and logging information was gathered during the visit that was integrated into the data base for determination of mineral resources and mineral reserves.

David Kidd of Golder has visited the project site. His most recent visit to the site was on March 2, 2012. His visits have included surface examinations of the proposed location of the tailings storage facility and surrounding areas that may be appropriate for obtaining materials for construction of the facility and reclamation cover.

2.5 TERMS OF REFERENCE AND UNITS OF MEASURE

This Feasibility Study Report update is intended for the use of THEMAC for the further development and advancement of Copper Flat into the detailed design stage. This report provides a mineral resource estimate, a classification of

resources in accordance with the Canadian Institute of Mining, Metallurgy and Petroleum (CIM) classification system and an evaluation of the property to provide a current view of the potential project economic outcome.

Imperial units (American System) of measurement are used in this report. Abbreviations are given in Section 2.5.4. All monetary values are in U.S. dollars (\$) unless otherwise noted.

2.5.1 Mineral Resources

The mineral resources and mineral reserves have been classified according to the "CIM Definition Standards on Mineral Resources and Mineral Reserves (November 2010). Accordingly, the Resources have been classified as Measured, Indicated or Inferred, and the Reserves have been classified as Proven, and Probable based on the Measured and Indicated Resources as defined below.

A Mineral Resource is a concentration or occurrence of natural, solid, inorganic or fossilized organic material in or on the Earth's crust in such form and quantity and of such a grade or quality that it has reasonable prospects for economic extraction. The location, quantity, grade, geological characteristics and continuity of a Mineral Resource are known, estimated or interpreted from specific geological evidence and knowledge.

An 'Inferred Mineral Resource' is that part of a Mineral Resource for which quantity and grade or quality can be estimated on the basis of geological evidence and limited sampling and reasonably assumed, but not verified, geological and grade continuity. The estimate is based on limited information and sampling gathered through appropriate techniques from locations such as outcrops, trenches, pits, workings and drillholes.

An 'Indicated Mineral Resource' is that part of a Mineral Resource for which quantity, grade or quality, densities, shape and physical characteristics can be estimated with a level of confidence sufficient to allow the appropriate application of technical and economic parameters, to support mine planning and evaluation of the economic viability of the deposit. The estimate is based on detailed and reliable exploration and testing information gathered through appropriate techniques from locations such as outcrops, trenches, pits, workings and drillholes that are spaced closely enough for geological and grade continuity to be reasonably assumed.

A 'Measured Mineral Resource' is that part of a Mineral Resource for which quantity, grade or quality, densities, shape, physical characteristics are so well established that they can be estimated with confidence sufficient to allow the appropriate application of technical and economic parameters, to support production planning and evaluation of the economic viability of the deposit. The estimate is based on detailed and reliable exploration, sampling and testing information gathered through appropriate techniques from locations such as outcrops, trenches, pits, workings and drillholes that are spaced closely enough to confirm both geological and grade continuity.

2.5.2 Mineral Reserves

A Mineral Reserve is the economically mineable part of a Measured or Indicated Mineral Resource demonstrated by at least a Preliminary Feasibility Study. This Study must include adequate information on mining, processing, metallurgical, economic and other relevant factors that demonstrate, at the time of reporting, that economic extraction can be justified. A Mineral Reserve includes diluting materials and allowances for losses that may occur when the material is mined.

A 'Probable Mineral Reserve' is the economically mineable part of an Indicated, and in some circumstances a Measured Mineral Resource demonstrated by at least a Preliminary Feasibility Study. This Study must include adequate information on mining, processing, metallurgical, economic, and other relevant factors that demonstrate, at the time of reporting, that economic extraction can be justified.

A 'Proven Mineral Reserve' is the economically mineable part of a Measured Mineral Resource demonstrated by at least a Preliminary Feasibility Study. This Study must include adequate information on mining, processing, metallurgical, economic, and other relevant factors that demonstrate, at the time of reporting, that economic extraction is justified.

2.5.3 Glossary

Term	Definition
Assay	The chemical analysis of mineral samples to determine the metal content.
Breccia	Rocks composed of large, sharp-angled fragments embedded in a fin-grained matrix of smaller particles or mineral cement.
Capital Expenditure	All other expenditures not classified as operating costs.
Composite	Combining more than one sample result to give an average result over a larger distance.
Concentrate	A metal-rich product resulting from a mineral enrichment process such as gravity concentration or flotation, in which most of the desired mineral has been separated from the waste material in the ore.
Crushing	Initial process of reducing ore particle size to render it more amenable for further processing.
Cut-off Grade (CoG)	The grade of mineralized rock, which determines as to whether or not it is economic to recover its gold content by further concentration.
Dilution	Waste, which is unavoidably mined with ore.
Dike	A sheet of rock that that formed in a crack in a pre-existing rock body. It is a type of tabular or sheet intrusion, that either cuts across layers in a planar wall rock structures, or into a layer or unlayered mass of rock.
Dip	Angle of inclination of a geological feature/rock from the horizontal.
Fault	The surface of a fracture along which movement has occurred.
Gangue	Non-valuable components of the ore.
Graben	An elongated block of the earth's crust bounded by faults that has dropped relative to the surrounding area.
Grade	The measure of concentration of copper within mineralized rock.
Haulage	A horizontal underground excavation which is used to transport mined ore.
Horst	A block of the earth's crust bounded by normal faults that is raised relative to the surrounding area.
Hydrocyclone	A process whereby material is graded according to size by exploiting centrifugal forces of particulate materials.
Igneous	Primary crystalline rock formed by the solidification of magma.
Kriging	An interpolation method of assigning values from samples to blocks that minimizes the estimation error.
Lithological	Geological description pertaining to different rock types.
LOM	Life-of-Mine.
LRP	Long Range Plan.
Material Properties	Mine properties.
Milling	A general term used to describe the process in which the ore is crushed and ground and subjected to physical or chemical treatment to extract the valuable metals to a concentrate or finished product.
Mineral/Mining Lease	A lease area for which mineral rights are held.
Mining Assets	The Material Properties and Significant Exploration Properties.

Porphyry	Igneous rock consisting of large-grained crystals (phenocrysts) such as quartz and feldspar scattered in a fine-grained groundmass.
Rift Valley	A linear lowland between several highlands or mountain ranges created by the action of a geologic rift or fault.
ROM	Run-of-Mine.
Sedimentary	Pertaining to rocks formed by the accumulation of sediments, formed by the erosion of other rocks.
Stratigraphy	The study of stratified rocks in terms of time and space.
Strike	Direction of line formed by the intersection of strata surfaces with the horizontal plane, always perpendicular to the dip direction.
Sulfide	A sulfur bearing mineral.
Sustaining Capital	Capital estimates of a routine nature, which is necessary for sustaining operations.
Tailings	Finely ground waste rock from which valuable minerals or metals have been extracted.
Thickening	The process of increasing the solids content of a slurry.
Total Expenditure	All expenditures including those of an operating and capital nature.
Variogram	A statistical representation of the characteristics (usually grade).

2.5.4 Copper Flat Rock Types

Term	Definition
Andesite	Volcanic flow rock surrounding the Copper Flat, Quartz Monzonite ore body, generally not mineralized, but does contain localized sulfides in the form of pyrite.
Breccia Pipe	Copper Flat Ore - Best described as a crackle breccia, which consists of largely subangular blocks of mineralized Quartz Monzonite, with locally abundant mineralized latite sourced from local dikes.
Biotite Breccia	Copper Flat Ore – One of two types of Quartz Monzonite Breccia with higher percentage of biotite in the matrix groundmass between the Quartz Monzonite rock fragments.
Chalcopyrite	Sulfide mineral which is the primary source of copper in the Copper Flat ore body. It is composed of copper, iron, and sulfur.
Diabase	Minor intrusive igneous rock local mapped in contact with Quartz Monzonite.
Feldspar Breccia	Copper Flat Ore - One of two types of Quartz Monzonite Breccia with higher percentage of quartz and feldspar in the matrix groundmass between the Quartz Monzonite rock fragments. Also known as Quartz Feldspar Breccia.
Latite	Igneous intrusive rock that occur at Copper Flat as dikes that primarily trend northwest or northwest.
Quartz Monzonite	Copper Flat Ore – Primary rock type in the Copper Flat ore body. The Quartz Monzonite hosts mineralization by pyrite, chalcopyrite, molybdenite, minor bornite, minor gold, and minor silver.
Pyrite	Sulfide mineral composed of iron and sulfur.

2.5.5 Abbreviations

Abbreviation	Unit or Term
a	ampere
AA	atomic absorption spectrophotometry
ABA	acid-base accounting
ACOE	US Army Corps of Engineers
Ag	silver
a/m ²	amperes per square meter
ANFO	ammonium nitrate fuel oil
APE	area of potential effect
ARD	acid rock drainage
ARDML	acid rock drainage and metal leaching
AST	above-ground storage tank
ASTM	American Society for Testing Materials
Au	gold
CuEq	copper equivalent grade
BATF	US Bureau of Alcohol Tobacco and Firearms
BDR	Baseline Data Report
bft ³	billion cubic feet (feet)
BLM	US Department of the Interior, Bureau of Land Management
CERCLA	Comprehensive Environmental Response, Compensation, and Recovery Act
CoG	cut-off grade
cfm	cubic feet per minute
CFR	Code of Federal Regulations
CIM	Canadian Institute of Mining, Metallurgy, and Petroleum
CPA	Certified Public Accountant
CRec	core recovery
Cu	copper
°	degree (degrees)
dia.	diameter
DOT	US Department of Transportation
EA	Environmental Assessment
EIS	Environmental Impact Statement
EMP	Environmental Management Plan
ESA	Endangered Species Act
°F	degrees Fahrenheit
FA	fire assay or financial assurance
famsl	feet above mean sea level
FCC	US Federal Communications Commission
FLPMA	Federal Land Policy Management Act
FOS	factor of safety
ft	foot (feet)
ft ²	square foot (feet)
ft ³	cubic foot (feet)
ft ³ /st	cubic foot (feet) per short ton
gal	gallon
gpm	gallons per minute

HDPE	height density polyethylene
hp	horsepower
ICP	inductively couple plasma
ID2	inverse-distance squared
ID3	inverse-distance cubed
ILS	intermediate leach solution
IM	isolated manifestation
in	inch
koz	thousand troy ounces
kst	thousand short tons
kst/d	thousand short tons per day
kst/y	thousand short tons per year
kV	kilovolt
kW	kilowatt
kWh	kilowatt-hour
kWh/st	kilowatt-hour per short ton
lb	pound
LLDDP	linear low density polyethylene plastic
LCRS	leakage collection and recovery system
LRGB	Lower Rio Grande Basin
LoM	life-of-mine
Ma	Million years ago
mi	mile
mi ²	square mile
Mlbs	million pounds
MARP	Mining Act Reclamation Program
MDA	maximum design acceleration (earthquake)
MMD	New Mexico Dept. of Energy, Minerals and Nat. Res. - Mining and Minerals Division
MME	Mine & Mill Engineering
MORP	Mine Operation and Reclamation Plan
Mo	molybdenum
Moz	million troy ounces
MPO	Mine Plan of Operations
MSHA	Mine Safety and Health Administration
Mst	million short tons
Mst/y	million short tons per year
MW	million watts
MVA	megavolt ampere
m.y.	million years
NAG	net acid generating
NEPA	National Environmental Policy Act of 1969 (as Amended)
NGO	non-governmental organization
NMAC	New Mexico Administrative Code
NMCC	New Mexico Copper Corporation
NMDOT	New Mexico Department of Transportation
NMED	New Mexico Environment Department
NMEMNRD	New Mexico Department of Energy, Minerals, and Natural Resources
NMGFD	New Mexico Game and Fish Department

NMOSE	New Mexico Office of the State Engineer
NI 43-101	Canadian National Instrument 43-101
NOAA	National Oceanic and Atmospheric Administration
NPDES	National Pollutant Discharge Elimination System
NRHP	National Register of Historic Places
NSR	net smelter return
OHWM	ordinary high-water mark
OSE	New Mexico Office of the State Engineer
oz	troy ounce
oz/st	troy ounce per short ton
%	percent
QP	NI 43-101 Qualified Person
PAG	potentially acid-generating
PAP	Permit Application Package
pcf	pounds per cubic foot
PCPE	perforated corrugated polyethylene
PLS	pregnant leach solution
PGA	peak ground acceleration
PMF	probable maximum flood
POO	Plan of Operations
ppb	parts per billion
ppm	parts per million
psi	pounds per square inch
QA/QC	quality assurance/quality control
RC	rotary circulation drilling
RoM	run-of-mine
RQD	Rock Quality Designation
SAP	sampling and analysis plan
SARA	Superfund Amendments and Reauthorization Act
SCP	spill contingency plan
SEC	U.S. Securities & Exchange Commission
sec	second
SG	specific gravity
SHPO	New Mexico State Historic Preservation Office
SLERA	Screening Level Ecological Risk Assessment
SPT	Standard Penetration Test
St	short ton (2,000 pounds)
st/h	short tons per hour
st/d	short tons per day
st/y	short tons per year
T	tonne (metric ton) (2,204.6 pounds)
TC-RC	treatment charges – refining charges, which are smelter charges
TDS	total dissolved solids
TPQ	threshold planning quantity
TSF	tailings storage facility
TSP	total suspended particulates
μ	micron or microns, micrometer or micrometers
UAA	Use Attainability Analysis

USFWS	US Fish and Wildlife Service
USGS	US Geological Survey
v	volt
VFD	variable frequency drive
W	watt
WOTUS	Waters of the U.S.
WRDF	waste rock disposal facility
XRD	x-ray diffraction
Y or y	year
yd ²	square yard
yd ³	cubic yard

3 RELIANCE ON OTHER EXPERTS

The Copper Flat Technical Report relies on reports and statements from legal and technical experts who are not Qualified Persons as defined by NI 43-101. The Qualified Persons responsible for preparation of this report have reviewed the information and conclusions provided and determined that they conform to industry standards, are professionally sound, and are acceptable for use in this report.

3.1 PROPERTY OWNERSHIP AND TITLE

Legal review of the Copper Flat property ownership and title was completed by Mr. Mark K. Adams, an attorney with the New Mexico law firm Rodey, Dickason, Sloan, Akin & Robb, PA (the Rodey Law Firm). Mr. Adams review and legal opinion are summarized in a June 2013 report titled *Updated Title Report - Copper Flat Properties - Sierra County, New Mexico* (Adams, 2013). In a letter prepared on October 28, 2013, Mr. Adams summarized the content of the June 2013 Updated Title Report and concluded that on the basis of his examination, NMCC owns a 100% interest in the mineral and surface estates in the patented mining claims, other patented lands, and unpatented mining claims and millsites included in the Copper Flat Properties, subject only to the royalties and advance royalties described in Part B and C of the Updated Title Report (Adams, 2013b). Mr. Adams updated the assessment of the property status in a letter dated February 6, 2020 (Adams, 2020). Detail regarding NMCC's landownership and title are described in Section 4.4 of this report. THEMAC is in possession of the Updated Title Report.

3.2 ROYALTIES

Interpretation of royalty obligations for economic modeling was provided by Mr. Mark K. Adams of the Rodey Law Firm. The royalty obligations are discussed in the June 2013 Updated Title Report prepared by Mr. Adams as discussed in Section 3.1 of this report (Adams, 2013). The royalty obligation details are also summarized in Section 4.4 of this report. THEMAC is in possession of all option and purchase agreements as well as correspondence with Mr. Adams that defines the royalty obligations.

3.3 TAXES

Examination and interpretation of New Mexico resource tax obligations for economic modeling was provided by Ms. Bobbi Hayes, a Certified Public Accountant (CPA) with Accounting and Consulting Group, LLP (ACG), a New Mexico accounting firm. ACG's analysis is documented in a memorandum dated May 16, 2013 (ACG, 2013).

THEMAC also researched the utilization of a local Industrial Revenue Bond (IRB) to be issued by Sierra County to offset the New Mexico Gross Receipts tax obligations towards certain tangible personal equipment which includes eligible equipment and machinery to be installed and operated at the mine. The applicability of utilizing an IRB was evaluated by Alan Hall, J.D. of the Rodey Law Firm in a memorandum dated October 1, 2013 (Hall, 2013). The capital equipment review was performed by Marcus Mims, CPA of CliftonLarsonAllen LLP (Clifton) (Mims, 2013). By segregating IRB-qualifying equipment from disqualifying equipment, Clifton quantified the potential tax benefit dependent on issuance of an IRB by Sierra County. THEMAC is in possession of supporting tax and IRB information provided by AGC, the Rodey Law Firm and Clifton.

3.4 ENVIRONMENTAL COMPLIANCE

Stuart Butzier, Vice President at the law firm of Modrall Sperling Roehl & Sisk PA (Modrall Sperling) has provided legal assistance concerning permitting and environmental issues. Mr. Butzier issued an opinion that "NMCC's management, and staff and NMCC's technical consultants have maintained compliance with all state and federal environmental compliance and permitting requirements" in a letter dated March 19, 2020 (Butzier, 2020).

4 PROPERTY DESCRIPTION AND LOCATION

The Copper Flat Project is a copper-molybdenum porphyry deposit located in Sierra County, South Central New Mexico. In 1982, Quintana Minerals Corporation (Quintana Minerals) brought the property into production as an open pit mine with a mill and concentrator (rated at 15,000 short tons per day [st/d]). The mine was in commercial production for three and a half months, but operations were halted when copper prices declined. In 1986, the mine buildings and equipment were removed and sold, however a considerable number of building foundations, roads and other infrastructure remain in place at the site.

NMCC's Copper Flat property totals approximately 5,077 acres of contiguous and noncontiguous mining claims, mill sites and fee lands. NMCC has outlined 2,190 contiguous acres within this property as the permit area, which fully encompasses the planned facility and operations and that forms the basis of the Company's permit applications. The permit area includes patented and unpatented mining claims and fee land. NMCC controls 100% of the property within the permit area.

NMCC's acquired the real property at Copper Flat in two phases. NMCC entered into an option and purchase agreement with the owner of the mining claims and other real property in 2009, which required a series of payments to fully exercise the option. NMCC completed the final option payment in May 2011 and acquired the mineral rights and approximately 3,815 acres of patented mining claims, unpatented mining claims and mill sites, and other real property. In a separate transaction signed in 2013, the Company acquired an additional 1,262 acres of private property in the immediate project area. The 2013 purchase agreement requires annual principle and interest payments that are ongoing and are expected to continue until 2023 when the balance is due.

The property occupied by the project is a mix of private property and public land managed by the U.S. Department of Interior Bureau of Land Management (BLM).

4.1 LOCATION

Copper Flat is in the Hillsboro Mining District in South Central New Mexico, in Sierra County. The Hillsboro Mining District is also identified as the Las Animas Mining District in some references. The center of the mineralization is at approximately 32.970300N latitude, 107.533527W longitude. The Project is approximately 150 miles south of Albuquerque, New Mexico and approximately 20 miles southwest of Truth or Consequences, New Mexico (straight line distances). Access from Truth or Consequences is by 24 miles of paved highway and 3 miles of all-weather gravel road. The Project location is shown in Figure 4-1.

The property is within the USGS Hillsboro NM quadrangle, north of New Mexico State Highway 152 between the communities of Caballo and Hillsboro.

Project lands occupy all or parts of Sections 30 and 31, Township 15 South, Range 6 West; Sections 22 to 27 and Sections 34 to 36, Township 15 South, Range 7 West; Section 6, Township 16 South, Range 6 West; and Sections 1 and 2, Township 16 South, Range 7 West, all of the New Mexico Principal Meridian.

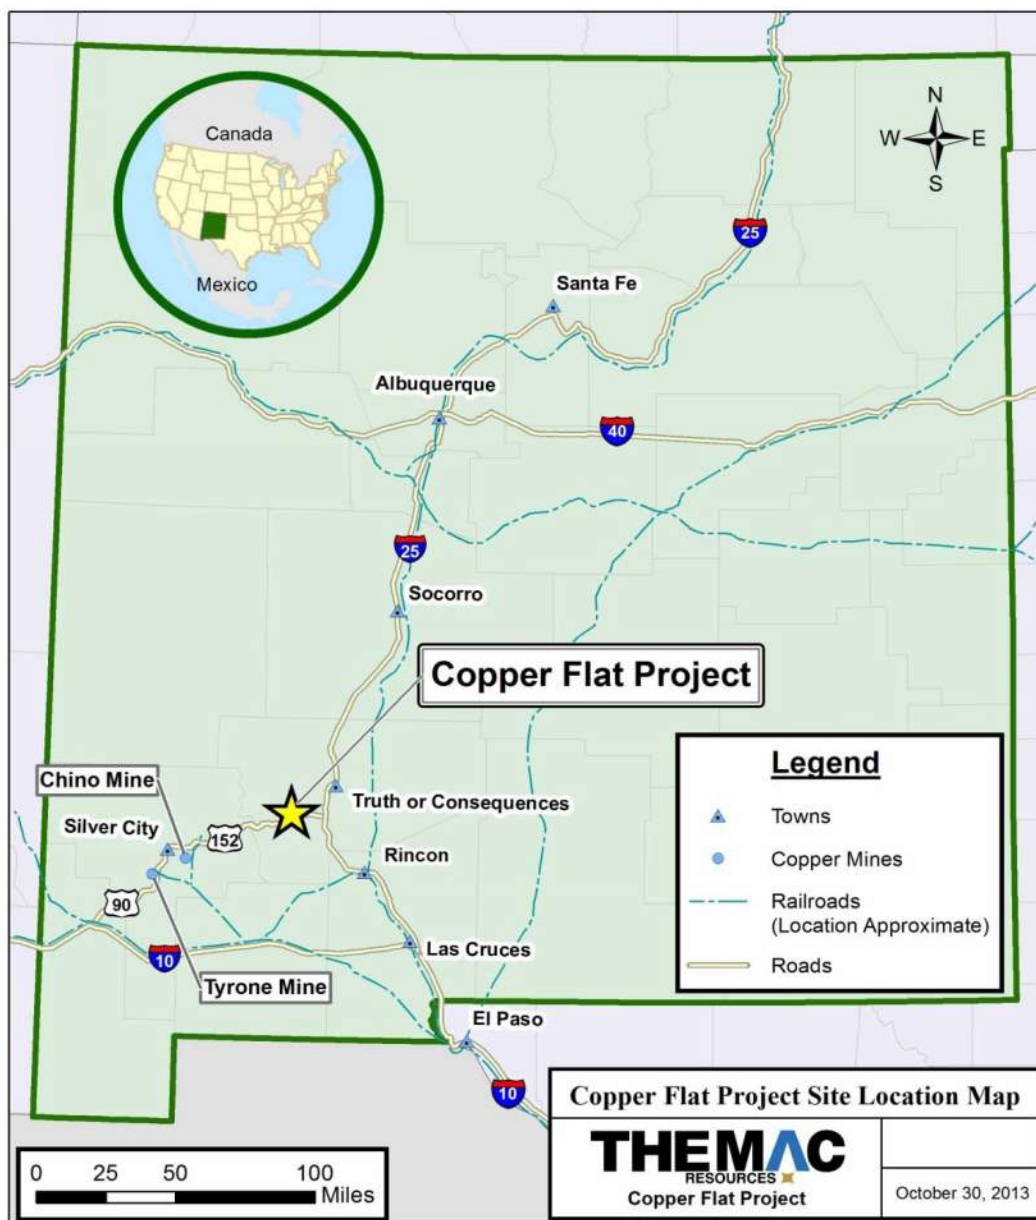


Figure 4-1: Project Location Map

4.2 MINERAL TENURE

Federal mining law requires holders of unpatented mining claims to pay an annual maintenance fee for each claim or site in lieu of the annual assessment work, or to submit a maintenance fee waiver certificate. The required maintenance fee for the upcoming year or maintenance fee waiver certificate is to be filed with the BLM on or before September 1st of each year. The annual BLM filing is to include a document listing the claim and site name(s) and the BLM serial number(s) for which the fees are being paid. New Mexico state law also requires the owner of unpatented mining claims to file a *Notice of Intention to Hold* with the clerk of the county in which the claims are located each year prior to December 31. BLM required maintenance fees for holding the Copper Flat lode and placer mining claims and mill sites have been paid annually and the required *Notice of Intention to Hold* has been recorded annually with Sierra County,

NM. Annual maintenance payments and County recording documents for NMCC unpatented mining claims and sites are current through the effective date of this report (Adams, 2020).

Patented claims and other fee lands are subject to county and state property taxes, paid annually. NMCC property tax payments are current through the effective date of this report (Adams, 2020).

The Project includes 29 patented mining claims, 202 unpatented lode mining claims, 41 unpatented placer mining claims, and 9 unpatented mill sites in contiguous and noncontiguous claim blocks. In addition to the mining claims and mill sites, the Project includes 22 fee land parcels totaling approximately 1,633 acres.

Approximately 30 of the unpatented mining claims are located on lands patented under the federal Stock Raising Homestead Act, whereby NMCC owns the claims and right to explore for development and mine minerals, and the surface is owned by another non-governmental party.

Unpatented claims located before 2009 and the unpatented mill sites were staked using compass and chain traverses and later surveyed. Unpatented claims located in 2009 and thereafter were staked using a Trimble GPS ground station and a handheld GPS. All fee lands were surveyed by licensed surveyors at various times during the Project's history, primarily in the 1970s and early 1980s. During late 2010 and in 2011, a licensed surveyor obtained data on all existing land survey points (to the extent they could be found on the ground) using current technology such as Trimble GPS ground stations. The attached map was created using this point data. Any missing points were extrapolated from pertinent documents, including mining claim location notices, deeds, U.S. mineral surveys and other surveys.

In 2012 and early 2013, a registered land and U.S. mineral surveyor re-surveyed and re-monumented the unpatented lode and placer mining claims as part of a comprehensive claim maintenance program. In 2017, the same surveyor returned to Copper Flat to re-survey and re-monument claim corners for the patented mining claims in the area of the future open pit and prepared a certified plat of the claim boundaries. The boundary plat was filed with the Sierra County Recorder's office in March 2017.

The United States has reserved by federal statute any oil, gas, coal, and certain other nonmetallic minerals not subject to the location of mining claims from the unpatented mining claims located after 1955 that are included in the Project. These reservations do not affect any of the patented claims or any of the unpatented claims located before 1955 over and around the mineral deposit. Figure 4-2 shows land status in the permit area and Figure 4-3 shows the mill site claims located east of the permit area and used for freshwater supply to the mine.

As described in Section 3.1, Reliance on Other Experts, legal review of the Copper Flat property ownership and title was completed by Mr. Mark K. Adams, an attorney with the Rodey Law Firm in New Mexico. Mr. Adams review and legal opinion are summarized in a June 2013 report titled *Updated Title Report - Copper Flat Properties - Sierra County, New Mexico* (Adams, 2013). In a letter prepared on October 28, 2013, Mr. Adams summarized the content of the June 2013 Title Report and concluded that on the basis of his examination, NMCC owns a 100% interest in the mineral and surface estates in the patented mining claims, other patented lands, and unpatented mining claims and mill sites included in the Copper Flat Properties, subject only to the royalties and advance royalties described in Part B and C of the Updated Title Report (Adams, 2013b). These royalty obligations are described in Section 4.4 of this report. In 2020, Mr. Adams was engaged to review NMCC's annual mining claim filings and property tax payments for NMCC's Copper Flat properties for the period from 2013 through the end of 2019. In a letter dated February 6, 2020, Mr. Adams stated his opinion that all BLM filings and property tax payments required to maintain the Copper Flat properties through the review period had been properly filed by NMCC (Adams, 2020).

4.3 LOCATION OF MINERALIZATION

The Copper Flat deposit is located entirely on patented and unpatented claims owned or controlled by NMCC. The deposit is hosted by the Cretaceous age CFQM and related breccia pipe that intrudes a roughly circular block of andesitic volcanic rocks about 4 miles in diameter. Although copper-molybdenum mineralization is contained within the Copper Flat porphyry stock and its associated breccia pipe, higher grade copper-molybdenum mineralization is localized in the western part of the breccia pipe and bordering CFQM in the vicinity of the Patten fault- Hunter fault zone intersection. Based on drilling, the Copper Flat deposit occupies an elliptically shaped area roughly 1,400 ft wide and 2,100 ft in length and is composed almost entirely of hypogene sulfide mineralization. Pyrite and chalcopyrite are the dominant sulfide minerals and nearly all the copper mineralization is in the form of chalcopyrite.

4.4 ROYALTIES, AGREEMENTS AND ENCUMBRANCES

4.4.1 Initial Option and Purchase Agreement

NMCC entered into an option and purchase agreement with the owner of mining claims and other real property located in and around Copper Flat in 2009. This agreement required a series of payments to exercise the option and NMCC completed the final option payment in May 2011. Pursuant to the completion of the obligations under this agreement, NMCC owns and controls 100% of the mineral rights of the Copper Flat Project.

Table 4-1: Summary of Copper Flat Properties

Mineral Tenure	Patented Mining Claims	Fee Land Parcels	Unpatented Mining Claims	Unpatented Millsites
Surface and Mineral Estates	26	16	-	-
Mining Rights	-	-	174	-
Surface Rights	-	-	-	9

The property acquired through the 2009 option and purchase agreement is subject to (a) quarterly advance royalty payments indexed to the price of copper beginning with completion of all permits required for commercial production from Copper Flat, (b) a 3.25% net smelter return royalty, and (c) a 5.00% NSR royalty on mineral production realized from the Chance, Feeder, Xmas, and Extension patented mining claims. The likelihood of mineral production from the Chance, Feeder, Xmas, and Extension patented mining claims is small and payments associated with this royalty are not expected to be significant.

An expert opinion regarding THEMAC's royalty obligations was provided by Mr. Mark K. Adams of the Rodey Law Firm as discussed in Section 3.4, Reliance on other Experts (Adams, 2013b).

4.4.2 2013 Real Estate Purchase Agreement

In a transaction signed in 2013, the Company acquired an additional 1,220 acres of private property in the immediate project area. The 2013 purchase agreement requires annual principle and interest payments that are ongoing and are expected to continue until 2023 when the balance is due. If the Company fails to make any payment under the terms of the Fancher Agreement, the vendors may issue notice of default which allows for a 30-day remedy period. If the period lapses without remedy, the vendors may elect to terminate the agreement, retain all payments made to date under the agreement and retain the land.

Table 4-2: Summary of Copper Flat Properties Acquired in 2013

Mineral Tenure	Patented Mining Claims	Fee Land Parcels	Unpatented Mining Claims	Unpatented Mill Sites
Surface and Mineral Estates	3	6	-	-
Mining Rights	-	-	-	-
Surface Rights	-	-	-	-

The agreement provides the seller with access to an existing well and the ability to continue an existing grazing lease as long as the continued activities do not conflict with mining operations. The purchase agreement does not include a royalty provision of any type.

4.4.3 Other Encumbrances

The Copper Flat properties are not subject to any other royalties, payment obligations, or other agreement, encumbrances, or back-in rights.

4.5 ENVIRONMENTAL LIABILITIES

4.5.1 Identified Environmental Liabilities

Exposed Concentrator Foundation

Several existing foundations were exposed by NMCC as part of the project evaluation; all except for the concentrator foundation were re-covered and the work accepted by the BLM. The concentrator foundation has been left un-exposed for further study as needed. NMCC plans to use the existing foundation for the new operation, however BLM requires re-covering the structure if the project does not proceed to construction. NMCC completed a cost estimate for completing the work which has been reviewed and approved by BLM. NMCC has funded a \$106,000 financial guarantee to complete the work. BLM completes site inspections and plan reviews on a regular basis and the NMCC plans and the current financial guarantee remains satisfactory.

Breach the Legacy TSF Dam

OSE Dam Safety required NMCC to breach the internal divider dike of the existing TSF in September 2017 as a condition of dam compliance. NMCC completed the task in April 2018 and the work was accepted by OSE in July 2018. The general condition of the existing tailings dam (constructed in 1982 by the prior operator) does not meet all dam safety requirements. However, the dam is not in operation and OSE has granted a waiver for several conditions, including an on-going burrowing rodent management program. NMCC is in compliance with all conditions of the OSE waiver. The State will not require THEMAC to bring the dam into compliance if (a) the structure is not returned to service and (b) THEMAC maintains the burrowing rodent program. The existing structure will be replaced with a new, compliant structure during project construction. If a new facility is not constructed, the State may require a breach of the existing dam.

Reclaim Legacy Waste Rock Storage

Several small waste rock storage areas remain from the prior operation. A portion of the stockpiles are located outside of the pit drainage area, which may be causing high TDS levels observed in groundwater near the Grayback Arroyo (effects associated with ARD are not observed). Plans to address this condition is included in the operation and reclamation plan. If the project does not proceed, it is assumed the State will require that THEMAC address the source

of the groundwater impact through re-grading, covering with growth media and re-vegetating to reduce storm water infiltration.

Remove Production Well Equipment and Reclaim Production Well Sites

Four freshwater production well sites were constructed by the prior operator. NMCC plans include using the wells for the new operation, however BLM may require removing surface equipment currently located at two wells and reclaiming the four sites if the project does not proceed. Reclamation of the sites is assumed to include removal of existing equipment; capping and locking the four wells; removing fencing and power lines; and re-vegetating areas around well heads and access roads.

Other Equipment Removal

Other NMCC equipment currently in place at Copper Flat includes small well equipment; cargo container storage; electrical equipment; and vehicles. Removing existing site equipment will not require significant cost as all units are portable, easily removed, and all have disposal value.

Except as noted above, all exploration and site investigation activities completed to date have been reclaimed and the reclamation of these areas has been accepted by the BLM and state authorities.

4.5.2 Environmental Compliance

THEMAC maintains performance standards and procedures at the Copper Flat site that includes safety, environmental compliance, site security, and housekeeping considerations. NMED Discharge Permit DP-1840, issued in December 2018, includes stipulations that must be addressed in calendar years 2019 and 2020; NMCC has completed activities needed to maintain compliance with permit requirements. NMCC and THEMAC have not received any letters of non-compliance from state or federal agencies and THEMAC knows of no site conditions or reports that are not in compliance with state or federal environmental laws.

In September 2013 the NMED approved new groundwater protection regulations specific to Copper Mine Facilities. The new regulations became effective on December 1, 2013 as NMED 20.6.7 and are also known as the New Mexico Copper Rule. A public hearing on NMED Discharge Permit DP-1840 for the Copper Flat Mine was held during September 2018. The Hearing Officer Report issued after the hearing concluded that NMED and NMCC met or exceeded all applicable public notice requirements during publication of the draft permit and leading up to the public hearing. Furthermore, the hearing officer report concluded that the design and operation of the Copper Flat Open Pit, waste rock stockpiles, mineral processing facilities, monitoring systems, and other mine facilities meet or exceed the requirements of the New Mexico Copper Rule (Orth, 2018a).

The New Mexico MMD, in a letter issued in July 2018, stated that the NMCC permit application package (PAP) for a new mine permit is “approvable in accordance with 19.10.6.605.D NMED”, and the agency instructed NMCC to submit a proposal for financial assurance under 19.10.12 NMED. Following this notice, MMD held a public hearing in October 2018 to receive comment on NMCC’s PAP, NMCC’s financial assurance proposal, and the State’s Draft Environmental Evaluation of NMCC’s plans for the Copper Flat Mine to receive input before the Agency begins drafting a permit in compliance with regulations enacted under the State Mining Act.

Modrall Sperling Roehl & Sisk PA (Modrall Sperling) provides NMCC with legal assistance on state and federal environmental, reclamation, closure, and land use permitting, and compliance matters. In a letter dated March 19, 2020, Mr. Stuart Butzier, a VP and Shareholder of Modrall Sperling, provides the opinion and belief that “NMCC management and staff and NMCC’s technical consultants have maintained compliance with all state and federal environmental compliance and permitting requirements. I am of the further opinion that the Copper Flat site has been

secured by NMCC in a stable and safe condition and maintained by NMCC through current activities that are being employed and implemented using (best management practices for the protection of the environment” (Modrall 2020).

4.6 PERMITTING

The mining and environmental permits issued for the 1982 Quintana Mine have expired or have been closed and require replacement with new permits. Table 4-3 lists the major permits and approvals needed for the planned Copper Flat Mine along with status of each as of the effective date of this report.

Table 4-3: Major Permits and Approvals Required for the Copper Flat Project

Permit/Approval	Authority	Status
Federal Permits and Approvals		
Environmental Impact Study	US Bureau of Land Management (BLM)	<u>Complete</u> Final EIS issued April 2019; BLM Record of Decision approving the alternative that conforms to NMCC's Copper Flat Operating Plan issued August 2019
Biological Opinion	US Fish and Wildlife Service	<u>Complete</u> USFWS Consultation completed and biological opinion issued February 25, 2019. BO included with FEIS-ROD.
Cultural Resource Inventory and Protection Plan	US Bureau of Land Management (BLM)	<u>Complete</u> Field surveys and 3 rd Party consultations complete. Programmatic Agreement for the Copper Flat Mine signed with BLM and state agencies December 2016. Field plan prepared and ready to submit/implement ahead of construction
Clean Water Act Permit	US Army Corps of Engineers (ACOE)	<u>Complete</u> Approval under Nationwide Permit 44 (Mining) issued February 2020.
43 CFR 3809 Plan of Operations (POO)	US Bureau of Land Management (BLM)	Plan of Operations reflecting EIS approved alternative complete and submitted to BLM; approval expected with completion of financial assurance plan.
Reclamation/Closure Plan and Financial Assurance	US Bureau of Land Management (BLM)	BLM is cooperating agency with State Agencies. BLM has accepted plan, assumptions and cost calculations. Final approval pending Agency approval of financial assurance plan.
National Pollutant Discharge Elimination System (NPDES)	US Environmental Protection Agency (EPA)	Initiate with construction decision.
Mine Registration	Mining Safety and Health Administration (MSHA)	Initiate with construction decision.
FCC License	Federal Communications Commission (FCC)	Initiate with construction decision.
Explosives Permit	Bureau of Alcohol, Tobacco, and Firearms (BATF)	Initiate with construction decision.
State Permits and Approvals		
Air Quality Permit	NMED Air Quality Bureau	<u>Complete</u> New Source Permit 0365-M3 issued June 2013.

Groundwater Discharge Permit	NMED Groundwater Bureau	<u>Complete</u> Groundwater Discharge Permit issued December 2018.
Stage I and Stage II Abatement Plans	NMED Groundwater Bureau	<u>Complete</u> Requirement satisfied by rolling conditions into DP-1840
Cultural Resource Inventory and Protection Plan	NM Department of Cultural Affairs - State Historic Preservation Office	Field surveys and 3 rd Party consultations complete. Programmatic Agreement for the Copper Flat Mine signed with BLM and state agencies December 2016. Field plan prepared and ready to submit/implement ahead of construction
State Highway Use Authority	NMDOT	<u>Complete</u> Transportation and road engineering studies complete and MOU regarding protections for State Highway 152 executed with NMDOT in July 2018
Mine Operating Permit	NMEMNRD Mining & Minerals Division (MMD)	Permit Application Package considered approvable in July 13, 2018, letter from Agency; financial assurance plan started. Agency Order reopening technical review and suspending financial assurance review issued March 31, 2020.
Reclamation/Closure Plan and Financial Assurance	NMEMNRD MMD & NMED	Cost estimate presented to Cooperating Agencies; agencies advise NMCC response to technical questions satisfactory and no additional technical comments. NMCC developing options for establishing reclamation bond. Agency Order reopening technical review and suspending financial assurance review issued March 31, 2020.
Water Supply	NMOSE	Acquired 861 acre-feet (AF) of perfected water right for mining use in Aug 2018. Lease executed Mar 2019 for 2400 AF; application accepted by OSE December 2019. Additional sources identified and negotiations ongoing.
New Dam Permit (TSF)	NMOSE Dam Safety Bureau	Initiate with TSF detail design
Mine Registration	NM EMNRD	Initiate with construction decision.
Landfill Permit	NMED Solid Waste Bureau	Initiate with construction decision.

The environmental baseline for the Copper Flat Mine was established by NMCC through a multi-year data collection program that was guided by a sampling and analysis plan developed in accordance with 19.10.6.602.D New Mexico Administrative Code (NMAC) and approved by multiple permitting agencies. Data was collected and analyzed for several factors, including climate; vegetation, wildlife; topsoil; groundwater; surface water; geology; geochemistry; cultural and historical resources; land use; and prior mining operations. Based on the results of the baseline studies, no endangered plant or wildlife species have been identified inside the permit boundary. NMCC's Baseline Data Characterization Reports have been submitted to the BLM and State permitting agencies; full copies of the reports may be accessed at the MMD's Copper Flat Mine web page at www.emnrd.state.nm.us/MMD/MARP/PermitSI027RN.html.

BLM classifies the Copper Flat Mine as a "Plan-Level Operation" under 43 CFR 3809 surface management rules, which requires BLM review and approval of a plan of operations (POO) and reclamation financial guarantee before operations may begin (43 CFR 3809.415). NMCC prepared the Copper Flat POO pursuant to 43 CFR 3809.401 and submitted to the BLM to initiate the National Environmental Policy Act (NEPA) environmental impact analysis. The POO was updated to reflect the approved EIS alternative and resubmitted to the BLM in August 2019; BLM approval of the POO is pending NMCC submittal of the reclamation financial guarantee.

The proposed operation has been evaluated by the Bureau of Land Management (BLM) through completion of a National Environmental Policy Act ("NEPA") compliant Environmental Impact Statement ("EIS"). Initial scoping for the EIS was conducted with public input in February 2012. The BLM released the Draft EIS ("DEIS") on the Copper Flat Copper Mine Project in November 2015, hosted two public meetings shortly thereafter and allowed 120 days to receive public feedback on the DEIS. On April 19, 2019, the BLM announced completion of the Final EIS ("FEIS") for the Copper Flat Mine and the document was released to the public.

The EIS was prepared by the Bureau of Land Management (BLM) Las Cruces District Office in consultation with several Cooperating Agencies that included: the U.S. Fish and Wildlife Service ("USFWS"); the New Mexico Energy, Minerals, and Natural Resources Department, the New Mexico Environment Department, the New Mexico Department of Game and Fish, and the New Mexico Office of the State Engineer. The EIS also considered public comments received during the scoping effort as well as comments received on the Draft EIS. Consultation with USFWS resulted in a Biological Assessment and the USFWS Biological Opinion, an important component of the NEPA process, was issued by the USFWS in February 2019.

Four alternatives were analyzed by the BLM in the EIS: a No Action alternative (the no mining alternative) and three action alternatives: the Proposed Action (processing 17,500 short tons of ore per day over a 16 year operating life); Alternative 1 (processing 25,000 short tons of ore per day over a 11 year operating life); and Alternative 2 (processing 30,000 short tons of ore per day over a 12 year operating life). The Proposed Action and the two alternative actions are similar in nature and each includes an open pit, a mineral concentration plant, waste rock dumps, a lined tailings storage facility, water wells, haul roads, and other ancillary facilities. Alternative 2, which will create nearly 300 direct jobs at the mine during the operation, aligns with THEMAC's plans for the Copper Flat Mine and this alternative was identified in the FEIS as the BLM's preferred alternative for mining at Copper Flat.

The Copper Flat Mine EIS was an extensive review that took seven years to complete. The FEIS identifies potential impacts on the physical, biological and social environment from all phases of the proposed project, including construction, mine operation and closure. The document identifies long-term, cumulative effects from this project and other activities in the region, while considering a reasonable range of alternatives that meet the Agency's legal mandates.

In a separate action, the BLM on August 22, 2019, issued a positive decision on the Copper Flat Mine FEIS. With this decision, the BLM formally approved the Alternative 2 Plan evaluated in the EIS. The BLM decision approves open pit mining and 30,000 tons per day mineral processing by sulfide flotation, which mirrors plans and designs developed through the feasibility study and matches the plans and designs used for the Company's state permit applications. With the EIS, the BLM determined that implementation of the approved alternative along with Company commitments to environmental monitoring and protection measures will not cause unnecessary or undue degradation of public lands and the Agency has determined the decision is consistent with other applicable legal requirements. In announcing the decision, the BLM recognized that the Copper Flat Mine will enhance economic development by creating jobs and enabling community growth. The full Copper Flat FEIS and Record of Decision ("ROD") are available for viewing and download from the BLM website at www.blm.gov/.

43 CFR 3809.401(c)(1) requires project operators to provide an inventory of cultural and paleontological resources with the proposed plan of operations. The required survey and inventory of potential resources was completed pursuant to Section 106 of the National Historic Preservation Act and findings reported to BLM and NM State Historic Preservation Division in February 2013. Required consultations with NM State Agencies and other interested parties was conducted and a Programmatic Agreement guiding protection activities was signed by NMCC, the BLM, the Hopi Tribe, the New Mexico State Historic Preservation Officer, the New Mexico State Land Office, and the New Mexico Energy, Minerals and Natural Resources Department in November 2016.

The Company has evaluated the Copper Flat site for jurisdictional waters of the US (WOTUS), which may include ephemeral drainages. Section 404 of the US Clean Water Act regulates the discharge of dredged or fill material into WOTUS. The program is administered by the US Army Corps of Engineers (USACOE) and a permit (404 Permit) is required before dredged or fill material may be placed or discharged into WOTUS. The Copper Flat facilities have been designed to avoid, to the most practicable extent, WOTUS, such that potential impacts are less than 0.02 acres (less than 0.008 hectares) for the entire project site, thus qualifying the project for approval under the USACOE's Nationwide Permit 44 for mining activities. The Company submitted a Pre-Construction Notification ("PCN") with supporting documents for a nation-wide permit to USACOE in October. The agencies evaluation of the PCN was completed and the agency issued authorization in a letter dated February 6, 2020, for NMCC to proceed under the Nationwide Permit 44.

The NMED Air Quality Bureau issued New Source Review Permit 0365-M3 for the New Mexico Copper Corporation Copper Flat Mine in June 2013. The term of this permit is permanent unless withdrawn or cancelled by the Department, and the permit remains in effect.

NMED Groundwater Bureau issued Groundwater Discharge Permit DP-1840 for the New Mexico Copper Corporation Copper Flat Mine in December 2018. The decision to issue Permit DP-1840 was appealed by project opponents; arguments were heard by the State Water Quality Control Commission ("WQCC") in August 2019, followed by a unanimous decision from the WQCC to uphold the permit. The WQCC decision has been appealed to the NM Court of Appeals and the appeal schedule is pending.

Work to obtain a mining permit from the NM Mines and Minerals Division (MMD) is ongoing. The Copper Flat Mine is being permitted as a new mine under Part 6 of the New Mexico Mining Regulations, which are administered by MMD. The NMCC permit application package, which includes construction, operation, reclamation and closure plans, was determined to be approvable by the Agency in a July 13, 2018 letter to NMCC. Following that letter, MMD provided the Company with a status letter on December 21, 2018, in which the Agency acknowledged significant progress by the Company towards fulfillment of permit requirements and identified the remaining steps to be completed for a mine permit:

- 1) Completion of the Hearing Officer's report on the October hearing. This report was completed and submitted to MMD in December 2018 (Orth, 2018b),
- 2) Completion of a financial assurance plan with approval and acceptance by MMD, NMED and the BLM ("FA Agencies");
- 3) MMD's receipt of the NMED Secretary's Determination "stating that the permit applicant has demonstrated that the activities to be permitted... will be expected to achieve compliance with all applicable air, water quality and other environmental standards if carried out as described in the permit application." The NMED indicated when they issued the Discharge Permit that the NMED's Secretary Determination will be considered after the Financial Assurance Plan is approved by all participating agencies; and
- 4) MMD's receipt of BLM's approval of the proposed mining operation. BLM has indicated that approval of the proposed mining operation will be considered after the Financial Assurance plan is approved by participating agencies.

Financial assurance for reclamation and closure of the Copper Flat Mine requires approval by MMD, NMED and BLM. The Company prepared and submitted to the Agencies a proposed reclamation and closure cost estimate for the life-of-mine plan and has revised the calculations to fully address Agency comments as work progressed. In correspondence dated August 21, 2019, MMD and NMED stated that NMCC's response to technical comments on the FA calculations was satisfactory and there were no additional technical comments regarding the calculations. In a separate action on the 3809 Plan of Operations, BLM indicated agreement with the State decision. NMCC has been

considering options for the schedule and form of financial assurance according to 19.10.12.1205(C) through 19.10.12.1207-1208 NMAC; however, on March 31, 2020, the Director of the MMD signed and issued to NMCC an Order to reopen the permit review process and to suspend MMD review of the reclamation plan cost estimate. NMCC is currently reviewing the contents of the Order in order to understand the issues presented and develop a response plan.

Other permits such as the OSE Dam Safety Permit for the mine's proposed Tailings Storage Facility and the Multi-Sector General Permit for potential storm water discharges at the facility from the Environmental Protection Agency will be addressed in the future as current priorities are achieved.

4.7 OTHER FACTORS AND RISKS AFFECTING ACCESS, TITLE, RIGHT OR ABILITY TO PERFORM

Water Rights

In 2015, the Company filed for court adjudication of nearly 7,500 acre-feet ("AF") of vested and inchoate water rights to operate the mine. On December 28, 2017, the State of New Mexico Third District Court ruled that the inchoate water rights controlled by the Company were invalid and extinguished as the result of non-use and the failure to pursue a continuous plan of development by prior owners of the water rights; leaving the Company with approximately 861 acre feet of vested water rights, a water element of 34 acre feet associated with the existing open pit, and a stock right in one well. The vested water rights that the Court has determined exist fall far short of the requirements for the Copper Flat Project. The Company filed an appeal of this decision on March 27, 2018. At the same time, parties opposing the Company's water rights filed cross appeals protesting the Court recognized water rights. The appeals have been assigned to the New Mexico Court of Appeals General Calendar. On February 27, 2019, the Company's Brief-in-Chief outlining arguments for reinstating the water rights was filed by Company attorneys to meet the Appeals Court schedule. In addition to the Company's filing, two separate Amicus Curiae Briefs supporting the Company's position were submitted to the Court. After review, the Court determined that the Amicus Briefs may bring attention to relevant discussion not included in briefs offered by the Parties and the briefs were accepted by the Court. Aspects of the December 2017 lower court ruling have also been appealed by Parties opposed to the Copper Flat Mine and appeal briefs from these parties were submitted to the Court on May 15, 2019. Motions for leave to file four Amicus Curiae Briefs in support of opposing arguments were submitted to the Court shortly thereafter, and the Court allowed the four briefs in November 2019. The Company's legal counsel prepared and submitted to the Court a consolidated response to arguments presented in the opposing Amicus Curiae within the Court specified 45-day deadline. A date to hear oral arguments in this appeal has not been established by the Court.

Lease and transfer of water rights to NMCC wells requires OSE approval. The OSE will deny a transfer of water rights if it will impair the other existing water rights. Applications filed with OSE require public notice to allow other water rights owners and interested parties the opportunity to protest. If the transfer is protested, the application will be forwarded to the Administrative Litigation Unit to be scheduled for hearing. Appeals may be taken to district court after the administrative hearing is held.

Permit Appeals

NMEDs decision to issue Discharge Permit DP-1840 was appealed to the State Water Quality Control Commission (WQCC) by project opponents, who argued six separate claims and requested a reversal of the permit or a remand to the Environment Department to either deny the permit or impose additional conditions. Arguments were heard by the State Water Quality Control Commission ("WQCC") in August 2019, after which the WQCC issued a unanimous decision to uphold the permit without change. The WQCC decision has been appealed to the NM Court of Appeals; the Court has not established dates for written and oral arguments in this appeal.

5 ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY

5.1 PHYSIOGRAPHY AND VEGETATION

The project area lies within the Mexican Highlands section of the Basin and Range Physiographic Province. The Copper Flat Property is located in the Las Animas Hills, along the western edge of the Rio Grande Valley. The Rio Grande Valley is approximately 30 miles wide and trends north south. The Rio Grande river flows north-south along the eastern edge of the valley and is about 14 miles east of the site.

Elevations generally range from about 5,200 feet above mean sea level (famsl) on the southeast side of the property (tailings dam area), to around 5,700 famsl on the northwest side of the property. The highest elevation locally is Animas Peak (on the north side of the property), which tops at about 6,160 famsl. The mountains of the Black Range rise to elevations above 9,000 famsl about 25 miles west of the project site.

The Project site exhibits plant communities dominated by desert grassland, creosote bush, and juniper woodlands (BLM, 1999). Desert grassland is predominant and is characterized by a dominant herbaceous layer consisting of grasses and forbs with scattered shrubs. The creosote bush community lies mostly east of the tailings storage facility and is characterized by a dominant overstory of creosote bush and tarbush with an understory of grasses and forbs. The juniper woodland community is located along streams and slopes and is characterized by a dominant overstory of juniper with an understory of forbs and grasses.

Much of the project site has been disturbed by previous mining activities. Existing disturbance created by the Quintana Minerals Operation in the early 1980s includes a pre-stripped pit area, waste rock piles, mill site with concrete foundations, and the tailings storage facility. Additional disturbance within the project area includes historic placer mining disturbance and recent placer mining disturbance from recreational mining activities. Recent studies determined that approximately 1,000 acres within the 2,190-acre permit area boundary has been previously disturbed.

5.2 CLIMATE

The climate in Sierra County is semi-arid high desert, with four distinct seasons. Summer temperatures are warm (maximum temperatures average 91°F; the recorded maximum is 107°F) and winter temperatures drop below freezing but are relatively mild (minimum temperatures average 25°F; the recorded minimum is -10°F).

On average, Sierra County experiences 291 sunny days per year and 44 days per year with measurable precipitation. The project area receives approximately 13 inches of precipitation annually, which occurs mostly as rainfall during July to September. Total snowfall at site averages five to eight inches per year. Snowfall is possible from October through April; however, it's most likely between December and February.

The predominate wind direction is from the west, and secondarily from the north. Wind speeds typically average 10 to 15 mph; wind speeds in excess of 50 mph and gusts to 90 mph may occur as major storms pass through the area.

5.3 ACCESSIBILITY

The property is easily accessed by motor vehicle using Federal and State highway systems. From the east, the project site is reached by traveling north or south on US Highway 25, which is part of the US Federal Interstate Highway System, then west on State Highway 152 approximately 13 miles to the mine access road turnoff. Traveling from the west, the property access road is approximately 65 road miles using State Highway 152 from Silver City, NM, a major copper mining center located in southwestern New Mexico.

After leaving State Highway 152, the property gate is reached by traveling approximately 2.5 miles on an existing all-

weather gravel road. Road closures resulting from inclement weather in the area are rare.

Driving time to the project site is approximately 3 hours from Albuquerque, NM; 2 hours from El Paso, TX; and 5 hours from Tucson, AZ.

5.4 LOCAL COMMUNITIES

Sierra County is a rural county. Historically, the economy of the region has been tied to mining, ranching, agriculture, and tourism.

Population centers in the project vicinity include:

- Hillsboro, NM. Population 125 (population statistics cited in this section are taken from the 2010 U.S. Census). Hillsboro is located approximately 4 miles (straight line) and 8 road miles southwest of the project site and is the closest community to the project site. Hillsboro was founded in 1877 following the discovery of gold in the area. The community was once the county seat of Sierra County and is now home to ranchers and artists.
- Truth or Consequences, NM. Population 6,475. Located on the Rio Grande River approximately 30 road miles northeast of the project site. Truth or Consequences is the county seat of Sierra County.
- Silver City, NM. Population 10,300. Located approximately 68 road miles west of the project site. Silver City was founded in 1870 after discovery of silver deposits in the area. The City is now a copper mining center in southwest New Mexico.
- Albuquerque, NM Metropolitan Statistical Area. Population 887,100. Located approximately 180 road miles northeast of the project site. Albuquerque was founded in 1706 as a Spanish military outpost and the city is now the largest City in the State of New Mexico.
- El Paso-Las Cruces, TX-NM Combined Statistical Area. Population 1,013,400. Located approximately 115 road miles southeast of the project site. The statistical area consists of the metropolitan areas of El Paso, Texas and Las Cruces, New Mexico.

5.5 REGIONAL TRANSPORTATION

Several major highways serve the region. The project area is bracketed by US Interstate Highway 25 to the east, US Interstate Highway I-10 to the south and US Interstate Highway I-40 to the north. New Mexico State Highway 152 runs west from I-25 to Silver City and passes within 3 miles of the property gate. Several commercial trucking firms operate in the region and freight pricing is expected to be competitive.

Two major railroads operate in southern New Mexico. Major rail yards closest to the mine are located at Rincon, NM, (BNSF Railroad, 45 miles from Copper Flat); Las Cruces, NM, (BNSF Railroad, 75 miles); Deming, NM, (Union Pacific Railroad, 75 miles); and El Paso, TX, (Union Pacific Railroad, 125 miles).

Ocean ports accessible by highway and rail transportation are located in Guaymas, Mexico (600 miles); Texas Gulf Coast (800 miles); California Pacific Coast (800 miles); and Vancouver, WA (1,800 miles).

Commercial airports providing passenger airline and air freight services are located in Albuquerque, NM, and El Paso, TX. Public use, general aviation airports serving private and charter flights are located at Truth or Consequences, NM, and Las Cruces, NM.

5.6 POWER SUPPLY

Power in Sierra County is supplied by Tri-State Generation and Transmission Association and distributed by Sierra Electric Cooperative, Inc. The Tri-State transmission line serving the local region is a 115 kV voltage power line that parallels US Interstate Highway 25 approximately 12.5 miles east of the mine site.

Quintana Minerals constructed the Caballo power switching station at the I-25 and State Highway 152 interchange along with a dedicated 115 kV power line to bring power from I-25 transmission line to the mine substation for the 1982 operation. Ownership of the Caballo switching station and the 115 kV line transferred to the power utilities during the 1980s. Tri-State owns and maintains the Caballo switching station and is using the station to isolate sections of the power grid when needed for maintenance. The dedicated 115 kV power line between the switching station and the mine is inactive; recent inspection determined that the line is in fair condition and can be returned to service with a limited amount of maintenance and the utility has stated willingness to re-connect the mine to the regional power grid.

In addition to the Tri-State transmission lines, a 345 kV power transmission line owned by El Paso Electric, a regional electric utility providing generation, transmission and distribution service in southern New Mexico and west Texas, runs in a north-south direction and crosses the inactive 115 kV power line approximately 7.0 miles east of the mine site.

Tri-State has stated that sufficient power generating capacity exists to meet mine needs; however, the utility identified an issue with the capacity of the power transmission system feeding the Caballo switching station. Alternatives to upgrade the Tri-State transmission lines have been developed by the utility; all are currently rejected due to high cost and/or significant delay to the project timeline. An alternative to connect the currently inactive Tri-State 115 kV line to the El Paso Electric 345 kV power transmission line has been identified as the most favorable alternative and is being pursued. Costs and schedules for permitting and construction have been developed by Tri-State and are included in the project estimate.

An emergency generator will be provided to maintain critical operations and allow a controlled shut down in the event the mine's power supply is disrupted.

5.7 WATER SUPPLY

The New Mexico Office of the State Engineer and Interstate Stream Commission (NMOSE) is responsible for administering water resources in the State of New Mexico. Copper Flat falls within the Lower Rio Grande Groundwater Basin, which follows the Rio Grande River from Elephant Butte Dam south to the Texas State Line and the International Border with Mexico. Rapid population growth, especially in the El Paso area, coupled with extended drought is placing ever increasing demands on the Basin's water resources.

NMCC acquired 7,481 acre-ft/yr of declared water rights, consisting of perfected and inchoate rights, through purchase agreements with two separate parties in 2010. All payments required under the purchase agreements have been completed and full title to the acquired water rights has passed to NMCC. The Company filed necessary documents for a change of ownership with the NM OSE and the completed documents have been recorded in Sierra County, NM.

In 2015, the Company filed for court adjudication of the acquired water rights. On December 28, 2017, the State of New Mexico Third District Court ruled that the full amount of inchoate water rights and a portion of the perfected water rights held by the Company were invalid and extinguished as the result of non-use and the failure to pursue a continuous plan of development by prior owners of the water rights; leaving the Company with approximately 861 acre feet of perfected groundwater rights plus a small amount of water rights associated with the existing pit lake and livestock water rights. The Company filed an appeal of this decision on March 27, 2018. At the same time, parties opposing the Company's water rights filed cross appeals protesting the Court recognized water rights. The appeals

have been assigned to the New Mexico Court of Appeals General Calendar. A date to hear oral arguments has not been established by the Court as of the date of this report.

Table 5-1: NMCC Water Rights

NM-OSE File Number	Location (NM Principal Meridian)	Function	Acquired Water Rights ¹ (Acre-Feet)	2017 Adjudicated Water Rights ^{2, 3} (Acre-Feet)
LRG-4652	Sec 30 T15S, R5W	Production Well PW-1	6,462	861
LRG-4652-S-1	Sec 31 T15S, R5W	Production Well PW-2		
LRG-4652-S-2	Sec 30 T15S, R5W	Production Well PW-3		
LRG-4652-S-3	Sec 31 T15S, R5W	Production Well PW-4		
LRG-4652-S-11	Sec 4 T16S, R6W	Supplemental Well		
LRG-4652-S-12	Sec 9 T16S, R6W	Supplemental Well		
LRG-4652-S-13	Sec 31 T15S, R6W	Supplemental Well		
LRG-4652-S-14	Sec 30 T15S, R5W	Supplemental Well		
LRG-4652-S-15	Sec 25 T15S, R6W	Supplemental Well		
LRG-4652-S-16	Sec 28 T15S, R6W	Supplemental Well		
LRG-4652-S-4	Sec 31 T15S, R6W	Supplemental Well	439	1
LRG-4652-S-5	Sec 30 T15S, R6W	Supplemental Well		
LRG-4652-S-6	Sec 30 T15S, R6W	Supplemental Well		
LRG-4652-S-7	Sec 31 T15S, R6W	Supplemental Well		
LRG-4652-S-8	Sec 31 T15S, R6W	Mine Office Well		
LRG-4652-S-9	Sec 31 T15S, R6W	Supplemental Well	121	
LRG-4652-S-10	Sec 31 T15S, R6W	Supplemental Well	242	
LRG-4652-S-17	Sec 26 T15S, R7W	Pit Lake	120	34
LRG-4654	Sec 25 T15S, R7W	Supplemental Well	97	
			7,481	897

¹ Acquired Water Rights includes vested and inchoate rights as declared with the NM-OSE

² 2017 Adjudication under appeal

³ Total Acre-Feet does not include livestock water rights held by NMCC

Ensuring pumping of the mine wells will not impair other water users is necessary to obtain a water permit in New Mexico. NMCC hydrologists developed a groundwater model to project how pumping from the Company's wells might affect the local groundwater table and the Rio Grande as it flows south toward Texas (the "Hydrogeologic Model") (JSAI, 201-2). The model has been reviewed by NMOSE and other regulatory agencies and agency input has been incorporated into the model. The Company is not aware of any material disagreements regarding the Hydrogeologic Model by any of the reviewing regulatory agencies.

To offset groundwater pumping effects that are projected to reach the river, the Company has acquired a lease from the Jicarilla Nation to release 3,000 AF of water per annum into the Rio Grande and is further reviewing additional options for further water offsets. The Jicarilla lease was authorized and approved by the United States Department of Interior and the United States Bureau of Reclamation in February 2016. Effects on neighboring wells have also been projected and there was no evidence given at the water rights adjudication of any injury to any other well. In addition, the Company committed in the EIS to ensure that any well user that becomes impaired through pumping of the mine wells will be provided with an appropriate water supply.

In March 2018, NMCC's application to appropriate water for use at the Copper Flat Mine Office was approved by the NMOSE.

In April 2019, an agreement to lease 2,400 AF of existing water right for use at the Copper Flat Mine was signed. The water is currently permitted in the Lower Rio Grande Groundwater Basin for multiple purposes, including commercial and industrial use. An application to OSE to change the point of diversion and place of use was completed and filed in August 2019. The application was accepted by OSE in December 2019, and the required public notice of the application was posted on the OSE website and in local newspapers. The application has not been approved by OSE; if approved, the agreement would bring the current water supply available for operations at Copper Flat to 3,261 AF, including the 861 AF of adjudicated water rights acquired through the 2010 Purchase Agreements, which is 53% of the 6,100 AF total required by the planned operation.

The Company has identified additional water rights in the LRG that may be available for lease and transfer to the Company's production wells. The Company is pursuing options to secure the full amount of water needed for the operation.

5.8 PLANT SITE

Earthworks and grading of the plant site, including areas for the concentrator, mine shop, mine substation, ancillary buildings, and mine service roads, was completed with construction of the Quintana Minerals Operation in the early 1980s. Facilities for the new operation will be constructed at the original Quintana plant site and there is sufficient area for the new facilities.

The primary crusher, concentrator, mine shop, warehouse, laboratory, and ancillary buildings will utilize building foundations that remain from the Quintana Operation. The foundations were uncovered for inspection in 2012 and 2013. Inspection and analysis by M3 Engineering determined that the foundations are acceptable for the planned re-use.

5.9 TAILINGS STORAGE AREA

An existing 370-acre tailing storage facility was constructed during the Quintana Minerals operation. The existing tailing storage site will continue to be used to store tailings, but the facility will be completely rebuilt to accommodate a new 536-acre tailing storage facility. Sufficient area exists within the permit boundary for the project to store tailings generated by the ore reserves developed by this study. Details regarding plans for the tailing storage area are provided in Section 20.2.

5.10 MATERIAL STOCKPILES

Sufficient area to store economic and uneconomic materials developed by the life-of-mine plan exists within the project permit boundary. Details regarding plans for the material stockpiles are provided in Section 18.

5.11 SOURCE OF PERSONNEL

During operation, the mine workforce will total 250 to 300 personnel. Southwestern New Mexico and Sierra County has a history of mining and agriculture, and NMCC will provide employment opportunities to individuals living in the immediate area of the mine. It is likely that personnel from outside the local area will be required to meet the full staffing needs of the mine; however, the Southwestern United States provides a large base of experienced personnel to complete the employee roster.

There are several communities within commuting distance from the mine and camps for construction and operating employees are not planned.

5.12 SUFFICIENCY OF SURFACE RIGHTS FOR MINING OPERATIONS

The Company has sufficient surface rights for the planned mining operation and facilities. NMCC owns the rights to 100% of the area within the 2,190-acre permit area. Within this area, NMCC facility designs, including the open pit, stockpiles, processing plant, tailing storage facility and other planned facilities occupy approximately 1,300 acres. Surface rights at the Copper Flat Property are provided through ownership of patented mining claims, private fee lands, unpatented mining claims and rights-of-way filed with the BLM. Details regarding property ownership and mining rights are provided in Section 4 of this report.

6 HISTORY

The first recorded production of placer and lode gold from the Hillsboro Mining District (the District), New Mexico occurred in 1877. Over 285,000 oz of placer and lode gold, valued at \$8.5 million, was produced over the next 100 years. Most of the gold and silver production came from underground and placer operations, located in and around the Copper Flat area (Harley, 1934; Segerstrom et al., 1975; Dunn, 1982, 1984). Gold was initially recovered using arrastras (stone grinding) and then by stamp mills in the district prior to 1881. A tent city named Gold Dust was founded in 1881 in the district and was home to numerous prospectors looking for placer gold deposits. A 10-stamp mill operated at the Bobtail mine on the Snake vein from about 1881 to 1884 and had a capacity of 20 to 25st/d. Placer deposits in Snake Gulch located southwest of the Project were also mined using hydraulic mining methods. Mills operated at the Richmond (1890-1892), Bonanza (1890-1910), Ready Pay/Porter (1898-1913), Snake (1910), and Wicks mines. A copper-matte smelter (capacity 30st/d) in the town of Hillsboro was built in 1892 and operated until the early 1900's. The Stenburg copper mine, located at the Project, was in operation between 1911 and 1931. Small-scale copper and precious metals mining took place in the district up until 1941 (Harley, 1934; Segerstrom et al., 1975; Dunn, 1982, 1984; Raugust, 2003).

Underground development was primarily focused on the Bigelow and Jackpot vein systems. The U.S. government's War Production Limitation Board, L-208, closed the last documented underground activity in 1942. Historic placer workings occupy almost every stream channel radiating from the Copper Flat intrusive center (Segerstrom et al., 1975; Dunn, 1982, 1984). Minor placer mining activity continues today conducted primarily by local prospecting clubs and weekenders.

6.1 OWNERSHIP

Prior to 1952, the Project was held by various owners. Newmont Mining Company (Newmont) explored the District for copper in 1952, followed by Hilltop Mining, Bear Creek Mining Company (BCMC), and Inspiration Development Company (Inspiration). Hilltop Mining worked in the area prior to BCMC, which was involved with the Project between 1958 and 1959. Inspiration acquired the Project in 1967 and leased it to Quintana Minerals in 1974 (Segerstrom et al., 1975; Dunn, 1982, 1984).

In 1979, Quintana Minerals formed a partnership with Phibro Minerals Enterprises, Inc. forming the Copper Flat Partnership, which was financed by Canadian Imperial Bank of Commerce (CIBC) located in Toronto, Ontario, Canada. Under this partnership, Quintana Minerals was the operator (Segerstrom et al., 1975; Dunn, 1982, 1984).

In August 1987, Inspiration leased its mining claims to Hydro Resources with the option to purchase, which was finalized by 1989. In 1989, Rio Gold optioned Copper Flat from Hydro Resources.

The Copper Flat Partnership, which at this time included Copper Flat Mining Co. Ltd, a subsidiary of Rio Gold, maintained control of the Project and held the property until 1993 when Gold Express optioned the Project. Gold Express acquired Copper Flat from Rio Gold with the intent of placing the property into production employing the 1982 design parameters. The following year, in June 1994, Alta Gold acquired the option on the Project from Gold Express. Alta Gold held the Project until its bankruptcy in 1999.

The property reverted back to Hydro Resources in 2001, in conjunction with Cu Flat and GCM (collectively the vendors). In July 2009, NMCC acquired an exclusive option over the Copper Flat property from the vendors. In May 2011, NMCC made the final payment on the exclusion option and now owns the property in total.

6.2 HISTORIC EXPLORATION AND DEVELOPMENT

In 1952, Newmont initiated the first modern exploration program for porphyry copper mineralization in the district. This included 3,369 ft of drilling in six angle holes in the central quartz monzonite (Kueller, 1955). The results were not encouraging enough for Newmont to continue. The Newmont drill and assay data is recorded and is available. BCMC followed in 1958-59 and drilled 9,346 ft in 20 widely spaced core holes. BCMC was testing for an enrichment blanket of secondary copper, which was not found. The BCMC drill and assay data is still available (Dunn, 1984).

Inspiration continued porphyry copper exploration starting in the late 1960's. By 1973, Inspiration had completed 30 core drillholes. Employing this drilling and the second splits from the BCMC data, Inspiration calculated a minable resource of 66 million short tons (Mst) with an average grade of 0.45 percent copper. Inspiration purchased the patented claims, performed metallurgical work, and completed two water wells on the property (Dunn, 1984).

Inspiration leased the property to Quintana Minerals in 1974. By late 1975, Quintana Minerals had drilled 141 holes using five rigs, drilling around the clock. Quintana Minerals' exploration program lead to a comprehensive mine development program which included extensive metallurgical work, underground drifting, bulk sampling, and drillhole composite testing) all performed by Colorado School of Mines Research Center. Quintana Minerals' program included detailed geologic investigations into the relationship between the breccia pipe and the quartz monzonite host rocks, as well as the relationship between host rocks and mineralization. In late 1976, the Project was placed on hold awaiting an improvement in metals prices.

In the first half of 1979, the Project was reactivated due to higher copper prices. Processing methods were reviewed and semi-autogenous grinding (SAG), and copper-molybdenum flotation separation became the basis for subsequent design work. In January 1980, a decision was made to develop the mine. Quintana Minerals' production history is discussed under Section 6.4, Production History.

In 1989, Hydro Resources of Albuquerque, New Mexico, acquired the Copper Flat property from Inspiration, along with all royalties. Hydro Resources maintains a considerable archive of information related to the Project dating back to Inspiration's involvement in the Project. This includes over 14,000 sample pulps and skeleton core from the Quintana drilling programs.

Rio Gold and Tenneco Minerals (Tenneco) drilled six large-diameter reverse circulation drillholes in 1990 and Tenneco left without further interest. Gold Express optioned the property in 1993 but performed no exploration or development.

Alta Gold then acquired the property from Gold Express in June 1994 and went as far as obtaining a draft final EIS for the Project issued in March 1999 but went bankrupt (due to financial problems with other assets) before any permits were issued.

Hydro Resources reacquired all the properties in 2001 (having previously temporarily owned the property), along with all royalties.

During late 2009, 2010, and 2011, NMCC conducted a sample verification programs that included pulp reject analysis and drilling. These recent activities are discussed in Sections 10 and 12 respectively.

6.3 HISTORIC RESERVE ESTIMATES AND AUDITS

The historical mineral resource and reserve estimates presented in this report are based on exploration and development activities, which started in the 1960's. Historic resource estimates do not comply with the CIM terminology under NI 43-101 guidelines, and the reader is cautioned that these estimates are not mineral resources or mineral reserves as defined by NI 43-101 (2002), and should not be relied upon.

The Copper Flat history of published ore reserve estimates and reserve audits begins with Inspiration Development in 1974. Prior to Dunn-Behre Dolbear's (DBD) reserve audit in 1993 for Gold Express, four previous reserve estimates were made for Copper Flat. This included Western Knapp Engineers (WKE) in 1976 for Quintana Minerals, Pincock, Allen & Holt (PAH) in 1980 and 1989 for Quintana Minerals, and Rio Gold and N.A. Degerstrom Inc. (NAD) who completed a mine plan in 1991 for Gold Express (Dunn-Behre Dolbear, 1993). Reserve comparisons are made on the most significant calculations in Table 6-1.

Table 6-1: Historical Mine Reserve Estimates Comparison for Copper Flat*

	WKE (1976)	PAH (1989)	NAD # (1991)
Cut-off-Grade (% Cu)	0.25	0.23	0.23
Tons (st) Ore (1,000)	59,897	60,720	59,119
Tons (st) Waste (1,000)**	105,016	60,007	60,164
Stripping Ratio	1.75:1	0.99:1	1.02:1
Ore Grade (% Cu)	0.43	0.425	0.425
Ore Grade (% Mo)	0.013	0.012	Not provided

*From Dunn Behre Dolbear, 1993, Table 7.1

**Includes low grade stockpile tonnage

Note: Historic resource and reserve estimates do not comply with the CIM terminology under Canadian Securities Administrators NI 43-101 guidelines. The reader is cautioned that these estimates are not mineral resources or mineral reserves and should not be relied upon.

With respect to historical mine reserve estimates; a qualified person has not done sufficient work to classify these historical estimates as current Mineral Resources or Mineral Reserves, and THEMAC is not treating these historic estimates as current Mineral Resources or Mineral Reserves. This information is being provided to the reader for historical context. Readers should review and rely upon the Mineral Resources or Mineral Reserves reported in Section 14 and 15 of this report.

6.4 HISTORIC PRODUCTION

Quintana Minerals prepared an Environmental Assessment report for state and federal agencies in 1975, and by mid-1976, an independent engineering firm Western Knapp Engineering (WKE) had prepared a formal Feasibility report. Final engineering was started with power contracts signed, when copper prices slumped and the open pit mining project was shelved in early 1977. With the recovery of metal prices in 1979, Quintana Minerals re-evaluated the economic viability of the Project, and authorized a new formal detailed engineering study. By this time, the value of the molybdenum, gold, and silver affected the mine economics.

Quintana Minerals formed a 70/30 percent partnership with Phibro Mineral Enterprises in late 1979, with Quintana Minerals as the operator. Financing was arranged through the CIBC, and construction was started in June of 1980 under the Copper Flat Partnership. The mineable reserves at that time were 60 Mst grading 0.42 percent copper and 0.012 percent molybdenum, plus credits in gold and silver.

Wright Engineers of Vancouver, B.C., Canada, were responsible for design engineering while W-J Engineers of San Bruno, California, were responsible for detailed engineering. M.M. Sundt Construction Company of Tucson, Arizona was the general contractor for construction. Quintana Minerals assumed responsibility for overall project management.

Figure 6-1 shows the Copper Flat mine of Quintana Minerals, in a photo taken in 1982. The photo shows the pre-stripped open pit in the background, as it is today. The then state-of-the-art milling facility is in the middle with mining equipment shops on the left, tailings thickener in the lower middle (tailings out of sight to lower left), crushing facilities on the right of mill, waste rock dumps out of sight on the right, and beyond the pit.

In mid-March 1982 after a \$112 million capital investment, the Copper Flat open pit copper mine began full production at a rated capacity 15,000 st/d, a waste to ore ratio of 1.8:1, and a cut-off grade of 0.25 percent copper. After just 3.5 months of production, the mine shut down on June 30, 1982, due to low copper prices (\$0.70/lb) and high interest rates on the CIBC loan. The mine produced 1.48 Mst of ore recovering 7.4 Mlbs of copper, 2,301 oz of gold, and 55,966 oz of silver during the period. Table 6-2 shows the production.

Table 6-2: Quintana Minerals, Inc. Mine Production at Copper Flat

	Actual	Planned
Tons Ore (st) Mined	1,478,047	1,892,387
Tons Waste (st) Mined	3,098,330	3,361,478
Grade, Copper (%)	0.448	0.433
Grade, Molybdenum (%)	0.0088	0.013
From Dunn Behre Dolbear, 1993, Table 7.1		

The Copper Flat mine passed its project stabilization with CIBC during this initial mining period before going into receivership. By late 1985, the surface facilities equipment were sold to the Ok Tedi mine in Papua New Guinea, and the site was reclaimed by CIBC as formally approved by state and federal requirements. The structural foundations, power lines, water wells, and in-ground infrastructure were left in-place for the future re-start.

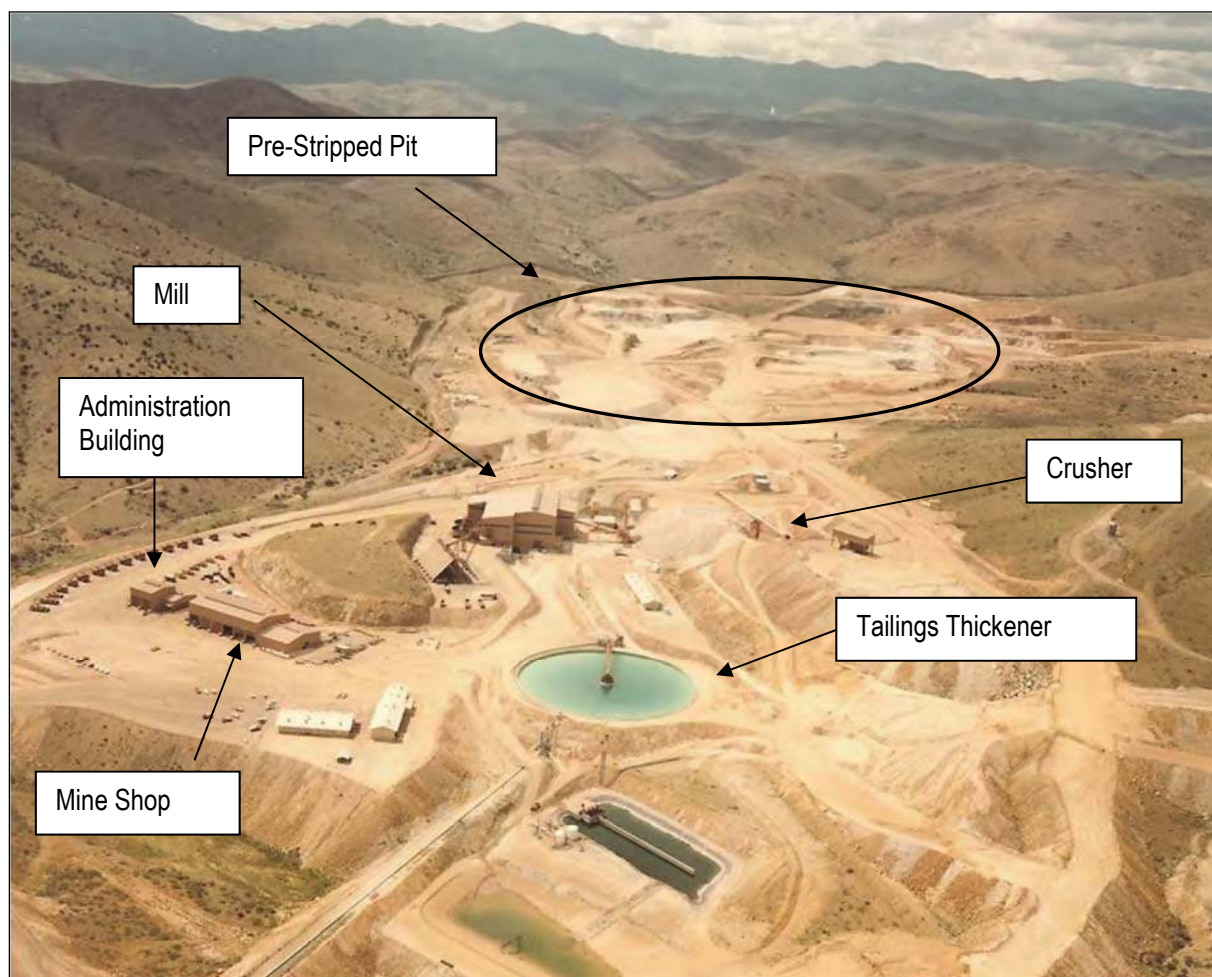


Figure 6-1: Copper Flat Mine in 1982

7 GEOLOGICAL SETTING AND MINERALIZATION

Copper Flat is a porphyry copper-molybdenum deposit located on the western margin of the Rio Grande Rift. The deposit is hosted by a small quartz monzonite stock having a porphyritic texture that intrudes a sequence of andesitic volcanic rocks of similar age covering an area approximately 4 miles in diameter.

7.1 REGIONAL GEOLOGY

The Copper Flat Mine lies within the Mexican Highlands portion of the Basin and Range Physiographic Province. It is located in the Hillsboro Mining District in Las Animas Hills, which are part of the Animas Uplift, a horst on the western edge of the Rio Grande valley. The Animas Uplift is separated from the Rio Grande by nearly 20 miles of Santa Fe Group alluvial sediments, referred to as the Palomas Basin of the Rio Grande valley. To the west of the Animas Uplift is the Warm Springs valley, a graben that parallels the Rio Grande valley. Further west, the Black Range forms the backbone of the Continental Divide, rising to about 9,000 ft above sea level. The surface geology of the Copper Flat region is shown in Figure 7-1.

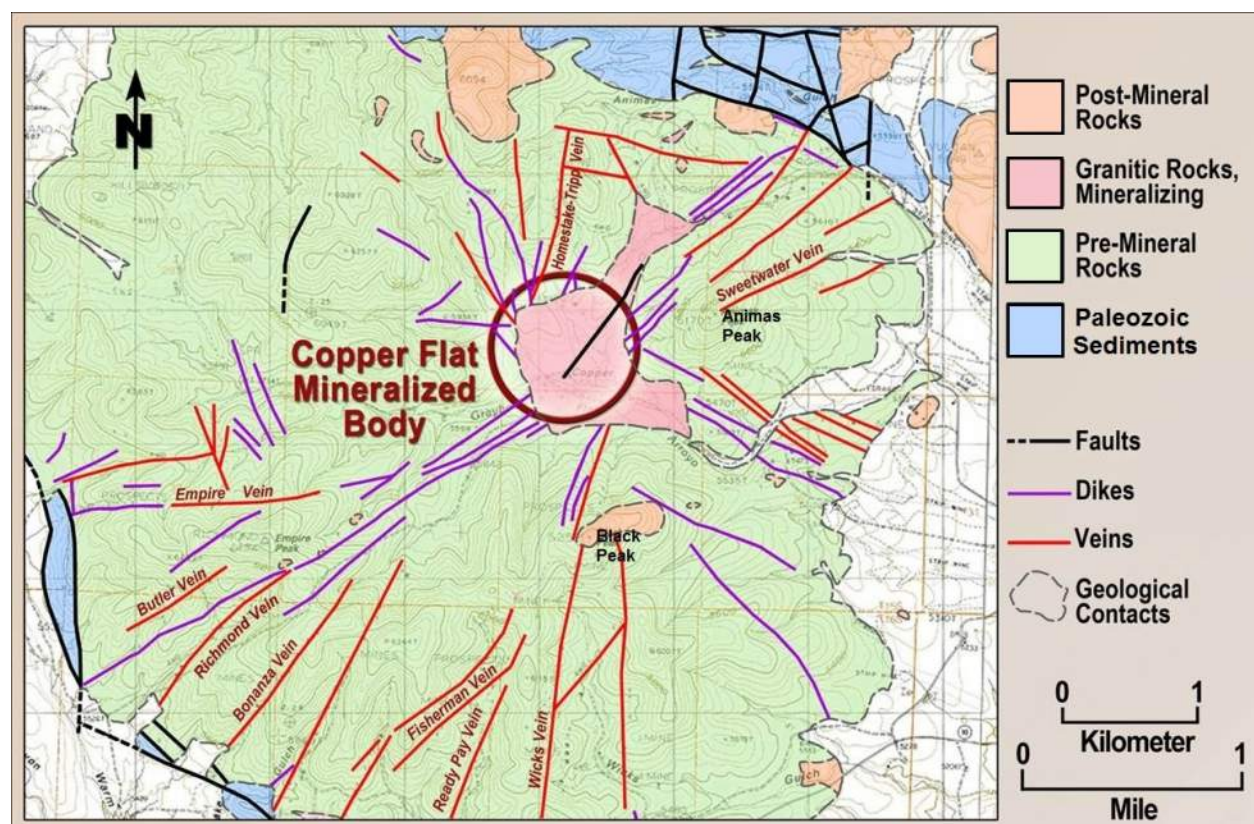


Figure 7-1: Regional Geology of Copper Flat Project Altered from P. Dunn (1982)

Basement rocks in the area consist of Precambrian granite and Paleozoic and Mesozoic sandstones, shales, limestones, and evaporites. Sedimentary units that crop out within the Animas Uplift include the Ordovician Montoya Limestone, the Silurian Fusselman Dolomite, and the Devonian Percha Shale. The Cretaceous-age Laramide orogeny, which was characterized by the intrusion of magma associated with the subduction of the Farallon plate beneath the North American plate, affected this region between 75 and 50 million years ago (Ma). Volcanic activity during the late Cretaceous and Tertiary periods resulted in localized flows, dikes, and intrusive bodies, some of which were associated with the development of the nearby Tertiary Emory and Good Sight-Cedar Hills calderas. Later basaltic flows resulted

from the tectonic activity associated with the formation of the Rio Grande rift. Tertiary and Quaternary alluvial sediments of the Santa Fe Group and more recent valley fill overlie the older Paleozoic and Mesozoic units in the area.

7.2 LOCAL GEOLOGY

The district geology is modified from Raugust (2003) and McLemore et al., (2000). The predominant geologic feature of the Hillsboro mining district is the Cretaceous Copper Flat andesite. The Hillsboro mining district comprises the Animas Hills, a low range formed by the Animas Hills horst at the western edge of the Rio Grande rift. Faults that bound the Animas Hills horst are related to the tectonic activity of the Miocene-age Rio Grande Rift (Dunn, 1982). Due to the difference in ages and in spite of its close proximity, there is no known connection between the Rio Grande rift and the older Copper Flat volcanic/intrusive complex. The Copper Flat volcanic/intrusive complex has been interpreted as an eroded stratovolcano based on the presence of agglomerate and flow band textures in some of the andesites (Richards, 2003).

Two quartz monzonite stocks, the Copper Flat Quartz Monzonite (CFQM) and the Warm Springs Quartz Monzonite (WSQM), intrude the core of the volcanic complex. The CFQM stock has a surface expression of approximately 0.4mi² and has been dated by the argon-argon (⁴⁰Ar/³⁹Ar) techniques to be 74.93 ±0.66 million years old (McLemore et al., 2000). The surrounding andesites also have been dated using argon-argon techniques to be 75.4 ±3.5 million years old (McLemore et al., 2000). The barren WSQM was emplaced after the period of mineralization but is still related to the other igneous rocks. Hedlund (1974) reported a K-Ar age date of 73.4 million years from biotite concentrate taken from drill core.

7.3 GEOLOGY OF THE COPPER FLAT OREBODY

The dominant geologic feature of the Animas Hills and Hillsboro district is the Copper Flat stratovolcano, a circular body of Cretaceous andesite that is 4 miles in diameter (Figure 7-1). The andesite is generally fine-grained with phenocrysts of plagioclase (andesine) and amphibole in a groundmass of plagioclase and potassium feldspar and rare quartz. Some agglomerates or flow breccias are locally present, but the andesite is generally massive. Magnetite is a common association with the mafic phenocrysts, and accessory apatite is found in nearly every thin section.

Although the depth of erosion is uncertain, the center of the stratovolcano was eroded to form a topographic low; the total depth of erosion is uncertain. To the east of the site, this andesite body is in fault contact with Santa Fe Group sediments, which are at least 2,000 ft thick in the immediate area of Copper Flat and thickening to the east. Near-vertical faults characterize the contacts on the remaining perimeter of the andesite body; these faults juxtapose the andesite with Paleozoic sedimentary rocks. Historical drill holes indicate the andesite is locally more than 3,000 ft thick. This feature, combined with the concentric fault pattern, indicate that the local geology represents a deeply eroded Cretaceous-age volcanic complex. Figure 7-2 is a simplified map of lithology on surface. Figure 7-3 is an east west cross section that illustrates the rock type geometries at depth.

7.3.1 Lithology

The core of the volcanic complex is a Cretaceous-age quartz monzonite stock that intruded into the center of the andesite sequence at the intersection of two principle structures that trend respectively N50°W and N20°E. The CFQM is an irregular-shaped stock underlying a surface area of approximately 0.40 square miles and has been dated to approximately 75 Ma. In the few exposures in which the CFQM is in contact with the andesite, the andesite shows no obvious signs of contact metamorphism. The CFQM is a medium- to coarse-grained, holocrystalline porphyry composed primarily of potassium feldspar, plagioclase, hornblende, and biotite; trace amounts of magnetite, apatite, zircon, and rutile are also present, along with localized mineralized zones containing pyrite, chalcopyrite, and molybdenite. About 15 percent of the monzonite is quartz, which occurs both as small phenocrysts and as part of the groundmass; however, quartz is absent in some parts of the stock.

Numerous dikes, some of which are more than a mile in length and mostly of latite composition, radiate from and cut the CFQM stock. Most of the dikes trend to the northeast or northwest and represent late stage differentiation of the CFQM stock. Immediately south of the quartz monzonite, the andesite is coarse-grained, perhaps indicating a shallow intrusive phase. An irregular mass of andesite breccia along the northwestern contact of the quartz monzonite contains potassium feldspar phenocrysts and andesitic rock fragments in a matrix of sericite with minor quartz. This may represent a pyroclastic unit. Magnetite, chlorite, epidote, and accessory apatite are also present in the andesite breccia.

7.3.2 Structure

Three principal structural zones are present at the Site and surrounding area, the most prominent of which is a northeast-striking fault that trends N 20°-40°E that includes the Hunter and parallel faults or the Hunter fault zone. In addition, west-northwest striking zones of structural weakness (N50°-70°W) are marked by the Patten and Greer faults, and east-northeast striking zones are marked by the Olympia and Lewellyn faults. All faults have a near-vertical dip; the Hunter fault system dips 80°W, the Patten dips approximately 70°S-80°S, and both the Olympia and Lewellyn fault systems dip between 80°S and 90°S. These three major fault zones appear to have been established prior to the emplacement of the CFQM and controlled subsequent igneous events and in the case of the Patten and Hunter controlled mineralization.

As previously stated, the CFQM emplacement is largely controlled by the three structural zones. The southern contact parallels and is cut by the Greer fault, although the contact is cut by the fault, and the southeastern and northwestern contacts are roughly parallel to the Olympia and Lewellyn faults, respectively. The CFQM stock is principally elongated along the Patten fault, as well as along the Hunter fault zone.

Although latite dikes strike in all the three principal fracture directions, most of the dikes strike northeast. The northeast trending fault zones contain a high proportion of wet gouge, often with no recognizable rock fragments. Reportedly in underground exposures, the material comprising the Hunter fault zone has the same consistency as wet concrete and has been observed to flow in underground headings. Based on recent drilling the Patten fault consists of a mixture of breccia and gouge. However, the material in the east-northeast fault zones contains only highly broken rock and minor gouge. The width of individual structures in all three systems varies along strike from less than a foot to nearly 25 ft. in the Patten fault east of the Project. Despite intense brecciation, the total displacement along the faults does not appear to exceed a few tens of feet. At the western edge of the Site, a younger porphyritic dike was emplaced in a fault that had offset an early latite dike, indicating that fault movement occurred during the time that dikes were being emplaced.

Post-dike movement is evident in all the three principal fault zones, and both the Hunter and Patten fault systems show signs of definite post-mineral movement. Fault movement has smeared sulfide deposits and offset the breccia pipe as well as the zones within the breccia pipe. Post-mineral movement along faults has resulted in wide, strongly brecciated fault zones. Some of the post-mineral dikes have been emplaced within these fault zones.

THEMAC has mapped the pit area and diversion cuts in detail at 1 inch equals 40 ft (1:480) and has examined the pre- and post-mineral stress orientations in the andesites and CFQM. Findings indicate no significant difference in the stress fields before and after mineralization.

7.3.3 Mineralization

Although copper occurs almost exclusively as chalcopyrite locally accompanied by trace amounts of bornite, minor amounts of chalcocite and copper oxide minerals are locally present near the surface and along fractures. The supergene enrichment typical of many porphyry copper deposits in the Southwest is virtually non-existent at Copper Flat. During the early mining days, a 20- to 50-ft leached oxide zone existed over the ore body, but this material was stripped during the mining activities that occurred in the early 1980s. Most of the remaining ore is unoxidized and consists primarily of chalcopyrite and pyrite with some molybdenite and locally traces of bornite, galena and sphalerite. Recently completed mineralogical studies indicate that fine grained disseminated chalcopyrite is often intergrown with pyrite and occurs interstitial to silicate minerals. Bornite and digenite coat and locally replace chalcopyrite but also occur interstitially to chalcopyrite and the silicates. Although deposition of chalcopyrite and molybdenite (76.2 Ma) was within the same mineralizing event with minor pyrite, bornite-digenite appears to represent a weaker and slightly later event of continuous copper mineralization.

Although low concentrations of gold (less than 100 parts per billion [ppb]) and silver (<2.0 ppm) occur throughout the deposit, intervals of higher gold concentrations (150 to more than 2,000 ppb) may be structurally controlled and are more commonly present in the eastern half of the deposit.

The sulfide mineralization first formed in narrow veinlets and as disseminations in the quartz monzonite with weakly developed sericitic alteration. This stage of mineralization was followed by the formation of the breccia pipe with the introduction of coarse, clotty pyrite, chalcopyrite, as well as molybdenite with strong potassic alteration either biotite or k-spar dominant.

The “breccia pipe”, which can best be described as a crackle breccia, consists largely of subangular fragments of mineralized CFQM, with locally abundant mineralized latite where dikes exposed in the CFQM projected into the brecciated zone that range in size from an inch to several inches in diameter. Andesite occurs only as mixed fragments partially in contact with intrusive CFQM and appears to represent the brecciation of relatively unaltered andesite xenoliths in the CFQM. The matrix contains varying proportions of quartz, biotite (phlogopite), potassium feldspar, pyrite, and chalcopyrite, with magnetite, molybdenite, fluorite, anhydrite, and calcite locally common. Apatite is a common accessory mineral. Breccia fragments are rimmed with either biotite or potassium feldspar, and the quartz and sulfide minerals have generally formed in the center of the matrix. It should be noted that the biotite breccia is gradational into both the quartz-feldspar breccia as well as the CFQM.

The total sulfide content ranges from 1 percent (by volume) in the eastern part of the breccia pipe and the surrounding CFQM to 5 percent in the CFQM to the south, north, and west. Sulfide content is highly variable within the breccia, with portions in the western part of the breccia containing as much as 20 percent sulfide minerals. Based on drilling, the strongest copper mineralization is concentrated in the western half of the breccia pipe and in the adjoining stockwork veined CFQM in the vicinity of the intersection of the Patten fault and the Hunter fault zone. Sulfide mineralization is concentrated in the CFQM and breccia pipe and drops significantly at the andesite contact. Minor pyrite mineralization extends into the andesite along the pre-mineral dikes and in quartz-pyrite-bearing structures, some of which were historically prospected for gold.

Molybdenite occurs in some steeply dipping quartz veins or as thin coatings on fractures. Minor sphalerite and galena are present in both carbonate and quartz veinlets in the CFQM stock. Evaluations of the mineralization at Copper Flat indicate that copper mineralization concentrates and trends along the N50°W structural influences, whereas the molybdenum, gold and silver appear to favor a N10°-20°E trend.

8 DEPOSIT TYPES

Copper Flat is a porphyry copper-molybdenum deposit that is approximately 1,400 by 2,100 ft in plan occurring within a small structurally controlled quartz monzonite stock that has intruded a circular block of andesite approximately 4 miles in diameter. The porphyry includes a variably mineralized west-northwest-trending hydrothermal “breccia pipe,” that lies immediately south of the Patten fault, that is about 1,400 ft long and 500 ft wide.

Copper Flat has been categorized as an alkalic copper-gold bearing breccia pipe, surrounded by and genetically linked to an alkalic porphyry system. The deposit is situated along the eastern edge of the Cretaceous Arizona-Sonora-New Mexico porphyry copper belt and along with Tyrone, New Mexico, forms a linear mineralized feature known as the Santa Rita lineament (SRK, 2010; McLemore et al., 2000).

Analogous deposits include Terrane Metal's Mount Milligan, British Colombia deposit and the Continental breccia pipe located in the Central Mining district of New Mexico (SRK, 2010).

Lowell (1988) was the first to suggest that the Hillsboro district was a gold-rich porphyry system type that develops in alkaline igneous settings. Jones (1992) described metal zoning associated with gold-rich porphyry systems that is directly applicable to the Copper Flat deposit and the Hillsboro mining district. In addition, McLemore et al., (2000) and McLemore (2001) documented chemical characteristics that identify the Copper Flat deposit as an alkalic copper-gold system.

Copper-molybdenum mineralization at the Copper Flat deposit occurs in a WNW trending, steeply dipping breccia pipe and the surrounding CFQM. The strongest Cu-Mo mineralization occurs in the western half of the breccia pipe and in strongly stockwork veined CFQM adjacent to the northern edge of the breccia pipe near the intersection of the Patten fault and the Hunter fault zone. A recent Re-Os age date performed on molybdenite yielded an age of 76.2 Ma.

Although low but recoverable gold (<100ppb) and silver (2.0 ppm) values occur throughout the deposit, the highest gold and silver values occur in the eastern part of the deposit. This mineralization is thought to be structurally controlled and related to northeast trending structures within or related to the Hunter fault zone.

Previous workers have spent a great deal of time describing and trying to explain the genesis of the “breccia pipe”, which can best be described as a crackle breccia. These people concluded that the absence of rock flour or gouge in the matrix suggests that brecciation was not the result of significant tectonic movement. The apparent lack of appreciable movement between the fragments and the gradational contact between true breccia and the zone of stockwork veining preclude any explosive mechanism for the brecciation. The mechanism for the formation of the Copper Flat mineralized breccia pipe that appears most compatible with the above observations is autobrecciation resulting from retrograde boiling, perhaps coupled with minor structural displacement. This occurs when the pressure of the mineralizing hydrothermal fluid exceeds the confining pressure (Phillips, 1973).

Unlike most porphyry copper deposits in the southwestern U.S there was very little supergene enrichment at Copper Flat. This was probably due to factors such as the low sulfide content, buffering nature of the host rocks, a static water table and burial beneath post-mineral volcanics. As a result, mineralization is primarily hypogene and pyrite dominant. Additionally, the Copper Flat deposit does not show the symmetrical and telescoped zoning of alteration types that is considered typical of most porphyry copper deposits. This may be due to the small size of the deposit, coupled with a relatively low fluid volume during the mineralizing process, and the alkaline nature of the mineralizing fluids. Alteration includes, potassic, two separate episodes of sericitic and propylitic, but on a smaller scale than other more “typical” porphyry systems. The geology of Copper Flat indicates that the hypogene mineralization and alteration, including the formation of the zone of brecciation (breccia pipe), was the result of the final crystallization of the CFQM melt and related dikes.

9 EXPLORATION

Copper Flat is an advanced development project that was in production for only a few months in the early 1980's. As such, most of the exploration completed since that time has been the addition of diamond drilling to confirm, expand, and better understand the deposit. The current and historic drilling will be discussed in Section 10.

During the 2012 exploration program, THEMAC personnel completed detailed surface mapping of all exposures within the historical pit, drainage cuts, and most of the outlying project area. Surface geochemical sampling was also completed to improve the understanding of the precious metal distribution outside of the deposit, as well as identify other potential exploration targets.

In addition to drilling, all of the historical core has been relogged to obtain lithologic and structural information using core photographs; additional mineralogical and metallurgical studies have been undertaken; geotechnical studies have been completed and a CSAMT geophysical survey completed in the central part of the project that was designed to investigate and define the extent of the CFQM and sulfide mineralization.

With the completion of the 2012 drilling program, the Copper Flat deposit is now considered to be characterized to the extent necessary for a Feasibility Study. However, upon commencement of mining, it may be possible to expand the reserve and resource with additional drilling. This drilling should be focused on attempting to extend the deposit to depth (below the planned pit bottom), better defining the margins of the deposit and extending and better defining the northeastern lobe of the deposit.

10 DRILLING

The Copper Flat deposit has been drilled over several iterations from 1952 through 2012. The majority of the drilling was completed in the late 1970's and early 1980's.

Drilling was first initiated at Copper Flat in the 1950's by Newmont mining. Previous technical reports indicate that Bear Creek mining also completed 20 holes in the late 1950's. The assay information from the 1950's programs are not in the current drill hole data base that is being used for mineral resources.

The majority of the drilling at Copper Flat was core completed between 1968 and 1978 by Inspiration and Quintana Minerals. During 1989 through 1991, Rio Gold and Tenneco drilled 6 large diameter reverse circulation (RC) holes but did not pursue the project. The Rio Gold assay results are not in the active Copper Flat data base.

The Inspiration and Quintana holes were diamond core drilling and most were reported to have been predominately NX size.

THEMAC drilled 48 holes from 2009-2012. THEMAC also re-assayed all available historic pulps for gold and silver. THEMAC drilling was all diamond core drilling and was predominately HQ size core.

Table 10-1 summarizes the drill programs completed on the project where there is data available for the determination of mineral resources. All of the drilling summarized below is diamond core drilling.

Table 10-1: Copper Flat Drill Data, Available for Determination of Resources

Company	Dates	Drill holes	IMC comments	Elements Assayed	IMC Summary
Inspiration Consolidated	1967-1973	CF-1 to CF-20	20 drill holes, 4 with no assay CF-14,CF-15,CF-20 and CF-5	Totcu (%) Moly (%)	769 assay intervals, 9,350 ft of drilling
Inspiration Development	1968-1971	IDC-1to IDC-29	31 drill holes, 4 holes no assay IDC-20, -29,-30,-31	totcu (%) moly (%) gold(opt) silver (opt)	3,290 assay intervals, 27,183 ft of drilling
Quintana Minerals	1974-1978	H Series	134 drill holes total, 129 w/total copper, 21 holes assayed for gold and silver	Totcu (%) Moly (%) Gold(opt) Silver (opt)	9,709 assay intervals, 97,210 ft of drilling
NMCC	2009-2012	CF Series & CNI Series	48 drill holes, 2 holes no assay CF-12-19,-20	Totcu (%) Moly (%) Gold(ppb) Silver (ppm)	8,422 assay intervals, 47,583 ft of drilling

Figure 10-1 illustrates the drill holes on site. The recent drilling completed by THEMAC is shown in red. Only the drill holes that have assay data that were used for mineral resources are shown on the map.

No reverse circulation drilling was used in the estimation of resources. All available historic information indicates that all of the drilling that was used for estimation of resources and reserves was diamond core drilling.

The drill hole assay data base is stored in electronic format at THEMAC offices with backup on file within the IMC data archives. The data base contains current and historic information regarding lithology and assay information. In addition to the electronic files, Quintana drill hole logs are available at the project site in their original paper format.

11 SAMPLE PREPARATION, ANALYSES AND SECURITY

The majority of the data base that is available for Copper Flat was developed by Quintana during the 1970's and 1980's. Recent drilling by THEMAC has been added to the data base to both confirm and expand the historic information.

This section will present the sample preparation procedures for:

- 1) the historic procedures applied by Quintana based on historic documents, and
- 2) the procedures currently being applied by THEMAC.

The procedures that were applied by IMC to assemble the working data base for development of mineral resources will be summarized at the end of this section.

The recent drill holes that have been completed by THEMAC were used to confirm the historic drilling when the new holes were located close to historic data. That confirmation process will be discussed in Section 12 regarding data verification.

IMC and John Marek (QP) holds the opinion that the sample preparation, analysis, and security of the data base is reliable based on the result of the comparison between historic and modern data and site review of the modern procedures that are being followed.

11.1 HISTORIC SAMPLE PREPARATION

The historic procedures applied by Quintana were documented by Peter Dunn in the 1992 Mining Engineers Handbook. This section will paraphrase that information.

The historic drilling by Inspiration and Quintana was diamond core drilling. Most of the Quintana holes were NX diameter. Drilling prior to 1975 utilized standard techniques of splitting the core and preparing ½ core for assay. Core recoveries were reported to range between 88% and 96% depending on the program and a later incentive bonus for core recovery.

During 1975, Quintana completed a comparison between the assay of both halves of split core. Dunn reports that the results were not satisfactory, so the sample preparation procedure was modified and a sample preparation facility was built on site. About 30 holes had been completed by the time the issue was identified and nearly 2,000 samples were re-prepared and re-assayed to correct the problems with the initial data. The modified procedure crushed the sample to a finer size before sample splitting.

The final sample preparation procedures applied by Quintana was:

- 1) The entire core (about 36 lbs) was crushed to ½ inch before being split
- 2) A 1/8th split was taken within a Jones splitter.
- 3) The split was crushed to 10 mesh before being split again.
- 4) The resulting split was about 2 lbs, which was pulverized to -100 mesh.
- 5) Of the -100 mesh pulp, about ½ lb was selected for assay.

Other documentation from Dunn in 1984 was reported by SRK in their earlier technical report on Copper Flat. That report states that the sample was crushed to 0.2 inch and split 3 times by riffle splitter to obtain a 1/8th split prior to crushing to 10 mesh.

Samples were assayed for total copper and moly. Near surface samples were also assayed for non-sulfide copper. Dunn states that samples were sent to Tucson for assay. At that time, the two commercial labs in Tucson were Skyline Labs, and Jacob's Assay Labs. Certifications on the labs at that time are not known. Standards that were made from Copper Flat material were sent with each assay shipment. Assay checks were completed, but the extent and procedures were not reported.

Many of the details of the historic sample and assay procedures are not known. Therefore, the recent drilling by THEMAC becomes important to verify the historic drill and assay results.

11.2 THEMAC PROCEDURES

THEMAC started drilling in late 2009 which continued into 2010. Drilling was predominately HQ diameter core holes. A second program by THEMAC was completed during 2012. The core handling and sampling procedures that are followed by THEMAC are summarized below:

- 1) Core is boxed at the drill rig by the drill contractor and labeled with drill depth and drill run intervals. Core is transported to the on-site logging facility by THEMAC employees.
- 2) Core photos are taken of the hole core.
- 3) The core is laid out in the core logging facility where geotechnical and geologic logging is completed by THEMAC geology staff. Sample intervals are marked by the geologist. Sample intervals are a minimum of 5 ft and a maximum of 10 ft long. The calculated average is 6.7 ft.
- 4) The core is diamond sawn and $\frac{1}{2}$ of the core is packaged for shipment to the Skyline labs. The other $\frac{1}{2}$ is retained in the permanent core storage.
- 5) Sample transport to the laboratory is provided by Skyline Assayers & Laboratory in Tucson, Arizona.

Skyline Assayers & Laboratory (Skyline) receives the samples and logs them into their LIMS system for tracking and reporting. Skyline is ISO/IEC 170215 Certified. Sample preparation procedures are as follows:

- 1) Samples are oven dried at 255-240° F for 8 to 24 hours
- 2) Samples are tagged and bar coded
- 3) Samples are crushed to 75% passing -10 mesh
- 4) Samples are homogenized by splitting 3 times in a riffle splitter, and then recombined for a final split of about 250 gm.
- 5) The 250gm sample is pulverized to 95% passing 150 mesh

Assay procedures are as follows at Skyline:

- 1) Copper and Moly by ICP methods. Typically, multi-element ICP is ordered. Some 2010 copper assays were reported by AA methods.
- 2) Gold is assayed by Fire assay methods with an AA finish. (FA-1)
- 3) Silver is reported with Aqua Regia dissolution with AA finish. (FA-8)

QAQC procedures by THEMAC are as follows:

- 1) Blank samples are inserted 1 out of every 20 samples
- 2) Standards are inserted 1 out of every 20 samples
- 3) Field duplicates are shipped 1 out of 20 samples. Field duplicates are a second split of the other $\frac{1}{2}$ of the split core as a check on sample preparation.
- 4) Independent check assays are planned to represent 5% of the samples. The selected check lab is ALS Chemex.

Analysis of the blanks, standards, field duplicates and independent check assays are discussed in Section 12.

11.3 DRILL HOLE COLLAR SURVEYS

The historic coordinate system for the Copper Flat Project was a local mine grid in English units that was established in the 1970's. Recent work at site began to take advantage of GPS survey to locate samples and drill holes. Some of that work was completed using UTM metric units.

THEMAC has now established a standard coordinate system for the project based on the UTM NAD83 system converted to Feet. THEMAC contracted Earl Watts of Geodetic Analysis, LLC to check the field survey of many drill collars and convert the mine grid and other coordinate information to the standard project system of UTM NAD83 Feet. The drill collars for the 2011 and 2012 drilling programs were surveyed by E. Schaff and Associates, Delta, Colorado. The UTM coordinates were subsequently provided to IMC.

IMC spot checked the resulting final coordinate system by plotting the drill hole locations on a paper map from the UTM NAD83 Feet coordinates that were provided. A historic map of drill coordinates in mine grid was also prepared at the same scale. The two maps were compared against each other and topographic information. The two maps located all drill holes in the proper position relative to each other.

IMC verification of the collar survey information indicates that the data base is consistent in the UTM NAD83 Feet coordinate system. As a result the survey information is reliable and can be used for the determination of mineral reserves and mineral resources.

From this point forward, the block model, mine plan and project evaluation will be in the established project coordinate system.

11.4 ASSEMBLY OF DATABASE

As noted earlier, the available drill hole information is a collection of historic and recently completed drill data. Some historic pulps were re-assayed and utilized when available.

THEMAC was able to find 34 original paper drill logs for drill holes that were drilled by Inspiration and Inspiration development. Within those logs there were assays for copper, moly, gold, and silver. IMC and THEMAC staff entered that data and compared it to the historic digital data base that was acquired by THEMAC upon acquisition of the property.

The paper logs are not identical to the electronic data base because the 34 holes all predate 1975 and are likely the holes that were re-prepared and re-assayed as described earlier in this section.

Statistical comparisons between the paper logs and the historic digital data base did not show a bias but did indicate a moderately higher variance within the paper log data than the digital data. This would be consistent with the reasoning behind the re-preparation process reported by Dunn.

However, there were more assays available in the paper logs for those 34 holes than in the digital data base. The digital data contained un-populated intervals that were populated within the paper logs. This amounts to about 1680 additional copper assays, 63 additional moly assays, and about 420 gold and silver assays. As a result of the IMC comparison between paper logs and the digital data base, the paper log assays were added to the data base when the digital data was not available.

The historic electronic data base that was provided by THEMAC to IMC was the starting basis for assembly of the working data base. IMC assembly variables were added to the data base for each metal and initialized to a code for “no assay” for each of the metals: copper, moly, gold, and silver. The assembly variables were populated by the priorities outline below.

The assembly priority for each of the metals was:

- 1) Historic digital assay data.
- 2) If the digital assays were not valued, the paper log entries from 34 of the drill holes were used in addition to the digital values.
- 3) 2009 – 2012 assays from THEMAC drilling were added.
- 4) If SRK and/or Skyline re-assays were available for the metal, they replaced the historic assay data.

The assays of historical pulps obtained during the re-assay program by THEMAC during 2010, 2011, and 2012 have been included in the current model.

12 DATA VERIFICATION

The drill hole data base for Copper Flat has been in existence since the 1980's. Previous work in 2010 and 2011 by THEMAC and their contractors completed a number of verifications steps to develop some confidence in the historic data. During 2011 and 2012, THEMAC drilled additional holes in order to: 1) provide additional confirmation of the historic drilling, 2) test for extensions to the mineralization, and 3) provide geotechnical information for slope stability.

This section presents an independent verification of the data base by IMC and John Marek (Qualified Person for this chapter). Previous work will be drawn upon and analyzed along with recent drill results.

In summary, IMC and John Marek (QP) hold the opinion that the data base as assembled for this study is reliable for the purposes of estimating mineral resources and mineral reserves. In assembling the data set for determination of mineral resources and reserves, some questionable historic data items have been removed from the data base.

The basic steps that will be discussed in this section are:

- 1) Reassay of historic pulps by THEMAC and SRK to confirm historic data.
- 2) Verification of THEMAC internal QAQC procedures and the results of those procedures.
- 3) Comparison of THEMAC drilling completed in 2010 and 2011 versus the historic drilling on a nearest neighbor basis.
- 4) Corrections and modifications to the data set applied by IMC prior to determination of mineral reserves and mineral resources.

12.1 PULP REASSAYS BY THEMAC AND SRK

During 2009 and 2010, THEMAC selected pulps from the available stored pulps on site for re-assay. Those samples were sent to Skyline Assayers in Tucson, Arizona for analysis. IMC obtained 601 of these pulp assay results which had values for both copper and moly.

During 2010, a second set of pulps was pulled from the historic pulp library for additional verification of the historic data and assay. During this effort SRK, acting as a contractor to THEMAC, selected the intervals for re-assay in an effort to provide broader spacial coverage and a representative distribution of the project grades. This second set of pulp re-assays was also submitted to Skyline in Tucson for assay.

In addition to copper and moly, gold and silver were also assayed during this program. The re-assay results are positive for copper and moly and provide confidence in the use of historic copper and moly value. A thorough statistical analysis of both of the pulp re-assay programs during 2012 by IMC indicated that all of the historic information could be combined with the more recent re-assays.

In addition, a substantial component of the historic drilling had not been assayed for gold or silver. As a result, IMC recommended re-assay of the remaining historic pulps that could be reliably located, sampled and re-assayed with particular emphasis on gold and silver assays.

THEMAC has followed up on that recommendation so that the historic pulp values have been re-assayed and incorporated into the data base. Gold and silver were the primary focus of this effort in order to bring the assay coverage for precious metals up to the same level as the project base metal assays.

At this time, there are 542 gold assays and 547 silver assays within the combined data base that are from the historical data base. These historic values amount to 3.5% of the entire data base that was used to estimate the model.

The analysis of the historic assays versus pulp re-assays was presented in the previous Technical Report dated 22 August 2012.

12.2 THEMAC QAQC

The drilling completed by THEMAC during 2010, 2011, and 2012 utilized industry standard procedures for QAQC. This section will address the results of that QAQC analysis. Based on the positive results from this QAQC effort, the confidence in the drilling programs from THEMAC was established. The new drilling from THEMAC was used to verify the historic information on a nearest neighbor basis.

The QAQC procedures that were applied by THEMAC during 2010, 2011 and 2012 were as follows:

- 1) Blanks are inserted approximately 1 out of 20 samples submitted to the lab.
- 2) Standards are submitted on a 1 out of 20 basis as blind samples to the lab.
- 3) Field Duplicates are based on the second half of sawn core. These are submitted to the lab as a check on sample preparation. A "slab" of core is retained in the core tray rather than use the entire remaining split.
- 4) Independent check assays were sent on a 1 in 20 basis for shipment to ALS Chemex.

The results of blank, standard, and field duplicate submissions for all of the THEMAC data are summarized in the following sub-sections.

12.2.1 Blanks

There were 392 blank samples (1 out of 20) submitted for the THEMAC drill program. From that set of blanks there was one interval that reported out of range for all four metals. The copper and gold grades reported for that blank were close to one of the standards values used in the same year. The high value blank could have been the result of a standard insertion as blank.

<u>Metal</u>	<u>Number of Blanks</u>	<u>Highest Value</u>
Copper	392	0.45% and 0.21%
Moly	392	0.013%
Gold	392	0.0025 oz/ton
Silver	392	0.111 oz/ton

The high value for all of the results above were from drill hole number CF12-11 at 382-387 ft. Copper results have one additional high sample at 0.21% copper.

In summary, 2 out of 392 out of tolerance for copper is an acceptable result for blanks. The other metals have only 1 out of 392 out of tolerance.

12.2.2 Standards

Standards were submitted as pulps within the split core sample submissions to the Skyline assay lab. Standards were obtained from WCM minerals as certified values. A total of 384 standards were submitted as part of the regular sample submission program to Skyline labs.

Figure 12-1 summarizes the results of THEMAC standards submission for copper, moly, gold, and silver. The graphs indicate that about 3 samples out of 384 were likely standards swaps. The results do not indicate a bias and a swap rate of 3 out of 384 is acceptable.

12.2.3 Field Duplicates

THEMAC submitted 382 field duplicates of split core to Skyline for assay. The results are summarized on Figure 12-2. The mean of the duplicates for all metals is within a close tolerance of the original mean. No bias has been observed with the core splitting, preparation, or assay procedures from this data.

12.2.4 Check Assays

THEMAC submitted 421 pulps to the ALS Chemex lab as third party checks on the original Skyline assays. Figure 12-3 summarizes the results of those assay values on X-Y plots. The plots do not indicate a bias or significant issue with the check assay results.

Comparisons of the mean values are summarized below as an indication of the positive check assay results for the 421 submitted pulps.

<u>Metal</u>	<u>Skyline Mean</u>	<u>ALS Chemex Mean</u>
Copper	0.178%	0.166%
Moly	0.005%	0.006%
Gold	0.0546 g/t	0.056 g/t
Silver	1.26 g/t	1.23 g/t

All means of all four metals pass the Student's T test for being from the same populations.

12.3 HISTORIC DRILLING VS THEMAC DRILLING

The 2011 THEMAC drill program was intended to confirm previous drilling as well as investigate new mineralization. The 2011 program generated data pairs that were physical close to previous Quintana drill holes. The THEMAC drilling was compared to the historic drilling to investigate the reliability of the historic drill data. Within the following discussion, the term “new” holes mean THEMAC drilling from 2010 and 2011. “Old” holes mean the historic data base prior to THEMAC drilling and comprised primarily of Quintana drill holes.

The additional holes completed during 2012 did not add a significant number of sample pairs to the nearest neighbor comparison of New vs Old. As a result, the nearest neighbor work was not updated, but is reported here for completeness.

Several of the new drill holes were planned to “scissor” old drill holes, meaning that they cross the old holes at an angle and are not specifically twin holes. They do however; generate local twins of a number of old drilling intervals with new drilling.

IMC paired the new drilling and old drilling on a nearest neighbor basis. The drill hole data was first composited to 25 ft down hole (length) composites as summarized Section 14. The comparison was completed between old and new composites that were at spacing of 25, 50, 75, and 100 ft. All of the discussion in this section will focus on the pairs of data that are less than 50 ft apart.

Figure 12-4 illustrates the results of pairing new vs old drilling for copper with a maximum spacing between composites of 50 ft (one model block). The new composite value is on the X axis and the nearby paired old composite value is on the Y axis. One will immediately note that there are 8 high values above 1.5% copper in the old data that are not reflected in the new drill hole data.

More detailed investigation showed that the 8 high composites are contained within two old drill holes numbered: 75-14 and 75-8. This result was initially caused for some concern because the new holes did not see the high grade.

The following observations were noted.

- 1) Old drill holes 75-14 and 75-8 were logged from photographs and the intervals in question were logged as intermittent breccia and quartz monzonite.
- 2) The new paired drill holes CF-10-06b and CF-11-04 were carefully logged in the core tray and both holes were logged as quartz monzonite with no breccia noted in these intervals.
- 3) The pulps from the entire drill hole 75-8 have been re-assayed by THEMAC. The pulp re-assays closely match the original high-grade assays and easily pass the T-statistic hypothesis tests.
- 4) Removing the 8 high values from consideration results in 141 data pairs that show no bias and comfortably pass the hypothesis tests as being from the same population.

The above points indicate one of two options: 1) The old drill hole pulp preparation was high biased in selected locations or: 2) The boundaries between brecciated high grade and nearby low grade can be abrupt.

The historic description of sample preparation by Quintana does not indicate any issues regarding sample preparation bias. In addition, it is difficult to bias copper assays as compared to other metals.

Historic writing by the Quintana staff indicates the grade variability that occurs in the breccia zones. The change in logged rock type between brecciated and non-brecciated rock within 25 to 50 ft is likely the explanation for the new holes not seeing the same high grade.

The above comparisons and observations have contributed to the mineral resource procedures whereby high grade zones are separated from surrounding low grade and high value composites receive limited search radius as it appears that high grade zones can be of limited extent.

The same situation occurs in the other metals (moly, gold, silver) in the same places as identified in the copper discussion above.

Table 12-1 summarizes the nearest neighbor results before and after removal of high-grade composite values from the old data set. The results further support the limitation of high-grade area impact from both old and new drilling during the estimation of mineral resources.

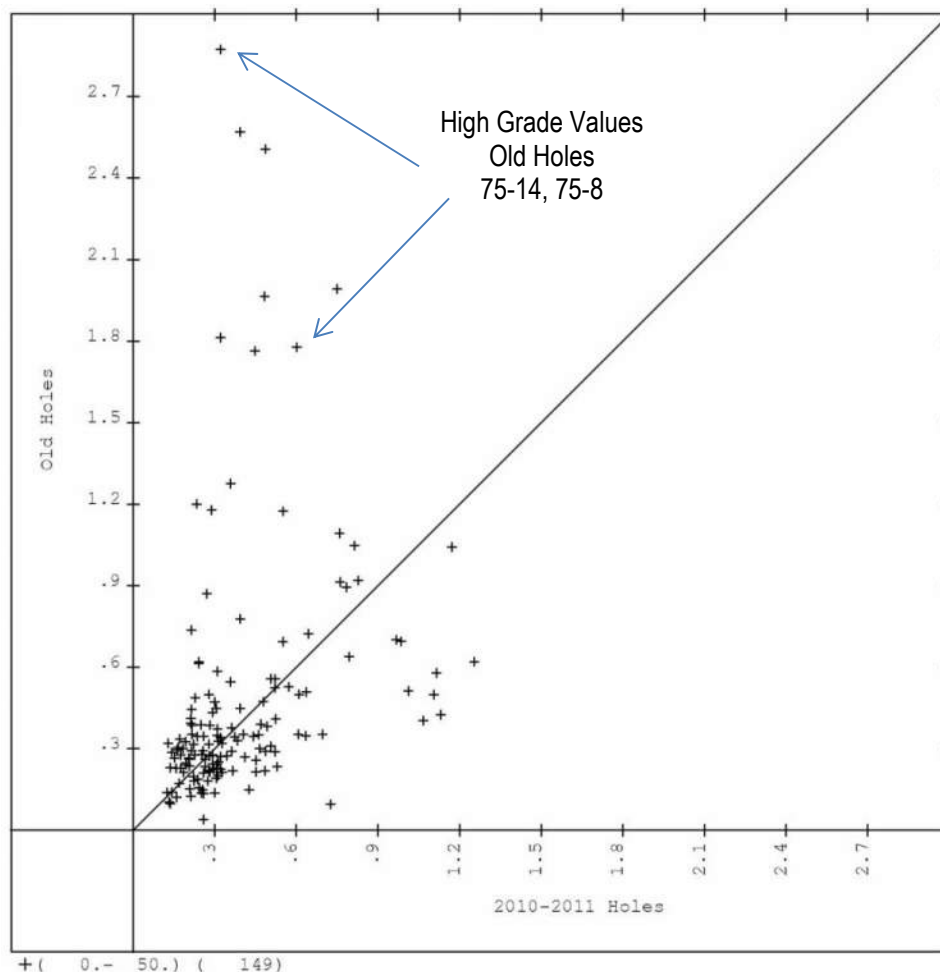


Figure 12-4: Nearest Neighbor Comparison of New vs Old Holes for Copper (Samples are 25 ft composites, Grades are in % Total Copper)

Table 12-1: Nearest Neighbor Comparison – 2010 and 2011 THEMAC Drilling vs. Historic Drilling – 25 ft Down Hole Composites Spaced 50 ft Apart

Metal	New vs Old, No Grade Limits				New vs Old, Remove Old High Grades				
	Number of Pairs	2010-2011 Mean	Historic Mean	Hypothesis Test Summary	Remove Old HG Above	Number of Pairs	2010-2011 Mean	Historic Mean	Hypothesis Test Summary
Copper %	149	0.392	0.484	Fail	1.50%	141	0.387	0.389	Pass
Moly %	135	0.017	0.020	Pass	0.090%	128	0.015	0.015	Pass
Gold oz/ton	62	0.003	0.006	Fail	0.010 oz/ton	48	0.003	0.004	Pass
Silver oz/ton	66	0.090	0.131	Fail	0.25 oz/ton	56	0.081	0.093	Pass

Hypothesis Tests include: T-statistic on Means, Paired T
Impact of High Grade values in old drilling within 50 ft is illustrated.

12.4 DATA CORRECTIONS

Two corrections were applied to the historic database by IMC prior to the development of mineral resource estimates. Those are discussed as follows:

12.4.1 2010-2011 Down Hole Surveys

THEMAC requested down hole surveys to be completed by the drilling contractor on all of the 2010 and 2011 drill holes. Reviews of the 2011 down hole survey data by IMC indicated substantial discrepancies in the data including 180-degree reversals and 90 degree turns in the drill holes within one sampling interval.

Discussions with the site geologist and reviews of the original set up orientations of the drill holes proved that the down hole surveys should not be trusted during the 2011 time period.

Further reviews of the 2010 drilling noted that the first down hole survey in every hole varied from the set up bearing by about 9 degrees. IMC understands that the down hole tools uses a magnetic compass and the magnetic declination at Copper Flat is 9 degrees. It appears that the drill contractor did not adjust for the local magnetic declination and some users did not know how to operate instrument.

As a result, IMC set all of the drill hole bearings for 2010 and 2011 drilling equal to the set up bearing established by and confirmed by the site geologists. Changes in down hole plunge from the down hole surveys were allowed to be used as they were likely a simple gravimetric devise that required no correction or interpretation.

The IMC correction would have little or no impact on the first several hundred feet of a drill hole. As the holes approach 1,000 ft in depth, there could be changes in hole location that could move the samples as much as 50 ft.

During the 2012 drilling program, all of the down hole surveys appear to be reliable and show little deviation other than the normal expectation from their planned bearing and inclination.

12.4.2 Underground Drift Data

The historic data base contained the channel assays from 4 underground drifts that had been driven to obtain metallurgical samples, sometime in the past. Reviews of maps and sections indicated that these drift samples appeared high valued compared to the nearby diamond drill hole data.

IMC completed a nearest neighbor comparison of the drift data versus nearby diamond drilling and found the drift channel data to be substantially high biased relative to drilling.

As a result of this outcome, the channel data was removed from the data set and not used for the development of mineral resources or mineral reserves.

13 MINERAL PROCESSING AND METALLURGICAL TESTING

The Copper Flat deposit is a porphyry-type copper deposit with recoverable concentrations of molybdenum, silver, and gold. The primary copper mineral is chalcopyrite. Considerable process design and metallurgical testing were accomplished prior to the Quintana operation of the property in 1982. Additional testing has been accomplished since then by others contemplating redevelopment of the property, including recent work by Minerals Advisory Group Research and Development (MAG), of Tucson, Arizona, commissioned by THEMAC. The process flow design and recovery estimation presented here is supported by the current test data as well as results from the Quintana operation.

13.1 METALLURGICAL TESTING PROGRAM

Metallurgical testing was conducted for Quintana prior to the development and operation of the mine in 1982. Additional work has been done for various companies investigating redevelopment of the property. M3 reviewed the test work and commissioned additional testing to complete a feasibility-level evaluation of process design and metal recoveries for THEMAC.

The primary process development was conducted by Colorado School of Mines Research Institute (CSMRI) (1976a and 1976b). This work included grindability testing, precious metal recovery investigation, and pilot plant testing. Lightner (1976) reported on molybdenite circuit testwork. Pincock Allen and Holt (PAH) (1979a, 1979b, and 1979c) reviewed the metallurgical information, performed statistical analyses, and reported on a flotation investigation conducted by the Koppers Company. Shantz (1981a and 1981b) reported on grind versus recovery information and sulfide content of the ores. Hood, et al. (undated) reported on testing and scale-up for the semi-autogenous grinding (SAG) mill. Operational data obtained from Quintana files was used to confirm metallurgical testing results and testifies to its validity.

Additional metallurgical testing has been conducted since the Quintana operation which provides additional information concerning the characteristics of the ore and supports the historical findings. METCON Research, Inc. (METCON) (1993) conducted preliminary flotation investigations in support of efforts to redevelop the property. Robinsky (1996) investigated tailings disposal for the redevelopment. Recently, comminution testing has been conducted by Hazen Research, Inc. (Hazen) (2011a, 2011b, and 2012) to confirm the grindability of three ore types, test the abrasiveness of the ore, and evaluate changes in grinding characteristics with depth in the orebody. Pocock Industrial (2011) conducted solid-liquid separation testing on tailings samples supplied by METCON from a blend quartz monzonite and breccia ore samples from recent drill core including sample characterization and particle size analysis, flocculant screening, gravity sedimentation, pulp rheology, pressure filtration, and vacuum filtration.

Feasibility metallurgical testing concluded with a battery of testing designed to evaluate gold deportment, recovery changes with respect to mining phase, and gravity recoverable gold. G&T Technical Services (G&T) (2012) investigated the presence of free gold in flotation tailings from samples with high gold contents. FLSmidth-Knelson (2012a) conducted testing on tailings from ore samples of more typical grades to investigate the potential for enhancing gold recovery using gravity methods.

MAG (2013a) conducted flotation testing to validate the parameters established by CSMRI, evaluate a variety of reagent suites, and produce sufficient concentrate to conduct testing for production of a molybdenum concentrate. Test work was conducted on recent drill core of three identified ore types: quartz monzonite (QM), biotite breccia (BB), and quartz feldspar breccia (QFB). Testing was further stratified between composites of ore that would be mined in the first five years and those mined later in the mine plan. Both composites consisted of 65 percent QM, 15 percent BB, and 20 percent QFB. Testing included bulk sample preparation (crushing and mixing and splitting test charges), test product sample preparation (pulverization), grind and regrind characterization, batch rougher, cleaner, and scavenger flotation, and locked-cycle flotation. Cu-Mo separation of bulk Cu-Mo concentrate and cleaning of

molybdenum concentrate. The “mine phase” composites were used to evaluate reagent suites that may be more selective at a lower pH. A six-cycle, locked-cycle test was conducted on an early mine phase composite.

Comparison of the results from the CSMRI 1976 locked-cycle test and 1982 mill operating results with MAG flotation results, presented in Table 13-1 below, showed that results have been reproduced by MAG on fresh ore. Testing of the current drill core produced low rougher flotation tailings of 0.02-0.03% copper which was consistent with the other results demonstrating that the core samples contained principally sulfide mineralization.

Table 13-1: Comparative Flotation Response from CSMRI 1976 Locked Cycle Test/1982 Mill Operating Results and MAG R&D Flotation Tests

CSMRI June 23, 1976 Rpt. Mill Monthly Report July 1, 1982 & MAG R&D July 2012 Report

Test Identification	Time Period	Product	Weight	Assay Values					Distribution				
				Cu	Fe	Mo	Au	Ag	Cu	Fe	Mo	Au	Ag
			%	%	%	%	oz/t	oz/t	%	%	%	%	%
CSMRI Testing of Core	1975-1976	Final Conc.	1.49	29.400			0.156	4.728	91.07			46.30	88.00
		Tail		0.024									
		Calc. Head		0.405			<0.005	0.083					
Milling Statistics Copper Sulfides	April/May/ June 1982	Final Conc.		28.420			0.164	4.030	73.00				
		Tail		0.094	1.05	0.0055							
		Calc. Head		0.350		0.0074							
MAG R&D Testing of Core	2012	Final Conc.	1.12	27.217	27.67	0.8960	0.150	4.078	90.45	15.10	69.19	71.10	82.7
		Tail		0.025	1.79	0.0041	0.001	0.032	9.55	84.91	30.81	28.90	17.3
		Calc. Head		0.355	2.12	0.0144	0.003	0.079	100.00	100.00	100.00	100.00	100.00

Samples of flotation products and tailings produced by MAG (2013a) were subjected to additional testing and analysis by other laboratories. Inductively Coupled Plasma/Mass Spectroscopy (ICP) work conducted on the concentrates demonstrated that the quality of the products met current standards and that no deleterious substances were contained in the concentrates.

Bulk rougher scavenger tails from both composites were examined by QEMSCAN at the Colorado School of Mines Advanced Mineralogy Research Center (CSM AMRC) to determine the occurrence of gold and silver. The QEMSCAN results indicate silver locked in silica, feldspar and muscovite/kaolinite. The average grain size of un-floated Ag-minerals was determined to be about 3-6 microns (μ). Additional settling and rheological characterization were conducted by Pocock Industrial, Inc. on tailings from individual rock type and composite samples. Pocock’s test results are summarized in Section 13.2 below.

13.2 METALLURGICAL TESTING RESULTS

Metallurgical testing results and properties of the ore, concentrates, and tailings are derived from the metallurgical testing program described in sections below and confirmed by the production statistics from the Quintana operation. Key characteristics with influence on the process design are comminution, flotation, solid-liquid separation, and gold deportment and recovery.

13.2.1 Comminution

Testing of grinding characteristics by Hazen (2012) provides the foundation for the grinding circuit design. Samples from Copper Flat were subjected to JKTech full drop-weight, SAG Mill Comminution (SMC), Bond ball mill work index

(BW_i), Bond rod mill work index (RW_i), Bond abrasion work index (A_i), and Bond crusher impact index (CW_i) testing, as summarized in Table 13-2.

Table 13-2: Comminution Test Results

Ore Type (Mine Phase)	BW _i kWh/t	RW _i kWh/t	A _i g	CW _i , kWh/t
Quartz Monzonite (Years 0-5)	13.1	11.5	0.1875	IS
Quartz Monzonite (Years 5+)	14.5	14.3	0.2281	IS
Biotite Breccia (Years 0 - 5)	13.6	12.8	0.3214	9.80
Biotite Breccia (Years 5+)	13.7	12.8	0.2120	13.61
Quartz Feldspar Breccia (Years 0-5)	13.5	13.3	0.1820	IS
Quartz Feldspar Breccia (Years 5+)	14.5	14.6	0.2142	IS

IS = Insufficient Sample

The SMC test was developed by SMC Testing Pty Ltd. to provide a cost-effective means of obtaining drop-weight parameters from drill core samples, as well as in situations in which limited quantities of material are available. The results of the evaluation were sent to JKTech to determine the JKSimMet parameters, as shown in Table 13-3.

Table 13-3: Comminution Test Results

Sample ID	SG	A	b	Axb	DW _i kWh/m ³	DW _i , %	M _{ia} , kWh/t	M _{ih} , kWh/t	M _{ic} , kWh/t	t _a
52978-1	2.57	61.9	1.06	65.6	3.93	26	13.3	8.9	4.6	0.66
52978-2	2.62	66.8	0.66	44.1	5.97	54	18.3	13.2	6.8	0.43
52978-3	2.59	62.4	1.00	62.1	4.15	29	13.8	9.3	4.8	0.62
52978-4	2.70	61.2	1.21	74.1	3.65	23	12.0	7.8	4.1	0.71
52978-5	2.62	71.5	0.72	51.5	5.07	41	16.0	11.2	5.8	0.51
52978-6	2.49	64.1	0.90	57.7	4.31	31	14.9	10.1	5.2	0.60

SMC Parameters:

SG: Specific Gravity
A: maximum breakage
A × b: overall AG-SAG hardness
M_{ia}: work index, coarse particle component
M_{ic}: work index, crusher component

DW_i: Drop Weight Index
b: relation between energy and impact breakage
kWh/m³: kilowatt hours per cubic meter
M_{ih}: work index, HPGR component
t_a: low energy abrasion component of breakage

Contract Support Services (2012) used the results of a drop-weight evaluation to calculate SAG mill parameters, as well as crusher appearance functions using JKSimMet parameters. The results of the comminution tests indicate that the Copper Flat Deposit samples were moderately soft to medium hardness with Bond work Indexes ranging from 13.1 to 14.5 kWh/t. The comminution test results confirm the previous JKTech work conducted for the Quintana Mines.

Hazen (2011) conducted testing for Bond Abrasion Index on Copper Flat samples. An average abrasion index (A_i) of 0.2756 was obtained for the quartz monzonite (0.2755) and breccia (0.2756) samples, and wear rates are presented in Table 13-4.

Table 13-4: Wear Rates for Copper Flat Samples

Equipment	Equation ($A_i > 0.021$)	Qtz. Monz. Wear Rate (lb/kWh)	Breccia Wear Rate (lb/kWh)
Wet Rod Mill	Rods: $0.35(A_i - 0.020)^{0.2}$ Liner: $0.35(A_i - 0.015)^{0.3}$	0.2664 0.0234	0.2664 0.0234
Wet Ball Mill (overflow and grate discharge)	Balls: $0.35(A_i - 0.015)^{0.33}$ Liner: $0.026(A_i - 0.020)^{0.2}$	0.2245 0.0174	0.2246 .0174
Dry Ball Mill (grate discharge, $A_i < 0.22$)	Balls: $0.05A_i^{0.5}$ Liner: $0.005A_i^{0.5}$	0.0262 0.0026	0.0262 0.0026
Crushers (gyratory, jaw, cone)	Liner: $(A_i + 0.22)/11$	0.0450	0.0451
Roller Crushers	Rod Shell: $(0.1A_i)^{0.67}$	0.911	0.911

13.2.2 Solid-Liquid Separation

Solids-liquid separation (SLS) parameters for the Copper Flat Project are based on testing reported by Pocock (2011) on combined flotation tails and flotation concentrate materials. The test work was conducted to generate data to design and size SLS equipment.

- The flocculant product selected from screening tests for best performance was Hychem AF 303, a medium to high molecular weight 7 percent charge density anionic polyacrylamide.
- The minimum flocculant dose anticipated varied by individual sample and thickener type or application desired but was in the overall range of 20 to 40 g/MT in the tested pH range of 9.0 to 9.9.
- Dynamic (high-rate) thickening tests indicated optimal feed solids concentration in the overall maximum range of 15 to 20 percent for the tails and concentrate materials for high rate-type thickeners to maintain sufficient settling velocities for minimum hydraulic equipment sizing basis recommended herein. Dynamic thickening tests conducted on the samples indicated a hydraulic net feed loading rate design basis in the maximum range of 4.5 to 5.5 m³/m²-hr for the tails material, and 3.5 to 4.5 m³/m²-hr for the concentrate material for optimal performance. Note: All thickening design basis given assume that maximum feed solids and minimum flocculant dose recommendations given in this report are followed.
- The overall maximum underflow density range for the tails material is 60 to 65 percent (but this could be limited to 60 to 62 percent with rake torque considerations based on un-sheared data). Likewise, the overall maximum underflow density range for the concentrate material is 61 to 66 percent (but this could be limited to 61 to 63 percent with rake torque considerations based on un-sheared data)
- Pressure filter testing for the tails material based on a tonnage throughput of 24,544 metric tons per day (mtpd) indicates a minimum sizing requirement of 898 chambers for a horizontal recess plate type press (with 2300 x 2500 mm plates, and 15 mm recess (30 mm full chamber)) with no cake wash.
- Pressure filter testing for the concentrate material based on a tonnage throughput of 450 mtpd indicates a minimum sizing requirement of 77 chambers for a horizontal recess plate type press (with 1000 mm plates, and 25 mm recess (50 mm full chamber)) with no cake wash.
- Results of vacuum filtration tests conducted on the concentrate material indicated maximum achievable production rates in the range of 341 kg/m²-hr with no excess flocculant used for filter aid (16.4 percent discharge cake moisture), and 454 kg/m²-hr with 60 grams per metric ton of filter aid used (20.4 percent discharge cake moisture).

13.2.3 Flotation

Extensive flotation testing has been conducted on the Copper Flat ore samples mainly by the CSMRI (1976a and 1976b) and PAH (1979a, 1979b, and 1979c) from which a process flow sheet was designed for the Quintana operation. The results of the CSMRI pilot plant demonstrated that the ore was amenable to conventional copper-moly flotation process with 92.5 percent of the copper and 81.2 percent of the molybdenum recovered in a copper-moly bulk concentrate with a 30 percent copper grade. Results of the molybdenite circuit tests showed that molybdenite was easily rejected from the concentrate and upgraded to a marketable product containing more than 53 percent molybdenum with an overall moly recovery of 62 percent.

PAH (1979a and 1979b) reviewed metallurgical test information and conducted statistical evaluation of the Pilot Plant metallurgical information on the Copper Flat Project for Quintana. The modified process flowsheet suggested by PAH consisted of crushing and grinding ore followed by bulk copper-moly rougher flotation. The bulk rougher flotation concentrate was reground and subjected to two stages of cleaner flotation. The cleaner concentrate was sent to a copper-moly separation circuit using a standard scheme of depressing copper with sodium hydrosulfide (NaHS) and floating molybdenite. The flotation tailing from the copper-moly separation circuit was the final copper concentrate assaying 28 percent copper. The rougher molybdenite concentrate was reground and cleaned to produce a saleable product.

MAG (2013a) conducted metallurgical testing program to evaluate the mineral processing parameters developed by CSMRI and evaluate other options that might enhance concentrate grade, recovery, and/or reagent consumption. The copper recoveries MAG reported were similar to those achieved in the CSMRI testing. Recoveries reported by MAG (2013a) for mine-stage composites and locked cycle testing are shown in Table 13-5.

Table 13-5: Flotation Test Results

Ore Type (Mine Phase)	Recovery (percent)			Silver
	Copper	Moly	Gold	
Early Mining Phase				
Composite (Years 0-5)	94	61	79	82.7
Late Mining Phase				
Composite (Years 6+)	91	60	76	82.7
Two Cycle Locked Test				
Average Locked Cycle (Years 0-5)	95	92.7	71.1	82.7

Flotation tests of individual rock type samples for each of the mining phases were conducted prior to testing the composite samples. Problems during the tests combined with assaying issues, especially for silver and gold, lead MAG (2013a) to conclude that the results of the composite tests are more reliable than the tests on individual rock types. The locked-cycle testing appears to confirm the recoveries for the early mining phase, but the precious metal recoveries are variable due, in part, to low concentrations of these metals in the samples (head assays) and difficulties in assaying gold and silver assay at these low values. Gold recovery is set at 71.1 percent and silver recovery at 82.7 percent based on results of additional assays conducted by five different laboratories. Bulk flotation testing was conducted to generate rougher concentrate for the molybdenum circuit testing which were expected to give better precious metals recovery results for comparison with the CSMRI testing and historical recoveries achieved during the Quintana operation.

Head assays for the pilot-scale molybdenum evaluation test program conducted on the new 0-5 year mine life interval composite was 0.32% copper, 2.71% iron, 0.0090% molybdenum, 0.71 g/t gold, and 3.0g/t silver. The same CSMRI standard reagents, conditions, and procedures utilized in the original bench scale bulk rougher and bulk cleaner flotation test program were employed in the pilot scale molybdenum evaluation test program.

The final molybdenum concentrate was 49.92% Mo, 0.49% copper, 0.95% Iron, 1g/t Au and 29g/t Ag. The final molybdenum rougher tail (final copper concentrate) gave 90.9% copper recovery with 25.08% Cu grade, 29.6% Fe, 4g/t Au, and 135g/t Ag and 0.004% molybdenum. Based on the results of this test regime, it has been demonstrated that a moly concentrate of 50% Mo is achievable with iron content below 1% and copper content below 0.5%. The testwork has indicated that it is possible to produce a moly final product that meets industry specifications for saleable moly concentrates.

13.2.4 Gold Deportment and Recovery

Historical Quintana production from Copper Flat suggested a recovery rate for gold at about 50 percent. Increases in gold recovery have an impact on the projected revenues for the operation. G&T (2012) evaluated the presence of gold in tailings by size fraction and evaluated the occurrence of that gold in terms of whether or not it was liberated or bound with pyrite or gangue minerals. FLSmidth-Knelson (2012a) conducted gravity gold recovery tests on Copper Flat composite sample of drill core from the deposit.

13.2.4.1 Gold Deportment

G&T (2012) searched rougher concentrate and a pre-concentrated rougher tailing for gold occurrences using an Automated Digital Imaging System (ADIS). The goal of this last step was to identify the deportment of gold in the tailing sample to identify whether gold recovery could be improved through gravity concentration. A size analysis was completed on a representative subsample and results are shown below in Table 13-6.

Table 13-6: Particle Size and Chemical Analysis

Size fraction microns	Weight grams	Metal Assays – percent or grams/tonne							
		Cu	Mo	Fe	S	C	As	Ag	Au
>150	12.3	0.21	0.065	4.16	1.68	0.61	0.002	2	1.21
<150>106	18.9	0.60	0.051	6.80	2.39	0.73	0.002	4	0.87
<106>75	15.9	0.81	0.057	8.00	2.30	0.75	<0.001	6	1.03
<75>53	11.9	0.79	0.033	7.30	2.16	0.69	<0.001	6	0.66
<53>38	9.4	1.08	0.026	8.30	2.07	0.72	<0.001	6	0.97
<38	31.7	1.15	0.020	8.80	1.83	0.99	<0.001	12	0.86
Calculated	100	0.83	0.039	7.50	2.05	0.80	<0.001	7	0.92
Measured Head	-	0.81	0.038	7.85	1.99	0.80	<0.001	6	0.83

ADIS searches on the rougher concentrate and final rougher tailing after pre-concentrating the tails produced the following observations.

- Gold occurrences in the rougher concentrate were in binary form with pyrite (35 percent), as liberated gold (24 percent) and in binary form with gangue (24 percent). The remaining occurrences were in binary form with chalcopyrite (17 percent).
- Gold in the pre-concentrated rougher tailings occurred interlocked in binary form with pyrite (56 percent) and as liberated gold (35 percent).
- Examination of gold occurrences in the rougher concentrate, tailing and recalculated feed reveals that about 42 percent of the gold was interlocked with pyrite in the rougher feed.

G&T (2012) concludes about 35 percent of the gold reporting to rougher tailings was liberated and addition of a gold gravity recovery stage to the process might increase overall gold recovery.

13.2.4.2 Gravity Gold Recovery

FLSmidth-Knelson conducted gravity gold recovery testing on a 73 kg sample of Copper Flat ore by progressively grinding the sample and passing it through a Knelson concentrator at a feed rate of approximately 800 g/min, sampling, and assaying the results, which are presented below in Table 13-7.

Table 13-7: Gravity Recovery with Grind Size

Grind Size	Grind Stage	Product	Mass g %		Assay Au (g/t)	Units Au	Distribution (%)
P ₈₀ = 830 μ	1	Concentrate	87.4	0.1	6.14	0.7	5.9
		Tails	247.4	0.3	0.12	0.0	0.3
P ₈₀ = 174 μ -75μ = 46.2%	2	Concentrate	367.5	0.5	2.35	1.2	9.5
		Tails	256.0	0.4	0.11	0.0	0.3
P ₈₀ = 78μ	3	Concentrate	254.3	0.3	4.78	1.7	13.3
		Tails	17121	98.3	0.09	8.8	70.7
	Head Totals		72934	100.0	0.12	12.5	100.0
	Knelson Concentrate		709.1	1.0	3.69	3.6	28.7

FLSmidth-Knelson (2012a) concludes that overall 28.6 percent of the gold in the sample was recovered by gravity. The gold head grade of the sample was calculated to be 0.12 g/tonne with a final gravity gold tailings grade of 0.08 g/tonne. The grind P80 of the final stage was 78 µ. The concentrate gold recovered is classified as fine with grain size P20 of 110, P50 of 45 and P80 of 22.

FLSmidth-Knelson (2012b) applied a mathematical model to the data from gravity gold recovery testing to predict gravity recovery within a grinding flotation circuit. The model calculates a gravity recoverable gold population balance in a grinding flotation circuit. Data from a database is used for preliminary modeling, and detailed audits may be carried out to “calibrate” the model to an operating circuit. Modeling results for gravity recovery of the Copper Flat Project are presented in Table 13-8.

Table 13-8: Gravity Recoverable Gold Modeling Results

Number of Units	Gravity Feed Rate		Gravity Recovery			Concentrate		Grav./Flot Recovery (%)	Overall Rec. Benefit (%)
	(mtph)	(% CL)	(% Au)	(% GRG)	(kg/day)	Weight (kg/day)	Grade (g/t)		
0	N/A	N/A	N/A	N/A	N/A	N/A	N/A	69.4	0.00
1	600	20	5.1	27.2	0.15	2640	56	78.5	1.69
2	1200	39	7.2	38.5	0.21	5280	40	82.1	2.36
3	1800	59	8.5	45.5	0.25	7920	32	84.4	2.79
4	2400	78	9.4	50.6	0.28	10560	26	86.0	3.10
5	3000	97	10.2	54.6	0.30	13200	23	87.3	3.34

The results show that two XD70 Knelson concentrators with screens, concentrate pumping, feed system, and structure would theoretically provide an increase in gold recovery of 2.36 percent, which equates to about 1.77 ounces per day extra gold.

13.3 BASIS FOR RECOVERY ESTIMATES

CSMRI (1976b) conducted flotation tests to determine optimum grind size, reagent screening and dosage tests, and locked-cycle tests to select flotation sequence and times. The results of the Pilot Plant investigation demonstrated approximately 92.5 percent of the copper and 81.2 percent of the molybdenum was recovered into a high-grade Cu-Mo bulk concentrate with a 30 percent copper grade. Results of the molybdenite circuit tests showed that molybdenite

was easily rejected from the concentrate and upgraded to a marketable product containing more than 53 percent molybdenum with expected overall moly recovery of 62 percent. The process employed to obtain these results consisted of grinding to approximately 96 percent minus 65 mesh (250 μ), or a P_{80} of about 140 μ , followed by flotation at pH of 11 with dithiophosphate and xanthate collectors. The rougher concentrate was reground to approximately 90 percent minus 325 mesh (44 μ), or a P_{80} of about 53 μ , and then upgraded in two stages of cleaner flotation.

MAG (2013a) conducted metallurgical tests to validate the CSMRI tests and to evaluate other options that might enhance concentrate grade, recovery, and/or reagent consumption. Results described in Sec. 13.2.3 indicate copper recovery of 95 percent, moly recovery of 92.7 percent, silver recovery of 82.7 percent and gold recovery of 71.1 percent.

FLSmidth-Knelson (2012) conducted test work and modeling that indicate an additional 2.6 percent gold is recoverable with two Knelson concentrators in the circuit. Estimated metal recoveries are presented in Table 13-9.

Table 13-9: Estimated Metal Recovery Rates

Composite	Copper Flat Ore Metal Recoveries -%			
	Copper	Molybdenum	Silver	Gold
Years 1 to 5	94.6	81.9	82.7	73.7
Years 6 and up	91.2	73.4	82.7	73.7

13.4 REPRESENTATIVENESS OF TESTING AND CHARACTERIZATION

Process development to determine concentrator unit operations and to set design criteria for the unit operations reported by CSMRI (1976a and 1976b) was validated by MAG (2013a) on samples of three ore types and composites from early and late phases of mining. M3 has reviewed the available metallurgical test data and concluded it was of sufficient quality and consistency to design the process facilities. The metallurgical testing program has followed industry accepted practices and is believed to be technically sound and representative for the deposit, although there can be no guarantee that all mineralogical assemblages have been tested. In addition, results obtained by testing ore samples may not always be representative of results obtained from production scale processing of the whole ore deposit. M3 has extrapolated the design criteria included in this document from test results. These preliminary design criteria may change as more computer simulation, results of recommended laboratory testing, or plant performance testing becomes available.

CSMRI's (1976a and 1976b) bench-scale and pilot froth flotation test data from samples of sulfide ore has shown that 92.5 percent copper recovery at a concentrate grade of 30 percent copper from feed grades between 0.30 and 0.60 percent copper is achievable. This was confirmed by the results of regression equations developed by PAH (1979b) that the overall copper recovery range between 91.4 and 93.5 percent with molybdenum recovery to a copper-moly concentrate of 80 percent can be consistently achieved. The results of the metallurgical tests conducted by MAG (2013a) confirmed those of the CSMRI tests with copper recovery of 91.8, Moly recovery of 60.7, silver recovery of 82.7% and a better gold recovery of 71.1. Gold recovery will improve by additional 2.6% to a total of 73.7% as a result of the addition of the Knelson's gravity concentrator in the grinding circuit.

13.5 PROCESSING FACTORS AND DELETERIOUS ELEMENTS

Although comprehensive metallurgical tests were conducted on the Copper Flat ore more than thirty years ago, the methodology and conclusions are technically feasible and the flowsheet of the previous 1982 mill is essentially still valid. Quintana Minerals designed and built the concentrator in 1982 with the rated capacity of 15,000 st/d with copper recovery reaching 88 percent in June 1982. The molybdenum circuit operated for only a short time in 1982 producing a 46 percent moly concentrate without the final cleaning stage. With a longer operating period, the plant could have achieved a saleable molybdenum concentrate product (greater than 50 percent moly) at an overall plant recovery of 62 percent. This is consistent with plant practices and recoveries for similar by-product operations.

Advances in equipment manufacturing technology, process control technology as well as reagent research in the last thirty years mean that the details in the flow sheet being proposed by M3 will be different from 1982 Quintana plant. It was therefore deemed prudent to conduct metallurgical tests recommended by M3 to take advantage of the technological advances achieved in the last thirty years. Test results reported by MAG (2013a) validate the metallurgical tests conducted by CSMRI and show that the parameters used by CSMRI gave better recoveries than the “modern” parameters.

CSMRI (1976b) conducted a pilot plant test and produced saleable molybdenum concentrate by floating copper and depressing molybdenum (weight ratio Cu:Mo = 35:1), so there is no reason to doubt that saleable moly concentrate can be produced using the modern flow sheet being used in the mining industry. It can be concluded from the results of the CSMRI pilot plant tests, the historical operation of the Quintana Minerals concentrator, and recent MAG (2013b) testing that there are no adverse processing factors that require any extraordinary process engineering or deleterious elements in the Copper Flat ore. The ore is of medium hardness, amenable to copper/moly flotation, gives products that thicken and filter readily and will produce saleable copper and moly concentrates.

13.6 CONCEPTUAL PROCESS FLOWSHEET

The conceptual process flowsheet (Figure 13-1) was developed for processing 1,333 st/hr to achieve a throughput of 10.8 million tons per year with an overall availability factor of 92.5 percent. The basis for the flowsheet and the capital and operating cost are given in Table 13-10.

The process flowsheet is very similar to the one developed by Quintana. The major equipment is also the same as originally installed by Quintana. The present flowsheet design incorporates modern equipment where applicable. For example, larger flotation cells have been selected for the rougher flotation, bulk cleaner flotation cells are column cells and vertical mills replaced the regrind mills. The design incorporated in this study is considered “Standard” practice in the mining industry today.

Table 13-10: Design Parameters for the Conceptual Process Flowsheet

Item	Amount
Tonnage/day	32,000
Availability	92.5%
Tons/hr	1333
Tons/yr	10,800,000
Feed Grade	
% Cu	0.42
% Mo	0.012
Oz/ton Au	0.003
Oz/ton Ag	0.08
Cu Concentrate Grade	
% Cu	28
Mo Concentrate Grade	
% Mo	>50
Concentrate Tonnage/day	
Cu	311
Mo	1.9
Recovery %	
Cu	91.8
Mo	60.7
Au	73.7
Ag	82.7

14 MINERAL RESOURCE ESTIMATES

The mineral resource and mineral reserve were developed from a computer-based block model that was based on the drill hole data base and geologic interpretation assembled for the Copper Flat Deposit.

The block model assembly and the component of the model that represents the mineral resource will be discussed in this section. Section 15 will discuss the sub-set of the resource that constitutes the mineral reserve.

The component of the mineralization that meets the mineral resource requirements for “reasonable prospects of economic extraction” was based on the floating cone pit guidance algorithm. The results of that work are summarized at the end of this section.

14.1 BLOCK MODEL

14.1.1 Model Location

The block model was assembled in the UTM NAD83 coordinate system converted to “feet”. This was established as the standard data location and mine planning grid for the project. Table 14-1 summarizes the block size and model location.

Table 14-1: Block Model Size and Location

Size and Location				
	Southwest	Northwest	Northeast	Southeast
Easting	861,000	861,000	866,500	866,500
Northing	11,975,000	11,980,500	11,980,500	11,975,000
Elevation Range		4,000	6,125	
Model Rotation	None			
		Columns	Rows	Levels
Size		110	110	85
Block Size		50 x 50 x 25 ft	Bench Ht = 25 ft	

The limited bench height is unusual for copper porphyry. However, the planned production rate does not require large loading units. The 25 ft bench height was selected as a reasonable value for production loading by front end loaders of the 15 to 19 cubic yard capacity.

The central portion of the deposit is drilled with spacing of 100 to 150 ft. The selection of the 50 ft horizontal block size corresponds to ½ to ⅓ of the drilling spacing. Roughly 3½ model blocks will be mined every day.

14.1.2 Drill Hole Data

As discussed in previous sections, IMC removed the underground drift sampling from the data base prior to grade estimation because that data appears to be high biased relative to the surrounding diamond drilling. Both historic diamond drilling, and the new holes drilled by THEMAC have been combined for use in block grade estimation.

The drill hole assay data was composited to 25 ft down hole (length) intervals. Individual assays were capped prior to compositing. The cap values are summarized below:

Assay Cap Values:

Copper	3.00%
Molybdenum	0.40%

Gold	0.08 oz/ton
Silver	0.70 oz/ton

The cap levels were established based on the review of cumulative frequency plots.

Table 14-2 summarizes the assay data after capping and the composite data that was applied prior to grade estimation.

Table 14-2: Drill Hole Data

Copper Flat Drill Hole Data				
Metal	Assays		25 ft Composites	
	Number	Mean	Number	Mean
Copper %	21,642	0.249	6,662	0.264
Molybdenum %	19,996	0.009	6,330	0.009
Gold, oz/ton	15,217	0.003	4,788	0.003
Silver, oz/ton	15,569	0.059	4,872	0.062

The counts presented above reflect the drill hole data that was used in the assembly of the block model after removal of the underground drift sampling.

14.1.3 Model Geology

Geologic interpretation of the major lithologic units was completed by THEMAC personnel and verified by IMC. That information was digitized on plan and assigned to the block model.

The initial interpretation addressed the major rock types of:

	<u>Model Code</u>
Quartz Monzonite	7
Coarse Crystalline Porphyry	14
Andesite	6
Breccia	12

The mineralization is contained within the Quartz Monzonite, Coarse Crystalline Porphyry, and Breccia Units. Andesite is barren and no grade has been assigned to that unit. Block grades in the andesite rock type were set to zero after completion of the grade estimation.

THEMAC geologists updated the estimate of “Breccia” which was amended for this model update. The material defined as Breccia is likely a stockwork alteration rather than a true breccia. Because the past terminology has been utilized throughout the project, the term breccia will still be applied to the hydrothermal stockwork zone. The only impact of the breccia code on the resource model was the application of a slightly heavier density in the breccia zone.

Structural boundaries and structure zones defined by faulting were interpreted by THEMAC geologists and verified by IMC. Faults were interpreted on plan and projected vertically downward. Blocks between the faults were assigned as codes to the block model. In addition, the major faults were assigned zones that surrounded the fault and could potentially control mineralization.

The 25 ft drill hole composites were assigned the codes of the fault blocks and fault zones. Basic statistics and a nearest neighbor approach were used to investigate if any of the structural blocks or zones were boundaries or controls on mineralization. The results of this work did not identify any structural controls that should be hard boundaries to mineralization outside of the grade boundaries that were utilized.

The fault blocks and fault zones were combined and simplified into a set of Structural Domains that were used to control the orientation of the search ellipse but they were not boundaries to mineralization.

The Domain Codes for Modeling were as follows:

<u>Domain</u>	<u>Description</u>
1	Central East with the Patton Zone
2	Central West, With Patton 2 and North Zones
3	Northeast
4	Northwest
5	Southeast
6	Southwest
7	Hunter Zone

Figure 14-1 illustrates the domain codes used in the model assembly process.

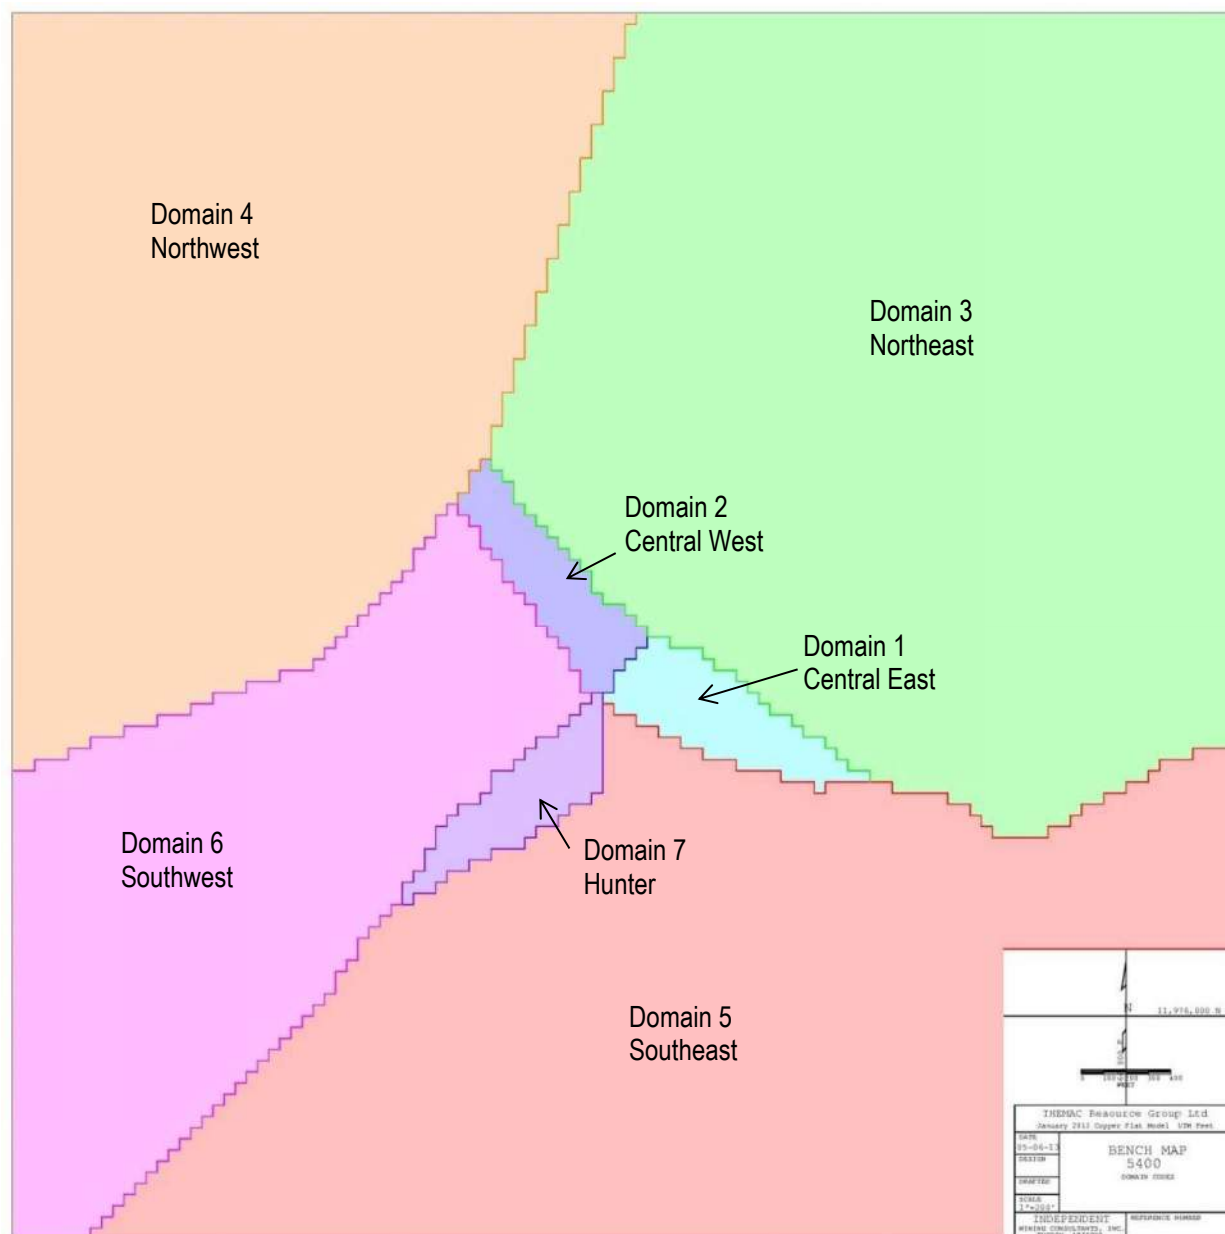


Figure 14-1: Map of Grade Estimation Domains Based on Structural Blocks and Zones (The Map Covers the Model Area)

14.1.4 Variography and Grade Boundaries

Basic statistics, probability plots and variograms were completed within the defined domain boundaries. Domains 1 through 6 all generally show preferred orientation parallel to the Patton and Patton Splay Faults at bearings of 307 degrees. The Hunter Domain (Domain 7) indicates the local structural control with a preferred north-south orientation.

Figure 14-2 and Figure 14-3 illustrate selected global indicator variograms for copper and moly which support the selection of search and orientation that are summarized in the next sub-section.

Variogram ranges up to 600 ft could be interpreted from the various plots that were completed. However, maximum ranges of 400 to 450 ft were selected to be in line with other copper-moly porphyry systems and to allow for better local estimation.


In all cases, vertical variograms showed good continuity and long ranges of influence. This is a typical response for deposits with predominately vertical drilling and represents an unavoidable spacial bias in the data collection process.

The cumulative frequency population plots applied to the 25 ft composites for copper and moly resulted in the selection of the following grade discriminator boundaries for copper, moly, and gold.

Copper Indicator Boundary	0.40% copper
Moly Indicator Boundary	0.012%
Gold Indicator Boundary	0.005 oz/ton

Review of geologic and assay cross sections often indicate abrupt grade changes between high values and low values as supported by the observed indicator discriminators. As a result, the vertical search was limited to 100 ft and the maximum number of composites from any drill hole was set at 3. This limits the vertical averaging or smearing of grades in the deposit and results in better local estimation for mine planning guidance.

The resulting grade estimation procedures and kriging parameters are presented in the next sub-section.

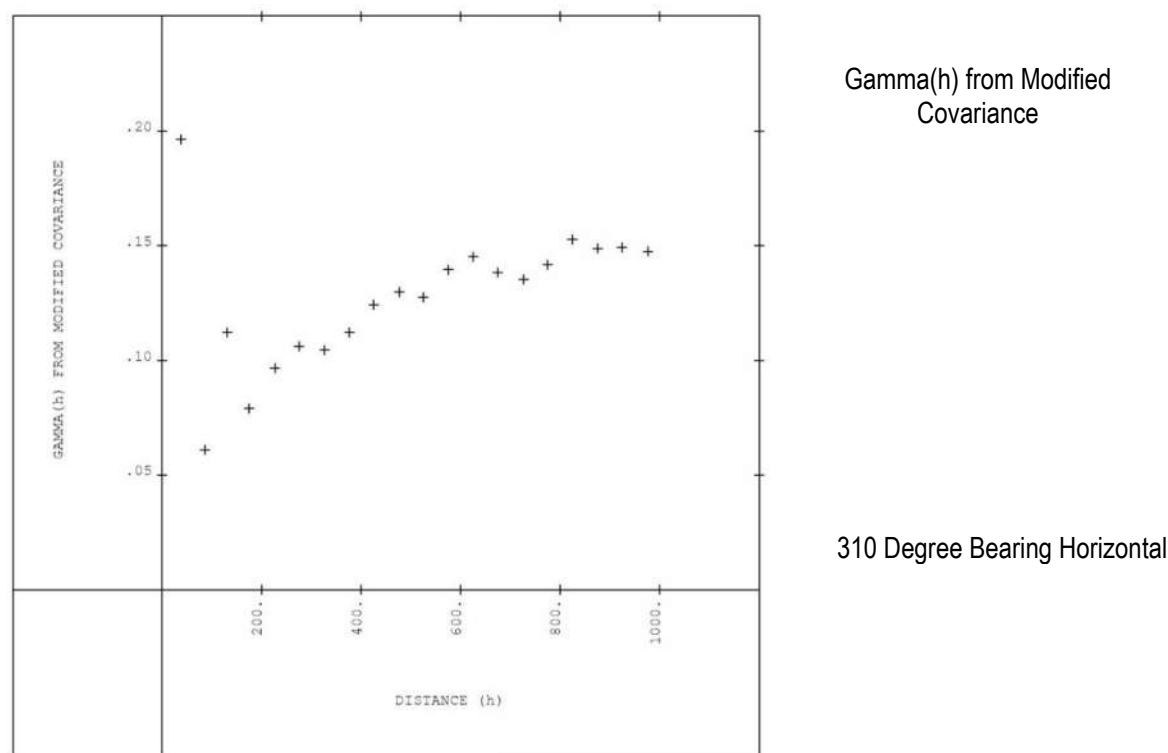

14.1.5 Block Grade Estimation

The block grades were estimated for copper, molybdenum, gold, and silver into the quartz monzonite, breccia, and coarse crystalline porphyry units. No grade assignment was made within the andesite and the boundary between the andesite and the other rock types was treated as a hard boundary. The quartz monzonite, breccia, and coarse crystalline porphyry boundaries were treated as soft boundaries.

Grade boundaries were used in the estimation of copper, molybdenum and gold. The grade boundaries were based on an indicator kriging procedure with discriminators of 0.40% total copper, 0.012% moly and 0.005 oz/ton gold. Silver was assigned by ordinary linear kriging.

The indicator grade boundaries were assigned within the quartz monzonite, breccia, and coarse crystalline porphyry units using a one stage indicator kriging procedure. The indicator procedures are summarized on Table 14-3.

Once the indicator fraction (probability) was assigned to the blocks, the blocks were coded on a 50% probability basis. Blocks with greater than a 0.5 fraction were coded as “inside the grade zone = 1” and those less than 0.5 were coded as “outside the grade zone = 0”. The composites were then back assigned the codes from the blocks that contained the composite. Consequently, both the composites and the blocks were coded as inside or outside of the grade boundary.

The grade boundaries were respected as hard boundaries during the grade estimation for copper, moly, and gold. Table 14-4 summarizes the grade estimation parameters. Ordinary linear kriging was used to assign grades to copper, moly, and gold inside and outside of the respective indicator grade boundaries.

A search limit was applied to the high-grade component on all of the grade estimates. Horizontal indicator variograms were completed over a range of increasing grade discriminators. When a discriminator was identified where the variogram became all sill, that value was search limited with 75 ft for copper and moly and 50 ft for gold and silver.

Table 14-3: Indicator Kriging Parameters – Block Grade Estimation

Metal	Discriminator Grade	Domain	Orientations, Bearing			Range and Search in Feet			Nugget	Total Sill C+Co
			Primary	Secondary	Tertiary	Primary	Secondary	Vertical		
Copper Moly	0.040 %	1,2 CW+CE	307	37	90	450	200	100	0.01	0.99
	0.012 %	3,4 NE+NW	307	37	90	450	300	100	0.01	0.99
		5,6 SE+SW	307	37	90	450	300	100	0.01	0.99
		7, Hunter	0	90	90	400	200	100	0.01	0.99
		Domains were not hard boundaries								
Gold	0.005 oz/ton	All Domains	37	127	90	400	300	100	0.01	0.99

Maximum = 10, Minimum = 2, Maximum per Hole = 3

Table 14-4: Grade Kriging Parameters – Block Grade Estimation

Metal	Indicator Position	Domain	Orientations, Bearing			Range and Search in Feet			Nugget	Total Sill C+Co	High Grade Search Limit	
			Primary	Secondary	Vertical	Primary	Secondary	Vertical			Grade	Distance (ft)
Copper	Inside and Outside	1,2 CW+CE	307	37	90	450	200	100	0.01	0.99	1.20% Cu	75
		3,4 NE+NW	307	37	90	450	300	100	0.01	0.99	1.20% Cu	75
		5,6 SE+SW	307	37	90	450	300	100	0.01	0.99	1.20% Cu	75
		7, Hunter	0	90	90	400	200	100	0.01	0.99	1.20% Cu	75
		0.40% Indicator was a hard boundary										
Moly	Inside and Outside	1,2 CW+CE	307	37	90	450	200	100	0.01	0.99	0.070% Mo	75
		3,4 NE+NW	307	37	90	450	300	100	0.01	0.99	0.070% Mo	75
		5,6 SE+SW	307	37	90	450	300	100	0.01	0.99	0.070% Mo	75
		7, Hunter	0	90	90	400	200	100	0.01	0.99	0.070% Mo	75
		0.012 % Indicator was a hard boundary										
Gold	Inside and Outside	All Domains	37	127	90	400	300	100	0.01	0.99	0.015 oz/t	50
Silver	Inside and Outside	All Domains	37	127	90	400	300	100	0.01	0.99	0.25 oz/t	50

Maximum = 10, Minimum = 2, Maximum per Hole = 3

Grade Estimation Respected Nearest Block Indicator Codes for Copper, Moly, and Gold

14.1.6 Density Assignment

Rock density information was collected by THEMAC during the 2010 drill programs. One hundred whole core samples were sent to Skyline during the spring of 2010 for bulk density determination. Samples were weighed in air then submerged in water and weighed. They were then dried, and process repeated so that the amount of water absorbed could be determined.

IMC sorted the data by the logged rock type and calculated the average density of the rock units that were tested. Most of samples were quartz monzonite and breccia. There were 17 out of 100 without a rock type code assigned. However, their density was similar to the results for the quartz monzonite.

Based on these test results, the following dry densities were assigned to the model.

Breccia	2.652 Specific Gravity	12.08 cu ft/ton
Quartz Monzonite	2.618 Specific Gravity	12.24 cu ft/ton

All other rock units were assigned the same density dry as the Quartz Monzonite.

14.1.7 Classification

Classification was assigned in conformance with NI43-101 and the standards and guidelines from the CIM. The data verification work has determined that the historic drill data can be used along with the new holes completed by THEMAC to estimate mineral resources and mineral reserves. However, due to the lack of geologic information in many of the historic drill holes, IMC has limited the determination of measured to require the presence of THEMAC drilling completed in 2010 thru 2012.

The procedure applied by IMC was a two-step process. At first, all drilling information was used to estimate block grades and an initial determination of measured, indicated, and inferred was established based on the Kriged Standard Deviation (KSD = Square root of kriged variance) and the number of composites used to estimate the block.

A second stage required that at least three of THEMAC drill holes be used in the grade estimation process for the block to be considered measured. This assured that measured material was surrounded by recent 2010-2012 drilling.

The classification is based on the estimation of copper grade and is summarized as follows:

<u>Procedure</u>	<u>Classification and Code</u>
If Copper or Moly was estimated	Inferred = 3
If Copper KSD ≤ 1.00 and Number of composites ≥ 4	Indicated = 2
If Copper KSD ≤ 0.60 and Number of composites = 10 And Number of THEMAC composites ≥ 7	Measured = 1

14.2 MINERAL RESOURCE

The mineral resource was based on the application of the floating cone algorithm to the block model to establish the component of the deposit that has "reasonable prospects of economic extraction". The mineral resources are therefore contained within a computer-generated open pit geometry. Details of the floating cone input parameters are presented in Section 15 regarding Mineral Reserves.

The floating cone software that was applied is IMC developed software. IMC software has been validated numerous times against all other major commercial software packages.

There were two key changes that were applied to the determination of mineral resources that differ from the table presented for mineral reserves.

- 1) Economic benefit was applied to the inferred material within the resource cone. No economic benefit was applied to inferred when determining the mineral reserve, mine plan, or project economics.
- 2) No effort was made to establish a pit with maximum return on investment; consequently, the mineral resource cone was the direct result of the following metal prices: \$3.00/lb copper, \$8.00/lb Moly, \$1350/oz Gold, \$20.00/oz Silver.

All of the estimated costs, recoveries, and slope angles that were applied to resource determination are otherwise identical to those presented in Section 15 regarding the mineral reserve floating cones. No constraints were applied to the resource regarding tailing or waste storage capacities.

Table 14-5 summarizes the total mineral resources that include the mineral reserve.

The qualified person for the estimation of the mineral resource was John Marek of Independent Mining Consultants, Inc. Metal price changes could materially change the estimated mineral resources in either a positive or negative way.

At this time, there are no unique situations relative to environmental or socio-economic conditions that would put the Copper Flat mineral resource at a higher level of risk than any other North American development resource.

The cutoff grades are presented in terms of Net Smelter Return (NSR) which reflects the combined benefit of producing copper, moly, gold, and silver.

$$\begin{aligned} \text{NSR} = & (\$3.00 - 0.3295) \times 0.9180 \times 0.9336 \times 20 + && \text{Copper Contribution} \\ & (\$8.00 - 1.562) \times 0.6070 \times 0.9578 \times 20 + && \text{Moly Contribution} \\ & (\$1350 - 6.00) \times 0.7080 \times 0.6992 + && \text{Gold Contribution} \\ & (\$20.00 - 0.50) \times 0.8200 \times 0.7564 && \text{Silver Contribution} \end{aligned}$$

The cutoff grade reflects the estimated cost to process the ore plus site G&A cost which total \$6.11/ton.

Table 14-5: Mineral Resources (7 October 2013)

Classification	Cutoff Grade NSR/Ton	Tonnage and Grade					Contained Metal			
		Ktons	Copper %	Moly %	Gold Oz/ton	Silver Oz/ton	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000
Measured	\$6.11	126,655	0.28	0.009	0.003	0.06	709,268	22,798	380	7,599
Indicated	\$6.11	<u>178,571</u>	<u>0.19</u>	<u>0.005</u>	<u>0.002</u>	<u>0.04</u>	<u>678,570</u>	<u>17,857</u>	<u>357</u>	<u>7,143</u>
Meas + Ind		305,226	0.23	0.007	0.002	0.05	1,387,838	40,655	737	14,742
Inferred	\$6.11	27,646	0.20	0.004	0.001	0.02	110,584	2,212	28	553

Notes:

Mineral Resources stated above include the mineral reserve
Mineral Resources are contained within a floating cone pit geometry at prices listed in text
Ktons means 1000 short tons. Short tons = 2000 lbs
Copper and Molybdenum grades are percent of dry weight
Gold and Silver are reported in Troy ounces / short ton

Metal Prices:

\$3.00/lb Copper, \$8.00/lb Mo, \$1350 /oz Gold, \$20.00/oz Silver

15 MINERAL RESERVE ESTIMATES

The mineral reserve was developed from the block model and is the total of all proven and probable category ore that is planned for processing. The mine plan that is presented in Section 16 details the development of that mine plan. The mineral reserve was established by tabulating the contained tonnage of measured and indicated material (proven and probable) within the designed final pit geometry at the planned cutoff grades. The final pit design and the internal phase (pushback) designs were guided by the results of the floating cone algorithm.

15.1 FLOATING CONES

The floating cone computer algorithm is a tool for guidance to mine design. The algorithm applies approximate costs and recoveries along with approximate pit slope angles to establish theoretical economic breakeven pit wall locations. All of the floating cone and mine plan discussions in this section and the subsequent sections address measured and indicated (proven and probable) ore only. Inferred is treated as waste from this point forward in the project evaluation.

The floating cone software that was applied for mine planning guidance was developed internally by IMC. Over a number of years, the IMC floating cone software has been validated against many of the commercial open pit software packages.

Economic input applied to the cone algorithm is necessarily preliminary as it is one of the first steps in the development of the mine plan. However, the cone geometries should be considered as approximate as they do not assure access or working room. The important result of the cones is the relative changes in geometry between cones of increasing metal prices. Lower metal prices result in smaller pits which provide guidance to the design of the initial pushbacks. The change in pit geometry as metal prices are increased indicates the best directions for the succeeding phase expansions to the ultimate pit.

Table 15-1 summarizes the input data to the floating cone. Process recoveries and estimated process costs were provided by the M3 project team. Slope angles were provided by the geotechnical contractor Mine Design Engineering (MDEng, 2013). MDEng provided inter-ramp slope angles for design guidance. IMC reduced those angles by 2 degrees to reflect the inclusion of haul roads in the final pit design. Mine operating costs were developed by IMC based on the results of the earlier pre-feasibility study.

Multiple floating cones were completed at a range of metal prices. Copper prices ranged from \$1.00/lb up to \$3.75/lb were applied within the cone runs. The base case ratios between copper prices and the other metal prices that are shown on Table 15-1 were maintained at all other price runs.

Once the multiple cones were completed, they were all tabulated at the base case metal prices of \$3.00/lb Copper, \$8.00/lb Moly, \$1350/oz Gold, and \$20.00/oz silver.

The Copper Flat pit design has a constraint because the tailings facility will hold about 125 million tons within the current permit parameters. The mine could potentially produce more than 125 million tonnes, but the costs to increase tailing storage capacity are not offset by the potential benefit of additional low-grade ore late in the mine life.

Substantial additional planning and scheduling effort was completed by IMC to establish the best overall final pit design that would produce the best 125 million tons on a time value of money basis. As a result, the \$2.25 cone was selected for design purposes.

In addition, the \$2.25 cone does not encroach on the drainage structures that have been established on the east and south sides of the pit.

Table 15-1 illustrates the \$2.25 floating cone that was used as the guide for final pit design.

15.2 FINAL PIT DESIGN

The final pit design is the last of three pushbacks that are planned for the production of the Copper Flat deposit. Access roads and working room for the equipment have been planned into the phase designs. The interramp slope angles that were recommended by MDEng have been used for the final pit design.

The following criteria were applied to the final pit and phase designs:

Mine Planning Parameters:

Haul Road Width	90 feet
Haul Road Grade	10%
Inter-ramp Slope Angles	
Northeast	41°
Southeast	39°
Breccia	36°
West	44°
Operating width between pushbacks	300 feet nominal

The final pit design inclusive of haul roads is illustrated on Figure 15-2. Additional mine plan drawings will be provided in Section 16 with the discussion of the mine plan and operation.

Section 14 reported that the block model is based on 50 by 50 ft blocks with a 25 ft bench height. The planned equipment at Copper Flat will be a good match for the 25 ft bench height. Block model grades were utilized to develop the mine plan without the incorporation of mining dilution or selective mining corrections. IMC experience with porphyry deposits of this type indicates that additional corrections are not prudent or warranted.

The application of the indicator kriging process as outlined in Section 14 reduces the “grade smearing” that is classically incorporated into models based on ordinary kriging, further reducing the need for selective mining correction factors.

Table 15-1: Floating Cone Input

Mining Cost		
Mine Opex Cost		\$1.560 /ton material
Sustaining Capital	<i>*Not Applied</i>	<u>\$0.000 /ton material</u>
Total, No Haul Increment		\$1.560 /ton material
Haul Increment per bench below	5425	\$0.044 /bench of depth
Processing Cost		
	Total per ton ore	\$6.11 /ton ore
Process Recovery		
	Copper	91.8%
	Moly	60.7%
	Gold	70.8%
	Silver	82.0%
Smelting and Refining Terms		
Assume 27% con grade, \$80+\$35/ton + 0.08/lb		
	Cost / Lb Cu	\$0.3295 /lb copper
	Smelter Recovery	96.5% 1% deduct at 27%
	Moly Roast + Trans	\$1.562 /lb Moly
	Roast Recovery	99.0%
	Gold Refining	\$6.00 /oz Gold
	Payable Gold	72.27%
	Silver Refining	\$0.50 /oz Silver
	Payable Silver	78.18%
	Royalty	3.25%
Metal Prices for Base Case		
	Copper	\$ 3.00 /lb
	Moly	\$ 8.00 /lb
	Gold	\$ 1,350.00 /troy oz
	Silver	\$ 20.00 /troy oz
Slope angles, MD_Eng Interramps Less 2 Degrees for Roads		
	Side of the Pit in Degrees	Degrees
	0 to 90 Northeast	41
	90 to Breccia Southeast	39
	Breccia	36
	Breccia to 360 West	44
Recommended overall angles given above are interramp minus approximately 2 degrees		

15.3 MINERAL RESERVE

The mineral reserve was developed by tabulating the contained measured and indicated (proven and probable) material inside of the designed pit at an NSR cutoff grade of \$6.11/ton. The mine plan and schedule that is presented in Section 16 indicates that the operating cutoff is slightly higher during the first five years in an effort to improve front end head grade and maximize project return on investment. The NSR for application of cutoff grade includes a benefit from copper, molybdenum, gold and silver.

The NSR for application to mineral reserve and mine planning is:

NSR =	$(\$3.00-0.3295) \times 0.9180 \times 0.9336 \times 20 +$	Copper Contribution
	$(\$8.00-1.562) \times 0.6070 \times 0.9578 \times 20 +$	Moly Contribution
	$(\$1350-6.00) \times 0.7080 \times 0.6992 +$	Gold Contribution
	$(\$20.00-0.50) \times 0.8200 \times 0.7564$	Silver Contribution

Low grade material that is above the internal cutoff of \$6.11/ton NSR and less than mill feed cutoff in the early years will be stored in two, low grade stockpiles that are located to the northeast of the pit and northeast of the crusher adjacent to the waste storage area. The low-grade material is not currently included within the mineral reserve. By default, it is included within the mineral resources.

The mineral reserve is summarized on Table 15-2. The mineral resource in addition to the mineral reserve is also included for clarity on Table 15-2. The total ore planned for processing in Section 16 matches the total proven and probable reserves on Table 15-2.

The qualified person for the estimation of the mineral reserve was John Marek of Independent Mining Consultants, Inc. Metal price changes could materially change the estimated mineral reserves in either a positive or negative way.

At this time, there are no unique situations relative to environmental or socio-economic conditions that would put the Copper Flat mineral resource at a higher level of risk than any other North American development reserve.

Table 15-2: Mineral Reserves (7 October 2013)

Classification	Cutoff Grade NSR/Ton	Mineral Reserves					Contained Metal				Recovered, Saleable Metal			
		Ktons	Copper %	Moly %	Gold Oz/ton	Silver Oz/ton	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000
Proven	Variable By Year \$12.75 to \$6.11	78,857	0.32	0.010	0.003	0.07	504,685	15,771	237	5,520	432,538	9,169	117	3,424
Probable	\$12.75 to \$6.11	<u>34,227</u>	<u>0.25</u>	<u>0.007</u>	<u>0.003</u>	<u>0.04</u>	<u>171,135</u>	<u>4,792</u>	<u>103</u>	<u>1,369</u>	<u>146,670</u>	<u>2,786</u>	<u>51</u>	<u>849</u>
Total Prov + Prob		113,084	0.30	0.009	0.003	0.06	675,820	20,563	340	6,889	579,208	11,955	168	4,273

Mineral Resources in Addition to Mineral Reserves														
Classification	Cutoff Grade NSR/Ton	Tonnage and Grade					Contained Metal							
		Ktons	Copper %	Moly %	Gold Oz/ton	Silver Oz/ton	Copper Lbs x 1000	Moly Lbs x 1000	Gold ozs x1000	Silver ozs x 1000				
Measured	\$6.11	47,798	0.21	0.007	0.003	0.04	204,583	7,027	143	2,079				
Indicated	\$6.11	<u>144,344</u>	<u>0.18</u>	<u>0.005</u>	<u>0.002</u>	<u>0.04</u>	<u>507,435</u>	<u>13,065</u>	<u>254</u>	<u>5,774</u>				
Meas + Ind		192,142	0.19	0.005	0.002	0.04	712,018	20,092	397	7,853				
Inferred	\$6.11	27,646	0.20	0.004	0.001	0.02	110,584	2,212	28	553				

Notes:

Mineral reserves equal the total ore planned for processing from the mine plan
Mineral Resources stated above do not include the mineral reserve
Mineral Resources are contained within a floating cone pit geometry at prices listed below.
Ktons means 1000 short tons. Short tons = 2000 lbs
Copper and Molybdenum grades are percent of dry weight
Gold and Silver are reported in Troy ounces / short ton

Metal Prices:

Mineral Reserve \$3.00 Copper, \$8.00 Moly \$1350 Gold, \$20.00 Silver, No Economic Credit to Inferred
Mineral Resource \$3.00 Copper, \$8.00 Moly \$1350 Gold, \$20.00 Silver

16 MINING METHODS

The Copper Flat Project is planned for production using conventional hard rock open pit mining methods. Ore production to the mill is planned at 29,600 tpd (10,800 ktons/yr) for the first 6 years followed by 27,125 tpd (9,900 ktons/yr) for the remaining mine life. The mine production schedule was developed with the goal of filling the mill at required ore rate and maximizing the project return on investment. The total material rate is tied to equipment productivity and amounts to 17,500 ktons/yr or 47,945 tpd for the first 5 years. The mine is scheduled to operate 365 days/yr with two, 12-hour shifts/day.

Bench heights are planned at 25 ft high. Drilling will be completed with three rotary blast hole rigs with 45,000 lb pull down capacity and 6.5 in diameter blast holes. The blasted rock will be loaded into 100-ton haul trucks using two 19 cu yd front end loaders.

The mine plan was developed with a phase approach. The phase designs, mine schedule, and mine equipment requirements are summarized in this section.

16.1 PHASE DESIGN

A floating cone algorithm was used as a guide to the design of the phases or pushbacks. Multiple floating cones were developed using the costs, slope angles and recoveries outlined in Section 15. Metal prices were changed in order to establish a series of multiple nested cone geometries. The results of this work indicated the starting point, final pit and the extraction sequence that maximized the NPV throughout the mine life.

Three phases were designed for the Copper Flat Project with approximately 300 ft of operating width on each bench within a phase. Phase 1 was sized to contain roughly 1.5 years of ore.

The design parameters for the phases were similar to those for the final pit as discussed in Section 15.

Mine Planning Parameters:

Haul Road Width		90 feet
Haul Road Grade		10% Maximum
Inter-ramp Slope Angles		
0° to 90°	Northeast	41 degrees
90° to Brec	Southeast	39 degrees
Breccia		36 degrees
Brec to 360°	West	44 degrees
Operating width between pushbacks		300 feet nominal

The phases were tabulated from the block model and those three tabulations were used as input to the development of the mine production schedule. Figure 16-1 illustrates the relative position of the phases on the 5425 elevation.

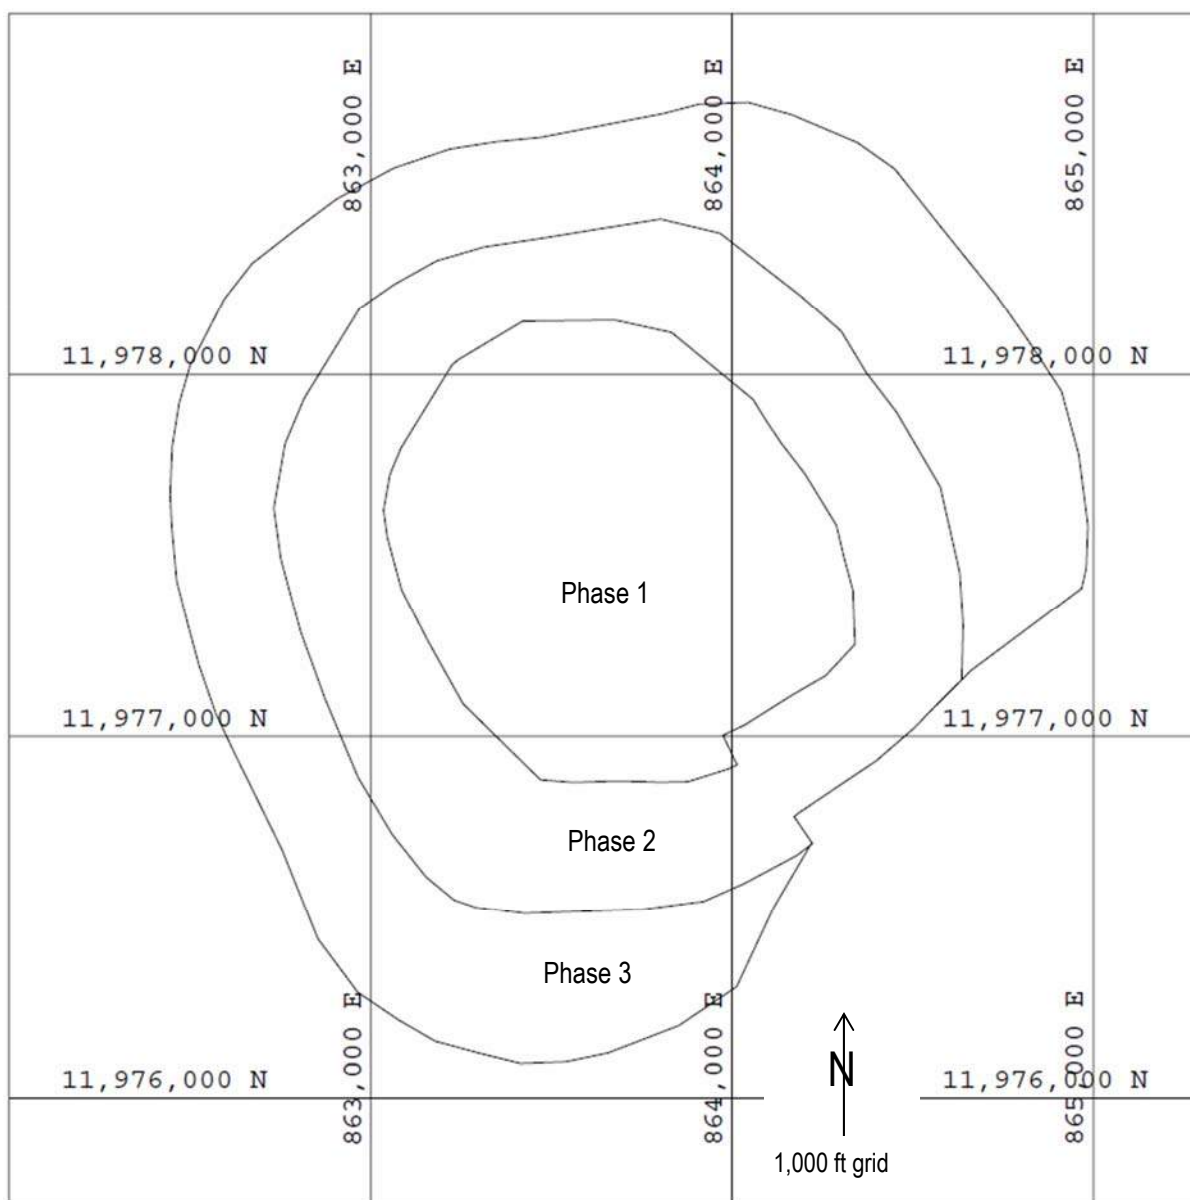


Figure 16-1: Relative Location of Phase Designs (5425 Bench)

16.2 MINE PRODUCTION SCHEDULE

The mine production schedule was developed with the goal of filling the mill at the required production rates and maximizing the project return on investment. Multiple mine production schedules were developed that analyzed alternative cutoff grade strategies versus mine total material movement. Total material rates were tied to the size and number of loading units so that the final selected schedule would provide efficient use of the capital equipment employed.

The multiple schedules were evaluated on a net present value basis at the project design prices that were used to establish the mineral reserve (Section 15). The best overall production schedule on an economic and practical basis was selected and is summarized on Table 16-1.

Preproduction stripping is minimal because the ore outcrops and the historic mining that has already occurred. Much of the preproduction waste stripping was completed when the mine was in operation in the 1980's under the ownership of Quintana Minerals. Preproduction is estimated to require 3 months at 1 shift per day of operation. The initial road pioneering and some pit rehab can occur prior to the preproduction period. Ore that is incurred during preproduction (360 ktons) is planned to be stockpiled near the crusher (or in the pit) and delivered to the mill during Year 1.

Low grade material that is above a cutoff of \$7.50/ton NSR and less than mill feed cutoff in the early years will be stored in two, waste storage facilities that are located to the northeast of the pit and northeast of the crusher. That material is not currently planned for processing and is consequently not included in the mineral reserves. The bottom of Table 16-1 illustrates the ore planned for processing inclusive of stockpile re-handling.

The cutoff grade for the mine schedule is an NSR (net smelter return) calculation that includes the credit of copper, moly, gold and silver. The Cutoff NSR calculation is summarized below.

The Cutoff NSR for the mine plan and mineral reserve is:

Cutoff NSR =	$(\$3.00-0.3295) \times 0.9180 \times 0.9336 \times 20 +$	Copper Contribution
	$(\$8.00-1.562) \times 0.6070 \times 0.9578 \times 20 +$	Moly Contribution
	$(\$1350-6.00) \times 0.7080 \times 0.6992 +$	Gold Contribution
	$(\$20.00-0.50) \times 0.8200 \times 0.7564$	Silver Contribution

The total proven and probable ore that is planned for processing on Table 16-1 is the mineral reserve as summarized in Section 15. Inferred mineralization is treated as waste within the mine plan and mineral reserve statement.

Table 16-1: Mine Production Schedule

Mine Plan Schedule											
Year	Cutoff NSR/ton \$/ton	Direct Mill Feed Ore						Waste			Total Material Ktons
		Ore Ktons	NSR \$/ton	Copper %	Moly %	Gold oz/ton	Silver Oz/ton	WSF 1 Ktons	WSF 2 Ktons	WSF 3 Ktons	
Preprod	\$12.00	360	22.824	0.43	0.007	0.003	0.06	32	30	48	470
Yr1 Q1	\$12.75	1,540	20.681	0.38	0.008	0.003	0.07	719	678	1,438	4,375
Yr1 Q2	\$12.75	2,000	22.960	0.41	0.012	0.004	0.08	541	279	1,555	4,375
Yr1 Q3	\$12.75	2,700	23.354	0.41	0.012	0.004	0.08	440	199	1,036	4,375
Yr1 Q4	\$12.75	2,700	23.533	0.42	0.013	0.004	0.08	373	190	1,112	4,375
Yr2	\$11.25	10,800	23.050	0.40	0.011	0.004	0.09	1,055	2,333	3,312	17,500
Yr3	\$10.00	10,800	16.338	0.29	0.007	0.003	0.06		2,544	4,156	17,500
Yr4	\$10.00	10,800	20.475	0.36	0.010	0.003	0.07		1,756	4,944	17,500
Yr5	\$9.25	10,800	18.193	0.32	0.011	0.003	0.07		628	6,072	17,500
Yr6	\$6.11	10,025	11.761	0.21	0.005	0.002	0.05			5,924	15,949
Yr7	\$6.11	9,900	11.986	0.21	0.005	0.002	0.05			2,491	12,391
Yr8	\$6.11	9,900	13.752	0.24	0.007	0.002	0.05			718	10,618
Yr9	\$6.11	9,900	16.008	0.28	0.008	0.002	0.06			71	9,971
Yr10	\$6.11	9,900	16.208	0.29	0.010	0.002	0.06			3	9,903
Yr11	\$6.11	9,900	15.940	0.27	0.012	0.003	0.06			1	9,901
Yr12	\$6.11	1,059	12.722	0.21	0.010	0.002	0.05			4	1,063
Totals		113,084	16.965	0.30	0.009	0.003	0.06	3,160	8,637	32,885	157,766

Mineral Reserve is the direct feed ore planned for processing.
Stockpiles are not included in the statement of mineral reserves.

16.3 WASTE AND LOW GRADE STORAGE

The annual mine schedule drawings at the end of the section illustrate the location and size development of the waste storage facilities.

The waste storage facilities are built to at 3 to 1 slopes (18.4 degrees) in order to facilitate reclamation at the end of the mine life. Dump lifts are 75 ft high and are dumped at angle of repose (35.54 degrees) with 120 ft setbacks left between lifts to maintain the 3 to 1 overall angle for future reclamation.

The three waste storage facilities have been segregated by cutoff grades. Waste Storage Facility 1, WSF 1, contains the highest-grade material. Waste Storage Facility 2, WSF 2, contains the next highest-grade material. Waste Storage Facility 3, WSF 3, contains all the remaining material. WSF 1 & 2 are planned so that they could be remined for a future processing opportunity or reclaimed in their current configuration.

Waste Storage Facility 1 is located to the northeast of the mine. The location of WSF 1 was selected to be a reasonable haul during the mine life for the storage of the material as well as a short haul distance to the crusher if becomes economical to remine it. WSF 1 is will store 3,160 ktons over the mine life.

Waste Storage Facility 2 is located northeast of the crusher and west of WSF 3. WSF 2 will be placed above WSF 3 starting at the 5,500 elevation. The location of WSF 1 was selected to be a reasonable haul during the mine life for the storage of the material as well as a short haul distance to the crusher if becomes economical to remine it. WSF 1 is will store 8,637 kttons over the mine life.

Waste Storage Facility 3 is located 3,000 to 4,000 ft east of the pit exit. The storage of waste material over the mine life is 32,885 kttons.

There is no provision for re-contouring of the waste dumps within the mine operating costs. Mine reclamation costs are not included within the mining costs because they were address separately by THEMAC and their contractors.

16.4 MINE EQUIPMENT REQUIREMENTS

Mine equipment is standard off-the-shelf units. Two front end wheel loaders were selected to match production requirements based on the financial analysis of the mine schedule. The mobility of the front-end loaders is a benefit to mine operations. A trade off study was performed between a front-end wheel loader and a hydraulic shovel. The front-end loader was selected because it had overall lower capital and operating cost and contributed to improved project economics.

Truck fleet requirements were developed from haul time simulation over profiles measured for each material type, by phase, for each year of the mine plan.

Table 16-2 summarizes the major mine equipment units that will be on site throughout the mine life. Additional minor units are included in the capital cost table in Section 21 that will be required to maintain and sustain mine operations.

Table 16-2: Mine Major Equipment Fleet on Hand

Mine Major Equipment Fleet On Hand (Units owned based on fleet build up and replacement)																
Equipment Type	Preprod	Yr1Q1	Yr1Q2	Yr1Q3	Yr1Q4	Yr2	Yr3	Yr4	Yr5	Yr6	Yr7	Yr8	Yr9	Yr10	Yr11	Yr12
CAT MD6290 Blast Hole Drill (45,000 lbs)	1	3	3	3	3	3	3	3	3	3	3	3	3	3	3	3
Cat 993K Loader (19 Cu Yd)	1	2	2	2	2	2	2	2	2	2	2	2	2	2	2	2
Cat 777G Haul Truck (100 Tons)	2	8	8	8	8	9	10	10	10	10	10	10	10	10	10	10
Cat D9T Track Dozer (410 hp)	1	3	3	3	3	3	3	3	3	3	3	3	3	3	3	3
Cat 834H Wheel Dozer (354 hp)	1	1	1	1	1	1	1	1	1	1	1	1	1	1	0	0
Cat 14M Motor Grader (14 ft)	1	2	2	2	2	2	2	2	2	2	1	1	1	1	1	1
Cat 773G Water Truck (10,000 Gal)	1	1	2	2	2	2	2	2	2	2	2	2	2	2	2	2
Sandvik DX-800 Rock Drill	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Cat 329D Excavator (2 Cu Yd)	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
TOTAL	10	22	23	23	23	24	25	25	25	25	24	24	24	24	23	23

16.5 MANPOWER REQUIREMENTS

Mine hourly manpower requirements were established to operate and maintain the mine mobile equipment. Blasting crews and laborers are also provided for in the manpower list. Table 16-3 and Table 16-4 illustrate the hourly and salaried manpower for the planned mine life.

Staff labor (Supervisory, Engineering, and Geology) are set at 22 persons for all years except preproduction and the final year when a smaller staff can be utilized.

Table 16-3: Mine Hourly Labor Requirements

Mine Hourly Labor Requirements																	
JOB TITLE	Annual Cost	Preprod	Yr1 Q1	Yr1 Q2	Yr1 Q3	Yr1 Q4	Yr2	Yr3	Yr4	Yr5	Yr6	Yr7	Yr8	Yr9	Yr10	Yr11	Yr12
MINE OPERATIONS:																	
Drill Operator	86,206	2	10	10	10	10	10	10	10	10	9	8	7	6	6	5	4
Loader Operator	86,206	2	8	8	8	8	8	8	8	8	8	8	6	4	4	4	4
Haul Truck Driver	78,340	2	23	26	24	26	27	30	33	32	29	23	21	22	25	28	29
Track Dozer Operator	82,502	1	6	6	6	6	6	6	6	6	6	6	6	6	6	4	4
RTD Operator (Wheel Dozer)	79,485	2	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4
Grader Operator	79,485	1	6	6	6	6	6	6	6	6	4	4	4	4	4	4	3
Water Truck Operator	72,669	1	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4
Utility Equip Operator (Service Crew)	79,485	2	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4
Blasting Crew	86,369	2	2	2	2	2	2	2	2	2	2	2	2	2	2	2	2
Laborer	66,867	2	8	8	8	8	8	8	8	8	8	8	8	8	8	8	8
Operations Total		17	75	78	76	78	79	82	85	84	78	71	66	64	67	67	66
MINE MAINTENANCE:																	
Mechanics I	86,206	2	13	13	13	13	14	14	14	14	13	12	11	10	11	12	11
Mechanics II	79,485	1	5	6	6	6	6	6	6	6	6	5	5	4	5	5	5
Welder	82,862	1	5	5	5	5	5	5	5	5	5	5	4	4	4	5	4
Fuel & Lube Crew	79,485	4	8	8	8	8	8	8	8	8	8	8	8	8	8	8	8
Tire Crew	79,485	2	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4
Laborer Mnt	66,867	1	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4
Maintenance Total		11	39	40	40	40	41	41	41	41	40	38	36	34	36	38	36
VS&A at 10.0%		3	11	12	12	12	12	12	13	13	12	11	10	10	10	11	10
TOTAL LABOR REQUIREMENT		31	125	130	128	130	132	135	139	138	130	120	112	108	113	116	112
Maint/Operations Ratio		0.65	0.52	0.51	0.53	0.51	0.52	0.50	0.48	0.49	0.51	0.54	0.55	0.53	0.54	0.57	0.55
Notes:																	
1. Utility Crew operates 988 Loader, 773F Trucks, Rock Drill, Excavators, the extra Water Truck, etc.																	
2. There will be one water truck operating at all times. The second water truck will be shared with utility crew.																	
3. VSA Basis: 10%																	
4. Annual cost includes benefits and anticipated overtime																	

Table 16-4: Salaried Staff Labor Requirements

Salaried Staff Labor Requirements																	
JOB TITLE	Annual																
	Cost (\$US)	Preprod	Yr1 Q1	Yr1 Q2	Yr1 Q3	Yr1 Q4	Yr2	Yr3	Yr4	Yr5	Yr6	Yr7	Yr8	Yr9	Yr10	Yr11	Yr12
Mine Manager	201,550	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Total		1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
MINE OPERATIONS:																	
General Foreman	139,000	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
FL Supervisors	115,648	1	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4
Drill & Blasting Supervisor	115,648	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Mine Clerk	51,952	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Mine Trainer	104,250	1	1	1	1	1	1	1	1	1	1	1	1	1	1	0	0
Mine Operations Total		5	8	8	8	8	8	8	8	8	8	8	8	8	8	7	7
MINE MAINTENANCE:																	
General Foreman Mnt	139,000	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
FL Supervisors Mnt	115,648	1	2	2	2	2	2	2	2	2	2	2	2	2	2	2	2
Maintenance Planners	97,300	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Maintenance Clerk	51,741	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Mine Maintenance Total		4	5	5	5	5	5	5	5	5	5	5	5	5	5	5	5
MINE ENGINEERING:																	
Chief Engineer	152,900	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Engineers	125,100	1	2	2	2	2	2	2	2	2	2	2	2	2	2	1	1
Sr. Surveyor	71,883	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Surveyor	71,883	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Mine Engineering Total		4	5	5	5	5	5	5	5	5	5	5	5	5	5	4	4
MINE GEOLOGY:																	
Mine Geologist	111,200	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1	1
Sampler	57,490	2	2	2	2	2	2	2	2	2	2	2	2	2	2	2	2
Mine Geology Total		3	3	3	3	3	3	3	3	3	3	3	3	3	3	3	3
TOTAL PERSONNEL		17	22	22	22	22	22	22	22	22	22	22	22	22	22	20	20

Annual Cost includes Fringe Benefits

16.6 MINE AND WASTE STORAGE PLANS

Figure 16-2 through Figure 16-13 illustrate the mine plans along with the low grade stockpiles and waste storage plans.

17 RECOVERY METHODS

The Copper Flat Project will produce copper and molybdenum flotation concentrates. The design basis for the conventional sulfide flotation mill is a throughput of 30,000 dry short tons per day or 10,800,000 dry short tons per year for approximately 12 years with reductions in throughput in Years 6 through 12 projected due to the mineralization becoming more difficult to grind.

17.1 PROCESS FACILITY DESCRIPTION

The process selected for recovering the copper and molybdenum minerals is considered “conventional.” The sulfide ore is crushed and ground to a fine size and processed through mineral flotation circuits. The following items summarize the process operations required to extract copper and molybdenum from the Copper Flat sulfide ore.

- Size reduction of the ore by a primary gyratory crusher to reduce the ore size from run-of-mine (ROM) to minus 175 mm.
- Stockpiling primary crushed ore and then reclaiming by feeders and conveyor belt.
- Grinding ore in a semi-autogenous (SAG) mill primary grinding circuit and a ball mill secondary circuit prior to processing in a flotation circuit. The ball mill will operate in closed circuit with hydrocyclones to deliver an ore size of 80 percent passing 140 μ to the flotation circuit.
- Gravity separation will be conducted on a bleed from the hydrocyclone underflow slurry to remove gravity recoverable gold ahead of flotation.
- The flotation plant will consist of copper and molybdenum flotation circuits. The copper and molybdenum minerals are concentrated in a bulk copper/moly concentrate. The moly mineral is separated from the copper minerals in a moly flotation circuit. The bulk (copper-moly) flotation circuit consists of rougher flotation, concentrate regrind, first cleaner /first cleaner-scavenger flotation, and second cleaner flotation. The moly flotation circuit will consist of moly separation (rougher) flotation, moly first cleaner flotation, concentrate regrind, moly second cleaner flotation and moly third cleaner flotation.
- Final copper concentrate is thickened, filtered, and loaded in trucks for shipment. Final molybdenite concentrate is thickened, filtered, dried, and packaged into containers for shipment.
- Flotation tailing is classified with hydrocyclones to produce sands to build a centerline dam and reclaim water for process recycle in a tailing disposal facility at the mill site.
- Water from tailing and concentrate dewatering is recycled for reuse in the process. Plant water stream types include reclaimed process water and freshwater.
- Storing, preparing, and distributing reagents used in the process. Reagents include lime, potassium amyl xanthate (PAX), Aero 238 collector, fuel oil, methyl isobutyl carbinol (MIBC), Flomin D-910, sodium hydrosulfide, flocculant, antiscalant and nitrogen.

17.2 CRUSHING

Run of Mine (ROM) ore will be trucked from the mine to the primary crusher where it will be dumped directly into the crusher dump pocket that feeds a gyratory crusher.

A hydraulically operated, pedestal-mounted, rock breaker will be installed at the dump pocket for use on oversized material.

Primary crushed ore will be withdrawn from the crusher discharge pocket by a variable speed, crusher discharge apron feeder. The crusher discharge feeder will feed the coarse ore conveyor that will discharge to coarse ore stockpile. The crushing production rate will be monitored by a belt scale mounted on the conveyor. Tramp iron will be removed using a self-cleaning magnet that will be located at the transfer point between the crusher discharge feeder and the stockpile feed conveyor. A metal detector and belt scale will be installed at the proximal end of the stockpile feed conveyor.

Dust control in the primary crushing area will be by dry dust collector and water spray systems.

An air compressor and instrument air dryer will be installed for operation and maintenance.

17.3 COARSE ORE STOCKPILE

Primary crushed ore will be discharged on the ground to a coarse ore stockpile. An existing reclaim tunnel is beneath the stockpile location. Approximately 17 percent of the capacity of the ore stockpile will be "live." During primary crusher down time, ore will be moved from the "dead" storage area to the "live" storage area by front-end loader or bulldozer.

Ore will be withdrawn from coarse ore reclaim stockpile by variable speed apron feeders. The feeders will discharge to a conveyor belt that feeds the SAG mill in the grinding circuit.

Fugitive dust will be controlled with water sprays at the discharge of the stockpile feed conveyor. Dust control in the coarse ore stockpile area will be by dry dust collector systems installed as part of the crushing area.

17.4 GRINDING

Ore will be ground to final product size in a SAG mill and ball mill grinding circuit. The SAG mill will operate in closed circuit with SAG mill discharge screen and pebble crusher. The SAG mill discharge screen undersize will flow by gravity to the primary cyclone feed sump and the screen oversize will be transported by conveyors to the pebble crusher. Pebble crushing will be conducted in a short-head cone crusher. The SAG mill discharge screen oversize can bypass the pebble crusher via diverter gate (3015-DG-001) ahead of the pebble crusher. The bypassed screen oversize will feed a second diverter gate (3015-DG-002) which will either feed the pebble crusher conveyor that transports crushed pebble to the SAG mill or dump pebbles to the pebble stockpile. Tramp iron, and broken media will be removed using a self-cleaning belt magnet that will be installed over the SAG mill oversize conveyor ahead of the pebble crusher.

Secondary grinding will be performed in a ball mill which will operate in closed circuit with a cluster of hydrocyclones. The ball mill will discharge into a cyclone feed sump. The contents of the sump will be transferred using variable speed horizontal centrifugal slurry pump to a hydrocyclone cluster.

Most of the hydrocyclone underflow slurry will report to the ball mill, but a portion of the underflow will be taken through a Knelson-type gravity concentrator circuit to collect gravity-recoverable gold. The gravity separation circuit will consist of two Knelson-type concentrators each of which will have an upstream scalping screen to remove oversize material. The gravity concentrates will pass through magnetic separators for removal of tramp iron and broken grinding media. The tailings from the gravity concentrators will be pumped back to the cyclone feed sump.

Hydrocyclone overflow (final grinding circuit product) will flow by gravity to the rougher flotation conditioning tank ahead of the rougher flotation cells. The overflow slurry will be sampled and analyzed for metallurgical control prior to flotation.

Grinding balls will be added to SAG mill and ball mill using ball loading systems.

Lime slurry will be added to the SAG mill and ball mill feed to adjust the pH of the slurry. If needed, lime slurry may also be added to the primary grinding sumps. In addition, fuel oil will be added to the SAG mill feed to aid in molybdenite collection.

Overhead cranes will be installed for maintenance of the grinding mills and cyclone feed pumps, and hydrocyclone.

17.5 FLOTATION

Primary grinding hydrocyclone overflow will flow by gravity to the bulk flotation circuit. The bulk flotation circuit will consist of a conditioning tank, one row of rougher flotation cells, a rougher concentrate vertical regrind mill, one row of first cleaner/cleaner-scavenger flotation cells and two second cleaner column flotation cells.

The rougher flotation row will consist of six tank type rougher flotation cells with a drop between each cell. Flotation reagents will be added to the hydrocyclone overflow in the rougher flotation conditioning tank where the slurry will be agitated to allow the reagents to react with the ore particles before feeding to the rougher flotation cells. The concentrate from the first two rougher flotation cells will be sampled and transported by gravity directly to the copper cleaner feed pump box. The flotation concentrate from the last four rougher flotation cells will also be sampled and transported by gravity to rougher concentrate regrind sump. Tailing from the rougher flotation cell will be sampled and transported to the tailings treatment facility. Rougher flotation tailings will be sampled for metallurgical control. Concentrate from the last four rougher flotation cells, combined with first cleaner-scavenger concentrate and regrind cyclone underflow, will be pumped from the copper regrind cyclone feed pump box to copper regrind cyclone cluster. Copper regrind cyclone underflow will flow by gravity to the copper regrind mill. The copper regrind mill will operate in closed circuit with hydrocyclone.

Regrind cyclone overflow (final regrind circuit product) will flow by gravity to an agitated conditioning tank. Second cleaner tailing and flotation reagents will also be added into this tank. Conditioning tank discharge will flow by gravity to the first cleaner/cleaner-scavenger flotation cells. The first cleaner flotation will consist of eight tank type flotation cells. Concentrate from the first cleaner flotation cells will be pumped to the concentrate distribution box. Tailing from the first cleaner flotation cells will flow by gravity to the first cleaner-scavenger cells. The first cleaner-scavenger flotation circuit will consist of six tank type rougher flotation cells. Concentrate from the cleaner-scavenger cells will be returned to the bulk concentrate regrind circuit sump using a froth pump. Tailing from the cleaner-scavenger cells will be pumped back to the rougher flotation circuit. Cleaner-scavenger tailing may be sent to the final tailing sump.

Two discharge ports in the concentrate distribution box will direct the slurry to the feed inlets for the second cleaner column cells operated in parallel. Second cleaner tailing slurry will be pumped from the two columns to the first cleaner conditioning tank from where it will be pumped to the first cleaner flotation cells. The second (column) cleaner concentrate slurry will be pumped to the copper-moly concentrate thickener.

Two blowers (one operating and one standby) will supply air to bulk second cleaner column cells and as required to the bulk mechanical rougher, first cleaner/cleaner-scavenger and second cleaner bulk flotation tank cells.

An air compressor with air receiver and an instrument air dryer will be installed for operation and maintenance.

A bridge crane will be installed for maintenance of the flotation and regrind equipment.

Flotation reagents will be added at several points in the bulk flotation circuit.

17.6 MOLYBDENITE FLOTATION

Bulk second cleaner concentrate will be transported to the copper-moly concentrate thickener. Thickener overflow will be pumped by a horizontal centrifugal pump from an overflow sump to the plant reclaim water storage tank. Copper-moly thickener underflow will be pumped by a variable speed horizontal centrifugal slurry pump to the molybdenite flotation circuit.

The molybdenum flotation circuit will consist of one row of copper-moly separation (rougher) flotation cells, one row of molybdenite first cleaner flotation cells, a moly regrind circuit, one molybdenite second cleaner flotation cell, and one molybdenite third cleaner flotation cell.

The copper-moly separation (rougher) flotation row will consist of eight mechanical rougher flotation cells. Concentrate from the copper-moly separation (rougher) cells will be pumped by froth pump to the molybdenite first cleaner flotation cells. Tailing from the copper-moly separation cells will flow by gravity to the copper concentrate thickener. Tails and concentrate from the copper-moly separation flotation cells will be sampled.

The molybdenite first cleaner flotation row will consist of four mechanical cells. Concentrate from the molybdenite first cleaner cells will be pumped by froth pump to the feed sump of the molybdenite concentrate regrind circuit. Tailing from the molybdenite first cleaner flotation cells will flow by gravity to the feed launder of the copper concentrate thickener. Concentrate from the moly first cleaner cells will be sampled.

Molybdenite concentrate regrinding will be performed in a vertical mill. Molybdenite first cleaner flotation concentrate will feed the vertical mill which will discharge into moly regrind discharge pump box and pumped to the moly second cleaner column cell.

Slurry will be pumped by the second moly cleaner feed pump to the molybdenite second cleaner flotation column cell. Tailing from the molybdenite second cleaner column cell will be pumped to the moly first cleaner flotation cells.

Molybdenite second cleaner concentrate will be pumped to the moly third cleaner column cell. Concentrate from the molybdenite third cleaner column cell will be pumped to the agitated moly filter feed tank that feeds the moly filtering and drying circuit. Tailing from the molybdenite third cleaner column cell will be pumped to the molybdenite regrind cyclone feed sump.

Two blowers (one operating and one standby) will supply air to the second and third moly cleaner column cells.

Flotation reagents will be added at several points in the molybdenite flotation circuit.

Molybdenite circuit process streams will be sampled for metallurgical control. Sample points include: concentrate from the copper-moly separation (rougher) flotation row; concentrate from molybdenite first cleaner flotation row; and concentrate from molybdenite third cleaner column cell.

17.7 CONCENTRATE DEWATERING

17.7.1 Copper Concentrate Dewatering

Final copper concentrate will be a combination of tailings from copper-moly separation flotation and moly first cleaner flotation cells. Each tailing stream will be sampled before being transported to the copper concentrate thickener feed box from where the combined tailings will be fed to the copper concentrate thickener. Thickener overflow will be

pumped from the overflow pump box by a horizontal centrifugal pump to the copper-moly concentrate thickener feed box. Thickener underflow will be pumped by variable speed horizontal centrifugal slurry pump to the copper concentrate stock tank from which it will be pumped to the copper concentrate filters.

Horizontal centrifugal pumps will transport copper concentrate slurry from agitated concentrate stock tank to two automatic plate-and-frame pressure filters. The filters will discharge batches of filter cake to a copper concentrate stockpile at the east end of the mill building. Filtrate and filter wash water will be returned to the feed box of the copper-moly concentrate thickener. A front-end loader will fill highway haulage trucks with copper concentrate on a built-in truck scale. A wheel wash system for the concentrate haulage trucks will ensure that concentrate will not be carried out of the load out area.

17.7.2 Molybdenite Concentration

Molybdenite concentrate from the molybdenite third cleaner column cell will flow by gravity to the moly filter feed tank. Concentrate from the agitated tank will be pumped to a disc filter for dewatering.

Filter cake will discharge to a conveyor that feeds a Holoflote-type hot oil dryer. The dryer will discharge via a screw conveyor to the molybdenite concentrate storage bins. Filtrate will be pumped to the copper-moly thickener.

17.8 TAILING DEWATERING

Tailing from the bulk rougher flotation row will flow by gravity to a tailings separation facility where hydrocyclones will be used to separate the coarser particles (sands) to build a centerline dam, as described in greater detail in Section 20.2. Underflow sands will be pumped to the crest of the tailings storage facility (TSF). Cyclone overflow fines will be pumped to the TSF and spigotted to the interior of the impoundment. Further settling of the fines produces a supernatant water pond at the back (upstream) of the impoundment that will be reclaimed and pumped to the Reclaim Reservoir. Drainage from the tailings materials will be captured by a synthetic liner and conveyed via an overliner drainage system to a seepage collection pond. The overliner drain will have perforated piping to collect the drainage and convey it to collector piping that discharges to the collection pond. Collected seepage water will be pumped to the Reclaim Reservoir.

17.9 REAGENT STORAGE AND MIXING

Reagents requiring handling, mixing, and distribution system include:

- Potassium Amyl Xanthate (PAX, collector)
- Methyl Isobutyl Carbinol (MIBC, frother)
- Sodium Hydrosulfide (NaHS), copper mineral depressant)
- Flocculant
- Pebble Lime (CaO, pH modifier)
- Fuel oil (molybdenite collector)
- Butyl dithiophosphate
- Antiscalant

Reagent consumption rates for the full scale plant operation have been estimated from the test results. The estimated reagent consumption rates for sulfide ore processing are shown in Table 17-1.

Table 17-1: Estimated Reagent Consumption Rates for Sulfide Ore

	Rate
Item	lb/ton ore
Copper Circuit	
Collector, Potassium Amyl Xanthate	0.030
Collector, Butyl Dithiophosphate	0.010
Frother, Methyl Isobutyl Carbinol (MIBC)	0.12
Collector, #2 Diesel Fuel	0.1
Lime (90% CaO)	2.4
Flocculant (for Concentrate Dewatering)	0.01
Molybdenite Circuit	
Sodium Hydrosulfide	0.25
#2 Diesel Fuel	0.007
Flomin 910	0.02
Methyl Isobutyl Carbinol (MIBC)	0.007

17.10 WATER SYSTEMS

The water system for the Copper Flat Project plant site will consist of two grades of water. The following sections describe the two grades of water that will be used at the plant site.

Freshwater – Area 4012

Freshwater for the Copper Flat Project will be supplied from offsite wells. Water from the wells will be pumped to freshwater tanks No.1 and No.2 before pumping to the Reclaim Reservoir Freshwater tank. Freshwater flows by gravity to the reclaim water reservoir as make up water for use in the concentrator and will also be pumped from the Reclaim Reservoir Freshwater tank to the Plant Fresh/Fire Water Storage Tank. Freshwater from the Plant Fresh/Fire Water Storage Tank will be distributed to:

- Fire water loop
- Chlorinator system and potable water tank for use in offices, laboratory, housing, eye wash stations, and rest rooms
- Gland seal water tank and pumped by horizontal centrifugal pumps to be used as seal water for mechanical equipment
- Mine water trucks to be used in road dust control
- Process use points (e.g. crusher dust suppression, column flotation, reagent mixing, moly plant)

Reclaim Water – Area 4013

Process water will be reclaimed from several locations and collected in the Reclaim Reservoir. Overflow from the copper-moly thickener will flow by gravity to the Reclaim Reservoir. Water reclaimed tailings cyclone overflow thickener, supernatant tailings impoundment water pond from the tailing pond, and water from the Seepage Collection Pond will be pumped to the reclaim water reservoir. Make-up water from the Reclaim Reservoir Freshwater Tank will also be added at the reclaim water reservoir. Water from Reclaim Water Reservoir will be pumped to the Reclaim Water Storage Tank and distributed by gravity to the concentrator usage points.

18 PROJECT INFRASTRUCTURE

The Project receives significant benefit from existing infrastructure that remains from the Quintana Minerals operation. Components of the existing infrastructure that will be placed back into service for the new operation are:

- Concrete foundations and structures required for the primary crusher, concentrator, mine substation, truck shop, assay lab and administration building;
- Conveyor tunnels for the crusher discharge belt and the coarse ore stockpile reclaim system;
- Four freshwater wells, two of which are equipped with pumps at this time, and eight miles of 20" steel pipeline to convey freshwater from the well field to the mill site;
- Twelve miles of 115 kV power line and structures connecting the mine substation to the utility power grid;
- Several mine roads, including a 2.5-mile gravel access road connecting the mine site to State Highway 152 and more than 2 miles of mine haul roads and service roads connecting the pit to the crusher, the mine shop and material stockpile areas.
- Other earthworks including mill site and mine shop grading, storm water culverts, and a water diversion structure and channel to divert a major watershed around the pit; and
- Nearly 2 million tons of pre-preproduction stripping to expose the ore body.

The value provided to the new operation by the existing infrastructure has been estimated and is summarized in Section 21 of this report.

The following sections describe upgrades to existing infrastructure or new infrastructure that is required for the new operation. Costs to complete the described work are included in the capital cost estimate for the project.

18.1 ROADS

State Highway 152 will be upgraded to add turning lanes at the mine access road for commercial truck traffic, and to add a 2.5-inch asphalt overlay to the existing road surface between the mine access road and Interstate Highway 25 (2 traffic lanes for 10.5 miles).

A ½ mile section of the existing gravel access road will be relocated around the location of the new tailings facility.

18.2 POWER

A new power substation and switch will be constructed at the 345 kV power line at or near the point where it crosses the existing 115 kV power line to the mine. The new substation will transform power to 115 kV for transmission to the mine and will include necessary equipment to balance loads on the 345 kV line.

The existing 115 kV high power transmission line terminates approximately 1,000 feet from the mine substation. The line will be extended to the substation and maintenance performed on the existing power line and structures.

A new 24.9 kV power line will be constructed from the mine substation to the freshwater well field 8 miles to the east to power the wells.

A new 1,800 kVA, 4.16 kV diesel powered generator will be installed at the mine substation to maintain the operation of thickener pumps and rakes, area ventilation, heat tracing, and limited lighting in the concentrator, mine shop and warehouse buildings during power outages.

18.3 WATER

New pumps will be installed in two of the four freshwater wells (two wells are currently equipment with pumps) and all four wells will be connected to the water conveyance pipeline. Each well will be capable of supplying a nominal 1,500 gallons of freshwater per minute. Operation of the pumps will be remotely monitored and controlled from the mill control room at the mine.

Three pump booster stations will be added to the water conveyance system to bring water from the well field to a new 300,000 gallon freshwater storage tank located on Animas Peak above the mill site.

18.4 RAIL

The Company will lease land and construct a concentrate storage shed to receive and store concentrates at the rail siding in the area. Several sidings exist in the vicinity of Copper Flat. The closest is the rail siding located at Rincon, New Mexico, which is 45 road miles from the project site. The shed will be fully enclosed for security and to control dust emissions from stored concentrate. Rail cars will be loaded by conveyor. Plans for the concentrate storage facility include a wheel loader, loadout hopper and conveyor, and a winch system for positioning rail cars under the loading conveyor.

Concentrate will be shipped by rail to the seaport at Guaymas, Mexico. Rail line to the port is existing and active. Facilities at the port will be owned and operated by a third party.

18.5 MATERIAL STOCKPILES

After crushing, coarse ore is stockpiled ahead of the grinding circuit. Coarse ore is reclaimed from the stockpile by apron feeders installed in the existing concrete reclaim tunnel. Total storage capacity of the coarse ore stockpile is approximately 75,000 short tons, or 2-1/2 days of mill throughput at the planned processing rate. Live capacity of the stockpile is approximately 15,000 short tons, or 12 hours of mill throughput. When necessary, ore will be feed to the mill from the "dead" storage area by front-end loader or bulldozer.

The majority of non-economic material will be permanently stored in three unlined waste rock disposal facilities (WRDFs) located east of the pit. The selected areas fully meet mine needs within the mine permit boundary. The non-economic stockpile is designed to facilitate re-grading to required slopes at mine closure. Additional details regarding the WRDFs are discussed in Section 20.3.1.

18.6 TAILINGS STORAGE FACILITY

A new tailings storage facility (TSF) will be constructed at the location of the existing Quintana Minerals facility that was constructed and briefly operated in 1981 and 1982. Ultimately, the new TSF will store tailings from processing the 113 million tons of reserves. The new facility will extend approximately 1,000 feet east of the existing Quintana Minerals starter dam (the tailings expansion area). Details regarding design, construction and operation of the TSF are provided in Section 20.2.

18.7 SANITARY WASTEWATER TREATMENT

A packaged water treatment plant will be installed at the mine to accommodate liquid sanitary wastes generated from the mine office, shower, and rest room facilities. For the feasibility study, the packaged water treatment plant was sized for a load based on mine headcount for a 24-hour day plus excess. To accommodate this loading, a 10,000 gallon per day plant is assumed based on 200 people per day at a usage rate of 50 gallons per day per person. The plant would generate effluent treated to secondary treatment levels. The plant discharge will be to the lined tailings

storage facility and recycled back to mill with the tailings process water. The location of the plant will be on a pre-existing concrete slab in the Mine plant area.

18.8 CENTRAL INFRASTRUCTURE CONTROL AND COMMUNICATIONS SYSTEMS

The concentrator at the Copper Flat property will incorporate modern, dependable and proven instrumentation and control systems. Mine communication systems will include a voice over IP telephone system, a computer system with networking, internet access and email capabilities, and a two-way multi-frequency radio system assigned to key functional groups as required (mine, processing, security, etc.).

18.8.1 Concentrator Monitoring and Control Center

The concentrator control room will serve as the center for communications, fire systems monitoring and emergencies in general. Mine security will also have redundant emergency communications. The control room will be manned on a twenty-four hour a day basis. A base station radio will be assigned to the control room as well as an outside telephone and computer-based communications. The control room operator will have the ability to communicate on all other site group frequencies.

Real time observation of strategic points within the operation will be accomplished by a TV camera system with monitors in the control room. A programmable logic controller (PLC) system will be used for stop- starts of the plant equipment. The control room will serve as the center of all control and recording of key process variables, outputs, functions and plant stoppages.

Process control and monitoring systems that provide real-time data to the operators will include, but are not limited to the following:

- Primary crusher- Crusher power draw, weigh scale on stockpile feed conveyor, appropriate metal detector and tramp iron magnets, crusher discharge hopper level indicators, etc.
- Coarse ore stockpile will have a height measuring device and the reclaim conveyor will have vendor supplied variable speed controls for each feeder.
- Each reagent system will have the ability to be batched to the necessary strength and stored until used in the plant. The delivery systems will have the ability to be measured and controlled from the plant control room.
- Grinding area- SAG Mill feed conveyor weight scale, water control to the SAG Mill that is in ratio to the tonnage rate, lime control to the SAG Mill, reagent control to the SAG Mill, pebble crusher power draw and crushed pebble conveyor weigh scale and tramp steel magnet will be included . Cyclone feed sump levels and auto water addition to the sump, pulp densities for the cyclone feed pump discharge as well as cyclone pressure is needed. The Ball Mill circuit will be monitored for mill power draw and automatic water addition at the feed end. Both grinding mills will have the vendor supplied controls, interlocks and monitors to protect the equipment.
- The copper Flotation circuit shall contain an on-stream X ray analyzer. A Particle Size Meter will also be included to measure grinding sizes for the primary cyclone overflow and the regrind cyclone overflows. Flotation sumps will have level indicators and automatic valves for water and/or reagents where applicable. Thickeners will have torque indicators with adjustable height rakes and automatic valves on the thickener underflow pumps.
- The moly plant will have a reagent delivery system that has the ability to measure and regulate reagent flows. Moly plant sumps will have level indicators and their discharge pumps will have pressure indicators. The pumps will be tied to the level indicators in their respective sumps to prevent starting in an empty sump condition.

- The copper filtering plant thickener will have a torque indicator and adjustable lift rakes. Thickener underflow and recycle systems will have automatic valves and a flow and density meter.
- Tailings and reclaim water system will have vertical pumps and will have remote start and stop control capability from the mill control room. Each pump will receive a control signal from the reclaim water storage tank. The reclaim water storage tank will have a level indicator and an automatic control on the anti-scalent addition line.

Process control and monitoring systems that monitor, measure, weigh and collect samples for assay will include, but are not limited to the following:

- A weigh scale on the coarse ore stockpile conveyor to facilitate reconciliation around mine-delivered tonnage versus tons crushed
- A weigh scale on the coarse ore reclaim conveyor for the metallurgical balance
- Automatic sample cutters will be utilized to ensure samples are taken on a regular basis and the shift composite samples will serve as a basis for the plant metallurgical balance
- Appropriate flow meters, scales and control valves will be installed where it is deemed necessary
- Before leaving the site, copper concentrate will be weighed and sampled for moisture and copper content as well as gold and silver content. A truck scale to weigh copper concentrate and truck wheel wash for environmental compliance are included in the feasibility study plans
- Molybdenum will be weighted and sampled for grade and moistures before being shipped offsite

18.8.2 Safety Systems

Safety systems will include, but are not limited to the following:

- The use of startup warnings such as horns and sirens will be used throughout the property;
- Interlock systems will be installed and maintained;
- A Sodium Hydrosulfide (NaHS) monitoring and alarm system will be installed in the concentrator;
- Fire detection and suppression systems will be installed and monitored from the mill control room and from mine security

19 MARKET STUDIES AND CONTRACTS

19.1 MARKET STUDIES

No formal market studies were undertaken in conjunction with preparation of this Technical Report.

As reported in Section 13, concentrates produced by the Copper Flat Mine are expected to be clean with no deleterious elements expected in amounts to cause material penalties. The copper concentrates are assumed to be shipped to a smelter in Asia for this report, however additional markets for the sale of concentrates exist in North America and Europe. Molybdenum concentrates are assumed to be saleable in the domestic US market. Gold concentrates are assumed to be shipped to a gold smelter/refinery for final processing.

Concentrate treatment factors used in this report have been compiled by THEMAC using public information sources. The smelter charges and payable metal used in the financial evaluation are presented in the table below.

Table 19-1: Smelter Treatment Factors

Copper Concentrates	
Payable Copper (%)	96.5
Payable Gold (%)	94.0
Gold Deduction (troy ounces per dry ton)	0
Payable Silver (%)	90.0
Silver Deduction (troy ounces per dry ton)	0
Treatment Charge	\$85.00
Refining Charge – Cu (per pound)	\$0.085
Refining Charge – Au (per troy ounce)	\$6.00
Refining Charge – Ag (per troy ounce)	\$0.50
Transportation Charges (per wet ton)	\$158.00
Moisture (%)	8.0
Molybdenum Concentrate	
Payable Molybdenum (%)	99.0
Roasting Charges (per pound)	\$1.50
Transportation Charges (per wet ton)	\$57.00
Moisture (%)	8.0

19.2 CONTRACTS

Copper Flat is presently under development and there are no sales contracts or offtake agreements for mine products currently in place. When operating, the Copper Flat mine will mine and process ores that contain copper, molybdenum, gold, and silver, which will be recovered for sale in the form of copper concentrate, molybdenum concentrate, and gravity gold concentrate as described in Section 17. Copper Flat will sell into a world market for these metals and the mine will be subject to prevailing smelting and refining costs and metal prices for the mine products. Sales contracts will be developed by THEMAC as financing for the project advances.

20 ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT

20.1 ENVIRONMENTAL STUDIES

Environmental data has been collected in the Copper Flat Mine permit area and in surrounding areas of interest since the late 1970s by various mining companies. In 2010, NMCC began planning a re-start of mining operations at Copper Flat, and the Company prepared a Sampling and Analysis Plan (SAP) for collecting environmental data at Copper Flat in accordance with 19.10.6.602.D NMAC and guidance for permitting a Part 6 New Mining Operation under the New Mexico Mining Act. Since that time, NMCC has undertaken and completed numerous environmental studies to evaluate existing conditions, predict future effects of the planned mining operation at Copper Flat, and support permitting requirements. Presented below is a list of the significant environmental studies undertaken by NMCC.

Study: Environmental Baseline **Status: Complete**

Provide data on pre-mine climate, geology, ground and surface water, vegetation, wildlife, soils, and air quality for use by all federal and state agencies in permitting process.

Study: Mine Rock Geochemistry **Status: Complete**

Provide Copper Flat mine rock characterization program and assessment of potential water quality from mine waste facilities, determine the potential for acid rock drainage and metal leaching (ARDML) from mining facilities, and perform quantitative risk assessment and evaluation of the options for design, construction, and closure of the tailings and waste rock disposal facilities.

Study: Pit Lake Characterization **Status: Complete**

Assess future pit lake chemistry associated with the Copper Flat Mine for comparison to existing pit lake water quality in order to demonstrate compliance with New Mexico Mining Act regulations "Performance and Reclamation Standards for New Mining Operations" at 19.10.6.603 NMAC.

Study: Federal Environmental Impact Statement **Status: Complete**

Analyze the potential environmental effects from the proposed Copper Flat Mine in Sierra County, New Mexico, and recommends potential mitigation measures in compliance with NEPA and the Council on Environmental Quality's regulations for implementing NEPA (40 CFR 1500–1508) and with the Secretary of the Interior's regulations contained in 43 CFR 3715 and 3809.

Study: State Environmental Evaluation **Status: Complete**

Analyze the reasonably foreseeable impacts of proposed activities on the pre-mining and post-mining environment and the local community, including other past, present and reasonably foreseeable future actions.

Study: Aquifer Pumping Test **Status: Complete**

Perform an aquifer pumping test using two of the mine site production wells to measure response at other supply wells in area to support development of a groundwater pumping and response model for the Copper Flat water supply wells.

Study: Hydrological Assessment

Status: Complete

Develop a determination of the probable hydrologic consequences of the operation and reclamation on both the permit and affected areas with respect to the hydrologic regime, quantity and quality of surface and groundwater systems that may be affected by the proposed operations (NMAC 19.10.6.602.(13)(g)(v)) of the Mining Act regulations.

Study: Biological Assessment

Status: Complete

Review, analyze, and document the direct, indirect, interrelated, interdependent, and cumulative effects on U.S. Fish and Wildlife Service (USFWS) Federally listed endangered, threatened, proposed, or candidate species as well as proposed or designated critical habitats to meet requirements of the Endangered Species Act [ESA] of 1973, 16 USC 1531 et seq.

Study: Cultural Resource Assessment

Status: Complete

Locate and assess all cultural resources and historic properties within the area of potential effects ("APE"), including historic districts, archaeological sites, isolated manifestations (IMs), historic buildings, and other objects over 50 years in age; assess each resource and historic property regarding potential eligibility for nomination to the National Register of Historic Places (NRHP); and evaluate the potential effects of the proposed mine plan on NRHP-eligible/listed resources within the APE.

Study: Waters of the US

Status: Complete

Perform field work, data collection and analysis to determine the limits of potential Waters of the U.S. (WOTUS) within the Copper Flat Project area through identification of bed and bank, and Ordinary High-Water Mark (OHWM) characteristics and calculate potential impacts on WOTUS of the proposed plan.

Study: Groundwater Test and Model

Status: Complete

Complete field measurements and project the effects to groundwater and surface water of the proposed groundwater pumping plan for the Copper Flat Mine.

Study: Stage 1 Abatement Investigation

Status: Phase 2 In Progress

Investigate and characterize existing site conditions in areas of known and potential impact from previous mining operations and collect data necessary to select and design an effective abatement option to meet requirements of NMAC 20.6.2.4106.C.

20.2 TAILING DISPOSAL AND WASTE MANAGEMENT

This report section provides a summary description of the feasibility level tailings disposal facility design. A detailed design report (Golder, 2016b) provides descriptions of the proposed facilities and supporting information used in feasibility design, engineering analysis, and cost estimation. The report is divided into two volumes. Volume 1 presents the geotechnical site exploration data and design of the TSF. Volume 2 presents the design of the tailings distribution and water reclaim systems, including the cyclone plant and associated pipelines, pumps and control systems.

A partial set of TSF design drawings is included in this technical report. The complete drawing set, including all details and sections referenced in the partial drawing set, is included in the detailed feasibility level TSF design report (Golder, 2016b).

A new tailings storage facility (TSF) will be constructed at Copper Flat in the location of the former (old) Quintana Resources facility that was constructed and briefly operated in 1981 and 1982. Existing site conditions and proposed facility locations are shown on Figure 20-1. The starter dam, splitter dike, and approximately 1.2 million tons of tailings from the Quintana operation remain on the site. Structural fill materials in the old dam and tailings will be excavated and incorporated in the new facility. The old decant system, pipeline footings, and reclaim pipelines will require demolition.

The old tailings disposal facility was designed to contain approximately 60 million tons of tailings. Recent exploration efforts have increased the ore reserve at Copper Flat to approximately 113 million tons. The new TSF will occupy the site of the old facility and will extend approximately 1,000 feet to the east of the old starter dam (the tailings expansion area). While the old Quintana TSF was an unlined facility, the new TSF will be underlain by a geomembrane liner and tailings drainage collection system.

High rates of tailings rise within the impoundment during the initial years of operation have led to adoption of a centerline construction scheme using compacted cyclone tailings sand (cyclone underflow) for tailings dam construction. This approach allows construction of a stable, drained tailings dam while reducing the quantity of fill material required for dam construction. The tailings distribution system for the new TSF will include a fixed cyclone plant. Cyclone underflow, which consists of the coarse (sand) fraction of the process tailings, will be routed to the crest of the dam and discharged on the dam crest and out-slope. The underflow on the dam crest will be compacted to a minimum of 90 percent of maximum density as determined by the American Society for Testing and Materials (ASTM) D698. Tailings slimes (cyclone overflow) will be discharged into the interior of the tailings impoundment. Periodically, when the cyclone plant is not in operation, whole tailings may be discharged into the interior of the TSF.

20.2.1 Site Description

20.2.1.1 Topography

The TSF site consists of a broad, shallow basin located at the head of a natural drainage that discharges to Grayback Wash. Elevation ranges from 5,170 to 5,435 famsl within the proposed TSF footprint. Topography is gently sloping over most of the site with the steepest slopes located around the west and southwest periphery of the facility.

Because the site is located in the head of a basin, requirements for diversion of water from upstream catchment areas will be limited.

20.2.1.2 Foundation Conditions

Silts, sands, and gravels that occur in the proposed TSF have been identified as piedmont alluvium and the older deposits of the Santa Fe Group (SHB, 1980) on which the piedmont alluvium was deposited. The Santa Fe Group is reported to consist of interfingered alluvial fan (gravel) and clay facies. Basalt flows are reported to occur in channels and arroyos cut into the piedmont and Santa Fe sediments. Basalt outcrops have been identified in an arroyo in the center of the TSF and locally around the site.

Groundwater is typically encountered at depths greater than 50 feet below the ground surface (ft-bgs) in the vicinity of the TSF. A small zone of perched water has been identified in the vicinity of the old Quintana dam; however, recent drill holes completed in the perched water area to a depth of 50 ft-bgs did not intercept water. Groundwater and local perched water are not anticipated to impact the design and operation of the TSF.

20.2.1.3 Construction Borrow Material

Potential borrow material sites outside the footprint of the proposed TSF are limited at Copper Flat. Therefore, construction materials will be borrowed from inside the TSF footprint. Materials derived from areas that will be buried early in the development of the TSF will require stockpiling for future use. In particular, topdressing, reclamation cover materials, and liner bedding fill material will require stockpiling. Proposed stockpile locations for topdressing, reclamation cover material and liner bedding fill are shown on Figure 20-1.

20.2.2 Design Studies

Design studies completed in support of the feasibility level design of the TSF include the following:

- Site exploration and geotechnical testing
- Tailings characterization
- Foundation settlement potential evaluation, and
- Consolidation modeling and storage capacity estimation

20.2.2.1 Site Exploration

Golder conducted a site exploration study between December 2012 and January 2013 to expand the coverage of the former SHB site investigation to include the new dam alignment and footprint area. The field study consisted of 31 test pit excavations and 28 drill holes completed in the TSF footprint and waste rock disposal facilities area. The site exploration plan is illustrated on Figure 20-2. Figure 20-3 illustrates cross sections through the foundation of the proposed tailings dam.

Drill hole logs indicate that the foundation in the tailings area consists primarily of alluvial deposits that including silt, sand and gravel underlain by clay. In the northwestern waste rock area, borings indicated the presence of gravelly silts and sands overlying conglomerate consisting primarily of andesite clasts. The conglomerate is underlain by unweathered andesite.

Drilling logs and geologic cross-sections indicate a high degree of variability in near surface materials both vertically and laterally, within the impoundment area and beneath the proposed dam. Silty/clayey horizons alternating with gravelly sand layers could potentially represent either the interfingering of the Santa Fe Group facies, or the more recent effects of local erosion and deposition.

In general, the interior of the impoundment is underlain by silty, clayey and gravelly sand, and cemented gravelly sand with a near surface layer of silty, wind-blown material. Eastward, toward the future dam site, interbedded clays and silts occur at depths typically greater than 20 feet; however, the composition of the foundation remains highly variable with interfingering, silty, sandy and clayey gravel units.

20.2.2.2 Geotechnical Testing

A detailed description of the geotechnical testing program is contained in *Feasibility Study Copper Flat Project, Sierra County, New Mexico, Volume 1-Tailings Storage Facility* (Golder, 2016b).

Within the interior, central, and western portions of the impoundment area, site soils consist predominantly of clayey sand with gravel (SC), well-graded silty sand with gravel (SW-SM) with lesser clayey and well-graded silty gravel (GC, GW-GM). Silty and clayey soils (CL-ML) locally occur.

The north cell of the old Quintana TSF contains tailings from mining conducted in the early 1980's. Old tailings samples were classified as silty sand (SM) and low plasticity silt (ML). Moisture content in the old tailings samples ranged from 6.0 to 11.3 percent.

Soils encountered in the footprint of the proposed dam are highly variable. Clayey sand and gravel (SC,GC) generally occur at shallow depth with interbedded high and low plasticity clays (CH,CL) and silts (ML,MH) occurring at depths below 20 ft-bgs. Clay intercepts indicate that the clay occurs in discontinuous lenses or in eastward dipping strata.

20.2.2.3 Tailings Characterization

Tailings properties used in feasibility level design are based on testing of a tailings sample produced by the Mineral Advisory Group (MAG) in Tucson, Arizona. Approximately 255 kg of Copper Flat flotation tailings solids (whole tailings) were provided by MAG in five sealed 55-gallon steel drums. Drums were delivered to the FLSmidth laboratory in Tucson, Arizona in July 2012 and the tailings were passed through a gMAX15U-20 cyclone on August 4, 2012. The test indicated a sand recovery of 41 percent with a minus 75-micron fraction under 16 percent. On the basis of the cyclone test, FLSmidth, using proprietary procedures, predicted 45 to 45.5 percent recovery and a minus 200 fraction of 18.2 to 18.3 percent for cyclone plant performance over the range of proposed design processing rates.

Cyclone underflow and overflow produced during the test and whole tailings (tailings not passed through the cyclone) were shipped to Golder's geotechnical laboratory in Lakewood, Colorado for testing. Gradation analyses were completed on the cyclone underflow, cyclone overflow and whole tailings. The cyclone overflow and whole tailings were subjected to flume testing to simulate discharge into the impoundment.

Flume testing involved the discharge of tailings slurry at the field anticipated solids content into a 12-inch flume at low velocity. The tailings flow down and settle in the flume. Samples were collected at various flume locations to evaluate changes in gradation and solids content. Gradation and slurry consolidation tests were conducted on samples from the head and tail sections of the flume to evaluate the characteristics of tailings found on the beach and in the interior of the impoundment (slimes).

Tailings characterization study results are presented in detail by Golder (Golder, 2016b). Test data were used to evaluate consolidation characteristics and evaluate storage capacity requirements.

20.2.2.4 Settlement Potential

Selected foundation samples were remolded to match field density and moisture content conditions and subjected to conventional one-dimensional consolidation testing to support estimation of settlement potential in the proposed dam foundation. Samples were selected to evaluate silty and clayey horizons where changes in loading conditions could result in additional consolidation.

Settlement prediction conservatively based on the laboratory consolidation testing of the fine fraction of remolded foundation samples indicates that the maximum settlement beneath the embankment will be approximately 2.1 feet in the area of the maximum dam (and tailings beach) foundation loads. Settlement decreases at a relatively uniform rate as the weight of post-construction loading decreases towards the outer toe of the embankment.

SPT testing conducted during drilling showed the foundation strata to be generally very dense to hard. On the basis of SPT test results, actual post-construction consolidation settlement of less than 1 foot is anticipated.

Dam construction will be more or less continuous during the life of the facility. The effects of foundation settlement include the potential for the loss of dry freeboard for stormwater storage. The potential loss of freeboard can be mitigated by elevating the dam crest with managed/targeted placement of cyclone underflow sand.

The potential for differential settlement that could impact the integrity of the TSF geomembrane liner was evaluated. The analyses indicate settlement will vary uniformly across areas subject to changing foundation loads and concerns related to liner foundation settlement were not identified.

The impoundment underdrain will pass beneath the dam in a steel pipe placed in a ditch backfilled with concrete. The settlement will not adversely impact the impoundment underdrain outlet pipe. There is adequate grade and elevation change along the outlet pipe alignment to accommodate predicted settlement.

A basalt outcrop identified by SHB (SHB, 1980) may lie beneath or in the vicinity of the impoundment underdrain pipe inlet near the upstream toe of the dam. The outcrop occurred in an area that was disturbed during Quintana dam construction activities and was not observed during the recent site exploration. If the inlet to the underdrain pipe bears on basalt, local differential settlement could occur along the pipe alignment, which could induce stress on the outlet pipe. If, during construction, a basalt outcrop is identified at the location of the inlet, an alignment change may be warranted to avoid having the outlet pipe bear on basalt.

20.2.2.5 Tailings Consolidation Analyses

Estimation of tailings consolidation rates was performed using the computer program FSConsol (Golder 2016b). FSConsol performs a one-dimensional, large-strain consolidation analysis using finite strain consolidation theory.

Material parameters were determined by fitting constitutive relationships to laboratory data. Data are based on slurry consolidation testing of whole tailings and cyclone overflow samples derived from the head and tail sections of a test flume discussed above.

The tailings impoundment was modeled by running analyses on single tailings columns or volumes filled with materials representing either the beach or slimes components of the tailings discharge. In each model run, the modeled tailings component is assumed to represent 100 percent of the inflow to the TSF.

Modeled tailings components include the following:

- Cyclone overflow beach; and
- Cyclone overflow slimes.

Because near constant operation of the cyclone plant will be required to generate sufficient sand for dam construction, whole tailings discharge into the impoundment will be limited and the characteristics of the whole tailings is expected to have little influence on post depositional tailings behavior.

If 100 percent of the inflow into the TSF impoundment is represented by the tail section flume samples (i.e., the finest fraction of the tailings), the predicted final density of the slimes fraction over the modeled profile will average approximately 31.7 pcf. With 100 percent of the inflow representative of tailings overflow beach materials, the modeling predicts a final average tailings density of approximately 74.6 pcf.

20.2.2.6 Estimation of Post-Deposition Density

Tailings density will vary with depth and location in the TSF interior. The highest density will be associated with desiccated tailings on the drier sections of the beach. Intermediate density is reflected by the FSConsol model of the cyclone underflow deposited on the beach. The consolidation modeling indicates the lowest density of 31.7 pcf is predicted for tailings representative of the slimes.

A solids mass balance was performed to assist in estimating relative proportions of tailings representative of beach and slimes components. Based on the sand and slimes (minus 75 micron) fractions of the cyclone overflow and the head and tailings section test flume samples, approximately 60 percent of the sand and slimes contained in the cyclone overflow reported to the flume head section, suggesting a 60:40 split between materials representative of the beach and slimes, respectively.

TSF capacity has been estimated by assuming a 60:40 split by mass between beach and slimes material. Volumetrically, the slimes will represent approximately 60 percent of the material placed in the TSF. The estimated average dry density of the tailings at the end of the mining operation is 48 pcf. The calculated TSF storage capacity is

approximately 96.9 million cy. Without consideration of managed deposition effects that can be anticipated to increase post deposition density, the required storage capacity is 93.4 million cy, assuming the cyclone plant is fully utilized.

Operational processes such as cycling discharge locations and minimizing the size of the free water pond will have the effect of increasing post deposition density. Realization of a higher than estimated post-deposition density as a result of operational factors may allow a lower final dam crest elevation, a reduction in sand required for embankment construction and lower utilization of the cyclone plant.

20.2.3 Design Criteria

Table 20-1 summarizes key design criteria assumed in feasibility level design of the new TSF.

Table 20-1: Design Criteria

Regional Design Factors	
Precipitation/Evaporation	Based on NOAA weather data for Hillsboro and Caballo Dam, New Mexico
Design Storm Events	100 percent of the 72-hour general storm probable maximum precipitation (PMP), 26 inches
Stability FOS	Minimum 1.5 for static conditions and 1.1 for seismic loading conditions
Seismicity PGA	USGS MDE, 2475-year return period, 0.13 times gravitational acceleration (0.13g)
TSF Design Factors	
Storage Capacity	112 million tons (net to tailings, NMCC)
Production Schedule	1,333 to 1,222 tpd (net to tailings NMCC)
Operating Life	11.1 years (NMCC)
Tailings Specific Gravity	2.64 (Golder test)
Tailings Solids Content (wt%)	29.1 percent solids by weight (whole tailings to cyclone plant), (M3)
Tailings post-deposition dry density	31.7 to 74.6 pounds per cubic foot (pcf) dry weight assumed for post-deposition cyclone overflow and beach and slimes. 92% of standard ASTM 698 maximum dry density (0.95*97 pcf= 92.2 pcf) for cyclone underflow sand. Sand compacted on dam crest. Self-weight compaction on the dam outslope.
Embankment Construction	Phase 1 earthen starter dam to elevation 5,250 feet with extensions to 5,280 feet. Post Phase 1 peripheral earthen dam extension constructed to 10 feet above grade. Centerline-raise construction using cyclone underflow sand. Cyclone underflow on dam crest compacted to minimum of 90 percent of American Society for Testing and Materials (ASTM) D698, relative density > 60 percent
Liner System	From bottom to top: Prepared foundation, 12-inch liner bedding fill, 80-mil HDPE geomembrane, overliner drainage collection layer with internal drainage pipe network beneath the tailings embankment and continuous beneath impoundment
Earthworks Slopes (assumed)	Soil cut slopes = 1.5H:1V (1.5 horizontal to 1 vertical) Rock cut slopes = 1H:1V Fill slopes = 2H:1V Lined slopes = 3H:1V to 2.5H:1V max Embankment out-slope = 3.2H:1V max, 4H:1V min Starter Dam, 2.5H:1V inner, 2H:1V outer
Drainage/Seepage Collection Pond	Double-lined pond with LCRS to contain dam and impoundment under drainage and surface water runoff. Pond to be constructed as an OSE non-jurisdictional facility.
Seepage Collection Pond Reclaim	Submersible turbine pumps with 3,267-tph (tons per hour) capacity
Collection Pond Capacity	Normal inventory, 24 hours reserve capacity for underdrain seepage for reclaim pump system upset, 100-year, 24-hour event (3.73 inches) stormwater storage capacity for runoff contributing areas

Tailings Management	Tailings routed through fifteen 15-inch cyclones at 88 tph feed rate per cyclone. 45.5 percent solids recovery (underflow, Krebs), minus 200 fraction in underflow less than 20 percent (Golder). Cyclone overflow discharged to tailings impoundment interior. Whole tailings discharged to TSF interior when cyclones not in operation.
Supernatant Reclaim	Floating barge with 3,267 tph capacity
TSF Water Storage and Stormwater Diversion Design Factors	
Dam Safety Hazard Ranking	Significant, due to environment risks associated with a release of tailings (OSE)
TSF Pond Design Freeboard	As required to accommodate wave run-up and provide minimum freeboard for design storm
TSF Pond Required Stormwater Storage	Contain flows from 1.0 times the 72-hour PMP storm event plus normal inventory of supernatant water
Hydrology Runoff Curve Numbers	100 - Impounded tailings and lined areas 50 - Tailings embankment sand shell 92 - Native ground surfaces
Stormwater Diversion	Divert runoff from undeveloped areas inside ultimate footprint where feasible. Divert exterior area runoff where feasible.
Underdrain System	Continuous underdrain layer beneath dam and TSF interior. Collected water will be returned to the process via seepage collection pond reclaim pump system
TSF Water Pond Surface Area	20 percent of tailings impoundment interior or a maximum of 40 acres assumed for feasibility level water balance calculations
TSF Water Pond Surface Evaporation	75 percent of average pan evaporation
Tailings Surface Evaporation	50 percent of average pan evaporation over wetted surface area

Notes:

FOS = factor of safety

MDE= maximum design earthquake

PGA = peak ground acceleration

HDPE = High density polyethylene

20.2.4 Permitting Authorities

The new TSF design will be required to comply with the design and dam safety guidelines and regulations of the OSE Dam Safety Bureau. The NMED Groundwater Division will be the permitting authority for the State of New Mexico discharge permit program. NMED has provided guidance on anticipated design requirements for the impoundment liner system, which have been incorporated in the feasibility level design.

20.2.5 Earthworks and Liner Construction

20.2.5.1 Topdressing and Reclamation Cover Removal

The majority of the materials that will be required to support revegetation and reclamation efforts will be obtained from within the footprint of the new TSF. Based on requirements at operating mine sites in New Mexico, it is anticipated that up to 3 feet of reclamation cover will be required for TSF closure. The grading plan incorporates borrowing and stockpiling of sufficient topdressing and cover material to establish a three-foot-thick reclamation cover over the tailings dam and impoundment.

20.2.5.2 Site Grading

The TSF grading plan is illustrated on Figure 20-4. The topography represented on the grading plan illustrates the TSF area following removal of borrow materials for reclamation cover, structural fill and drain construction.

Site grading will include removal of the old starter dam and splitter dike for use as structural fill in the new starter dam and toe berm. Additional borrowed structural fill and drainage material will be required to complete construction of the new TSF. These materials will be borrowed from within the TSF footprint. Borrow areas developed during phased construction will extend across construction phase limits but will lie within the ultimate TSF footprint.

It is assumed that existing tailings will be excavated and used in construction of the bedding fill layer for the TSF geomembrane liner. Use of the existing tailings as liner bedding fill will effectively cap the old tailings and mitigate long term impacts to ground water by controlling seepage through the old tailings and leaching of soluble constituents. The proposed handling of the old tailings has been discussed with NMED and has received tentative approval.

20.2.5.3 Starter Dam and Toe Berm

Phase 1 grading and starter dam construction are illustrated on Figure 20-5. The ultimate configuration of the tailings dam is shown on Figure 20-6. Dam sections are shown on Figure 20-7.

A temporary toe berm will be constructed around the periphery of the TSF. The purpose of the toe berm is to direct dam underdrainage and dam surface water runoff to the seepage collection pond. The toe berm will be relocated during each construction phase, and the dam underdrain will be extended to the new toe berm. Where the tailings dam will butt against inward sloping natural ground on the southwest and west periphery, a toe berm will not be required. In these locations, the TSF liner system will be anchored in a trench excavated in natural ground.

The Phase 1 starter dam will be constructed to an elevation between 5,250 and 5,280 famsl with 2.5H:1V inner slope and a 2H:1V outer slope. The upstream face of the starter dam will be lined with 80 mil HDPE geomembrane. The starter dam will be constructed over the impoundment liner, and underdrain collection systems. In Phases 2 through 5, starter dam extensions will be constructed to a height of 10 feet over the liner surface.

20.2.5.4 TSF Liner System

The design includes a composite liner system with a continuous overliner drainage layer (underdrain). The liner will consist of an 80-mil high density polyethylene (HDPE) geomembrane placed on a 12-inch thick liner bedding fill layer. In Phase 1, the liner bedding fill will consist of a minimum of 12 inches of tailings recovered from the north cell of the old dam. Post Phase 1, liner bedding fill will consist of a 12-inch layer of selectively borrowed native material or crushed and screened native material.

20.2.5.5 Tailings Drainage

The tailings underdrain system is shown on Figure 20-8. Drainage from future tailings will be collected in two separate underdrain systems and routed to the seepage collection pond. Drainage from the impoundment interior will be collected in a continuous underdrain constructed over the geomembrane liner. A separate blanket drain will underlie the tailings dam (dam underdrain).

The impoundment underdrain will consist of an 18-inch thick layer of select native drain fill material with an internal drainpipe network of 4-inch diameter drainage laterals spaced 35 feet apart. The lateral drainpipe will be Type N-12, perforated corrugated polyethylene pipe (PCPE). The lateral drainage network will route drainage to 10-inch diameter type N-12 PCPE primary drainage pipes. The primary drainpipes will be placed within an envelope of primary drain fill produced by crushing and screening of local gravelly soils.

The impoundment underdrain flow will be routed through a 14-inch diameter schedule 80 steel pipe where the system passes beneath the tailings dam to the discharge at the seepage collection pond. During initial operations, the impoundment underdrain may be exposed to standing water prior to its burial with tailings slimes. To control the water level in the seepage collection pond, impoundment underdrain outlet to the seepage collection pond will be fitted with a shutoff valve so that the drain flow can be slowed or stopped as needed to maintain stormwater storage capacity in the seepage collection pond.

The dam underdrain will consist of an 18-inch thick layer of primary drain fill placed on the geomembrane liner with an internal drainpipe network of 4-inch diameter Type N-12 PCPE pipes to route dam drainage to the toe of the dam and the seepage collection pond. The dam underdrain pipes will be placed at a spacing of 45 feet. In the later construction phases, 10-inch diameter Type N-12 PCPE drainage pipes will be installed. No valves or shut-off will be included in the dam underdrain.

20.2.5.6 Seepage Collection Pond

The location of the seepage collection pond plan is shown on Figure 20-9. The seepage collection pond will be a lined with 60-mil lower and 80-mil upper HDPE geomembranes. An HDPE drain net will be placed between the liners to serve as the seepage collection pond leakage collection and recovery system (LCRS) and minimize hydraulic head on the lower pond liner. The pond will be fitted with a sump filled with drain material and LCRS pump to recover leakage through the upper geomembrane.

The seepage collection pond will contain seepage from the impoundment underdrain and the dam underdrain, as well as runoff from the downstream face of the tailings dam. The pond is sized to contain 24 hours of seepage flow at the maximum estimated drainage and seepage rates, as well as runoff incident on the downstream dam face from the 100-year, 24-hour storm event of 3.94 inches (Golder, 2016b). The required capacity is approximately 6.3 million gallons. As shown, the capacity of the seepage collection pond is approximately 9.8 million gallons with 2 feet of dry freeboard and dead storage. The pond can be used to store up to 3.5 million gallons of fresh make-up water during start-up, if needed, while maintaining capacity for stormwater storage and TSF drainage.

20.2.6 Tailings Transport and Distribution

20.2.6.1 System Components

The tailings distribution system consists of a cyclone plant, a cyclone underflow distribution system, a cyclone overflow distribution system, an emergency pond, and a pump equipment pad. The purpose of the emergency pond is to allow drainage of sumps and pipelines during upset conditions. It provides emergency storage for up to 1.0 hours of the full whole tailings discharge from the flotation plant plus additional capacity for twice the volume of solids and water contained in all pipes and sumps that drain to the cyclone station. The design of the cyclone plant and tailings distribution system is presented by Golder (Golder, 2013).

The general plan of the cyclone plant and emergency pond area is shown on Figure 20-10. The tailings delivery and distribution system are shown in the plan on Figure 20-11. Figure 20-12 is the process flow diagram for the tailings distribution and water reclaim systems (Golder, 2013). The water reclaim system piping plan is presented in Figure 20-13.

20.2.6.2 Operating Description

Tailings will be obtained from a sump located at the flotation plant and transported by gravity flow to the cyclone plant. The maximum feed to the cyclone plant will be 1,333 tons per hour (tph) of tailings solids in 29.1 weight percent slurry at a total flow rate of 13,276 gpm. Cyclone underflow will be delivered to the TSF and used for dam construction. The cyclone overflow will be routed to the interior of the TSF in a separate piping system. The cyclone plant will recover up to 45.6 percent of the tailings stream and produce an underflow slurry (sand) with a solids content of 70 weight percent. Delivery of the cyclone underflow sand will require pumping through the life of the facility. The cyclone overflow will have a solids content of approximately 19.5 to 19.6 percent by weight and slurry water will have a delivery rate of approximately 11,940 gpm.

Two cyclone underflow pipelines will be used to deliver sand to the dam. The one leg will run around the north side of the TSF, and one leg will be routed around the south side of the TSF. Each leg is sized to transport 100 percent of the cyclone underflow. This allows for continuous availability of sand delivery to the dam through either or both legs.

Cyclone underflow sand will be discharged through 4-inch spigots placed every 333 feet. Each spigot will include one 4-inch manual pinch valve. The underflow pipelines will also have in-line knife-gate isolation valves every 2,000 feet to allow for isolation and relocation of the pipe as the dam rises. The knife-gate isolation valves will be quick-disconnect with hydraulic actuators powered by a mobile hydraulic power unit mounted on a pick-up truck.

Two cyclone overflow delivery pipelines, one leg to the north side and one leg to the south side of the TSF, will transport the cyclone overflow to the TSF interior (impoundment interior). The cyclone overflow will be discharged via spigots placed every 667 feet. Each spigot will include a manual pinch valve. Each cyclone overflow pipe is sized to carry 100 percent of the cyclone overflow to permit pipeline relocation without interrupting operation as the TSF elevation rises. One leg will remain active while the other is serviced or relocated.

The cyclone overflow pipelines will also have knife-gate isolation valves placed every 2,000 feet to allow for isolation and relocation of the pipe as the impoundment rises. The knife-gate isolation valves will be quick-disconnect with hydraulic actuators powered by a mobile hydraulic power unit mounted on a pickup truck.

When the cyclone plant is not in operation, whole tailings will be discharged to the impoundment interior through the cyclone overflow distribution system. Due to the requirements for sand to construct the dam, near constant operation of the cyclone plant will be required. As such, the mill and processing facilities should not be operated unless the cyclone plant is in operation, and cyclone plant maintenance should be undertaken when the mill and processing facilities are down for maintenance. Filling rates and tailings post depositional behavior should be observed during operations. If actual consolidations rates exceed predicted rates, it may be possible to reduce utilization of the cyclone plant and allow periodic deposition of whole tailings into the TSF.

20.2.6.3 Dam Construction

Based on cyclone testing and operational simulations, a maximum of approximately 50 million tons of tailings sand can be produced over the life of the mine. Assuming an underflow post placement dry density of 89.24 pcf (equivalent to 92 percent of the ASTM D698 maximum dry density of 97 pcf) up to 42.3 million cy of sand will be produced. Approximately 39.6 million cy of underflow will be required to construct the sand embankment to an elevation of 5,460 feet. Producing sufficient sand for dam construction will require near constant operation of the cyclone plant.

During operations, 10 feet of freeboard will be maintained from the top of the tailings beach to the crest of the dam. When sand is not required on the crest of the dam, it should be placed on the dam out-slope. Failure to utilize all available sand for dam construction could result in loss of storage capacity in the later years of operation.

Sand line spigots will be used to deposit the cyclone underflow on the dam crest or in paddocks (bermed areas), or on the outer slope of the sand dam. It is anticipated that sand placed on the dam crest will be spread and compacted. Sand placed on the embankment out-slope and in paddocks will be subject to self-weight compaction. All underflow sand is anticipated to require dozer spreading and grading.

20.2.7 Process Water Reclaim

The process water reclaim system is illustrated Figure 20-13 and will recycle water from two collection sources: the seepage collection pond and the supernatant pool. The TSF reclaim system in the seepage collection pond will consist of submersible turbine pumps placed in a reinforced concrete sump. The sump floor will be recessed below the pond floor to reduce dead storage. The submersible turbine pumps will be capable of completely draining the seepage collection pond.

Process water collecting on the top surface of the TSF will be recycled through barge-mounted pumps placed in the supernatant pool. The barge will be accessed from a ramp constructed with borrowed fill or waste rock. The barge will migrate westward and upward parallel to the access ramp as the tailings surface rises.

Reclaimed water will be returned to the process water reservoir. Reclaim pump capacity will be 13,500 gpm from the TSF barge and 4,000 gpm from the seepage reclaim pond. The TSF barge reclaim rate is approximately equivalent to the maximum rate at which process water will be delivered to the cyclone plant when the mill is in operation. In the event of a significant storm event where excess stormwater is in storage, delivery of water from external sources can be suspended and stormwater contained in the TSF and seepage collection pond can be returned to the process facilities and consumed as bound water in the tailings or lost to evaporation.

20.2.8 Water Balance

Figure 20-14 summarizes the results of a water balance analysis of the proposed TSF for average rainfall conditions. The water balance model incorporates water input from slurry water inflow, direct precipitation on the impoundment surface and run-on from minor undiverted areas located around the periphery of the facility. Onsite pan evaporation data were used to estimate evaporative losses. Because the in-site evaporation pan was not operated between December and March, evaporation data for winter months were estimated from Hillsboro, New Mexico evapotranspiration (ET₀) estimates. Missing winter evaporation data are based on the ratio of site to Hillsboro, New Mexico evaporation for months when data are available from both sites. NOAA data from Hillsboro and Caballo, New Mexico were used to estimate monthly precipitation.

Water balance model losses include entrainment of water with the tailings solids, evaporation from the exposed tailings beach, evaporation from the supernatant pool, and evaporation of water from the cyclone underflow paced on the surface of the dam. Entrainment represents the most significant water loss and is estimated on the basis of the final, post deposition dry density for cyclone underflow and overflow

On average, approximately 12,000 to 13,000 gpm of water will be delivered to the TSF with the cyclone overflow and underflow. As shown in Figure 20-14, estimated average process water recovery rate is 9,215 gpm. The estimated average make-up water requirement will be approximately 3,169 gpm over the life of the project.

As noted above, the water balance examines reclaim rates for average rainfall conditions. If the site experiences periods where precipitation rates vary from average conditions, reclaim rates and make-up water requirements can also be expected to vary. The water reclaim system is capable of recovering water at a rate adequate to meet make-up water requirements and temporarily reduce demand on external water sources. The water balance does not consider additions from the open pit or waste rock disposal facility stormwater ponds.

20.3 WASTE MANAGEMENT

20.3.1 Mine Waste Rock

Three stockpiles for storage of waste rock mined from the open pit are included in Independent Mining Consultants (IMC) mine designs. The final embankments of the stockpiles are built out at a 3:1 overall slope with periodic setbacks to facilitate reclamation grading. Additional description of the design, layout, and advancement of the facilities is provided in Section 16 (Mining Methods).

Interceptor ditches and berms will be constructed upslope from the stockpiles to limit the run-on of stormwater. Runoff and sediment collection ditches and water impoundments will be constructed at the bottom of the stockpiles to collect and contain stormwater coming from the top and sides of the stockpiles. The stormwater impoundments are designed to fully contain the runoff volume associated with a 100-year, 24-hour storm event and the impoundments will be lined to meet state regulations regarding impacted stormwater. Stormwater collected in the impoundments will be pumped to the process water circuit for re-use.

NMCC operating plans include procedures to identify and manage potentially acid generating (PAG) waste rock from the open pit, which are described in the Copper Flat Mine Operating and Reclamation Plan (MORP) (NMCC, 2016). PAG waste will be identified in the pit using a combination of visual and analytical procedures. After identification, the material will be placed in designated areas the stockpile that become fully encapsulated in all directions by naturally buffering waste rock.

After mining, the stockpiles will be re-graded and erosion control features installed. After grading, top surfaces and banks of the stockpiles will be covered with a soil cover designed to limit water infiltration into the waste rock and vegetation established to meet agency approved reclamation designs. After closure, runoff from the reclaimed stockpiles will be non-impacted stormwater and stormwater collection ditches and impoundments will be regraded and reclaimed to allow positive drainage.

20.3.2 Hazardous Materials and Petroleum Products

The term “hazardous materials” is defined in 49 CFR§171.08 and hazardous substances are designated in 40 CFR§302.4 and the Comprehensive Environmental Response, Compensation, and Liability Act (CERCLA) as amended by the Superfund Amendments and Reauthorization Act (SARA) Title III. Wastes generated under the process of mining at Copper Flat are classified as special non-hazardous wastes under the federal Bevill Exemption (40 CFR§261.4(b)(7)). NMCC Title 20 regulations detail the design criteria for secondary containment and leak detection on new above ground storage tanks (ASTs) and pipelines.

Hazardous materials will be transported to the Copper Flat Mine by DOT regulated transporters and stored on site in DOT approved containers. Spill containment structures will be provided for storage containers. Hazardous materials that do not meet the criteria of the Bevill exemption will be managed in accordance with regulations identified in 40 CFR § 262 Standards Applicable to Generators of Hazardous Waste.

Hazardous materials and substances that may be transported, stored, and used at the Copper Flat Mine in quantities less than the Threshold Planning Quantity (TPQ) designated by SARA Title III for emergency planning will include blasting components, petroleum products, and small quantities of solvents for laboratory use.

Blasting components, including ammonium nitrate and diesel fuel, will be stored onsite in bins and tanks (see above), respectively. THEMAC currently anticipates utilizing two explosives magazines (one for boosters and one for blasting caps), each no larger than 8 ft × 8 ft, with 1,000-pound capacities. In addition, THEMAC will utilize one, 75-ton capacity, 3,000 ft³ silo for storage of ammonium nitrate. All explosive materials will be stored away from the plant site in

compliance with MSHA, New Mexico State Mine Inspector's regulations, and U.S. Department of Homeland Security requirements. Management of hazardous materials at the Copper Flat Project will comply with all applicable federal, state, and local requirements as appropriate, including the inventorying and reporting requirements of Title III of CERCLA, also known as the Emergency Planning and Community Right to Know Act.

All petroleum products, kerosene, and reagents used at the mine will be stored in above ground tanks within a secondary containment area with a usable containment volume that is at least 110 percent of the volume of the largest vessel in the area.

Hazardous wastes other than those from the laboratory will be managed in a short-term storage facility prior to shipment to an offsite licensed disposal facility. These materials may include waste paints and thinners. Spent solvents and used oils will be returned to recycling facilities. Waste oil and lubricants will be collected and hauled offsite by a buyer/contractor for recycling. Solvents will be collected by a subcontractor and recycled offsite.

Laboratory wastes will be generated by an on-site assay laboratory. Laboratory reagents and waste will be stored in approved containers like other wastes and periodically recycled back into the mill process stream.

An ongoing inventory of all materials used at the mine site and mill will be provided on a monthly basis to the appropriate federal, state, and local regulatory agencies. The local fire department will be kept informed about materials stored onsite and appropriate emergency response. THEMAC does not intend to dispose of any hazardous materials or petroleum products on-site.

20.3.3 Wastewater Treatment

A packaged wastewater treatment plant will be installed at the mine to accommodate wastewater generated from the mine office, shower, and rest room facilities. The design capacity of the treatment plant is based on the expected peak shift headcount plus an allowance for contractors and visitors. To accommodate this loading, a 10,000 gallon per day plant has been selected based on 200 people per day generating 50 gallons per day per person. The plant will generate effluent treated to secondary treatment levels, which will be directed to the lined tailings storage facility for recycling back to mill through the process water reclaim system.

20.3.4 Solid Waste Disposal

Nonhazardous solid wastes generated by the mine include paper, cardboard, wood, scrap metal and other domestic trash. NMCC will implement and maintain a recycling program to reduce the amount of material requiring disposal in a landfill for disposal. Nonhazardous solid wastes that cannot be recycled will be placed in a permitted on-site Class III sanitary landfill on private land or by other methods approved by the State and Sierra County.

20.3.5 Spill Contingency Plan

A Spill Contingency Plan (SCP) has been prepared pursuant to Title 43, Part 3809 of the Code of Federal Regulations (CFR), which requires inclusion of a formal SCP in the Plan of Operations for mining operations. The SCP establishes procedures for response to oil, fuel and hazardous material spills, including control, cleanup and reporting in order to limit the potential for impacts from spills of oil, fuel, oil-related products, and hazardous substances to the environment.

The SCP is included with the Federal 3809 Plan of Operations filed with the BLM (NMCC, 2019b). The plan is distributed to site personnel and used as a guide in the training of employees. The plan addresses mitigation of potential spills associated with existing and planned project activities as well as activities of onsite contractors. The use, transportation, and storage of reagents and fuels is covered in the plan. The emergency reporting procedures are posted in key locations throughout the project area.

20.4 PERMIT STATUS

The mining and environmental permits issued for the 1982 Quintana Mine have expired or have been closed and require replacement with new permits. Table 20-2 lists the major permits and approvals needed for the Copper Flat Mine along with status of each as of the effective date of this report.

Table 20-2: Major Permits and Approvals Required for the Copper Flat Mine

Permit/Approval	Authority	Status
Federal Permits and Approvals		
Environmental Impact Study	US Bureau of Land Management (BLM)	<u>Complete</u> Final EIS issued April 2019; BLM Record of Decision approving the alternative that conforms to NMCC's Copper Flat Operating Plan issued August 2019
Biological Opinion	US Fish and Wildlife Service	<u>Complete</u> USFWS Consultation completed and biological opinion issued February 25, 2019. BO included with FEIS-ROD.
Cultural Resource Inventory and Protection Plan	US Bureau of Land Management (BLM)	<u>Complete</u> Field surveys and 3 rd Party consultations complete. Programmatic Agreement for the Copper Flat Mine signed with BLM and state agencies December 2016. Field plan prepared and ready to submit/implement ahead of construction
Clean Water Act Permit	US Army Corps of Engineers (ACOE)	<u>Complete</u> Approval under Nationwide Permit 44 (Mining) issued February 2020.
43 CFR 3809 Plan of Operations (POO)	US Bureau of Land Management (BLM)	Plan of Operations reflecting EIS approved alternative complete and submitted to BLM; approval expected with completion of financial assurance plan.
Reclamation/Closure Plan and Financial Assurance	US Bureau of Land Management (BLM)	BLM is cooperating agency with State Agencies. BLM has accepted plan, assumptions and cost calculations. Final approval pending Agency approval of financial assurance plan.
National Pollutant Discharge Elimination System (NPDES)	US Environmental Protection Agency (EPA)	Initiate with construction decision.
Mine Registration	Mining Safety and Health Administration (MSHA)	Initiate with construction decision.
FCC License	Federal Communications Commission (FCC)	Initiate with construction decision.
Explosives Permit	Bureau of Alcohol, Tobacco, and Firearms (BATF)	Initiate with construction decision.
State Permits and Approvals		
Air Quality Permit	NMED Air Quality Bureau	<u>Complete</u> New Source Permit 0365-M3 issued June 2013.
Groundwater Discharge Permit	NMED Groundwater Bureau	<u>Complete</u> Groundwater Discharge Permit issued December 2018.

Stage I and Stage II Abatement Plans	NMED Groundwater Bureau	<u>Complete</u> Requirement satisfied by rolling conditions into DP-1840
Cultural Resource Inventory and Protection Plan	NM Department of Cultural Affairs - State Historic Preservation Office	Field surveys and 3 rd Party consultations complete. Programmatic Agreement for the Copper Flat Mine signed with BLM and state agencies December 2016. Field plan prepared and ready to submit/implement ahead of construction
State Highway Use Authority	NMDOT	<u>Complete</u> Transportation and road engineering studies complete and MOU regarding protections for State Highway 152 executed with NMDOT in July 2018
Mine Operating Permit	NMEMNRD Mining & Minerals Division (MMD)	Permit Application Package considered approvable in July 13, 2018, letter from Agency; financial assurance plan started. Agency Order reopening technical review and suspending financial assurance review issued March 31, 2020.
Reclamation/Closure Plan and Financial Assurance	NMEMNRD MMD & NMED	Cost estimate presented to Cooperating Agencies; agencies advise NMCC response to technical questions satisfactory and no additional technical comments. NMCC developing options for establishing reclamation bond. Agency Order reopening technical review and suspending financial assurance review issued March 31, 2020.
Water Supply	NMOSE	Acquired 861 acre-feet (AF) of perfected water right for mining use in Aug 2018. Lease executed Mar 2019 for 2400 AF; application accepted by OSE December 2019. Additional sources identified and negotiations ongoing.
New Dam Permit (TSF)	NMOSE Dam Safety Bureau	Initiate with TSF detail design
Mine Registration	NM EMNRD	Initiate with construction decision.
Landfill Permit	NMED Solid Waste Bureau	Initiate with construction decision.

Work to obtain a mining permit from the NM Mines and Minerals Division (MMD) is ongoing. The Copper Flat Mine is being permitted as a new mine under Part 6 of the New Mexico Mining Regulations, which are administered by MMD. The NMCC permit application package, which includes construction, operation, reclamation and closure plans was determined to be approvable by the Agency in a July 13, 2018 letter to NMCC. Following that letter, MMD provided the Company with a status letter on December 21, 2018, in which the Agency acknowledged significant progress by the Company towards fulfillment of permit requirements and identified the remaining steps to be completed for a mine permit:

- 1) Completion of the Hearing Officer's report on the October hearing. This report was completed and submitted to MMD in December 2018, and subsequently posted on the MMD website for public review,
- 2) Completion of a financial assurance plan with approval and acceptance by MMD, NMED and the BLM ("FA Agencies"),
- 3) MMD's receipt of the NMED Secretary's Determination "stating that the permit applicant has demonstrated that the activities to be permitted... will be expected to achieve compliance with all applicable air, water quality, and other environmental standards if carried out as described in the permit application." The NMED indicated when they issued the Discharge Permit that the NMED's Secretary Determination will be considered after the Financial Assurance Plan is approved by all participating agencies, and

- 4) MMD's receipt of BLM's approval of the proposed mining operation. BLM has indicated that approval of the proposed mining operation will be considered after the Financial Assurance plan is approved by participating agencies.

Other permits such as the OSE Dam Safety Permit for the mine's proposed Tailings Storage Facility and the Multi-Sector General Permit for potential storm water discharges at the facility from the Environmental Protection Agency will be addressed in the future as current priorities are achieved.

20.5 SOCIOECONOMICS AND COMMUNITY

The Copper Flat Mine is in Sierra County, New Mexico, approximately 170 highway miles south of Albuquerque, New Mexico. The county seat of Sierra County is Truth or Consequences, which is approximately 30 highway miles from the Copper Flat property. Communities within a 1-hour drive time from the property include Truth or Consequences; Williamsburg; Elephant Butte; Hillsboro; and Hatch.

The primary economic drivers in Sierra County are agriculture, healthcare, and tourism. Data from the US Census Bureau lists the Sierra County population as 13,270, 11,988, and 10,949 in the years 2000, 2010 and 2018 respectively. The 2010 population density of the County was 2.9 residents per square mile. In 2018, the unemployment rate for persons 16 and older living in Sierra County was 10.9%, and 24.8% of the Sierra County population were living below the poverty level.

NMCC engaged The Arrowhead Center, a division of New Mexico State University focused on economic analysis and business development, to prepare a socioeconomic study of the Copper Flat Mine. The study evaluated the socioeconomic impacts of the prefeasibility study operating plan, which differs slightly from the feasibility study plan, however the plans are similar in most aspects and the results remain relevant to current plans for Copper Flat. Study findings are presented in *The Socioeconomic Impacts of THEMAC Resources Group Ltd. Copper Flat Mine Project in Sierra County, New Mexico* (Popp, Peach & Delgado, 2012) and the report was distributed to the BLM and cooperating state agencies. The Arrowhead Study concludes the mine would create over 181 jobs in Sierra County and an additional 1,170 jobs within the state. Furthermore, the study indicates the mine will result in significant economic benefit to the local communities, Sierra County, and the State and generate revenue through payment of severance taxes, processor's tax, property taxes, gross receipts taxes, compensating taxes, personal income tax and corporate tax.

The EIS prepared by BLM considered socioeconomic factors in the analysis. The Final EIS concluded the mine would potentially create significant beneficial impacts of major magnitude due to the creation of jobs, labor income, and tax revenues. The proposed action would support over \$1.2 billion in economic activity, about 4,100 jobs with salaries worth over a total of \$300 million and generate \$18.4 million in local and State revenue during the life of the project. The BLM's Record of Decision on the EIS expressed the Agency's opinion that the Copper Flat Mine will enhance economic development by creating jobs and enabling community growth and presented the determination that implementation of the approved alternative along with Company commitments to environmental monitoring and protection measures will not cause unnecessary or undue degradation of public lands and the approved action is consistent with other applicable legal requirements.

Local community leaders and residents have expressed support for the Copper Flat Mine as demonstrated by the following statement from the Sierra County Manager: "After assessing New Mexico Copper Corporation's business model and environmental safeguards, the County Commission has approved two resolutions of support for the mine. The City of Elephant Butte and Village of Williamsburg have also approved resolutions of support. The vast majority of Sierra County residents support the mine. NMCC is trying to reopen a mine that has been operating on and off for generations in an area where mining of copper and other precious metals has been a part of the community since the

1880s. Mining, particularly at the Copper Flat site, is culturally and historically connected to Sierra County” (Orth, 2018b).

20.6 MINE CLOSURE, RECLAMATION, AND BONDING

20.6.1 Reclamation Plan

NMCC has prepared a detailed reclamation and closure plan (Mine Closure Plan) and cost estimate to describe how the mine will be reclaimed to meet the performance standards and requirements of the New Mexico Mining Act described in New Mexico Administrative Code (NMAC) 19.10.6.602.D.(15) and 19.10.6.603; meet closure requirements in the Copper Mine Rules described in 20.6.7.18 NMAC, 20.6.7.33 NMAC, 20.6.7.34 NMAC and 20.6.7.35 NMAC; and meet mine reclamation regulations set forth by the Bureau of Land Management (BLM) (3809.401(b)(3) and 3809.420(b)(3)).

Engineering and details for the Mine Closure Plan were developed by Golder and Associates under the direction of NMCC. Plan elements, including design criteria and design drawings, are provided in an October 7, 2016, Golder design report (Golder, 2016a). Designs developed for the Mine Closure Plan incorporate existing and expected future conditions of the Copper Flat site and the configuration of the site at the end of the mine operation. The Mine Closure Plan describes contemporaneous reclamation that will be conducted during mine operations, facilities to be reclaimed and closed following cessation of mining operations, and the components of the site that will remain post-closure.

In July 2018, the MMD issued a letter stating that NMCC’s operation and reclamation plans are technically approvable in accordance with 19.10.6.605.E NMAC. In December 2018, the NMED found that NMCC’s plans and designs meet the requirements of the Copper Rule and the Agency issued Discharge Permit DP-1840 to New Mexico Copper. In April 2019, the BLM issued the completed Environmental Impact Statement on NMCC’s proposed plan of operations, which includes reclamation and closure plans, for the Copper Flat Mine.

The Mine Closure Plan is designed to configure and stabilize the site against erosion; return the site to the current land uses of wildlife habitat, livestock grazing, and recreation; and develop a self-sustaining ecosystem. Key aspects of the Closure Plan are:

1. Salvage topsoil and growth media during construction and operation and store for use in reclamation;
2. Remove and properly dispose of operating materials, supplies, and waste materials;
3. Remove surface facilities, building foundations, and equipment;
4. Regrade disturbed areas for stability and reclamation cover placement;
5. Cover disturbed areas with topsoil and growth media to support vegetation growth;
6. Re-seed disturbed areas with approved vegetation species;
7. Provide stormwater management and erosion protection;
8. Long-term monitoring of groundwater quality and reclamation progress; and
9. Reclamation works repair and maintenance.

20.6.2 Reclamation Bond

The MMD, NMED, and BLM require financial assurance (“FA”) for reclamation of areas disturbed by exploration and mine operations. Agreements between the agencies allow reclamation bonds for New Mexico mineral projects to be

held jointly by the MMD, the NMED, and the BLM. The three agencies are cooperating on approval of reclamation costs for Copper Flat, including direct and indirect costs, and the three agencies will jointly hold the reclamation bond.

The Company has calculated the cost to reclaim and perform closure activities at the Copper Flat Mine for the purpose of establishing financial assurance to complete the Mine Closure Plan to meet the requirements of 19.10.12 NMAC and BLM Reclamation Cost Estimation Guidelines. Reclamation and closure costs were compiled by SRK Consulting Inc. under the direction of NMCC. These costs include costs for contractor performance of all reclamation and closure activities outlined in the Mine Closure Plan, rental fees for all equipment required to perform the work, contractor mobilization and demobilization fees, water management services, long-term sampling and monitoring services, and agency management and contract administration costs. The financial assurance calculation for reclamation, closure, and long-term management of the Copper Flat property, including contractor completion, equipment rental, and agency oversight, totals \$71.3 million.

In the July 2018 letter regarding the approvable PAP, the MMD also instructed NMCC to submit a proposal for financial assurance under 19.10.12 NMAC. Proposed calculations have been submitted for Agency review and Agency comments have been addressed as the work progressed. In correspondence dated August 21, 2019, MMD and NMED stated that NMCC's response to technical comments on the FA calculations was satisfactory and there were no additional technical comments regarding the calculations. In a separate action on the 3809 Plan of Operations, BLM indicated agreement with the State decision. NMCC has been considering options for the schedule and form of financial assurance according to 19.10.12.1205(C) through 19.10.12.1207-1208 NMAC; however, on March 31, 2020, the Director of the MMD signed and issued to NMCC an Order to reopen the permit review process and to suspend MMD review of the reclamation plan cost estimate. NMCC is currently reviewing the contents of the Order in order to understand the issues presented and develop a response plan.

In addition to the financial assurance calculation, the Company has also estimated costs for completing reclamation and closure costs using Company labor and equipment, supplemented by contractors and rental equipment as needed. The calculation includes water management services, long-term sampling and monitoring services, and contingency. The cost estimate for Company performed reclamation, closure, and long-term management of the Copper Flat property, including contingency, totals \$45.4 million. THEMAC currently has established two separate reclamation bonds for project development activities at Copper Flat; the current reclamation bonds are summarized in Table 20-3.

Table 20-3: Current Copper Flat Reclamation Bonds

Agency	Amount	Purpose
BLM	\$25,000	Reclaim access and excavation from inspection of existing Copper Flat freshwater pipeline
BLM	\$106,442	Reclaim Copper Flat concentrator foundation area that was exposed for inspection

21 CAPITAL AND OPERATING COSTS

21.1 PROCESS OPERATING COST ESTIMATE

This section addresses process plant operating and maintenance costs and general and administrative (G&A) costs. The process plant operating costs are summarized by cost element of labor, electric power, reagents, maintenance parts and supplies and services (Table 21-1). Annual operating cost use Year 3 as “typical” unless otherwise noted.

Table 21-1: Process Operating Cost Summary

Annual Production		
Milled Tons	10,800,000	
	Annual Cost	Unit Cost per Ton
Labor	\$9,091,841	\$0.84
Reagents	\$4,107,343	\$0.38
Steel Consumption	\$8,794,440	\$0.81
Electrical Power	\$18,397,566	\$1.70
Maintenance Parts & Services	\$4,020,297	\$0.37
Supplies & Services	\$4,427,722	\$0.41
Tailings Operations	\$4,291,497	\$0.40
Total	\$53,130,707	\$4.92

21.1.1 Process Labor and Fringes

The process plant operating and maintenance labor costs were derived from a staffing plan and are based on labor rates from an industry survey for this region and modified where necessary. The annual salaries include overtime and benefits for both salaried and hourly employees. The benefits rate used is 39 percent; an increase from the previous rate of 35 percent to reflect increases in medical benefit costs as summarized in Table 21-2.

Table 21-2: Process Labor Summary

	Personnel	Annual Cost
Operation	52	\$5,112,334
Maintenance	38	\$3,979,507
Total	90	\$9,091,841

21.1.2 Reagents

Consumption rates were determined from the metallurgical test data or industry practice. Budget quotations were received for reagents supplied from local sources where available, with an allowance for freight to site or from historical data from other projects.

A summary of process reagent consumption and cost is shown in Table 21-3.

Table 21-3: Process Plant Reagents

Reagents	lb/ton ore	lbs/year	\$/lb	Annual Cost	\$/ton ore
Lime	2.40	25,920,000	\$0.10	\$2,624,400	\$0.243
Sodium Hydrosulfide (NaHS)	0.025	270,000	\$0.48	\$129,938	\$0.012
Flocculant	0.001	14,040	\$1.01	\$14,198	\$0.001
Antiscalant	0.005	54,000	\$0.51	\$27,540	\$0.003
AERO 238	0.005	54,000	\$2.05	\$110,768	\$0.010
Moly Collector (Flomin 910)	0.020	216,000	\$1.88	\$406,080	\$0.038
PAX	0.030	324,000	\$1.65	\$534,600	\$0.050
MIBC	0.070	756,000	\$0.91	\$688,905	\$0.064
#2 Diesel	0.026	280,800	\$0.31	\$87,763	\$0.019

21.1.3 Maintenance Wear Parts and Consumables

Wear parts consumption (liners) and grinding media were estimated on a pound/ton basis. The consumption rate and unit costs were used to calculate the annual costs and cost per unit of production. These consumption rates and costs are shown in Table 21-4.

Table 21-4: Grinding Media and Wear Items

Mill Ore Tons (annual production)		10,800,000			
Grinding Media	lb/ton ore	lbs/year	\$/lb	Annual Cost	\$/ton ore
Primary Crusher Liners	0.03	324,000	\$3.50	\$1,134,000	\$0.11
SAG Mill Liners	0.05	540,000	\$1.08	\$583,200	\$0.05
Ball Mill Liners	0.06	648,000	\$1.12	\$725,760	\$0.07
SAG Mill - Grinding Balls	0.40	4,320,000	\$0.61	\$2,635,200	\$0.24
Ball Mill - Grinding Balls	0.60	6,480,000	\$0.56	\$3,628,800	\$0.34
Regrind Mill - Grinding Balls	0.01	108,000	\$0.81	\$87,480	\$0.01
Total Liners & Grinding Media Cost				\$8,794,440	\$0.81

21.1.4 Process Facilities Maintenance

An allowance was made to cover the cost of maintenance for the process facilities and all items not specifically identified. It is estimated to be \$4.0 million annually and is based on the capital equipment cost.

21.1.5 Electrical Power

Electrical power costs were based on current pricing from Sierra Electric at a rate of \$0.078 per kWh. The electric power consumption was based on the equipment list connected loads, discounted for operating time and anticipated operating load level. This results with an estimated power cost of \$18.4 million annually.

21.1.6 Process Supplies and Services

An allowance was estimated for items such as lubricants, diesel fuel, safety items, small vehicle cost, liquid nitrogen facility, outside services, flocculant system, and miscellaneous supplies. The allowances were estimated from historical information or from other operations and projects. Water supply leases are also included in this category an estimated to be \$0.9 million annually at a unit price of \$175 per acre-foot. The unit cost per ton is estimated to be \$0.40 per ton and for a typical year of operations is approximately \$4.4 million.

21.1.7 General and Administration Costs

G&A costs include labor and fringes for the administrative employees, accounting department, purchasing, human resources, community relations, safety and environmental departments. Also included are office supplies, communications, legal fees, community relations and outside services. These costs are summarized in Table 21-5.

A staff of 25 employees for the departments mentioned above and labor rates that are based on an industry survey for this region and modified where necessary are used in calculating the labor cost. The same benefit rate of 39 percent was applied for salaried and hourly employees. All other G&A costs are annual allowances.

Table 21-5: General Administration Summary

Ore Tons Processed	10,800,000	
Cost Item	Annual Cost	\$/ton ore
Labor & Fringes	\$2,358,303	\$0.218
Corporate Overhead	\$650,000	\$0.060
Accounting (excluding labor)	\$25,200	\$0.002
Safety (excluding labor)	\$25,200	\$0.002
Human Resources (excluding labor)	\$25,200	\$0.002
Security (excluding labor)	\$25,200	\$0.002
Janitorial Services (contract)	\$63,000	\$0.006
Community Relations (excluding labor)	\$63,000	\$0.006
Office Operating Supplies and Postage	\$60,000	\$0.006
Maintenance Supplies	\$644,068	\$0.060
Maintenance Labor, Fringes, and Allocations	\$161,017	\$0.015
Power	\$27,692	\$0.003
Propane	\$12,000	\$0.001
Phone/Communications	\$72,000	\$0.007
Licenses, Fees, and Vehicle Taxes	\$33,600	\$0.003
Claims Assessment	\$40,000	\$0.004
Legal	\$126,000	\$0.012
Insurances	\$698,044	\$0.065
Subs, Dues, PR, and Donations	\$25,200	\$0.002
Travel, Lodging, and Meals	\$126,000	\$0.01
Training	\$63,000	\$0.006
Total General & Administrative Cost	\$ 5,323,724	\$0.493

21.2 MINE OPERATING COSTS

Mine operating costs were developed based on first principals for the mine plan and equipment list presented earlier in Section 16. The unit costs for labor were provided by THEMAC. Fuel costs were set at \$2.14 USD per gallon.

Table 21-6 summarizes the mine operating costs by the unit operations. Preproduction is established to be 6 months in duration operating 1 shift/day. The cost per ton in all periods is based on the total tonnage moved within the mine plan.

Table 21-7 summarizes the total mine operating cost per time period along with the total mine capital cost. This table includes a column showing total mine operating costs by year of operation.

The mine operating costs include:

- 1) Drilling, blasting, loading, and hauling of material from the mine to the crusher, stockpile, or waste storage facilities. Maintenance of the waste storage areas and stockpiles is included in the mining costs. Maintenance of mine mobile equipment is included in the operating costs.
- 2) Mine supervision, mine engineering, geology and ore control are included in the G&A category.
- 3) Operating labor and maintenance labor for the mine mobile equipment are included.
- 4) Mine access road construction and maintenance are included. If mine haul trucks drive on the road, its cost and maintenance are included in the mine operating costs.
- 5) The small stockpile (360 ktons) that is generated during preproduction stripping is re-handed to the plant in Year 1.
- 6) A general mine allowance is included that is intended to cover mine pumping costs and general operating supplies that cannot be assigned to one of the unit operations.
- 7) A general maintenance allowance is included that is intended to cover the general operating supplies of the maintenance group.
- 8) An increased maintenance allowance is included during the final years of production due to the age of the mine equipment.
- 9) Lease payments for all Major Mine Equipment and Mine Support Equipment, but the initial down payment is capitalized.

The mine operating costs DO NOT include:

- 1) Crushing, conveying or processing
- 2) Site reclamation or recontouring costs.

The mine is planned to work 2 shifts per day for 365 days per year. Five days (10 shifts) of lost time are assumed due to weather delays.

Table 21-6: Summary of Mine Operating Costs (\$US)

Mining Year	Total Material (kt)	Drilled/ Blasted (kt)	Drilling	Blasting	Loading	Hauling	Auxiliary	General Mine	General Maint.	Mine G&A	TOTAL	Cost per ton of Mined Material	Cost per Ore ton
PP	470	470	145	109	223	231	646	84	162	494	2,094	4.455	5.816
Yr Q1	4,375	4,375	796	657	950	1,780	1,681	554	520	831	7,769	1.776	5.045
Yr Q2	4,375	4,375	797	657	951	1,954	1,700	545	522	837	7,963	1.82	3.981
Yr Q3	4,375	4,375	799	657	953	1,841	1,735	584	525	835	7,930	1.813	2.937
Yr Q4	4,375	4,375	798	657	952	1,965	1,733	579	525	839	8,047	1.839	2.98
Yr 2	17,500	17,500	3,190	2,628	3,806	8,502	6,897	2,399	2,098	3,365	32,885	1.879	3.045
Yr 3	17,500	17,500	3,177	2,628	3,794	9,908	6,771	2,336	2,098	3,389	34,101	1.949	3.158
Yr 4	17,500	17,500	3,179	2,628	3,796	10,056	6,715	2,277	2,098	3,405	34,154	1.952	3.162
Yr 5	17,500	17,500	3,099	2,628	3,636	9,441	6,583	2,193	2,090	3,357	33,027	1.887	3.058
Yr 6	15,949	15,949	2,441	2,411	2,423	8,652	4,404	2,026	2,014	3,340	27,711	1.737	2.764
Yr 7	12,391	12,391	2,068	1,911	2,054	6,771	4,318	1,876	1,865	3,285	24,148	1.949	2.439
Yr 8	10,618	10,618	1,880	1,663	1,868	5,921	4,360	1,806	1,795	3,269	22,561	2.125	2.279
Yr 9	9,971	9,971	1,814	1,572	1,802	6,075	4,089	1,780	1,769	3,277	22,179	2.224	2.24
Yr 10	9,903	9,903	1,797	1,562	1,786	6,903	4,041	1,778	1,766	3,300	22,933	2.316	2.316
Yr 11	9,901	9,901	1,788	1,562	1,777	7,768	3,869	1,777	1,766	3,307	23,614	2.385	2.385
Yr 12	1,063	1,063	160	171	159	967	482	202	212	403	2,756	2.592	2.602
TOTAL	157,766	157,766	27,927	24,102	30,928	88,735	60,025	22,796	21,823	37,535	313,871	1.989	2.776
PERCENT			8.9%	7.7%	9.9%	28.4%	19.2%	7.3%	7.0%	12.0%	100.0%		

Table 21-7: Summary of Mine Capital and Operating Costs

Summary of Mine Capital and Operating Costs Leased New Equipment (\$USx1000)								
Year	Mine Equipment		Total Mine Capital	Operating Costs			Total Operating Cost	TOTAL COST
	Initial Capital Cost	Sustaining Capital Cost		Operating Consum. Cost	Fleet Lease/Dep. Cost	Operating Labor Cost		
PP	8,396		8,396	516	567	1,011	2,094	10,490
Yr Q1		1,775	1,775	3,747	958	3,064	7,769	9,544
Yr Q2		124	124	3,814	1,018	3,131	7,963	8,087
Yr Q3		0	0	3,801	1,018	3,111	7,930	7,930
Yr Q4		0	0	3,875	1,018	3,154	8,047	8,047
Yr 2		170	170	15,781	4,403	12,701	32,885	33,055
Yr 3		170	170	16,410	4,734	12,958	34,101	34,272
Yr 4		404	404	16,289	4,734	13,131	34,154	34,558
Yr 5		0	0	16,251	4,167	12,609	33,027	33,027
Yr 6		60	60	14,568	721	12,422	27,711	27,771
Yr 7		3,571	3,571	12,005	331	11,812	24,148	27,719
Yr 8		510	510	10,921	0	11,640	22,561	23,071
Yr 9		3,385	3,385	10,453	0	11,726	22,179	25,564
Yr 10		0	0	10,948	0	11,984	22,933	22,933
Yr 11		0	0	11,552	0	12,061	23,614	23,614
Yr 12		0	0	1,366	0	1,390	2,756	2,756
TOTAL	8,396	10,169	18,565	152,299	23,669	137,903	313,871	332,435

Note: An allowance for clearing & grubbing is NOT included.

21.3 CAPITAL COST ESTIMATE

21.3.1 Mine Capital Cost

Mine capital cost for mobile equipment was developed from the mine equipment list presented in Section 16. Unit costs for all the major equipment and most of the minor equipment were based on typical lease rates and lease pricing structures observed in 2017. Unit costs for the minor equipment unable to be quoted were based on IMC file data. Older quotes for minor units were inflated as required.

Mine capital costs do include:

- 1) All mine mobile equipment required to drill, blast, load, and haul the material from the pit to the appropriate destinations. The initial lease cost payment is included in the capital costs.
- 2) Auxiliary equipment to maintain the mine and material storage areas in good working order as well as construct the mine haul roads and maintain them.
- 3) Equipment to maintain the mine fleet such as tire handlers and forklifts.
- 4) Light vehicles for mine operations and staff personnel.
- 5) An allowance is included for initial shop tools.
- 6) An allowance is included for initial spare parts inventory.
- 7) Mine engineering equipment (computers, survey equipment, etc.) is included.

- 8) Mine communication network and system.
- 9) Equipment replacements are included as required based on the useful life of the equipment.

Mine capital costs DO NOT include:

- 1) Mine office buildings, or shop facilities. They are included elsewhere in the project capital list.
- 2) Mobile equipment that is not required by the mine. (i.e. no mobile units for the plant).
- 3) Infrastructure or process plant related costs.

The equipment is shown as purchase in the year it is required for operation.

Table 21-8 presents the detailed purchase schedule for the mine equipment.

Table 21-7 summarizes the mine capital costs by year along with the mine operating costs and shows preproduction stripping as part of the mine capital cost. The cost is broken out separately to illustrate that it is not a cost to purchase mine equipment.

Table 21-8: Mine Equipment Capital Costs

Sum of all Mine Equipment Capital Costs																													
	Unit Cost (\$1000)	Life Hours	PP No. (\$1000)		Yr Q1 No. (\$1000)		Yr Q2 No. (\$1000)		Yr Q3 No. (\$1000)		Yr Q4 No. (\$1000)		Yr 2 No. (\$1000)		Yr 3 No. (\$1000)		Yr 4 No. (\$1000)		Yr 5 No. (\$1000)		Yr 6 No. (\$1000)		Yr 7 No. (\$1000)		Yr 8 No. (\$1000)		Yr 9 No. (\$1000)		Project Total
MINE MAJOR EQUIPMENT:																													
Sankvik D245S Blasthole Rotary Drill (6.5 in bit / 45000 lb pulldown)	1,314	65,000	1	39	1	39	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	79
CAT 993K Front End Loader (19 CuYd bucket / 1050 HP)	2,792	45,000	1	84	1	84	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	2	2,792	2,960	
CAT 777G Haul Truck (83.8 CuYd bed / 100 t)	1,538	100,000	2	92	6	277	0	0	0	0	0	1	46	1	46	0	0	0	0	0	0	0	0	0	0	0	0	0	461
CAT D9T Track Dozers (15 ft blade / 436 HP)	1,068	45,000	1	32	2	64	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	96	
CAT 834K Wheel Dozer (16.9 ft blade / 562 HP)	1,185	45,000	1	36	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	1	593	628	
CAT 14M Motor Graders (14 ft blade / 259 HP)	570	45,000	1	17	1	17	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	34	
CAT 773G WT Water Truck (13000 gal tank / 60 t)	1,117	80,000	1	34	0	0	1	34	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	67	
Sankvik DX-800 Rock Drill (3 in bit / 13000 lb)	650	65,000	1	20	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	20	
Subtotal Major Equipment			362		481		34		0		0		46		46		0		0		0		0		0		3,385		4,345
MINE SUPPORT EQUIPMENT:		Years																											
Blasthole Stemmer (skid steer- CAT226D)	44	7	1	44	0		0		0		0		0		0		0		0		1	44	0		0		88		
Blasters Flatbed Truck (2 T)	59	7	1	59	0		0		0		0		0		0		0		0		1	59	0		0		117		
ANFO/Slurry Truck (21,400 Lb)	499	7	1	499	0		0		0		0		0		0		0		0		1	499	0		0		998		
Fuel/Lube Truck 3,000 gal fuel, 7-250 gal lube	980	7	2	1,961	0		0		0		0		0		0		0		0		1	980	0		0		2,941		
Spare Loader Bucket (17 CuYd)	196	18	1	196	0		0		0		0		0		0		0		0			0	0		0		196		
Flatbed Truck (8 - 10 ton)	89	7	1	89	0		0		0		0		0		0		0		0		1	89	0		0		177		
Crane Truck (19 ton) - 2017 Terex BT3870	218	7	1	218	0		0		0		0		0		0		0		0		1	218	0		0		436		
Cat 988 with Tire Handler	973	7	1	973	0		0		0		0		0		0		0		0		1	973	0		0		1,946		
Mechanics Truck (5t crane, air comp. & welder)	394	7	1	394	0		0		0		0		0		0		0		0		1	394	0		0		788		
Tractor & Lowboy (highway)	213	18	1	213	0		0		0		0		0		0		0		0			0	0		0		213		
Shop Forklift (Hyster H100XM)	57	18	1	57	0		0		0		0		0		0		0		0			0	0		0		57		
RT Forklift (Sellick S160-4)	106	9	1	106	0		0		0		0		0		0		0		0			0	1	106	0		212		
Man Van	35	4	2	70	0		0		0		0		0		0		2	70	0			0	2	70	0		210		
Pickup Truck (4x4)	33	4	10	334	0		0		0		0		0		0		10	334	0			0	10	334	0		1,002		
Light Plants	14	18	6	87	0		0		0		0		0		0		0		0		6	87	0		0		174		
Mine Radios (Handheld & Fixed Units)	1	7	50	50	10	10	1	1	0		0	1	1	1	0		0		60	60	6	0	0		0		123		
Mine Communications Network	417	18	1	417	0		0		0		0		0		0		0		0			0	0		0		417		
Water Pipe - Dewatering	91	18	1	91	0		0		0		0		0		0		0		0			0	0		0		91		
Mine Pumps (Diesel Trailer Mounted- CAT engine)	228	7	1	228	0		0		0		0		0		0		0		0		1	228	0		0		457		
Mine Planning Software	510	18	1	510	0		0		0		0		0		0		0		0			0	0		0		510		
Tire Press	212	18	1	212	0		0		0		0		0		0		0		0			0	0		0		212		
Shop Jacks	35	18	1	35	0		0		0		0		0		0		0		0			0	0		0		35		
Ammonium Nitrate Storage	75	18	1	75	0		0		0		0		0		0		0		0			0	0		0		75		
Subtotal Mine Support Equipment			6,917		10		1		0		0		1		1		404		0		60		3,571		510		0	11,475	
Other:																													
Engineering/Geology Equipment	150	18	1	150	0		0		0		0		0		0		0		0		0		0		0		150		
Shop Tools (3% of Major Equipment)		3.0%		362	481		34		0		0		46		46		0		0		0		0		0		969		
Initial Spare Parts (5% of Major Equipment)		5.0%		604	802		56		0		0		77		77		0		0		0		0		0		1,616		
Contingency (0%)		0.0%		0	0		0		0		0		0		0		0		0		0		0		0		0		
TOTAL EQUIPMENT/FACILITIES CAPITAL			8,396		1,775		124		0		0		170		170		404		0		60		3,571		510		3,385	2,735	

21.3.2 Plant Capital Costs

Capital costs for the processing plant were estimated using budgetary equipment quotes, material take-offs for concrete, steel, and earthwork, estimates from vendors and consultants, and estimates based on experience with similar projects of this type. Some of the costs and quantity estimates used by M3 were supplied by other consultants.

- Golder Associates (Golder) provided quantities and costs associated with construction and operation of the tailings storage facility and associated ponds.
- Costs for installation of substation to obtain power for the mining operation were provided by Sierra Electric, the local electrical cooperative that controls the service area in which the mine is located.

The capital cost estimates include both initial capital and sustaining capital for the project. Initial capital is defined as all capital costs through the end of construction. Capital costs predicted for later years are carried as sustaining capital in the financial model. All costs are in 1st quarter 2018 US dollars.

The accuracy of this estimate for those items identified in the scope-of-work is estimated to be within the range of ± 15 percent. Outside consultants provided estimates for the primary power supply, water supply to the mine site, and TSF. These consultants reported that their estimates are compatible with the overall estimate accuracy of ± 15 percent.

Based on the level of engineering completed and definition of scope, M3 estimated the contingency at 15 percent of the direct and indirect costs (Contracted Cost).

21.3.2.1 Direct Costs

Site work quantities were estimated by Golder for the tailings liner preparation and construction, seepage collection pond, tailings distribution system, and waste rock disposal run-off ponds. Tailings dam mobile equipment was estimated separately and is included in Owner's costs.

Structural steel and concrete quantities for the plant buildings were estimated using material take-offs based on preliminary designs. Concrete quantities were reduced as a consequence of the assumption that existing concrete in the primary crusher structure, coarse ore reclaim tunnel, concentrator, truck shop, and administration building were reusable. Inspection of uncovered portions of these structures indicated they were in excellent condition, supporting that assumption. Concrete work was also estimated to remove, modify, or add to the existing structures to accommodate the preliminary designs.

Concrete costs were estimated based upon an informal survey of current and recent projects in New Mexico.

Steel costs were based upon a recent large steel purchase for a mine plant of similar scale. Competitive bids were collected from the US, Canada, and Mexico. M3 considers the resulting bid prices to be representative of world structural steel prices during the first quarter of 2018.

Architectural costs are based on M3 records of similar-sized projects for the major buildings. Pre-engineered building quotes were obtained for some of the smaller buildings for comparison.

Vendor quotes supplied cost data for major mine equipment. Small support equipment cost was estimated by an allowance of 5 percent.

M3 prepared a comprehensive Equipment List based on the flowsheets developed for the project. Major process plant equipment such as crushers, mills, flotation cells, filters, tanks, agitators, pumps, conveyors, and major electrical components were priced from vendor budgetary quotations. Other equipment prices were based on M3's historical

records including budgetary and equipment purchase pricing from recent, similar projects. Some historic records were scaled to correct for size or capacity difference. Installation costs are based on allowances for materials and M3's judgment and experience for labor. Over 85 percent, of total plant mechanical equipment cost came directly from 2018 vendor budgetary quotes for this or other projects.

Piping quantities were based on material takeoffs using the feasibility study design. Long-run piping in the process area and water supply, fire suppression, and potable water systems was estimated on a footage basis. Piping for the tailing disposal system is included in Golder's capital cost estimates.

Instrumentation costs were estimated using piping and instrumentation diagrams for the project.

Quality Assurance Testing is estimated at 2 percent of total direct costs for civil, concrete, piping, steel, and electrical costs.

Surveying is estimated at 1 percent of total direct costs for civil, concrete, and steel costs.

Freight allowance includes the following components.

- Freight is included at 7 percent of total materials and plant equipment costs.
- Duties, Customs, and In-transit warehousing are included at 1 percent of total materials and plant equipment costs.

21.3.2.2 Indirect Costs

Indirect costs include such things as indirect field costs, mobilization costs, contractor fees, and freight costs. There are no indirect field or camp and busing costs estimated for this project. Contractor fees are included in the direct costs. Indirect costs estimated for this project include mobilization and freight.

Mobilization is calculated as 0.5 percent of Total Direct Costs without mine and mobile equipment but including Quality Assurance Testing and Surveying.

Engineering, Procurement, and Construction Management (EPCM) services and fees are estimated as follows.

- Management and accounting are 0.75 percent of total direct field costs without pre-stripping and mine equipment.
- Engineering is 6 percent of total direct field costs without pre-stripping and mine equipment.
- Project services are 1 percent of total direct field costs without pre-stripping and mine equipment.
- Project control is 0.75 percent of total direct field costs without pre-stripping and mine equipment.
- Construction management is 6.5 percent of total direct field costs without pre-stripping and mine equipment.
- EPCM fee is 1 percent of total direct field costs without pre-stripping and mine equipment.
- EPCM construction trailers are 0.2 percent of total direct field costs without pre-stripping and mine equipment.
- Temporary facilities and support are 0.5 percent of total direct field costs without pre-stripping and mine equipment.
- Construction power is 0.1 percent of direct costs.

Other indirect allowances in the estimate based on plant equipment costs include supervision of specialty construction (1 percent), precommissioning (0.3 percent), commissioning (0.3 percent), and capital spares (2 percent). Commissioning spare parts are estimated at 0.5 percent of equipment purchase costs.

The following taxes have been considered for this estimate:

- Sales tax is not included in the cost of equipment.
- New Mexico Gross Receipts Tax is a blended rate that includes deductions of Industrial Revenue Bonds and out-of-state purchases that yields a rate of 4.50 percent.
- Payroll taxes are included in the labor rates

Working capital is not included in the capital cost but is accounted for in the financial model (Section 22).

Sustaining Capital is not included in the initial Capital Cost Estimate but has been estimated on the same basis as the initial capital. The major components of sustaining capital are additions to the mine equipment fleet in later years, and tailings management facility expansions including additional earthwork and liner placement. Estimated costs are applied in future years in the financial model (Section 22). Sustaining costs are included in the financial model.

21.3.3 Tailings Capital and Operating Cost

Table 21-9 includes a summary of feasibility-level capital and operating costs for the TSF. Contingency costs are 15 percent for pumping, piping, and cyclone components, and 15 percent for activities that include earthwork and could be influenced by subsurface conditions. Contingency costs are identified on Table 21-9; however, they are not included in the capital and operating cost totals, or in the net present value (NPV) calculations. Engineering, procurement and construction management (EPCM) costs are also not included. It is assumed that EPCM and contingency cost will be applied globally in the overall feasibility study cost estimate.

Table 21-9: Tailings Storage Facility Capital and Operating Cost Estimate

Single Lined TSF at 30Ktpd Mining Rate, Continuous Underdrain Cost Estimate and Economic Analysis Copper Flat TSF Copper Flat Project Feasibility Study Update November 2017														
Nominal Mining Rate		30,000	tpd											
Net Tons to Tailings Year 1-5		1,333	tph											
Net Tons to Tailings Year 6-11		1,222	tph											
Total Reserves		113,000,000	tons											
Mine Life		11.1	years											
Item /Area	Total LOM		Year 1	Year 2	Year 3	Year 4	Year 5	Year 6	Year 7	Year 8	Year 9	Year 10	Year 11	Year 12
Tons Processed	113,084,000		9,300,000	10,800,000	10,800,000	10,800,000	10,800,000	10,025,000	9,900,000	9,900,000	9,900,000	9,900,000	9,900,000	1,059,000
Capital Costs														
TSF Earthworks and Liner Installation	\$60,150,000		\$43,223,000	\$5,837,000			\$7,584,000		\$3,506,000					
Impoundment Underdrain Outlet Works	\$381,000		\$381,000											
Seepage Reclaim Pond (earthworks and liner)	\$1,023,000		\$1,023,000											
TSF Equipment Allowance (dozer, compactor, etc.)	\$2,000,000		\$2,000,000											
Emergency Pond, Cyclone plant site work	\$230,000		\$230,000											
Projected CAPEX (additional pipes, pump upgrade, etc.)	\$1,369,447		\$367,875	\$93,386				\$171,844	\$736,343					
Cyclone Station	\$6,590,554		\$6,590,554											
Seepage Pond (Reclaim works)	\$2,331,656		\$2,331,656											
TSF Barge	\$4,032,935		\$4,032,935											
Pipes	\$4,448,025		\$4,448,025											
Capital Expenditure (CAPEX)	\$82,556,617		\$64,628,045	\$5,930,386			\$7,584,000	\$171,844	\$4,242,343					
Contingency (15%)	\$12,383,493		\$9,694,207	\$889,558			\$1,137,600	\$25,777	\$636,351					
Total CAPEX including contingency	\$94,940,110		\$74,322,252	\$6,819,944			\$8,721,600	\$197,620	\$4,878,694					
Operating Costs														
Pipeline/cyclone plant operating cost (labor)	\$20,096,135		\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$1,810,463	\$181,046
Spares	\$5,331,428		\$455,928	\$425,031	\$404,650	\$424,291	\$452,763	\$440,527	\$442,948	\$471,628	\$521,922	\$599,758	\$629,076	\$62,908
Power (\$0.07807/kWh)	\$5,569,899		\$717,312	\$725,187	\$602,007	\$602,007	\$602,007	\$417,237	\$450,651	\$450,651	\$450,651	\$265,881	\$265,881	\$20,429
Underflow spread and compact (\$0.30/ton)	\$15,435,471		\$1,474,377	\$1,474,377	\$1,474,377	\$1,474,377	\$1,474,377	\$1,321,899	\$1,321,899	\$1,321,899	\$1,321,899	\$1,321,899	\$1,321,899	\$132,190
Operating Expenditure (OPEX)	\$46,432,934		\$4,458,080	\$4,435,058	\$4,291,497	\$4,311,138	\$4,339,610	\$3,990,125	\$4,025,960	\$4,054,640	\$4,104,934	\$3,998,000	\$4,027,318	\$396,573
Unit Cost (\$/ton)	\$0.41		\$0.48	\$0.41	\$0.40	\$0.40	\$0.40	\$0.40	\$0.41	\$0.41	\$0.41	\$0.40	\$0.41	\$0.37
Contingency (15%)	\$6,964,940		\$668,712	\$665,259	\$643,725	\$646,671	\$650,941	\$598,519	\$603,894	\$608,196	\$615,740	\$599,700	\$604,098	\$59,486
Total OPEX including contingency	\$53,397,874		\$5,126,792	\$5,100,317	\$4,935,222	\$4,957,809	\$4,990,551	\$4,588,644	\$4,629,854	\$4,662,836	\$4,720,674	\$4,597,700	\$4,631,416	\$456,059
Unit Cost (\$/ton) incl. contingency	\$0.47		\$0.55	\$0.47	\$0.46	\$0.46	\$0.46	\$0.46	\$0.47	\$0.47	\$0.48	\$0.46	\$0.47	\$0.43
Total (CAPEX and OPEX)	\$128,989,551		\$69,086,125	\$10,365,444	\$4,291,497	\$4,311,138	\$11,923,610	\$4,161,969	\$8,268,303	\$4,054,640	\$4,104,934	\$3,998,000	\$4,027,318	\$396,573
Total (CAPEX and OPEX) including contingency	\$148,337,984		\$79,449,044	\$11,920,261	\$4,935,222	\$4,957,809	\$13,712,151	\$4,786,264	\$9,508,548	\$4,662,836	\$4,720,674	\$4,597,700	\$4,631,416	\$456,059
Notes:														
1) Taxes have been excluded from this cost estimate.														

21.3.4 Current Value of Existing Infrastructure

The Copper Flat Project takes advantage of significant infrastructure improvements that are a legacy from the Quintana operation in the early 1980s. Existing infrastructure that will be reused during redevelopment includes the items listed below. The value of these improvements was evaluated to provide an estimate of the additional capital cost that would be required, had this work not been done by Quintana or not have been useable by NMCC for this project.

- 115 kV powerline from the Caballo Substation to the mine site.
- Production wellfield and 20-inch pipeline from the wellfield to the mine site.
- Diversion channel collecting stormwater from west and south of the pit and diverting unimpacted flows down Grayback Wash.
- Existing concrete foundations and structures including
 - Primary crusher structure
 - Coarse ore reclaim tunnel
 - Concentrator building foundation
 - Metallurgical laboratory foundation
 - Truck shop foundation
 - Administration building foundation
- Pre-stripping of waste material to prepare for open pit mining

Estimates for the listed improvements were prepared using standard methodologies. Quantity takeoffs for excavation, backfilling, drilling and blasting, earthmoving, and concrete were prepared and submitted to the estimator for costing. Records of pre-mining waste material moved were used to estimate the cost of pre-stripping. Existing topographic surfaces were compared with pre-mine topography to estimate excavation quantities. Engineering drawings for the plant were used to estimate quantities of steel and concrete necessary for the foundations and concrete structures. Plans for the water supply and electrical supply system were used to identify quantities for the electrical and water supply construction. The estimator used these quantities to estimate the present value of these improvements, as shown in Table 21-10. The total estimated present value is a conservative estimate of the additional capital cost that would be required for the project, if the Quintana operation had not been constructed.

The 2013 cost estimates were reviewed in 2018 by a construction contractor specializing in industrial construction and were judged to be within the range of construction costs for these items at that time.

Table 21-10: Current Value Cost of Reused Quintana Infrastructure

Item	Replacement Cost
Freshwater system – four wells and steel water line	\$9,500,000
115 kVa power line to the mine site	\$2,900,000
Grayback Wash diversion ditch	\$23,100,000
Primary crusher structure and earthworks	\$5,300,000
Coarse ore reclaim tunnel and earthworks	\$3,800,000
Concentrator foundation	\$4,800,000
Laboratory building foundation	\$200,000
Truck shop foundation	\$1,900,000
Former administration building foundation	\$100,000
Pit pre-stripping	\$2,300,000
Total Current Value of Reused Infrastructure	\$53,900,000

22 ECONOMIC ANALYSIS

22.1 INTRODUCTION

The financial evaluation presents the determination of the Net Present Value (NPV), payback period (time in years to recapture the initial capital investment), and the Internal Rate of Return (IRR) for the project. Annual cash flow projections were estimated over the life of the mine based on the estimates of capital expenditures and production cost and sales revenue. The sales revenue is based on the production of a copper concentrate and a molybdenum concentrate. The estimates of capital expenditures and site production costs have been developed specifically for this project and have been presented in earlier sections of this report.

22.2 MINE PRODUCTION STATISTICS

Mine production is reported as ore and waste from the mining operation. The annual production figures were obtained from the mine plan as reported earlier in this report.

The life of mine ore quantities and ore grades are presented in the table below.

Table 22-1: Life of Mine Ore, Waste Quantities, and Ore Grade

	Tons	Copper	Molybdenum	Gold	Silver
	(kt)	%	%	(oz/ton)	(oz/ton)
Direct Mill Feed Ore	113,084	0.298	0.009	0.003	0.064
Total Ore Processed	113,084	0.298	0.009	0.003	0.064
Waste	44,682				

22.3 PLANT PRODUCTION STATISTICS

The design basis for the process plant is 10.8 million tons per year.

Average metallurgical recoveries projected for the operation are shown in Table 22-2.

Table 22-2: Average Metallurgical Recoveries

Product	LOM Average	Years 1 – 5	Years 6 - LOM
Copper	93.1 %	94.6%	91.2%
Molybdenum	78.0%	81.9%	73.4%
Gold	73.7%	73.7%	73.7%
Silver	82.7%	82.7%	82.7%

Estimated life of mine recoveries (before smelter deductions) from the process plant is presented in Table 22-3.

Table 22-3: Recovered Metal Production

Metal	Recovered Quantity
Copper (klbs)	628,015
Molybdenum (klbs)	15,717
Gold (kozs)	227
Silver (kozs)	5,950

22.3.1 Smelter Terms

The copper concentrates are assumed to be shipped to a smelter in Asia with terms negotiated at the time of the agreement. Molybdenum concentrates are assumed to be saleable in the domestic US market. Development of contract terms used for smelting and refining is provided in Section 19 of this report. The smelter charges and payable metal used in the financial evaluation are presented in the table below.

Table 22-4: Smelter Treatment Factors

Copper Concentrates	
Payable Copper (%)	96.5
Payable Gold (%)	94.0
Gold Deduction (troy ounces per dry ton)	0
Payable Silver (%)	90.0
Silver Deduction (troy ounces per dry ton)	0
Treatment Charge	\$85.00
Refining Charge – Cu (per pound)	\$0.085
Refining Charge – Au (per troy ounce)	\$6.00
Refining Charge – Ag (per troy ounce)	\$0.50
Transportation Charges (per wet ton)	\$158.00
Moisture (%)	8.0
Molybdenum Concentrate	
Payable Molybdenum (%)	99.0
Roasting Charges (per pound)	\$1.50
Transportation Charges (per wet ton)	\$57.00
Moisture (%)	8.0

The estimated payable metals (recovered quantity less smelter deductions) over the life of mine are shown in Table 22-5.

Table 22-5: Estimated Payable Metals

Metal	Payable Quantity
Copper (klbs)	605,586
Molybdenum (klbs)	15,560
Gold (kozs)	214
Silver (kozs)	5,355

22.3.2 Capital Expenditure

22.3.2.1 Initial Capital

The financial indicators have been determined assuming 100 percent equity financing of the initial capital. Any acquisition cost or expenditures prior to start of the full project period have been treated as “sunk” cost and are not included in the analysis, except for carry forward depreciation needed for tax calculations. The initial capital carried in the financial model for new construction and pre-production mine development, and owner costs total \$373.9 million as outlined in Table 22-6. This amount is assumed to be expended over a 3-year period; the majority will be expended in the two years before production with a small amount carried over into the first production year.

Table 22-6: Initial Capital

	\$ in millions
Mining (includes preproduction)	\$10.5
Process Plant	\$328.5
Owner's Cost	\$35.0
Total	\$374.0

22.3.3 Sustaining Capital

A schedule of capital cost expenditures during the production period was estimated and included in the financial analysis under the category of sustaining capital. The total life of mine sustaining capital is estimated to be \$40.9 million. This capital will be expended over an 8-year period starting in operating Year 1.

22.3.4 Working Capital

A 60-day delay of receipt of revenue from sales is used for accounts receivables. A delay of payment for accounts payable of 30 days is also incorporated into the financial model. All the working capital is recaptured at the end of the mine life and the final value of these accounts is \$0.

22.3.5 Residual and Salvage Value

The mine is currently scheduled to operate 11.1 years, a relatively short period relative to the operating life of the process equipment proposed for the operation. Used equipment markets have been reviewed and residual and salvage values totaling \$30.3 million has been assumed for equipment and property at the end of the mine life.

22.3.6 Revenue

Annual revenue is determined by applying estimated metal prices to the annual payable metal estimated for each operating year. Sales prices have been applied to all life of mine production without escalation or hedging. The revenue is the gross value of payable metals sold before treatment charges and transportation charges. Metal sales prices used in the evaluation are as follows:

Copper	\$3.25/pound
Molybdenum	\$10.50/pound
Gold	\$1,300.00/ounce
Silver	\$16.00/ounce

22.4 CASH OPERATING COST

The average cash operating cost calculated over the full life-of-mine is estimated at \$12.14 per ton of ore processed before credits applied for by-product revenue and excluding the cost of the capitalized pre-stripping. After crediting by-product revenue against costs, the average LOM cash operating cost is \$1.35 per pound of copper recovered. Cash operating costs include mine operations, process plant operations, site general and administrative costs, smelting and refining charges, royalties, and shipping charges.

22.4.1 Royalty

Royalties for the mine include an Advance Royalty and a Net Smelter Return (NSR) Royalty. Payment of the Advance Royalty begins during the third month after all state and federal permits to operate the mine are received and is paid every three months thereafter. Payment is in the amount of \$50,000.00 if the price of copper is less than \$2.00 per

pound or \$112,500.00 if the price of copper is \$2.00 per pound or higher. The NSR Royalty of 3.25 percent applies to the gross revenue of all mineral products from the mine. Advance Royalty payments continue until the aggregate amount of the Advance and NSR Royalties paid reach \$10 million; however, Advance Royalty payments are credited back against the amount of NSR Royalty Payment otherwise due. The economic model includes calculations to estimate Advance and NSR Royalties as required by the agreement.

Table 22-7 shows estimated LOM cash operating costs by cost center per ton of ore processed and per lb of copper recovered.

Table 22-7: Life of Mine Net Direct Cash Cost (C1 Cost)

Cost Center	\$/Ore Ton	\$/lb Cu
Mine	\$2.75	\$0.50
Process Plant	\$5.01	\$0.90
General Administration	\$0.53	\$0.10
Smelting/Refining Treatment	\$3.24	\$0.58
Royalty	\$0.61	\$0.11
Total Operating Cost Before By-Product Revenue	\$12.14	\$2.19
	By-Product Revenue	(\$0.84)
	Total Operating Cost After By-Product Credits	\$1.35

22.5 TOTAL PRODUCTION COST

The average total production cost over the full life-of-mine is estimated to be \$12.79 per ton of ore processed excluding any credit for by-product revenue. After credit for by-product revenue, the average LOM total production cost is \$1.46 per pound of copper recovered. Cash production costs are cash operating costs plus royalty, salvage value, reclamation and closure costs, ad valorem tax, severance tax, resources excise tax, high wage jobs tax credit, and corporate overhead.

22.5.1 Reclamation and Closure

NMCC prepared a detailed reclamation and closure plan and cost estimate as described in Section 20.6.1. The MMD, NMED, and BLM require financial assurance for reclamation of areas disturbed by exploration and mine operations. The financial assurance calculation for reclamation, closure, and long-term management of the Copper Flat property, including contractor completion, equipment rental, and agency oversight totals \$71.3 million. NMCC has included bonding costs to cover the financial assurance obligations at a rate of \$6.00 per \$1,000 of the calculated value, which total \$7.45 million. NMCC has also included the estimated cost of \$45.4 million for the Company to perform reclamation, closure, and long-term management of the Copper Flat property including contingency.

22.5.2 Depreciation

Depreciation is calculated using the MACRS method starting with the first year of production. Depreciation is calculated for initial capital and sustaining capital used assuming a 7-year life. The last year of production is the catch-up year if the assets are not fully depreciated at that time.

22.6 DEPLETION

The percentage depletion method was used in the evaluation. It is determined as a percentage of gross income from the property, not to exceed 50% of taxable income before the depletion deduction. A rate of 15% is used for copper, gold, and silver, and a rate of 22% is used for molybdenum.

22.7 TAXATION

22.7.1 Income Tax

Taxable income for income tax purposes is defined as metal revenues minus operating expenses, royalty, property and severance taxes, reclamation and closure expense, depreciation and depletion. Income tax rates for state and federal are as follows:

- State rate 5.9%
- Federal rate 21.0%
- Combined effective tax rate 25.7%

The combined effective tax rate was calculated as follows (use decimal format to calculate): state rate (5.9%) + federal rate (21.0%*(1-state rate 5.9%)).

22.7.2 New Mexico Gross Receipts Tax

The State of New Mexico imposes a Gross Receipts Tax (GRT) on sales and services provided in the State. The tax rate varies by location; the prevailing GRT at the Project site is 6.9375%. Individuals and companies engaged in business activities within the state are required to pay the GRT on goods and services sold within the State of New Mexico. For goods and services purchased outside of the state, a compensating tax is levied at a rate of 5.125% in order to protect New Mexico businesses from unfair competition from out-of-state businesses not subject to GRT. Both GRT and compensating tax are paid by the selling business, and both are typically passed on to the purchasing party.

A buyer's Gross Receipts Tax liability may be reduced through the use of Industrial Revenue Bonds for eligible expenditures. The Project may obtain an exemption from a portion of GRT and compensating taxes from the issuance of an industrial revenue bond (IRB) under the authority of the County Industrial Revenue Bond Act (Ch. 4, Art. 59, New Mexico Statutes Annotated). An IRB is an economic development tool that assigns the county's tax exemption status to the issuer. The county would be the legal purchaser and owner of the IRB property, then in turn lease the property back to the issuer. In this case, the Company would essentially acquire the tax status of the county, becoming exempt from compensating tax and GRT on purchases of eligible mining and processing equipment.

The Company engaged the law firm, Rodey, Dickason, Sloan, Akin, & Robb, P.A., and the accounting firm, CliftonLarsonAllen LLP (Mims, 2013), to outline legal requirements for use of an IRB on this project, to identify IRB-qualifying equipment proposed for the operation, and to analyze the proposed capital expenditure list in order to develop an appropriate GRT rate to apply to the economic model. Following this review, an effective GRT rate of 4.50% was applied to project capital as an overall average to include the use of IRB(s) and applicable GRT and compensating tax rates.

The Company is continuing efforts with the external consultants to finalize issuance of the IRB. This effort will also require participation and agreement of Sierra County officials. As GRT and compensating taxes are not direct tax revenues to Sierra County, the economic feasibility of issuance is likely. Further, as the Project will be subject to the Copper Ad Valorem Tax, Sierra County will be a direct beneficiary on the levied Copper Ad Valorem Tax.

22.7.3 Other Applicable Taxes

Applicable taxes and tax credits, such as the High Wage Jobs Tax Credit, were reviewed by Accounting and Consulting Group, LLP (ACG). ACG similarly performed an analysis on the potential tax benefit of tax credits and this work is reflected in the economic model.

Withholding Taxes

The employer-portion of withholding taxes is withheld from employees' paychecks for prepayment of the employee's individual income tax and is a fiduciary tax liability of the employer.

The Project will offset withholding taxes with tax credits earned from the State of New Mexico's High Wage Jobs Tax Credit. The credit allows for 10% of wages meeting a certain criterion of wage and benefit level and proof of newly created jobs, with a maximum annual credit of \$12K per newly created position. To qualify for the credit, the employee hired must be a New Mexico resident and occupy the position for 48 weeks out of a 52-week year. Once the position has been filled by an eligible employee, the credit is available for four years.

In order to qualify, the position must be created after July 1, 2004 and prior to July 1, 2026 and the wages and benefits must be at least \$40,000 per annum for jobs performed in a municipality or unincorporated area of a county with a population less than 40,000. Current planning and forecasting show the Company will meet requirements to qualify for the credit and this tax benefit is included in the economic model. As the tax benefit extends over a four-year period, the annual tax savings range from \$2.1M to \$2.3M per year dependent on the employment cycle.

Resource Excise Tax:

Three related excise taxes are collected by the State of New Mexico for natural resources including metals: resources tax, processor tax, and service tax. The processor tax is imposed on any processor of natural resources in New Mexico at the following rates on the taxable value (sale price) of the natural resources:

- All natural resources except potash and molybdenum: 0.75%
- Potash: 0.5%
- Molybdenum: 0.125%

The resource excise tax is imposed on the severer of natural resources, but the taxable value of any natural resource on which the processor tax is paid is exempt from the resource tax. The service tax is imposed for the privilege of severing or processing natural resources owned by others and does not apply to the Copper Flat Project.

Severance Tax (SEV):

New Mexico imposes a SEV on the privilege of severing natural resources. Copper is levied at 0.50 percent of the taxable value of the natural resource; gold and silver at 0.20 percent; and, molybdenum at 0.125 percent.

Ad Valorem Taxes:

Once in production the Company will be subject to the Copper Ad Valorem Tax. In lieu of real estate and tangible personal property taxes, once a copper property is in production, the State of New Mexico will levy a tax calculated as follows:

- The value of any mine and all real property and personal property held or used for the mining of ore from the mine:
 - Any part of which is mined for processing in a concentrator shall be thirty percent of the value of salable copper and other minerals contained in concentrate produced from the ore produced from the mine; or
 - Which is mined solely for solvent extraction or electrowinning shall be twenty percent of the value of salable copper and other minerals produced through solvent extraction or electrowinning from the ore produced from the mine;

- The value of a concentrator and all real property and personal property held or used in connection with the concentrator shall be twenty-five percent of the value of salable copper and other minerals contained in concentrate produced in the concentrator;
- The value of a precipitation plant and all real property and personal property held or used in connection with the precipitation plant shall be twenty-five percent of the value of salable copper and other minerals contained in precipitate produced in the precipitation plant;
- The value of the solvent extraction or electrowinning plant and all real property and personal property held or used in connection with the solvent extraction or electrowinning plant shall be one hundred thirty-five percent of the value of salable copper and other minerals produced through the solvent extraction or electrowinning process, less four times the value of property determined for the same tax year under Subparagraph (b) of Paragraph (1) of this subsection; and,
- The value of a smelter and all real property and personal property held or used in connection with the smelter shall be twenty-one percent of the value of salable copper and other minerals produced in the smelter

22.8 PROJECT FINANCING

The project is evaluated on an unleveraged and un-inflated basis.

22.9 NET INCOME AFTER TAX

Net income after tax amounts to \$515.2 million over the full life-of-mine.

22.10 NET PRESENT VALUE AND INTERNAL RATE OF RETURN

The economic analysis is presented on an after-tax basis and indicates that the project has an after-tax Internal Rate of Return (IRR) of 20.8percent with a payback period of 3.3 years. Table 22-8 compares the base case project financial indicators with the financial indicators when different variables are applied. The results show that metal prices have the most impact on the project while variance in the operating cost has the least impact on project economics.

Table 22-8: After-Tax Sensitivity Analysis

		NPV @ 0%	NPV @ 8%	IRR	Payback (yrs)
Base Case		\$545,158	\$235,174	20.8%	3.3
Metal Prices	20%	\$933,871	\$474,972	31.5%	2.4
	-20%	\$146,812	(\$14,141)	6.9%	7.1
Capital Cost	20%	\$481,671	\$173,043	16.3%	3.9
	-20%	\$607,132	\$295,781	26.8%	2.7
Operating Cost	20%	\$387,326	\$136,923	15.7%	3.8
	-20%	\$700,288	\$330,247	25.5%	2.9

22.11 COPPER PRICE SENSITIVITY CASES

The Feasibility Study includes financial analysis on three scenarios with varying metal prices: 1) The base case uses

a long-term copper price of \$3.25/lb, and 2) A price upside case based on a \$3.60/lb long term copper price (all other metal prices held constant).

The after-tax financial return is shown in Table 22-9, unleveraged and with no escalation in commodity prices.

Table 22-9: Financial Return by Copper Price

Case	NPV@0% (US\$000)	NPV@8% (US\$000)	IRR (%)	Payback (Years)
Base Case	\$545,000	\$235,000	20.8	3.3
Upside Price	\$711,000	\$338,000	25.6	2.9

Base Case: Copper \$3.25/lb, Moly \$10.50/lb, Gold \$1,300/oz and Silver \$16.00/oz

Upside Sensitivity: Copper \$3.60/lb, Moly \$10.50/lb, Gold \$1,300/oz and Silver \$16.00/oz

Table 22-10: Financial Model (Page 1 of 3)

Copper Flat Feasibility Study Update		2019	2020	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033	2034
	Total	-4	-3	-2	-1	1	2	3	4	5	6	7	8	9	10	11	12
Mining Operations																	
Direct Mill Feed Ore																	
Beginning Inventory (kt)	113,084	113,084	113,084	113,084	113,084	112,724	103,784	92,984	82,184	71,384	60,584	50,559	40,659	30,759	20,859	10,959	1,059
Mined (kt)	113,084	-	-	-	360	8,940	10,800	10,800	10,800	10,800	10,025	9,900	9,900	9,900	9,900	9,900	1,059
Ending Inventory (kt)	-	113,084	113,084	113,084	112,724	103,784	92,984	82,184	71,384	60,584	50,559	40,659	30,759	20,859	10,959	1,059	-
Copper Grade (%)	0.298%	0.000%	0.000%	0.000%	0.430%	0.410%	0.400%	0.290%	0.360%	0.320%	0.210%	0.210%	0.240%	0.280%	0.290%	0.270%	0.210%
Moly Grade (%)	0.009%	0.000%	0.000%	0.000%	0.007%	0.012%	0.011%	0.007%	0.010%	0.011%	0.005%	0.005%	0.007%	0.008%	0.010%	0.012%	0.010%
Gold Grade (oz/t)	0.003	-	-	-	0.003	0.004	0.004	0.003	0.003	0.003	0.002	0.002	0.002	0.002	0.002	0.003	0.002
Silver Grade (oz/t)	0.064	-	-	-	0.060	0.080	0.090	0.060	0.070	0.070	0.050	0.050	0.050	0.060	0.060	0.060	0.050
Contained Copper (klbs)	674,297	-	-	-	3,096	73,308	86,400	62,640	77,760	69,120	42,105	41,580	47,520	55,440	57,420	53,460	4,448
Contained Moly (klbs)	20,150	-	-	-	50	2,146	2,376	1,512	2,160	2,376	1,003	990	1,386	1,584	1,980	2,376	212
Contained Gold (oz/t)	308	-	-	-	1	36	43	32	32	32	20	20	20	20	20	30	2
Contained Silver (oz/t)	7,195	-	-	-	22	715	972	648	756	756	501	495	495	594	594	594	53
"High" Low Grade Stockpile Ore																	
Beginning Inventory (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Mined (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Ending Inventory (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Copper Grade (%)	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%
Moly Grade (%)	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%
Gold Grade (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Silver Grade (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Copper (klbs)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Moly (klbs)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Gold (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Silver (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
"Low" Low Grade Stockpile Ore																	
Beginning Inventory (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Mined (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Ending Inventory (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Copper Grade (%)	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%
Moly Grade (%)	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%	0.000%
Gold Grade (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Silver Grade (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Copper (klbs)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Moly (klbs)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Gold (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Silver (oz/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Total Ore																	
Beginning Inventory (kt)	113,084	113,084	113,084	113,084	113,084	112,724	103,784	92,984	82,184	71,384	60,584	50,559	40,659	30,759	20,859	10,959	1,059
Mined (kt)	113,084	-	-	-	360	8,940	10,800	10,800	10,800	10,800	10,025	9,900	9,900	9,900	9,900	9,900	1,059
Ending Inventory (kt)	-	113,084	113,084	113,084	112,724	103,784	92,984	82,184	71,384	60,584	50,559	40,659	30,759	20,859	10,959	1,059	-
Copper Grade (%)	0.298%	0.000%	0.000%	0.000%	0.430%	0.410%	0.400%	0.290%	0.360%	0.320%	0.210%	0.210%	0.240%	0.280%	0.290%	0.270%	0.210%
Moly Grade (%)	0.009%	0.000%	0.000%	0.000%	0.007%	0.012%	0.011%	0.007%	0.010%	0.011%	0.005%	0.005%	0.007%	0.008%	0.010%	0.012%	0.010%
Gold Grade (oz/t)	0.003	-	-	-	0.003	0.004	0.004	0.003	0.003	0.003	0.002	0.002	0.002	0.002	0.002	0.003	0.002
Silver Grade (oz/t)	0.064	-	-	-	0.060	0.080	0.090	0.060	0.070	0.070	0.050	0.050	0.050	0.060	0.060	0.060	0.050
Contained Copper (klbs)	674,297	-	-	-	3,096	73,308	86,400	62,640	77,760	69,120	42,105	41,580	47,520	55,440	57,420	53,460	4,448
Contained Moly (klbs)	20,150	-	-	-	50	2,146	2,376	1,512	2,160	2,376	1,003	990	1,386	1,584	1,980	2,376	212
Contained Gold (oz/t)	308	-	-	-	1	36	43	32	32	32	20	20	20	20	20	30	2
Contained Silver (oz/t)	7,195	-	-	-	22	715	972	648	756	756	501	495	495	594	594	594	53
Waste																	
Beginning Inventory (kt)	44,682	44,682	44,682	44,682	44,682	44,572	36,012	29,312	22,612	15,912	9,212	3,288	797	79	8	5	4
Mined (kt)	44,682	-	-	-	110	8,560	6,700	6,700	6,700	6,700	5,924	2,491	718	71	3	1	4
Ending Inventory (kt)	-	44,682	44,682	44,682	44,572	36,012	29,312	22,612	15,912	9,212	3,288	797	79	8	5	4	-
Total Material Mined (kt)	157,766	-	-	-	470	17,500	17,500	17,500	17,500	17,500	15,949	12,391	10,618	9,971	9,903	9,901	1,063
Stockpile Rehandle	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Total Material Moved (kt)	157,766	-	-	-	470	17,500	17,500	17,500	17,500	17,500	15,949	12,391	10,618	9,971	9,903	9,901	1,063

Table 22-11: Financial Model (Page 2 of 3)

Copper Flat Feasibility Study Update		2019	2020	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033	2034
	Total	-4	-3	-2	-1	1	2	3	4	5	6	7	8	9	10	11	12
Process Plant Operations																	
Concentrator																	
Beginning Ore Inventory (kt)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Mined Ore to Concentrator (kt)	113,084	-	-	-	-	9,300	10,800	10,800	10,800	10,800	10,025	9,900	9,900	9,900	9,900	9,900	1,059
Mined Ore - Processed (kt)	113,084	-	-	-	-	9,300	10,800	10,800	10,800	10,800	10,025	9,900	9,900	9,900	9,900	9,900	1,059
Ending Ore Inventory	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Copper Grade (%)	0.298%	0.000%	0.000%	0.000%	0.000%	0.411%	0.400%	0.290%	0.360%	0.320%	0.210%	0.210%	0.240%	0.280%	0.290%	0.270%	0.210%
Moly Grade (%)	0.009%	0.000%	0.000%	0.000%	0.000%	0.012%	0.011%	0.007%	0.010%	0.011%	0.005%	0.005%	0.007%	0.008%	0.010%	0.012%	0.010%
Gold Grade (oz/t)	0.003	-	-	-	-	0.004	0.004	0.003	0.003	0.003	0.002	0.002	0.002	0.002	0.002	0.003	0.002
Silver Grade (oz/t)	0.064	-	-	-	-	0.079	0.090	0.060	0.070	0.070	0.050	0.050	0.050	0.060	0.060	0.060	0.050
Contained Copper (klbs)	674,297	-	-	-	-	76,404	86,400	62,640	77,760	69,120	42,105	41,580	47,520	55,440	57,420	53,460	4,448
Contained Moly (klbs)	20,150	-	-	-	-	2,196	2,376	1,512	2,160	2,376	1,003	990	1,386	1,584	1,980	2,376	212
Contained Gold (oz/t)	308	-	-	-	-	37	43	32	32	32	20	20	20	20	20	30	2
Contained Silver (oz/t)	7,195	-	-	-	-	737	972	648	756	756	501	495	495	594	594	594	53
Recovery Copper (%)	93.14%	0.00%	0.00%	0.00%	94.60%	94.60%	94.60%	94.60%	94.60%	94.60%	92.14%	91.20%	91.20%	91.20%	91.20%	91.20%	91.20%
Recovery Moly (%)	78.00%	0.00%	0.00%	0.00%	81.90%	81.90%	81.90%	81.90%	81.90%	81.90%	75.76%	73.40%	73.40%	73.40%	73.40%	73.40%	73.40%
Recovery Gold (%)	73.70%	0.00%	0.00%	0.00%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%	73.70%
Recovery Silver (%)	82.70%	0.00%	0.00%	0.00%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%	82.70%
Copper Concentrate (kt)	1,121	-	-	-	-	129	146	106	131	117	69	68	77	90	94	87	7
Copper Concentrator Grade (%)	28.00%	0.00%	0.00%	0.00%	0.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%	28.00%
Recovered Copper (klbs)	628,015	-	-	-	-	72,278	81,734	59,257	73,561	65,388	38,797	37,921	43,338	50,561	52,367	48,756	4,056
Recovered Gold (koz)	227	-	-	-	-	27	32	24	24	24	15	15	15	15	15	22	2
Recovered Silver (koz)	5,950	-	-	-	-	609	804	536	625	625	415	409	409	491	491	491	44
Moly Concentrate (kt)	14	-	-	-	-	2	2	1	2	2	1	1	1	1	1	2	0
Moly Concentrator Grade (%)	55.00%	0.00%	0.00%	0.00%	0.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%	55.00%
Recovered Moly (klbs)	15,717	-	-	-	-	1,799	1,946	1,238	1,769	1,946	760	727	1,017	1,163	1,453	1,744	155
Payable Metals																	
Payable Copper (klbs)	605,586	-	-	-	-	69,697	78,815	57,141	70,934	63,052	37,412	36,567	41,790	48,756	50,497	47,014	3,912
Payable Moly (klbs)	15,560	-	-	-	-	1,781	1,926	1,226	1,751	1,926	752	719	1,007	1,151	1,439	1,727	154
Payable Gold (koz)	214	-	-	-	-	26	30	22	22	22	14	14	14	14	14	21	1
Payable Silver (koz)	5,355	-	-	-	-	548	723	482	563	563	373	368	368	442	442	442	39
Income Statement (\$000)																	
Metal Prices																	
Copper (\$/lb)	\$ 3.25	\$ -	\$ -	\$ -	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25	\$ 3.25
Moly (\$/lb)	\$ 10.50	\$ -	\$ -	\$ -	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50	\$ 10.50
Gold (\$/oz)	\$ 1,300.00	\$ -	\$ -	\$ -	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00	\$ 1,300.00
Silver (\$/oz)	\$ 16.00	\$ -	\$ -	\$ -	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00	\$ 16.00
Revenues																	
Copper Concentrate																	
Copper Revenue (\$ 000)	\$ 1,968,155	\$ -	\$ -	\$ -	\$ -	\$ 226,515	\$ 256,150	\$ 185,709	\$ 230,535	\$ 204,920	\$ 121,588	\$ 118,842	\$ 135,819	\$ 158,455	\$ 164,115	\$ 152,796	\$ 12,712
Moly Revenue (\$ 000)	\$ 163,375	-	-	-	-	\$ 18,696	\$ 20,228	\$ 12,872	\$ 18,389	\$ 20,228	\$ 7,895	\$ 7,554	\$ 10,575	\$ 12,086	\$ 15,107	\$ 18,129	\$ 1,616
Gold Revenue (\$ 000)	\$ 277,667	-	-	-	-	\$ 33,179	\$ 38,907	\$ 29,180	\$ 29,180	\$ 29,180	\$ 18,057	\$ 17,832	\$ 17,832	\$ 17,832	\$ 17,832	\$ 26,748	\$ 1,908
Silver Revenue (\$ 000)	\$ 85,684	-	-	-	-	\$ 8,774	\$ 11,575	\$ 7,717	\$ 9,003	\$ 9,003	\$ 5,969	\$ 5,895	\$ 5,895	\$ 7,074	\$ 7,074	\$ 7,074	\$ 631
Total Revenues	\$ 2,494,881	\$ -	\$ -	\$ -	\$ -	\$ 287,163	\$ 326,860	\$ 235,478	\$ 287,107	\$ 263,331	\$ 153,510	\$ 150,122	\$ 170,121	\$ 195,447	\$ 204,128	\$ 204,747	\$ 16,867
Operating Cost																	
Mining	\$ 311,777	\$ -	\$ -	\$ -	\$ -	\$ 31,709	\$ 32,885	\$ 34,101	\$ 34,154	\$ 33,027	\$ 27,711	\$ 24,148	\$ 22,561	\$ 22,179	\$ 22,933	\$ 23,614	\$ 2,756
Process Plant	\$ 566,996	\$ -	\$ -	\$ -	\$ -	\$ 48,952	\$ 53,277	\$ 53,131	\$ 53,153	\$ 53,180	\$ 50,298	\$ 49,925	\$ 49,955	\$ 50,005	\$ 49,897	\$ 49,927	\$ 5,295
General Administration	\$ 59,822	\$ -	\$ -	\$ -	\$ -	\$ 5,392	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 5,324	\$ 1,193
Royalty	\$ 69,003	\$ -	\$ -	\$ 113	\$ 450	\$ 7,381	\$ 9,055	\$ 6,525	\$ 7,921	\$ 7,285	\$ 4,253	\$ 4,160	\$ 4,699	\$ 5,385	\$ 5,620	\$ 5,689	\$ 467
Treatment & Refining Charges																	
Copper Concentrate																	
Treatment Charges	\$ 95,324	\$ -	\$ -	\$ -	\$ -	\$ 10,971	\$ 12,406	\$ 8,994	\$ 11,166	\$ 9,925	\$ 5,889	\$ 5,756	\$ 6,578	\$ 7,674	\$ 7,949	\$ 7,400	\$ 616
Copper Refining Charges	\$ 51,475	\$ -	\$ -	\$ -	\$ -	\$ 5,924	\$ 6,699	\$ 4,857	\$ 6,029	\$ 5,359	\$ 3,180	\$ 3,108	\$ 3,552	\$ 4,144	\$ 4,292	\$ 3,996	\$ 332
Gold Refining Charges	\$ 1,282	\$ -	\$ -	\$ -	\$ -	\$ 153	\$ 180	\$ 135	\$ 135	\$ 135	\$ 83	\$ 82	\$ 82	\$ 82	\$ 82	\$ 123	\$ 9
Silver Refining Charges	\$ 2,678	\$ -	\$ -	\$ -	\$ -	\$ 274	\$ 362	\$ 241	\$ 281	\$ 187	\$ 184	\$ 184	\$ 184	\$ 221	\$ 221	\$ 221	\$ 20
Transportation	\$ 191,365	\$ -	\$ -	\$ -	\$ -	\$ 22,024	\$ 24,906	\$ 18,057	\$ 22,415	\$ 19,925	\$ 11,822	\$ 11,555	\$ 13,206	\$ 15,407	\$ 15,957	\$ 14,857	\$ 1,236
Moly Concentrate																	
Roasting Charge	\$ 23,575	\$ -	\$ -	\$ -	\$ -	\$ 2,698	\$ 2,919	\$ 1,857	\$ 2,654	\$ 2,919	\$ 1,139	\$ 1,090	\$ 1,526	\$ 1,744	\$ 2,180	\$ 2,616	\$ 233
Transportation	\$ 880	\$ -	\$ -	\$ -	\$ -	\$ 101	\$ 109	\$ 69	\$ 99	\$ 109	\$ 43	\$ 41	\$ 57	\$ 65	\$ 81	\$ 98	\$ 9
Total Operating Cost	\$ 1,374,175	\$ -	\$ -	\$ 113	\$ 450	\$ 135,579	\$ 148,121	\$ 133,292	\$ 143,330	\$ 137,468	\$ 109,928	\$ 105,373	\$ 107,724	\$ 112,231	\$ 114,537	\$ 113,865	\$ 12,165

Table 22-12: Financial Model (Page 3 of 3)

Copper Flat Feasibility Study Update		2019	2020	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033	2034	
Total		-4	-3	-2	-1	1	2	3	4	5	6	7	8	9	10	11	12	
Ad Valorem Tax	\$	10,517			-	1,345	1,531	1,103	1,345	1,234	719	703	797	687	622	432	-	
Severance Tax	\$	2,075			-	239	272	197	239	218	128	125	141	162	169	170	14	
Resources Excise Tax	\$	17,691			-	2,037	2,325	1,686	2,038	1,849	1,102	1,079	1,210	1,390	1,437	1,422	116	
High Wage Jobs Tax Credit	\$	(8,430)			-	(2,107)	(2,107)	(2,107)	(2,107)	-	-	-	-	-	-	-	-	
Corporate and ABQ Overhead	\$	28,047	\$	15,894	\$	1,676	\$	1,676	\$	1,000	\$	500	\$	500	\$	500	\$	500
Salvage Value	\$	(30,318)			-	-	-	-	-	-	-	-	-	-	-	(16,655)	(13,663)	
Reclamation & Closure	\$	52,868	\$	-	\$	-	\$	496	\$	1,256	\$	171	\$	192	\$	160	\$	390
Total Production Cost	\$	1,446,625	\$	15,894	\$	1,676	\$	2,285	\$	3,382	\$	138,264	\$	150,834	\$	134,830	\$	145,735
Operating Income	\$	1,048,256	\$	(15,894)	\$	(1,676)	\$	(2,285)	\$	(3,382)	\$	148,900	\$	176,026	\$	100,648	\$	141,372
Depreciation																		
Initial Capital	\$	404,851				\$	-	\$	57,853	\$	99,148	\$	70,808	\$	50,566	\$	36,153	
Sustaining Capital	\$	40,865				\$	-	\$	750	\$	2,296	\$	3,718	\$	3,780	\$	3,952	
Total Depreciation	\$	445,717	\$	-	\$	-	\$	-	\$	57,853	\$	99,898	\$	73,105	\$	54,284	\$	39,933
Net Income after Depreciation	\$	602,539	\$	(15,894)	\$	(1,676)	\$	(2,285)	\$	(3,382)	\$	91,046	\$	76,128	\$	27,543	\$	87,088
Income Taxes	\$	88,218	\$	-	\$	-	\$	-	\$	6,061	\$	9,763	\$	3,530	\$	11,170	\$	10,481
Net Income after Taxes	\$	514,322	\$	(15,894)	\$	(1,676)	\$	(2,285)	\$	(3,382)	\$	84,985	\$	66,364	\$	24,013	\$	75,919
Cash Flow																		
Operating Income	\$	1,048,256	\$	(15,894)	\$	(1,676)	\$	(2,285)	\$	(3,382)	\$	148,900	\$	176,026	\$	100,648	\$	141,372
Working Capital																		
Account Recievable (60 days)	\$	-	\$	-	\$	-	\$	-	\$	(47,205)	\$	(6,525)	\$	15,022	\$	(8,487)	\$	3,908
Accounts Payable (30 days)	\$	-	\$	-	\$	-	\$	56	\$	(19)	\$	11,107	\$	1,031	\$	(1,219)	\$	825
Inventory - Parts, Supplies	\$	-	\$	-	\$	-	\$	-	\$	-	\$	-	\$	-	\$	-	\$	-
Total Working Capital	\$	0	\$	-	\$	-	\$	56	\$	(19)	\$	(36,098)	\$	(5,495)	\$	13,803	\$	(7,662)
Capital Expenditures																		
Initial Capital																		
Mine	\$	10,490	\$	-	\$	-	\$	-	\$	10,490	\$	-	\$	-	\$	-	\$	-
Process Plant	\$	328,526	\$	-	\$	-	\$	49,279	\$	262,821	\$	16,426	\$	-	\$	-	\$	-
Owners Cost	\$	35,000	\$	-	\$	-	\$	3,500	\$	31,500	\$	-	\$	-	\$	-	\$	-
Sustaining Capital																		
Mine	\$	10,169	\$	-	\$	-	\$	-	\$	1,898	\$	170	\$	404	\$	-	\$	60
Process Plant	\$	30,697	\$	-	\$	-	\$	-	\$	3,350	\$	6,904	\$	7,301	\$	8,356	\$	151
Total Capital Expenditures	\$	414,881	\$	-	\$	-	\$	52,779	\$	304,810	\$	21,675	\$	7,074	\$	7,471	\$	404
Cash Flow before Taxes	\$	633,375	\$	(15,894)	\$	(1,676)	\$	(55,007)	\$	(308,211)	\$	91,127	\$	163,457	\$	106,979	\$	133,306
Cummulative Cash Flow before Taxes	\$		\$	(15,894)	\$	(17,570)	\$	(72,577)	\$	(380,789)	\$	(289,662)	\$	(126,205)	\$	(19,226)	\$	114,081
Income Taxes	\$	88,218	\$	-	\$	-	\$	-	\$	6,061	\$	9,763	\$	3,530	\$	11,170	\$	10,481
Cash Flow after Taxes	\$	545,158	\$	(15,894)	\$	(1,676)	\$	(55,007)	\$	(308,211)	\$	85,065	\$	153,694	\$	103,450	\$	122,137
Cummulative Cash Flow after Taxes	\$		\$	(15,894)	\$	(17,570)	\$	(72,577)	\$	(380,789)	\$	(295,724)	\$	(142,030)	\$	(38,580)	\$	83,557
Economic Indicators before Taxes																		
NPV @ 0%	0%	\$	633,375															
NPV @ 8%	8%	\$	285,370															
IRR			23.0%															
Payback	Years		3.1															
Economic Indicators after Taxes																		
NPV @ 0%	0%	\$	545,158															
NPV @ 8%	8%	\$	235,174															
IRR			20.8%															
Payback	Years		3.3															

23 ADJACENT PROPERTIES

Adjacent lands include federal, state and private property. Federal lands are administered by the BLM, and locally there are numerous placer and lode claims on the federal land held by individuals and clubs for recreational gold panning from surface mineral concentrations.

While other styles of mineralization occur near or immediately adjacent to the project, such as narrow, locally high-grade Au-Ag veins having limited size potential and historic polymetallic replacement deposits, there are no other known porphyry copper deposits adjacent to or in close proximity to the Copper Flat Project. The closest known occurrences of bulk copper mineralization are outside of Silver City, NM, and are approximately 33 miles (straight-line) away from the Copper Flat property.

24 OTHER RELEVANT DATA AND INFORMATION

The status of environmental permitting is presented in Sections 4.6 and 20.4 of this report. The status of environmental studies is presented in Section 20.1. Acquisition of water rights, financial assurance, project financing, obtaining the mine permit and tailings dam permit, developing a project development plan, and detailed engineering remain to be completed before making the decision to proceed with construction of the project.

25 INTERPRETATION AND CONCLUSIONS

The Copper Flat Project has completed several important permits and may be ready for a development decision soon. A permit that remains is a mining permit from the Mining and Minerals Division of the New Mexico Energy, Minerals and Natural Resources Department (MMD). A recent order received from the Director of MMD states requirements necessary water rights, demonstrate that NMCC has obtained or is likely to obtain a dam safety permit for the tailings storage facility, and complete financial assurance of reclamation and closure of the site before a mining permit can be issued. The economic analysis provided in this report demonstrates that the project is economically viable. The objectives for the NMCC management team should be focused on further development and evaluation of the project including moving forward on detailed engineering and a detailed estimate for cost control.

25.1 CONCLUSIONS

The reserve model and reserve classification developed for this report meets or exceeds CIM reporting standards. It is believed that the quality and quantity of the data used to develop the reserve model is sufficient and the methodology used to prepare the reserve model is correct. Consequently, it is believed that the reserve model will be a reasonable predictor of the copper and molybdenum grades and tonnages specified in the report's mine plan.

Comprehensive metallurgical testing conducted on the Copper Flat mineralization more than thirty years ago and the process used in the 1982 Quintana Minerals operation are still valid, as confirmed by recent metallurgical test results. The results of the CSMRI pilot plant tests, recent metallurgical testing, and operation of the Quintana concentrator for three and-a-half months in 1982 demonstrate the success of the process and that there are no adverse processing factors that require any extraordinary process engineering or deleterious elements in the Copper Flat ore. The ore is of medium hardness, amenable to copper/moly flotation, gives products that thicken and filter readily and will produce saleable copper and moly concentrates. The conceptual process flow sheet and processing design developed as part of this study is considered "Standard" practice in the mining industry. It is believed that the processing plant is capable of achieving an average of 10.8 million tons per year and that the process will yield metal recoveries as stated in the report.

The tailings storage facility design developed for this study utilizes best technological practices to ensure containment of the processed tailings. Additionally, the design capacity of the tailings storage facility is sufficient to contain the reserves stated in this report in an environmentally sound manner.

Access has been secured to all land within the permit boundary, removing uncertainties concerning the ability to implement the plans in this report in terms of land access.

Access to electrical power to sustain the operation as specified in this report is believed to be reasonable and achievable.

An adequate water supply is also necessary to sustain the operation described in this report. The amount of water currently approved for use at Copper Flat is not sufficient to operate as currently planned; additional water sources with potential to supply the difference have been identified and access to the amount needed for the operation is considered to be achievable.

25.2 RISKS

The following risks are noted for the Project:

- Market risks associated with base metal and precious metal mining projects always exist. The economics of this project is used a base case of \$3.25 copper price, \$9.50 molybdenum price, \$1,300 gold price and \$16 silver price.
- Capital costs and construction estimates were based on recent prevailing costs in the construction industry, which are presently moderately competitive. If the competitiveness of the construction industry were to change, the cost of the project could increase at the time of actual construction.

25.2.1 Tailings Risks

The following risks with respect to the TSF are noted:

- In general, earthwork construction projects face inherent risk associated with unexpected subsurface conditions. Time and financial restraints allow only a small portion of the underlying foundation materials to be inspected and tested. Unexpected conditions could impact borrow material availability and construction costs.
- Alternatives for TSF construction are constrained by existing permit limits. The TSF site is both the construction area and the source of borrow materials. Multiple handling of some of the construction materials will be required, and a significant volume of material must be excavated and stockpiled during initial construction.
- Buried infrastructure from the old Quintana TSF may impact construction costs. The capital cost estimate for TSF earthworks includes an allowance of \$1,000,000 for removal of the old decant towers and buried structures. Available information and the regulatory restrictions imposed on site access and subsurface investigation do not allow an assessment of the extent of buried structures that could require demolition and disposal during construction of the new facility, and their impact on construction costs.
- Unthickened cyclone overflow delivered at the proposed processing rate will exhibit less than optimum consolidation behavior under field conditions due to the fine-grained nature of the tailings and a high rate of rise inside the TSF. As such, a large storage volume is required to meet disposal requirements and under existing property restrictions, the alternative available to provide storage capacity is to increase the height of the TSF. The design proposed herein will require near constant operation of the cyclone plant in order to provide sufficient cyclone underflow sand to construct the dam to the elevation needed to contain the tailings. Failure to maximize sand recovery through cyclone plant operation will result in the discharge of whole tailings into the TSF and as a consequence, sand and storage capacity will be lost. It may be feasible to use waste rock or borrowed fill material to supplement the cyclone underflow for dam construction, however, costs associated with fill placement for such methods are anticipated to exceed those of sand use and borrowed fill placement costs could adversely impact project economics.
- Tailings provided for use in geotechnical evaluation of tailings behavior, however well selected to be representative of future tailings, were derived from small samples relative to the mass of the ore reserve. Variations in the mined ore and the tailings delivered to the impoundment could potentially impact predicted TSF operation and performance.
- Given the current site constraints, mine processing plan and ore reserve, designing a TSF with the capacity to meet tailings storage requirements places a high demand on the availability of cyclone underflow sand for dam construction. It is estimated that cyclone plant utilization must exceed 97 percent in order to meet construction sand requirements. The required utilization rate is higher than the utilization rates typically used in the design of similar facilities and milling, and processing rates may be impacted if sand production must be a priority. In order to maintain cyclone plant operation and produce the quantity of construction sand at the

quality required for dam construction, the operator will need to commit to continuous operation and rigorous operating procedures.

25.3 OPPORTUNITIES

The following opportunities are noted for the project:

- Upside market potential associated with base metal and precious metal pricing exists. The economics of this project is used a base case of \$3.25 copper price, \$10.50 molybdenum price, \$1,300 gold price and \$16 silver price.
- Other activities as discussed in the recommendations section of this report, once implemented, have the potential to improve project economics.
- The economic model forming the basis of the study assumes all mill processing equipment is purchased new. However, the standard mining and ore treatment methods considered create an opportunity to reduce project capital costs through the utilization of used, refurbished equipment or equipment that becomes available through canceled orders.
- The study assumes mining is self-performed with leased mining equipment. An opportunity to realize a benefit in the overall operation may exist through employment of a contract miner. Mining costs are typically increased with a contract miner; however, offsetting benefits may be realized by contracting the mine operations and mine maintenance functions to an outside party.

25.3.1 Tailings Opportunities

The following opportunities with respect to the TSF are noted:

- Initial earthwork requirements could be substantially reduced if alternative sources for construction borrow and reclamation cover materials could be developed outside the TSF footprint.
- The operator should monitor tailings consolidation and post deposition density during operations. If tailings consolidation rates exceed predictions, it may be possible to decrease cyclone plant utilization, reduce the ultimate height of the TSF, and reduce sand demand.
- While producing adequate sand may impact the operator's maintenance and operating schedules, there are several tailings distribution system design features that will facilitate high cyclone plant utilization.
- The plant will contain 20 cyclones in a single cluster with 16 cyclones required to process the tailings inflow. There will be extra cyclones that can be brought online if one fails. Normal maintenance of the cyclones can be undertaken while the plant is in operation.
- Cyclones have no moving parts and while subject to wear they are relatively maintenance free.
- It is assumed that the operator will monitor cyclone plant conditions and conduct maintenance of other cyclone plant components coincident with process facility maintenance shutdowns (the design process plant availability is 92.5 percent).
- If the cyclone plant cannot be operated for short periods of time, discharge from the flotation plant can be routed to an emergency pond for temporary storage. Tailings collected in the emergency pond can then be returned to the cyclone plant feed sump when the processing facilities are down for maintenance. Use of the emergency pond during periodic upset conditions will reduce the loss of construction sand.

- The cyclone underflow distribution system has two legs, one routed southward and one northward around the TSF. Each leg is capable of transporting the entire cyclone underflow and can be operated independently. Underflow discharge can be maintained in one leg while the other is serviced or relocated. The availability of two underflow distribution pipes will facilitate continuous sand placement on the dam.
- Replacement of individual cyclones is a relatively easy process. The operator should have spares on site to cover this eventuality.

26 RECOMMENDATIONS

Because the economic analysis provided in this report demonstrates that the project is economically viable, the THEMAC management team should focus on further development and evaluation of the project including moving forward on detailed engineering. Costs for detailed engineering estimated at \$14.7 million are included in the feasibility study capital cost estimate.

26.1 MINING AND MODELING

The following recommendations should be considered by NMCC regarding mining and modeling.

- 1) Geologic interpretation of rock type and structure should continue as detailed engineering advances. Improved definitions of rock and structure could improve grade estimation and prediction of process response.
- 2) Communication should be continued between the project geology team and the process design engineers. Updated understanding of geology could impact process design and testing in the future.
- 3) Geotechnical work in the pit may be considered as detailed engineering advances. Improved understanding of pit slope stability could have an impact on future pit designs.

26.2 METALLURGY

Metallurgical testing was conducted as part of the feasibility study, as presented in Section 13. The results of that work in conjunction with previous testing and review of production data from the previous operation of the mine are deemed to be sufficient to support development of the project. No additional metallurgical testing is recommended at this time.

26.3 TAILING STORAGE FACILITY

Sufficient testing of materials has been conducted to assign design criteria and to support detailed engineering of the TSF. Detailed engineering of the TSF should include the development of an operating plan that will facilitate meeting cyclone plant operation and sand production requirements. No additional material testing is recommended at this time.

26.4 ENVIRONMENTAL

The mine waste rock disposal facilities will be constructed to facilitate final grading for reclamation. During detailed operating plan development, consider and advance strategies to complete final grading, topsoil spreading and seeding concurrently with mining activities.

26.5 PROJECT DEVELOPMENT

Proceed with development of a project execution plan to guide activities leading to and initiating project construction.

26.6 WATER RESOURCES

Secure a water supply in full amount needed to support the operation.

27 REFERENCES

- ACG, 2013. *Tax Liability Opinion Letter to New Mexico Copper Corporation*, Accounting & Consulting Group, LLP, May 16, 2013.
- Adams, M.K., 2013. *Updated Title Report – Copper Flat Properties – Sierra County, New Mexico*, Rodey, Dickason, Sloan, Akin & Robb, PA, June 26, 2013.
- Adams, M.K., 2013b. *Updated Title Report – Copper Flat Properties – Sierra County, New Mexico, Summary Letter to New Mexico Copper Corporation*, Rodey, Dickason, Sloan, Akin & Robb, PA, October 28, 2013.
- Adams, M.K., 2020. *Copper Flat Properties Identified in Updated Title Report of Rodey, Dickason, Sloan, Akin & Robb, P.A. dated June 26, 2013 (the "Properties")*, February 6, 2020.
- Adrian Brown Consultants, Inc. (ABC), 1996. *Groundwater Impact Evaluation, Copper Flat Project*, Prepared for Alta Gold Company, September 1996.
- Butzier, S.B., 2020. *Status of Environmental Compliance of New Mexico Copper Corporation's Copper Flat Project*, March 19, 2020.
- Colorado School of Mines Research Institute (CSMRI), 1976a. *Recovery of Precious Metals from the Copper Flats Deposit*, Technical Report, June 1976.
- Contract Support Services, Inc., 2012. *Results - NMCC Copper Flat Simulations to Determine Maximum Throughput for two 60/40 Ore Blends, with and without Pebble Crusher Rev B*, March 2, 2012.
- CSMRI, 1976b. *Process Development and Pilot Plant Operations for Treatment of the Copper Flats Deposit*, Technical Report, July 1976.
- DuMars, C.T. and Robinson, C.R., 2013. *New Mexico Office of the State Engineer Files No. LRG-4652 through LRG-4652-S-17, LRG-4654*, Law and Resource Planning Associates, PC, June 10, 2013.
- Dunn, P.G., 1984. *Geologic Studies During the Development of the Copper Flat Porphyry Deposit*, Mining Engineering, February, 1984, pg.151. Dunn, P.G., 1992. *Development Geology of the Copper Flat Porphyry Copper Deposit*, in *SME Mining Engineering Handbook*, 2nd Edition, Vol 1. Howard L. Hartman, Senior Editor, Society of Mining, Metallurgy, and Exploration, Inc.
- Dunn, P.G., 1982. *Geology of the Copper Flat porphyry copper deposit, Hillsboro, Sierra County, New Mexico: in Advances in Geology of the Porphyry Copper Deposits Southwestern North America*, Spencer R. Titley, Editor, University of Arizona Press, Tucson, Arizona, pp. 313-325.
- Dunn-Behre Dolbear, 1993. *Due Diligence Study of the Copper Flat Porphyry Copper Project, New Mexico*, Unpublished Report for Gold Express Corp. dated January 1993.
- FLSmith Knelson, 2012. *Gravity Test Work Report*, May 3, 2012.
- G&T Technical Services (G&T), 2012. *Understanding Gold Deportment at the Copper Flats Deposit*. February 22, 2012.
- Golder Associates (Golder), 2016a, *Mine Reclamation and Closure Plan, Copper Flat Mine*, October 7, 2016.
- Golder Associates (Golder), 2016b. *Feasibility Level Design, 30,000 TPD Tailings Storage Facility, Volume 1; Tailings Distribution and Water Reclaim System Feasibility Study, Volume 2, Copper Flat Project, Sierra County, New Mexico*. December 16, 2016.
- Golder Associates (Golder), 2017. *Copper Flat Project TSF Capital and Operating Cost Estimate Update*, December 19, 2017.

- Hall, A., 2013. *Memorandum Re: Industrial Revenue Bond for Copper Flat Project*, Rodey, Dickason, Sloan, Akin & Robb, PA, October 1, 2013.
- Harley, G.T., 1934. *The Geology and Ore Deposits of Sierra County, New Mexico: New Mexico School of Mines, State Bureau of Mines and Mineral Resources Bulletin No. 10*, pp. 160-170.
- Hazen Research, Inc. (Hazen), 2011a. *Comminution Testing, Final Report*, June 23, 2011.
- Hazen, 2011b. *Final Report for Bond Abrasion Tests*, August 11, 2011.
- Hazen, 2012. *Comminution Testing for Copper Flat Project*, February 10, 2012.
- Hedlund, D. C., 1974. *Age and Structural Setting of Basemetal Mineralization in the Hillsboro San Lorenzo Area, Southwestern New Mexico*, in Siemers, C. T., Woodward, L. A.
- Hood, M., Peña, F., Avelar, J.T. and Bailey, J., undated. *Sampling and Scale-up of SAG Tests*, undated.
- John Shomaker and Associates, Inc., 2012. *Conceptual Model of Groundwater Flow in the Animas Uplift and Palomas Basin, Copper Flat Project, Sierra County, New Mexico*, John Shomaker and Associates, Inc., Albuquerque, New Mexico. May 2012.
- John Shomaker and Associates, Inc., 2013. *Status Report for Stage 1 Abatement at the Copper Flat Mine Site Near Hillsboro, New Mexico*, John Shomaker and Associates, Inc., Albuquerque, New Mexico. June 2013.
- John Shomaker and Associates, Inc., 2013b. *Draft Capacity Analysis of Supply Wells Associated with LRG-4652 et al., and LRG-4654*, John Shomaker and Associates, Inc., Albuquerque, New Mexico. April, 2013.
- John Shomaker and Associates, Inc., 2014. *Results from First Year of Stage 1 Abatement Investigation at the Copper Flat Mine Site Near Hillsboro, New Mexico*, May 2014.
- Jones, B.K., 1992. *Application of Metal Zoning to Gold Exploration in Porphyry Copper Systems*. Journal of Geochemical Exploration, 43, pp.127-155.
- Kuellmer, F.J., 1955. *Geology of a Disseminated Copper Deposit near Hillsboro, Sierra County, New Mexico*, New Mexico Bureau of Mines and Mineral Resources, Circular 34, 46p.
- Inglebinck, M., 2013. *Memorandum Guidance for Treatment and Refining Charges to be used in the Definitive Feasibility Study for New Mexico Copper Corporation*, June 3, 2013.
- Lightner, F.H., 1976. *Molybdenite Circuit Testwork, Copper Flat, Hillsboro Project*, May 1976.
- Livingston, 2011. *Copper Flat Project Water Supply Delivery System*. Livingston Associates, PC, Alamogordo, New Mexico, November 2011.
- Lowell, J. D. 1988. *Gold Mineralization in Porphyry Copper Deposits*, AIME-SME Preprint No. 88-117, 17p.
- M3 Engineering & Technology Corp. (M3), 2011. *Copper Flat Project, Prefeasibility Tradeoff Studies, New Mexico, USA*. November 18, 2011.
- M3 Engineering & Technology Corp.(M3), 2012a. *Copper Flat Project, Form 43-101F1 Technical Report, Prefeasibility Study, New Mexico, USA*. August 22, 2012.
- M3 Engineering & Technology Corp.(M3), 2012b. *Copper Flat Project, Tailings Disposition Tradeoff Study, New Mexico, USA*. November 27, 2012
- M3 Engineering & Technology Corp. (M3), 2013. *Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study, New Mexico, USA*. November 21, 2013.

- McLemore, V.T., Munroe, E.A., Heizler, M.T. and McKee, C. 1999. *Geochemistry of the Copper Flat Porphyry and Associated Deposits in the Hillsboro Mining District, Sierra County, New Mexico, USA*, in: Journal of Geochemical Exploration 67, pp. 167–189.
- McLemore, V.T., Munroe, E.A., Heizler, M.T. and McKee, C. 2000. *Geology and Evolution of the Mineral Deposits in the Hillsboro District, Sierra County, New Mexico, Geology and Ore Deposits 2000*. in The Great Basin and Beyond, proceedings Volume One, 17p.
- McLemore, V.T., 2001. *Geology and evolution of the Copper Flat porphyry system, Sierra County, New Mexico*. New Mexico Bureau of Mines and Mineral Resources.
- METCON Research, Inc. (METCON), 1993. *Preliminary Metallurgical Investigation (Flotation), Copper Flats Project*, December 15, 1993.
- Mims, M.J., 2013, Effective Tax Rate Analysis for the Copper Flat Project (Spreadsheet Calculation), CliftonLarsonAllen LLP, September 18, 2013.
- Mine Design Engineering (MDEng), 2013, Feasibility Level Geotechnical Analysis for the Open Pit Mine Plans of the Copper Flat Copper-Molybdenum Project, Sierra County, NM, February 4, 2013.
- Minerals Advisory Group Research & Development (MAG), 2013a, *Copper Flats Project Final Report*, July 2013.
- Minerals Advisory Group Research & Development (MAG), 2013b, *Copper Flats Project Molybdenum Evaluation of Composite 0-5 Year Mine Life Interval*, March 2013.
- Munroe, E., McLemore, V.T. and Kyle, P., 1999. *Waste Rock Pile Characterization, Heterogeneity, and Geochemical Anomalies in the Hillsboro Mining District, Sierra County, New Mexico*, in: Journal of Geochemical Exploration, Volume. 67, pp. 391-405.
- Nevada Bureau of Land Management (NBLM), 2010. *Nevada Bureau of Land Management Rock Characterization Resources and Water Analysis Guidance for Mining Activities*, Instruction Memorandum NV-2010-014, January 8, 2010).
- Newcomer, R.W. Jr., Shomaker, J.W., Finch, S.T. Jr., 1993. *Hydrologic Assessment Copper Flat Project*. Sierra County, New Mexico, Report for Gold Express Corporation. New Mexico Department of Workforce Solutions Economic Research & Analysis Bureau, 2008. *Wage Information for Job Seeker, Southwestern WIA Area*.
- New Mexico Copper Corp (NMCC), 2017, *Updated Mining Operation and Reclamation Plan for the Copper Flat Mine, Revision 1*, July 2017.
- New Mexico Copper Corp (NMCC), 2019a, List of Mining Claims, August 1, 2019.
- New Mexico Copper Corp (NMCC), 2019b, *Copper Flat Mine 43 CFR 3809 Plan of Operations*, May 2019.
- New Mexico MMD, 2018, *Approvable Permit Application Package, Copper Flat Mine, Sierra County, Permit Tracking No, S1027RN*, July 13, 2018.
- New Mexico MMD, 2018b, *Status Update and Steps Remaining for Permit Issuance, Copper Flat Mine, Sierra County, Permit Tracking No, S1027RN*, December 21, 2018.
- New Mexico MMD, 2019, *No Additional Technical Comment on Financial Assurance Cost Estimate, Submit SRCE R2 for Copper Flat Mine, Sierra County, Permit Tracking No, S1027RN*, August 21, 2019.
- New Mexico MMD, 2020, *Rescission of Notice of Technical Approvability, Copper Flat Mine, Sierra County, Permit Tracking No, S1027RN*, March 31, 2020.
- Orth, F., 2018a, *Hearing Officer's Report, Proposed Findings of Fact and Conclusions of Law In the Matter of the Application of New Mexico Copper Corporation for a Groundwater Discharge Permit For the Copper Flat Mine DP-1840*, December 3, 2018.

- Orth, F., 2018b, *Hearing Officer Report, In the Matter of the Application of New Mexico Copper Corporation for a Mine Permit For the Copper Flat Mine, Sierra County, New Mexico, Permit No. S1027RN*, December 28, 2018.
- Phillips, W.J., 1973. *Mechanical Effects of Retrograde Boiling and its Probable Importance in the Formation of Some Porphyry Ore Deposits*, in: Institution of Mining Metallurgy Transactions, Sec. B, V. 82, pp. 90-98.
- Pincock, Allen, and Holt (PAH), 1979a. *Review of Selected Metallurgical Test Information, Copper Flat Project*, Technical Report, March 1979.
- Pincock, Allen, and Holt (PAH), 1979b. *Statistical Evaluation of Pilot Plant Metallurgical Information*, Technical Report, July 23, 1979.
- Pincock, Allen, and Holt (PAH), 1979c. *Appendix I: Koppers Company Grinding Data*, in Flotation Investigation – Hillsboro Ore Samples, for Quintana Minerals Corporation, unpublished report, December 1979.
- Pincock, Allen, and Holt (PAH), 1980. *1980 Reserve Estimate*, for Quintana Minerals Corporation, unpublished report.
- Pincock, Allen, and Holt (PAH), 1989. *1989 Reserve Estimate*, for Quintana Minerals Corporation, unpublished report.
- Pincock, Allen, and Holt (PAH), March 1998, *1998 Reserve Audit, Copper Flat*, Technical Report.
- Pincock, Allen, and Holt (PAH), March 1999, *1999 Reserve Audit, Copper Flat*, Technical Report.
- Pocock Industrial, Inc., 2011, *Sample Characterization & PSA, Flocculant Screening, Gravity Sedimentation, Pulp Rheology, Pressure Filtration, and Vacuum Filtration Studies*, October, 2011
- Popp, A.V., Peach, J. and Delgado, L., 2012. *The Socioeconomic Impacts of THEMAC Resources Group Ltd. Copper Flat Mine Project in Sierra County, New Mexico*, Arrowhead Center, NMSU, August 15, 2012.
- Raugust, J. S., 2003. *The Natural Defenses of Copper Flat, Sierra County, New Mexico*, New Mexico Bureau of Geology and Mineral Resources, Open File Report, NMBGMR OFR-475, 485p.
- Raugust, J.S. and McLemore, V.T., 2004. *The Natural Defenses of Copper Flat, Sierra County, New Mexico: American Society of Mining and Reclamation, 2004 National Meeting of the American Society of Mining and Reclamation and the 25th West Virginia Surface Mine Drainage Task Forces*, April 18-24, 2004, pp. 1508-1531.
- Reeves, C.C. Jr., 1963. *Economic Geology of a Part of the Hillsboro, New Mexico, Mining District*, in: Journal of Economic Geology, vol. 58, pp. 1278-1284.
- Richards, J.P., 2003. *Tectono-Magmatic Precursors for Geophysical Data Over a Copper Gold Porphyry Cu-(Mo-Au) Deposit Formation*, in: Journal of Economic Geology, V. 96 pp. 1419–1431.
- Segerstrom, K. and Antweiler, J.C., III, 1975. *Placer-Gold Deposits of the Las Animas District, Sierra Count, New Mexico*, U.S. Geological Survey Open-File Report 75-206, 38p.
- Shantz, R., 1981a. *Preliminary Results of Flotation Tests: Grind vs. Recovery*, July 30, 1981.
- Shantz, R., 1981b. *Pyrite and Chalcopyrite Content of QMC Materials*, August 27, 1981.
- Shomaker, J.W., 1993. *Effects of pumping for water supply and mine dewatering, Copper Flat Project, Sierra County, New Mexico*. Consultant's report prepared by John W. Shomaker, Inc. for Gold Express Corporation, 19 p.

- SRK Consulting (U.S.), Inc. (SRK), 1996. *Copper Flat Mine Mining Permit Application, Volume 1, Project Description*, for Alta Gold Company, February 1996, 142p.
- SRK Consulting (U.S.), Inc. (SRK), 1997. *Copper Flat Mine, Compilation of Pit Lake Studies*, December 1997.
- SRK Consulting (U.S.), Inc. (SRK), 1999. *Preliminary Final Environmental Impact Statement Copper Flat Project*, March 1999.
- SRK Consulting (U.S.), Inc. (SRK), 2010. *NI 43-101 Preliminary Assessment THEMAC Resources Group Limited Copper Flat Project Sierra County, New Mexico*, June 2010.
- SRK Consulting (U.S.), Inc. (SRK), 2013. *Geochemical Characterization Report for the Copper Flat Project, New Mexico*, June 2013.
- SRK Consulting (U.S.), Inc. (SRK), 2013b. *Predictive Geochemical Modeling of Pit Lake Water Quality at the Copper Flat Project, New Mexico*, September 2013.
- SRK Consulting (U.S.), Inc. (SRK), 2013c. *Copper Flat Project 2013 Feasibility Study Closure Estimate – FINAL*, November 18, 2013.
- SRK Consulting (U.S.), Inc. (SRK) and Adrian Brown Consultants, Inc. (SRK-ABC). 1995. *Copper Flat Mine Hydrogeological Studies. Copper Flat, New Mexico*. Prepared for Alta Gold Company. May 12, 1995.
- THEMAC Resources, Ltd. (THEMAC), 2013. *Previous Disturbance Areas within Copper Flat Permit Boundary*. May 2013.
- U.S. Army Corps of Engineers (ACOE), 2020. *Nationwide Permit (NWP) Verification - Action N0, SPA-2019-00301, Copper Flat Mine Project*, February 6, 2020.
- U.S. Bureau of Land Management (BLM), 1996. *Draft Environmental Impact Statement Copper Flat Project, New Mexico*, February 1996.
- U.S. Bureau of Land Management (BLM), 1999. *Preliminary Final Environmental Impact Statement Copper Flat Project*, Las Cruces Field Office.
- U.S. Bureau of Land Management (BLM), 2010. http://www.blm.gov/mt/st/en/prog/mining/claim_info.html, accessed June 11, 2010.
- U.S. Bureau of Land Management (BLM), 2019a, *Copper Flat Copper Mine Final Environmental Impact Statement*, Sierra County, New Mexico, April 19, 2019.
- U.S. Bureau of Land Management (BLM), 2019b, *Copper Flat Mine Environmental Impact Statement Record of Decision*, August 2019.

APPENDIX A: FEASIBILITY STUDY CONTRIBUTORS AND PROFESSIONAL QUALIFICATIONS

Certificate of Qualified Person

Richard K Zimmerman

I, Richard K Zimmerman, R.G., SME-RM, do hereby certify that:

1. I am currently employed as a Registered Professional Geologist by:
M3 Engineering & Technology Corporation
2051 W. Sunset Road, Ste. 101
Tucson, Arizona 85704
U.S.A.
2. I am a graduate of Carleton College and received a Bachelor of Arts degree in Geology in 1976. I am also a graduate of the University of Michigan and received a M.Sc. degree in Geology 1980.
3. I am a:
 - Registered Professional Geology in the State of Arizona (No. 24064)
 - Registered Member in good standing of the Society for Mining, Metallurgy and Exploration, Inc. (No. 3612900RM)
4. I have practiced geology, mineral exploration, environmental remediation, and project management for 40 years. I have worked for mining and exploration companies for 8 years, engineering consulting firms for 22 years, and for M3 Engineering & Technology Corporation for 9 years. My experience includes mine geology and exploration, ore reserve estimation, capital and operating cost estimation, mine process plant design, and managing feasibility studies for mining projects.
5. I have read National Instrument 43-101 (NI 43-101) and Form 43-101F1, and the Technical Report has been prepared in compliance with that instrument and form.
6. I have read the definition of "qualified person" set out NI 43-101 and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
7. I am responsible for Sections 1, 2, 3, 7, 8, 9, 19, 24, 25, 26.4, 26.5, 26.6, 27 of the technical report titled "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study Update, New Mexico, USA" (the "Technical Report"), dated effective 11 December 2018, prepared for THEMAC Resources Group, Ltd.
8. My most recent visit to the project site was on 31 January 2013. I had prior involvement with the property that is subject of the Technical Report managing prefeasibility and feasibility studies for the Project.
9. As of the effective date of the technical report, to the best of my knowledge, information and belief, the Technical Report contains all scientific and technical information required to be disclosed to make the report not misleading.
10. I am independent of the issuer applying all of the tests in section 1.5 of National Instrument 43-101.
11. I consent to the filing of the Technical Report with any stock exchange and other regulatory authority and any publication by them of the Technical Report for regulatory purposes, including electronic publication in the public company files on their websites accessible by the public.

Signed and dated this 9th day of April 2020.

(Signed and sealed) "Richard K Zimmerman"

Richard K Zimmerman, M.Sc., R.G., SME-RM No. 3612900RM

Certificate of Qualified Person

Jeffrey C. Smith

I, Jeffrey C. Smith, P.E. do hereby certify that:

1. I am the Chief Operating Officer of:
THEMAC Resources Group, Copper Flat Mine
85 Copper Rock Rd.
Hillsboro, NM 88048
USA
2. I am a graduate of The University of Arizona in Tucson, Arizona, where I earned a Bachelor of Science Degree in Mining Engineering in 1979, and I am also a graduate of the Stanford University Graduate School of Business where I earned a Master of Science Degree in Management in 1998.
3. I am a:
Registered Professional Engineer (Mining) in the State of Arizona (No. 46114)
Registered Professional Engineer (Mining) in the State of Nevada (No. 6906)
Registered Member of the Society for Mining, Metallurgy, and Exploration (No. 3000816RM)
4. I have worked as a mining engineer, operations manager, mine manager, vice president, and chief operating officer within the mining industry for 40 years. My work experience includes open pit design; short and long term mine planning; ore reserve estimation; surveying, ore control, supervising drilling, sampling and assay programs; front line supervision; managing open pit and underground mines; managing ore processing plants; planning and managing mobile and fixed plant maintenance; budgeting; cost estimating; reclamation planning and estimating; environmental compliance; mine administration; and capital project management.
5. I have read the definition of "Qualified Person" set out in National Instrument 43-101 ("NI 43-101") and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "Qualified Person" for the purposes of NI 43-101.
6. I maintain an office at the Copper Flat Mine Property and am onsite on a regular basis. The most recent dates I was at the Copper Flat property was March 16 through March 20, 2020.
7. I am an employee of THEMAC Resources and not independent of the issuer. I have been employed by THEMAC since December 2012. I have held my current position with THEMAC since June 2013. In my current position, I am responsible for all activities associated with development of the Copper Flat Mine, including engineering, permitting, regulatory compliance, and administrative functions.
8. I am responsible for Sections 4, 5, 6, 18, 20, and 23 of the technical report titled, "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study Update, New Mexico, USA" (the "Technical Report") dated effective 11 December 2018, prepared for THEMAC Resources Group, Ltd.
9. I have read National Instrument 43-101 and Form 43-101F1 and to my knowledge the Technical Report has been prepared in compliance with the instrument and form.
10. As of the effective date of the Technical Report, to the best of my knowledge, information and belief, the Technical Report contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Signed and dated this 9th day of April 2020.

(Signed and sealed) "Jeffrey C. Smith"

Jeffrey C Smith, M.Sc., P.E.

Certificate of Qualified Person

John M. Marek

I, John M. Marek, P.E. do hereby certify that:

1. I am currently employed as the President and a Senior Mining Engineer by: Independent Mining Consultants, Inc.

3560 E. Gas Road
Tucson, Arizona, USA 85714
2. This certificate is part of the report titled "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study Update, New Mexico, USA", dated effective 11 December 2018 prepared for THEMAC Resources Group, Ltd.
3. I graduated with the following degrees from the Colorado School of Mines:
 - Bachelors of Science, Mineral Engineering – Physics 1974
 - Masters of Science, Mining Engineering 1976

I am a:

- Registered Professional Mining Engineer in the State of Arizona USA Registration # 12772
 - Registered Professional Engineer in the State of Colorado USA Registration # 16191
 - Registered Member of the American Institute of Mining and Metallurgical Engineers, Society of Mining Engineers
4. I have worked as a mining engineer, geoscientist, and reserve estimation specialist for more than 40 years. I have managed drill programs, overseen sampling programs, and interpreted geologic occurrences in both precious metals and base metals for numerous projects over that time frame. My advanced training at the university included geostatistics, and I have built upon that initial training as a resource modeler and reserve estimation specialist in base and precious metals for my entire career. I have acted as the Qualified Person on these topics for numerous Technical Reports. My work experience includes mine planning, equipment selection, mine cost estimation and mine feasibility studies for base and precious metals projects worldwide,
 5. I visited the Copper Flat property on September 7 – 8, 2011.
 6. I am responsible for Sections 10, 11, 12, 14, 15, 16, 21.2, 21.3.1, and 26.1 of the report titled "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study Update, New Mexico, USA", dated effective 11 December 2018.
 7. I am independent of THEMAC Resources Group Limited applying the tests in Section 1.5 of National Instrument 43-101.
 8. Independent Mining Consultants, Inc. has worked on this project during 2011 and 2012. IMC also completed minor support work during 2016 and 2017. John M. Marek worked briefly on the project as a junior engineer during the early 1980's while employed at different company. John Marek was an author of the document "Copper Flat Project, Form 43-101F1 Technical Report, Mineral Resource Statement" dated 23 January 2012.
 9. I have read National Instrument 43-101 and Form 43-101F1, and to my knowledge, the Technical Report has been prepared in compliance with that instrument and form.
 10. As of the effective date of the Technical Report, to the best of my knowledge, information and belief, the Technical Report contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.
 11. I consent to the filing of the Technical Report with any stock exchange and other regulatory authority and any publication by them, including electronic publication in the public company files on their websites accessible by the

public, of the Technical Report

Signed and dated this 9th day of April 2020.

(Signed and sealed) "John M. Marek"

John M. Marek

Registered Member of the American Institute of Mining and Metallurgical Engineers,
Society of Mining Engineers

Certificate Of Qualified Person

Thomas L. Drielick

I, Thomas L. Drielick, P.E., do hereby certify that:

1. I am currently employed as Sr. Vice President by:
M3 Engineering & Technology Corporation
2051 W. Sunset Road, Ste. 101
Tucson, Arizona 85704
U.S.A.
2. I am a graduate of Michigan Technological University and received a Bachelor of Science degree in Metallurgical Engineering in 1970. I am also a graduate of Southern Illinois University and received an M.B.A. degree in 1973.
2. I am a:
 - Registered Professional Engineer in the State of Arizona (No. 22958)
 - Registered Professional Engineer in the State of Michigan (No. 6201055633)
 - Member in good standing of the Society for Mining, Metallurgy and Exploration, Inc. (No. 850920)
 - Member in good standing of AACE (Association for the Advancement of Cost Engineering) International, Inc. (No. 05031)
3. I have practiced metallurgical and mineral processing engineering and project management for 49 years. I have worked for mining and exploration companies for 18 years and for M3 Engineering and Technology Corporation for 31 years.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 ("NI 43-101") and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I am responsible for the preparation of Section 13 "Mineral Processing and Metallurgical Testing", Section 17 "Recovery Methods", Section 22 "Economic Analysis", Section 21.1 "Process Operating Cost Estimate", Section 21.3.2 "Plant Capital Cost", Section 21.3.4 "Current Value of Existing Infrastructure", and Section 26.2 "Metallurgy" of the technical report titled "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study Update, New Mexico, USA" dated effective 11 December 2018 (the "Technical Report").
6. I have prior involvement with the property that is the subject of the Technical Report. I was a contributing author of a previous Technical Report on the subject property titled "Copper Flat Project, Form 43-101F1 Technical Report, Prefeasibility Study" (the "Technical Report") dated August 22, 2012. I was also contributing author of the Technical Report on the subject property titled "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study, New Mexico, USA" (the "Technical Report") dated effective October 7, 2013.
7. As of the effective date of the Technical Report, to the best of my knowledge, information and belief, the Technical Report contains all scientific and technical information required to be disclosed to make the report not misleading.
8. I am independent of the issuer applying all of the tests in section 1.5 of National Instrument 43-101.
9. I have read National Instrument 43-101 and Form 43-101F1, and the Technical Report has been prepared in compliance with that instrument and form.

10. I consent to the filing of the Technical Report with any stock exchange and other regulatory authority and any publication by them for regulatory purposes, including electronic publication in the public company files on their websites accessible by the public, of the Technical Report.

Signed and dated this 9th day of April 2020.

(Signed and sealed) "Thomas L. Drielick"
Thomas L. Drielick, P.E.



CERTIFICATE OF QUALIFIED PERSON

CERTIFICATE OF QUALIFIED PERSON
David A. Kidd

I, David A. Kidd, PE, state that:

- (a) I am a Principal/Senior Program Manager at:
Golder Associates Inc.
7458 N. La Cholla Blvd.
Tucson, AZ 85741
- (b) This certificate applies to the technical report titled "Copper Flat Project, Form 43-101F1 Technical Report, Feasibility Study Update, New Mexico, USA" (the "Technical Report"), dated effective 11 December 2018, prepared for THEMAC Resources Group, Ltd.
- (c) I am a "qualified person" for the purposes of National Instrument 43-101 (the "Instrument"). My qualifications as a qualified person are as follows. I am a graduate of the University of Arizona with Bachelors (1987) and Masters (1989) of Science degrees in Civil Engineering with an emphasis in Geotechnical Engineering. I am a Registered Professional Engineer in good standing in New Mexico, Arizona and Nevada. I am also a Registered Member of the Society for Mining, Metallurgy, and Exploration. My relevant experience after graduation and over the past 32 years for the purpose of the Technical Report includes the design, operation, inspection, maintenance and closure of approximately 35 tailing impoundments.
- (d) My most recent personal inspection of each property described in the Technical Report occurred on March 2, 2012 and was for a duration of 1 day.
- (d) I am responsible for Sections 20.2, 21.3.3, 25.2.1, 25.3.1, and 26.3 of the Technical Report.
- (e) I am independent of the issuer as described in section 1.5 of the Instrument.
- (f) I have not had prior involvement with the property that is the subject of the Technical Report.
- (g) I have read National Instrument 43-101. The Technical Report has been prepared in compliance with this Instrument; and
- (h) At the effective date of the Technical Report, to the best of my knowledge, information, and belief, the part of Technical Report for which I am responsible, contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated at Tucson, AZ this 9th of April, 2020.

(Signed and Sealed) "David A. Kidd"
David A. Kidd, PE
New Mexico Civil Engineer Registration No. 13778